

860


UCRL- 89869
PREPRINT

Spent Fuel Cladding
Containment Credit Tests

C. N. Wilson
V. M. Oversby

Waste Management 84 Conference
Tucson, Arizona
March 11-15, 1984

February 1984



This is a preprint of a paper intended for publication in a journal or proceedings. Since changes may be made before publication, this preprint is made available with the understanding that it will not be cited or reproduced without the permission of the author.

SPENT FUEL CLADDING CONTAINMENT CREDIT TESTS

C. N. Wilson
Westinghouse Hanford Company

V. M. Oversby
Lawrence Livermore National Laboratory

ABSTRACT

Preliminary tests are being conducted to evaluate the effectiveness of defected cladding as a barrier to radionuclide release from spent fuel rods stored in a geological repository. The tests are being conducted at the Hanford Engineering Development Laboratory for the Lawrence Livermore National Laboratory Waste Package Task of the Nevada Nuclear Waste Storage Investigations (NNWSI) tuff repository project. In these tests, spent PWR fuel rod specimens with various artificially induced cladding defects are leach tested in a test matrix which also includes both bare fuel specimens (unclad) and undefected spent fuel rod specimens. Artificial cladding defects are made by laser drilling and sawing to give defect areas in the 10^4 to 10^6 μm^2 range. Periodic samples are taken of the leach solution and fused quartz rods contained in the test vessels. Results for the first 180 days of testing are presented.

Work performed under the auspices of the U.S. Department of Energy by the Lawrence Livermore National Laboratory under contract number W-7405-ENG-48.

1.0 INTRODUCTION

The most likely mechanism for release of radionuclides from a geologic repository to the biosphere is dissolution into ground water and migration as a result of ground water flow. The repository horizon for the Nevada Nuclear Waste Storage Investigations (NNWSI) Project is a welded devitrified tuff which is above the water table. However, a limited amount of water will infiltrate through the rock providing a potential mechanism for radionuclide transport to the underlying water table. Most of the available quantitative data on the radionuclide release from spent fuel is derived from leach testing of bare fuel particles. Using such data to model the NNWSI repository, the "source term" for radionuclide transport may be unnecessarily conservative. The amount of conservatism would depend upon: 1) portion of stored rods breached at a given time during the post-containmentment period; 2) the amount of inhibition to radionuclide release provided by breached cladding; and 3) the long-term stability of spent fuel rods in the repository environment.

For fuel currently being discharged from Light Water Reactors (LWR), the portion of rods containing breaches is estimated to be in the 10^{-3} to 10^{-4} range.⁽¹⁾ The typical in-reactor breach is a series of small pin holes or a fine crack. The pin holes are typically only a few microns in size, and the cracks are typically several microns wide and a few millimeters to a few centimeters in length. However, larger cladding failures may occur. Spent fuel pool storage⁽²⁾ experience suggests that radionuclide release rates from rods containing small breaches may be limited during repository storage if longer time processes (such as cladding corrosion or fuel swelling due to oxidation) do not cause a progressive loss of cladding integrity under NNWSI proposed terminal storage conditions.

The objective of the Spent Fuel Cladding Containment Credit Tests⁽³⁾ is to determine the extent to which cladding containing a defined and stable breach provides a barrier to radionuclide release. The tests are conducted as a scoping study to provide initial data and to provide direction for future studies if a significant barrier effect for breached cladding is indicated.

2.0 TEST DESCRIPTION

Sections of pressurized water reactor (PWR) spent fuel rods with artificially induced cladding defects are comparatively leach tested in deionized water under air at ambient hot cell temperature (22°C to 28°C). The test matrix includes four specimen types: 1) rod segments with undefected cladding, 2) rod segments with small laser drilled holes through the cladding to the fuel, 3) rod segments with a fine axially machined slit through the cladding and 4) rod segments which are axially split open and the cladding separated from the bare fuel. Cladding defect sizes per kg fuel are $\sim 10^6 \mu\text{m}^2/\text{kg}$ for the laser drilled defects and $\sim 10^8 \mu\text{m}^2/\text{kg}$ for the slit defect, versus an expected $1 \mu\text{m}^2/\text{kg}$ to $10^5 \mu\text{m}^2/\text{kg}$ range for a typical in-reactor breach. Additional characteristics of the fuel and test specimens are given in Table 1. A 60 day post-test metallographic section through a laser drilled cladding defect is shown in Figure 1.


The test apparatus is shown in Figure 2. The bare fuel and cladding hulls are placed in a fused quartz basket. As a result of thermal cracking of the UO_2 pellets during irradiation, the bare fuel material is present as pellet pieces with mean particle size in the 2 to 3 mm range. The undefected, laser drilled and slit cladding specimens are fitted with end caps which provide a water tight seal by compression of ethylene propylene O-rings against the cladding exterior. The upper end cap is vented to allow water entering the defect to fill the specimen internal free volume and completely water log the fuel. Several fused quartz rods are contained in each test vessel which can be periodically removed to monitor radionuclide plateout during the tests.

Each test vessel is initially filled with 250 ml of deionized water giving the approximate solution level shown in Figure 2. Solution samples (10 ml) are removed at day 1, 5, 15, 30 and every 30 days thereafter. Ten ml of fresh deionized water is added for each solution sample taken to maintain a constant solution level. Fused quartz rods are periodically removed, rinsed with fresh deionized water, stripped with HNO_3 and the strip solution

TABLE 1

SPENT FUEL SPECIMEN CHARACTERISTICS(3)

Fuel Type:	PWR 15 x 15
Burnup:	25,500 to 27,700 MWD/MTU
Discharge Date:	November 1975
Fission Gas Release:	~0.3%
Initial Enrichment:	2.559 wt% ²³⁵ U
Initial UO ₂ Density:	92% Theoretical
Specimen length:	5 inches
Hole Defect Specimen:	2 laser drilled holes ~200 μm diameter
Slit Defect Specimen:	Axial slit ~2 cm long by 150 μm wide

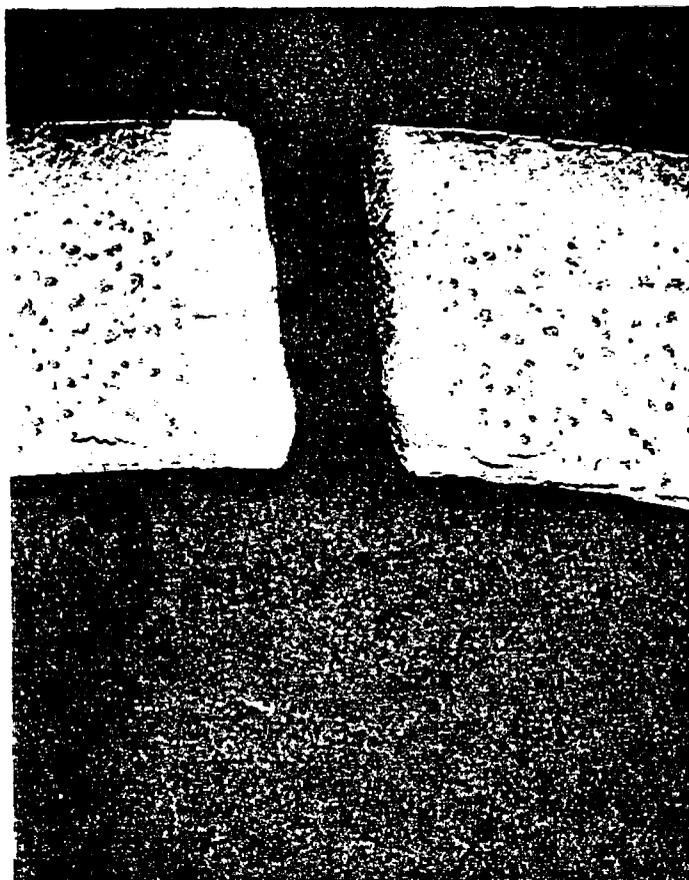

L500471

75X

FIGURE 1. Post-test metallographic section through a laser drilled test specimen at the cladding defect location. Test duration was 60 days. No visible attack of the fuel by the leaching solution was observed.

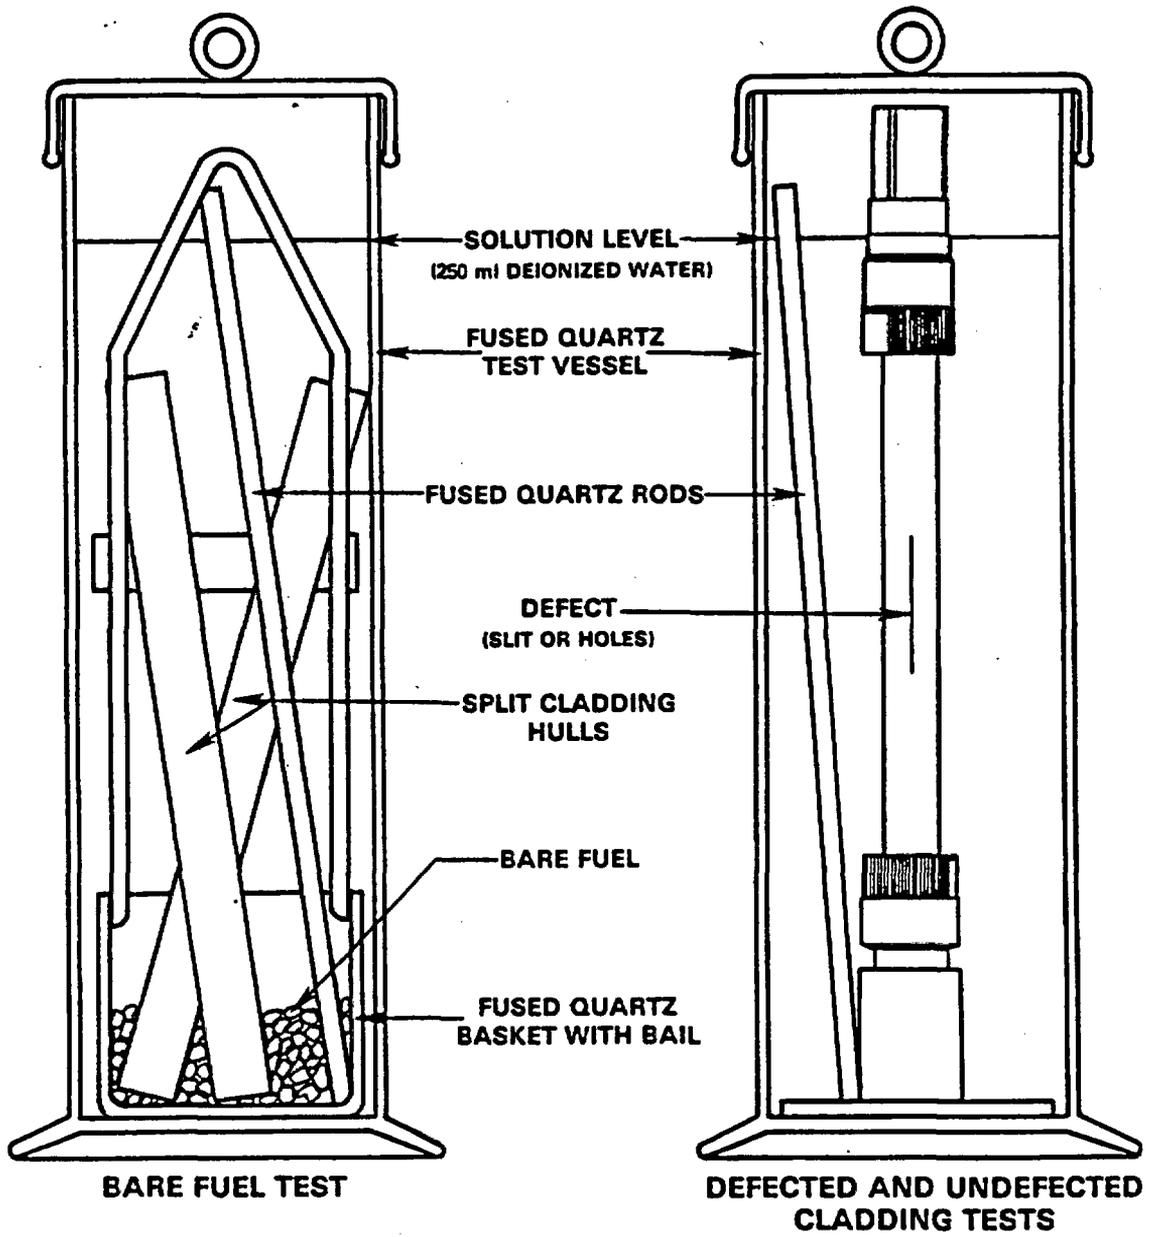


FIGURE 2. Test Apparatus.

radiochemically analyzed. Rod samples are taken at day 5, 30, 60, 120 and every 60 days thereafter. Each sample is radiochemically analyzed by alpha and gamma spectrographic methods and analyzed for uranium by the laser excited fluorescence method. Additional radiochemical analyses requiring chemical separations are being made on selected samples.

3.0 RESULTS AND DISCUSSION

Uranium, ^{239}Pu plus ^{240}Pu and ^{137}Cs results for solution and fused quartz rod samples through 180 days are given in Figure 3. The solution concentration for each species that would result if 10^{-5} of the test specimen inventory were dissolved in the 250 ml of test solution is indicated on each of the solution data plots. The quantity of each species corresponding to 10^{-5} of the test specimen inventory is indicated on each of the fused quartz rod data plots. The 10^{-5} inventory values are given to relate the data to geologic repository release rate limits given in 10 CFR 60,⁽⁴⁾ and are established using ORIGEN code calculated inventory data for PWR fuel 10 years after discharge.⁽⁵⁾ The 10CFR60 limits are based on 1000 year inventories. For uranium and plutonium the 10 and 1000 year inventories are similar; ^{137}Cs has decayed to negligible levels by 1000 years after disposal. Data given in each plot for the "undefected" specimen indicates released levels for each species from cladding exterior surface contamination. The primary source of the cladding exterior contamination is sectioning and handling of the fuel specimens in contaminated hot cells. The cladding exterior surfaces were decontaminated to approximately 50 dpm smearable alpha prior to final specimen preparation in a clean hot cell. However, the remaining exterior contamination levels are most likely greater than those to be expected on whole fuel rods received at a repository.

It is interesting to note from the Figure 3 data that most of the release in both the bare fuel and defected cladding tests appears to have occurred during the first 30 days. Substantially reduced releases of uranium and plutonium were observed in the defected cladding tests in comparison to the bare fuel test. Reduced uranium release with the defected cladding specimens is particularly noteworthy since, after an initial preferential release of highly soluble fission products such as cesium, it is expected that UO_2 matrix dissolution will control radionuclide release. Localized solution oxygen depletion and saturation effects within the defected cladding may account for the observed lower actinide release from these specimens.

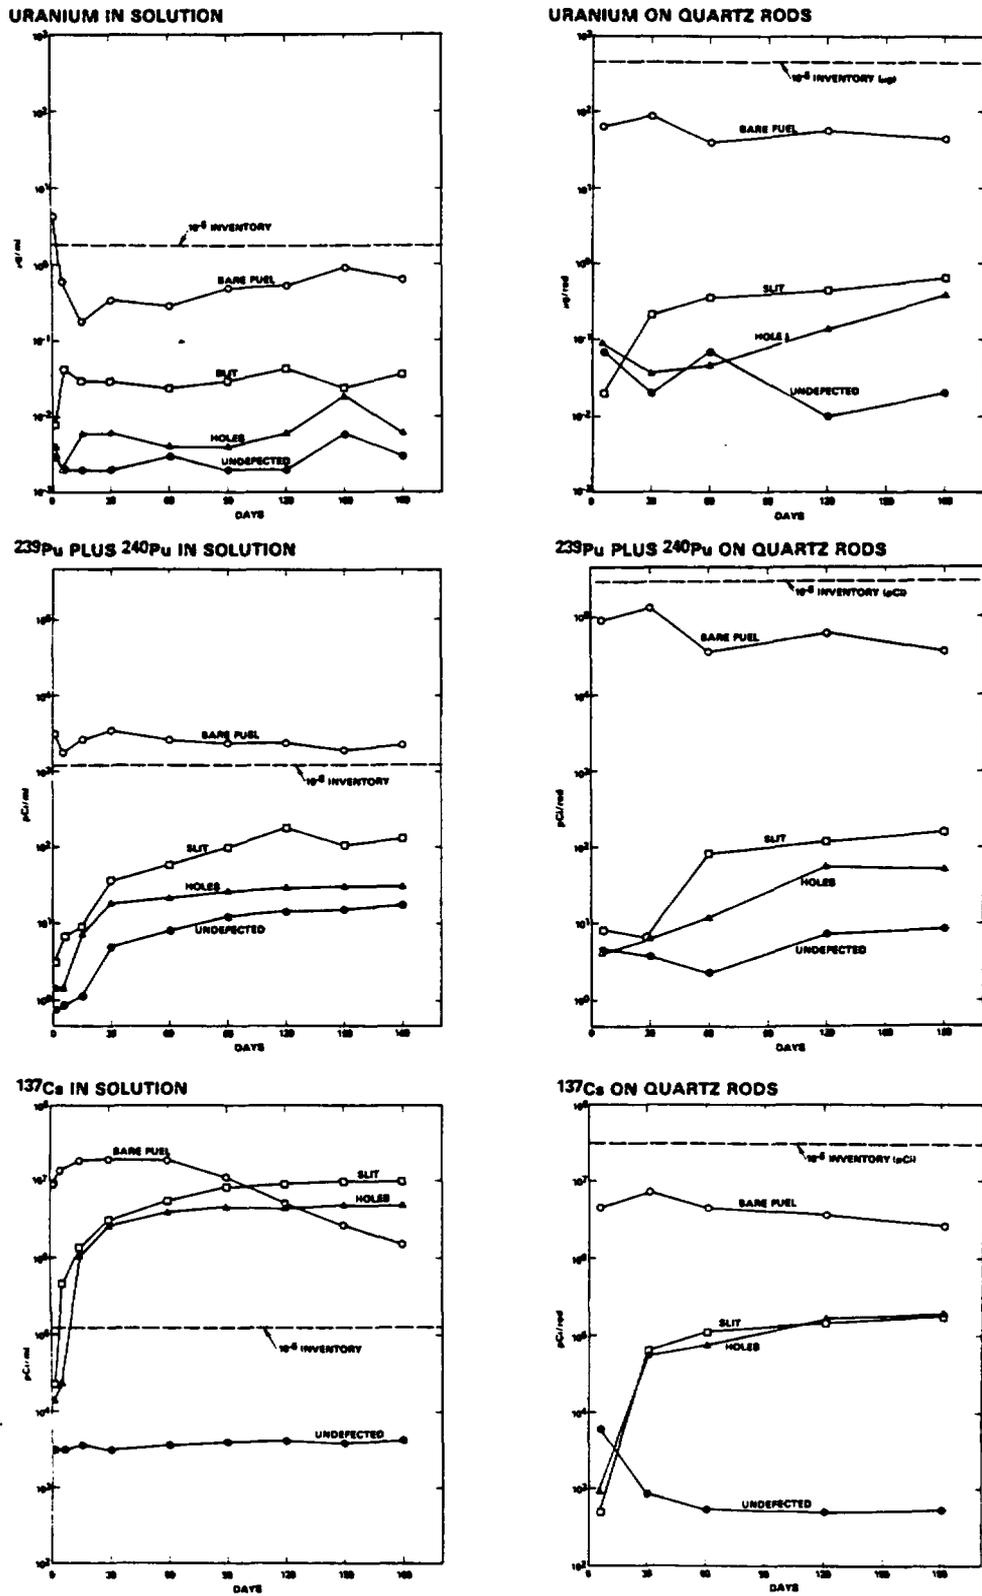


FIGURE 3. Uranium, ^{239}Pu plus ^{240}Pu and ^{137}Cs measured in solution and on fused quartz rod specimens during the first 180 days testing.

The absence of well defined solubility limits when "solution" sample results are compared to fused quartz rod sample results, suggests that the quantities of fuel source species measured in solution samples are not solution concentrations in equilibrium with a "plateout" phase. A possible explanation is that a portion of the fuel source species measured in solution samples are in a colloidal state. (However, all solution samples were clear.) A solution sample taken from the bare fuel test (202 days) was filtered through 0.4 μm and 18 A filters to identify what portion of the radionuclide species released were in a colloidal state. Results are given in Table 2. Most of the plutonium, the antimony and approximately half the cesium passed through the 18 A filter. However, only about 1% of the uranium, curium, europium and cobalt passed the 18 A filter, and most of the uranium was collected on the 0.4 μm filter. A substantial portion of the total radionuclide release from spent fuel to water may be tied up in colloid phases. Planned future tests and sample analyses will further investigate the state of radionuclides released from spent fuel.

TABLE 2
 RADIOCHEMICAL DATA FOR 202 DAY
 SOLUTION SAMPLE FROM BARE FUEL
 IN pCi/ml or ($\mu\text{g/ml}$)

	<u>Not Filtered</u>	<u>Filtered 0.4 μm</u>	<u>Filtered 18 A</u>
^{244}Cm	2.1×10^4	2.9×10^3	1.6×10^2
$^{239} + ^{240}\text{Pu}$	2.2×10^3	2.2×10^3	1.8×10^3
^{154}Eu	5.5×10^4	7.7×10^3	7.7×10^2
^{137}Cs	1.4×10^6	9.4×10^5	5.6×10^5
^{125}Sb	2.0×10^4	2.3×10^4	2.4×10^4
^{60}Co	1.1×10^5	8.7×10^4	6.6×10^2
Uranium	(0.30)	(0.003)	(0.002)

The relatively high solubility of cesium is reflected in its higher initial solution levels relative to the 10^{-5} inventory concentration in the bare fuel and defected cladding tests. Two unexpected observations are the quantities of cesium observed on fused quartz rods and the decrease in solution cesium content over the bare fuel after 60 days. Cesium on the rod samples may be contained in fine colloidal particles adsorbed on the rods. Partial association of cesium with colloid particles is suggested by the filtered sample data in Table 2. It is interesting to note that cesium coming out of the "solution" phase over the bare fuel is not coming out onto the fused quartz rods. Reaction of cesium with the leached fuel particles is a possible explanation since the only other materials in the bare fuel test (zircaloy and fused quartz) are common to the other tests, and fuel particle surfaces are more highly leached and exposed in the bare fuel test.

4.0 SUMMARY

A series of tests has been described in which radionuclide releases from PWR spent fuel rod segments containing artificially induced cladding defects are compared to radionuclide releases from an equal quantity of bare unclad fuel. Results for the first 180 days indicate: 1) that the quantity of radionuclides released from the fuel through the cladding defects was lower in comparison to the quantity released from the bare fuel, and 2) most of the observed release from both defected cladding specimens and the bare fuel specimen appears to have occurred during the first 30 days. The testing is continuing, and future sample analyses are planned to more comprehensively evaluate the state of released radionuclides and the degree to which defected cladding is a barrier to radionuclide release.

5.0 REFERENCES

1. R. E. Woodley, Characteristics of Spent LWR Fuel Relevant to Its Storage in Geologic Repositories, HEDL-TME 83-28, Hanford Engineering Development Laboratory, Richland, WA, October 1983.
2. A. B. Johnson, Jr., Behavior of Spent Nuclear Fuel in Water Pool Storage, BNWL-2256, Pacific Northwest Laboratory, Richland, WA, September 1977.
3. C. N. Wilson, Test Plan for Spent Fuel Cladding Containment Credit Tests, HEDL-TC-2353-2, Hanford Engineering Development Laboratory, Richland, WA, November 1983.
4. Code of Federal Regulations, "Disposal of High-Level Radioactive Wastes in Geologic Repositories-Licensing Procedures," Title 10, Chapter 1, Part 60, June 30, 1983 (cited as 10 CFR 60).
5. C. W. Alexander and J. O. Blomeke, et al., Projections of Spent Fuel to be Discharged by the US Nuclear Power Industry, ORNL-TM-6008, Oak Ridge National Laboratory, Oak Ridge, TN, October 1977.

DISCLAIMER

This document was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor the University of California nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial products, process, or service by trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or the University of California. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government thereof, and shall not be used for advertising or product endorsement purposes.

Technical Information Department · Lawrence Livermore National Laboratory
University of California · Livermore, California 94550

