

Peripheral Oxide

Utility: Comanche 2 Cleaned


Assembly: HH80

Face: 2

Date: 18-Oct-2003

Elevation	R02	R03	R06	R08	R10	R12	R14
111.9	25.9	38.4	32.3	33.5	47.1	37.0	31.8
112.9	27.0	48.8	34.1	37.8	54.6	46.1	39.0
113.9	27.9	62.9	35.2	44.2	68.3	58.4	46.4
114.9	29.4	64.9	37.1	50.4	81.5	68.9	57.2
115.9	29.3	60.4	40.0	55.9	88.2	74.5	64.0
116.9	28.9	68.0	41.2	61.4	92.7	79.4	66.5
117.9	28.5	68.0	42.6	65.4	93.6	82.3	69.0
118.9	28.0	64.4	42.2	66.7	92.2	82.3	67.9
119.9	28.5	62.4	44.7	68.4	91.9	83.2	70.3
120.9	28.7	62.5	44.9	67.3	93.2	82.5	70.9
121.9	28.8	62.7	44.2	64.8	88.6	77.3	65.7
122.9	29.4	63.4	47.4	62.6	84.0	74.6	61.8
123.9	29.6	59.5	47.1	55.6	73.8	67.1	52.8
124.9	30.0	56.0	46.2	50.8	62.8	58.6	47.3
125.9	30.6	52.1	43.4	46.8	57.4	52.6	44.1
max	30.6	68.0	47.4	68.4	93.6	83.2	70.9

Peripheral Rod Oxide after Crud Clean (Comanche P

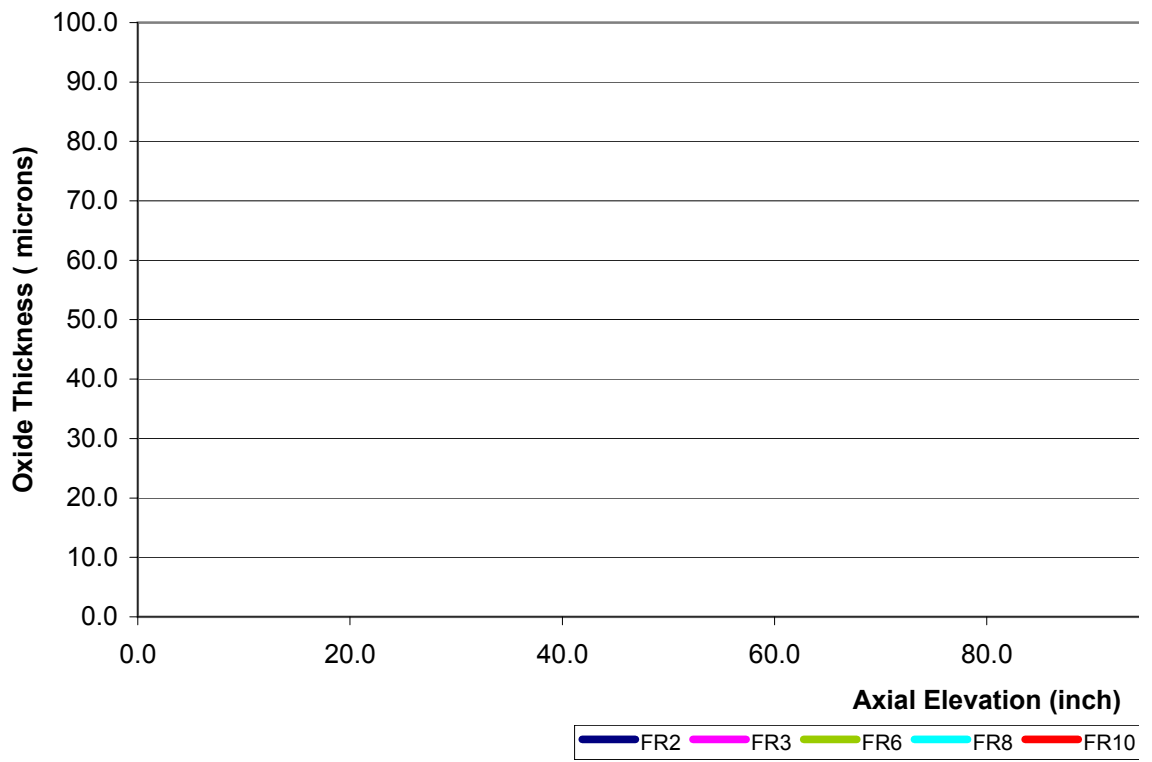

nanche Peak 2, FA HH80, FACE 2)

