Progress Energy

MAY 0 7 2004

Serial: HNP-04-076

U.S. Nuclear Regulatory Commission
ATTENTION: Document Control Desk
Washington, DC 20555

SHEARON HARRIS NUCLEAR POWER PLANT, UNIT NO. 1
DOCKET NO. 50-400/LICENSE NO. NPF-63
ONE-YEAR SPECIAL REPORT
STEAM GENERATOR TUBE INSERVICE INSPECTION RESULTS

Ladies and Gentlemen:

In accordance with Technical Specification 4.4.5.5.b of the Harris Nuclear Plant (HNP), Carolina Power and Light Company doing business as Progress Energy Carolinas, Inc., provides the attached Special Report, which transmits the results of the steam generator (SG) tube inservice inspections performed in May 2003 during the HNP Refueling Outage (RFO) Number 11.

Attachment 1 provides the summary of the HNP RFO-11 SG tube inservice inspection results.

Attachment 2 provides the HNP RFO-11 eddy current testing (ECT) signals of interest.

Please refer any question regarding this submittal to Mr. John Caves at (919) 362-3137.

Sincerely,

Brian C. McCabe for

J. R. Caves
Supervisor – Licensing/Regulatory Programs
Harris Nuclear Plant

JRC/jpy

Attachments:

1. Summary of the HNP RFO-11 Steam Generator (SG) Tube Inservice Inspection Results
2. The HNP RFO-11 Eddy Current Testing (ECT) Signals of Interest

Progress Energy Carolinas, Inc.
Harris Nuclear Plant
P.O. Box 165
New Hill, NC 27562

A047

c:

Mr. R. A. Musser, NRC Senior Resident Inspector
Mr. C. P. Patel, NRC Project Manager
Mr. L. A. Reyes, NRC Regional Administrator

Bc :

Mr. W. F. Conway
Mr. F. Diya
Mr. D. G. Eisenhut
Mr. K. N. Harris
Mr. C. S. Hinnant
Mr. M. T. Janus
Mr. R. D. Martin
Mr. R. D. Mullis
Mr. J. M. Taylor
Mr. B. C. Waldrep
Mr. W. G. Wendland
Licensing Files (2 copies)
Nuclear Records

SHEARON HARRIS NUCLEAR POWER PLANT, UNIT NO. 1
DOCKET NO. 50-400/LICENSE NO. NPF-63
ONE-YEAR SPECIAL REPORT
STEAM GENERATOR TUBE INSERVICE INSPECTION RESULTS

Summary of the HNP RFO-11
Steam Generator (SG) Tube Inservice Inspection Results

Technical Specification 4.4.5.5.b of the Harris Nuclear Plant (HNP) requires the complete results of the steam generator (SG) tube inservice inspection shall be submitted in a Special Report within 12 months following completion of the inspection. The Special Report shall include:

1. Number and extent of tubes inspected.

2. Location and percent of wall-thickness penetration for each indication of an imperfection, and

3. Identification of tubes plugged.

The first inservice inspection of the SG following replacement was performed in Refueling Outage (RFO) Number 11 and completed on May 7, 2003.

1. Number and extent of tubes inspected:

SG "A":

Number of Tubes available for inspection	Number of Tubes Inspected	Examination Method	Extent of tubes inspected
6,306	6,306	Bobbin	Tube end to opposite tube end

SG "B":

Number of Tubes available for inspection	Number of Tubes Inspected	Examination Method	Extent of tubes inspected
6,306	6,306	Bobbin	Tube end to opposite tube end

SG "C":

Number of Tubes available for inspection	Number of Tubes Inspected	Examination Method	Extent of tubes inspected
6,307	6,307	Bobbin	Tube end to opposite tube end
	17	Rotating Coil	Benign indications in select areas

2. **Location and percent of wall-thickness penetration for each indication of an imperfection:**

   No recordable eddy current testing (ECT) indications with wall-thickness penetration were identified from the results of this first inservice inspection.

   Attachment 2 provides the HNP RFO-11 ECT signals of interest.

3. **Identification of tubes plugged:**

   SG "A":

   One tube plugged (pre-service): R106C85

   SG "B":

   One tube plugged (pre-service): R114C73

   SG "C":

   No tubes are plugged in this SG.

SHEARON HARRIS NUCLEAR POWER PLANT, UNIT NO. 1
DOCKET NO. 50-400/LICENSE NO. NPF-63
ONE-YEAR SPECIAL REPORT
STEAM GENERATOR TUBE INSERVICE INSPECTION RESULTS

The HNP RFO-11 Eddy Current Testing (ECT) Signals of Interest

SG "A":	
Dents (DNT)	12 pages
Non-Quantifiable Signals (NQS)	3 pages
Permeability Variations (PVN)	2 pages
SG "B":	
Dents (DNT)	22 pages
Non-Quantifiable Signals (NQS)	3 pages
Permeability Variations (PVN)	2 pages
SG "C":	
Dents (DNT)	26 pages
Non-Quantifiable Signals (NQS)	3 pages
Permeability Variations (PVN)	2 pages
Special Interest Rotating Coil Inspection	2 pages
Total pages:	77 pages

SG - A DENTS

Shearon Harris RFO11 CQL D75

X 319 TUBE WITH DENT

* 4 STAY

▫ 1 PLUGGED TUBE

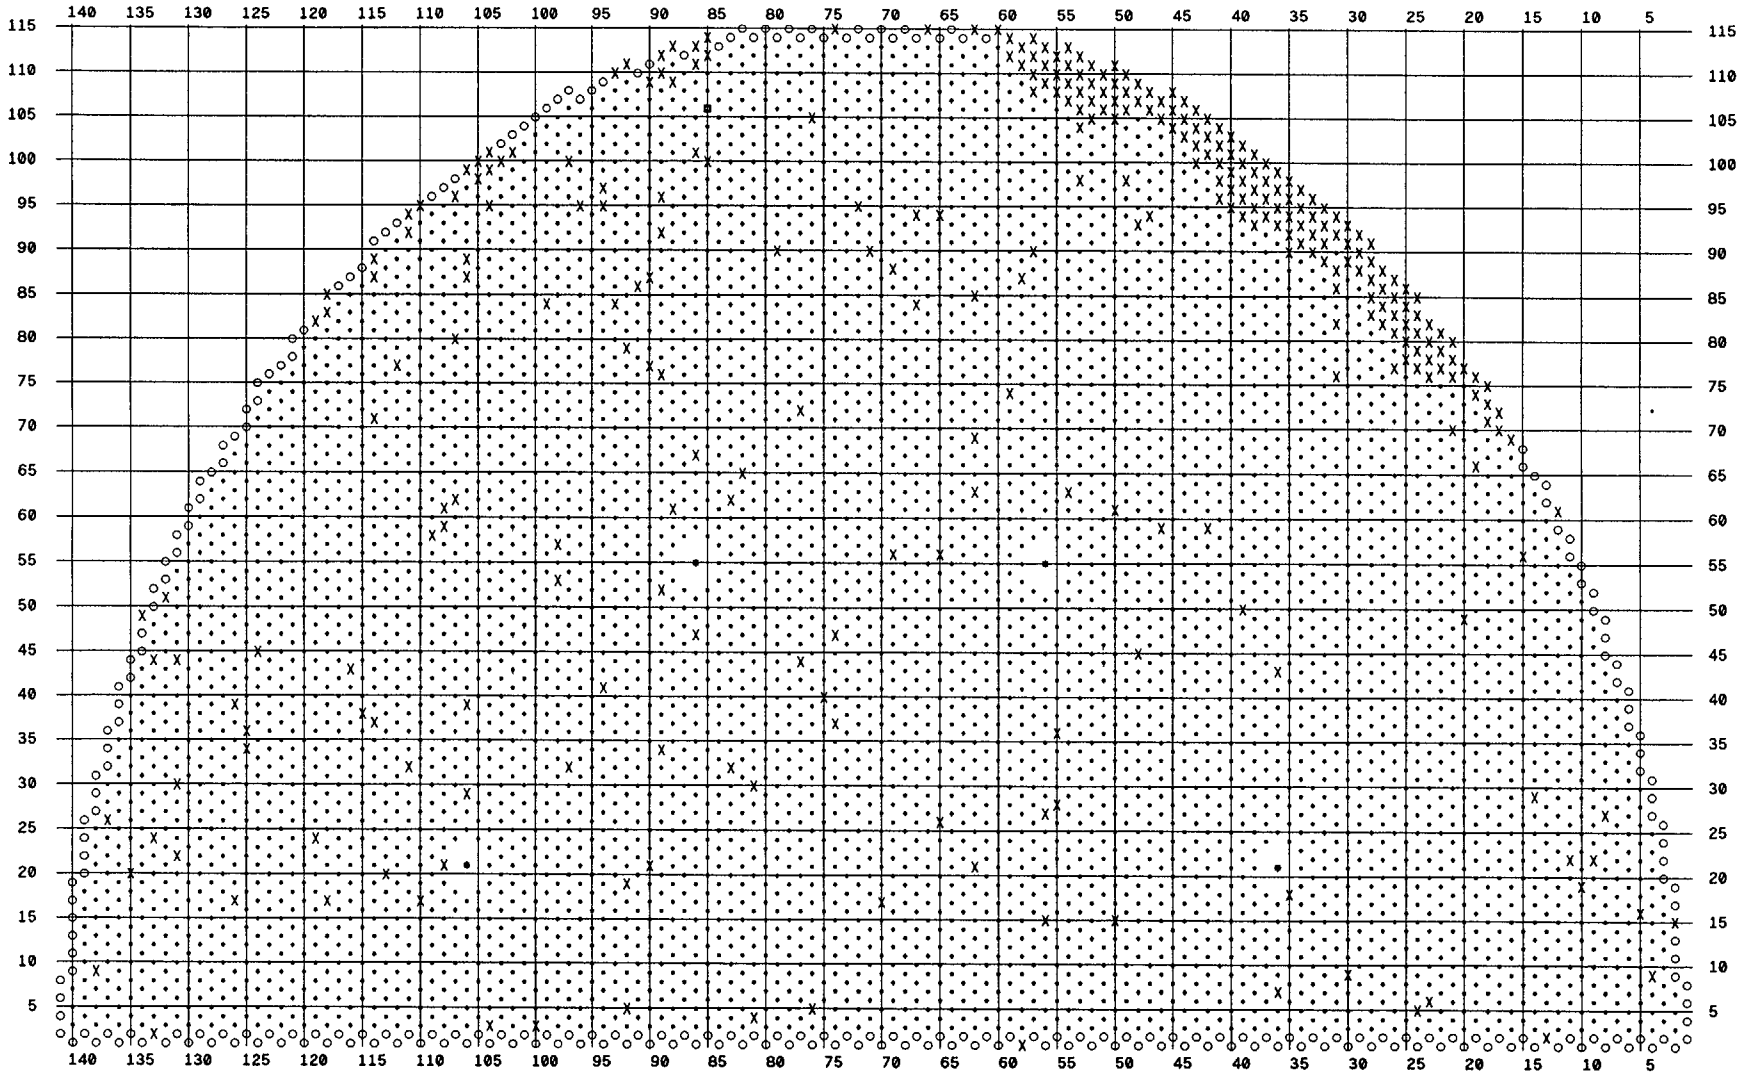

Westinghouse Electric Company LLC - NSBU ST2000 05/07/2003 22:26:06

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
15	2	1.06	181	DNT		P1	08H	.94		TEC	TEH	.560	ZBATF	40	H	
9	4	1.77	182	DNT		P1	02H	3.73		TEC	TEH	.560	ZBATF	41	H	
16	5	1.07	182	DNT		P1	05C	21.10		TEC	TEH	.560	ZBATF	40	H	
27	8	1.07	181	DNT		P1	04H	5.87		TEC	TEH	.560	ZBATF	41	H	
22	9	1.42	177	DNT		P1	03C	-.51		TEC	TEH	.560	ZBATF	41	H	
19	10	1.43	180	DNT		P1	TSH	18.20		TEC	TEH	.560	ZBATF	40	H	
19	10	1.07	179	DNT		P1	TSH	18.59		TEC	TEH	.560	ZBATF	40	H	
22	11	1.01	186	DNT		P1	03H	2.79		TEC	TEH	.560	ZBATF	41	H	
61	12	1.65	172	DNT		P1	08C	24.75		TEC	TEH	.560	ZBATF	40	H	
2	13	1.02	180	DNT		P1	07C	7.10		09H	TEC	.560	ZBACS	34	C	
29	14	1.48	174	DNT		P1	07C	9.08		TEC	TEH	.560	ZBATF	10	H	
56	15	1.48	178	DNT		P1	01H	37.43		TEC	TEH	.560	ZBATF	15	H	
69	16	1.41	175	DNT		P1	09C	-.69		TEC	TEH	.560	ZBATF	15	H	
70	17	1.07	179	DNT		P1	04H	18.94		TEC	TEH	.560	ZBATF	16	H	
70	17	1.46	175	DNT		P1	09H	-.81		TEC	TEH	.560	ZBATF	16	H	
70	17	1.04	177	DNT		P1	09C	-.71		TEC	TEH	.560	ZBATF	16	H	
72	17	1.83	177	DNT		P1	09H	-.81		TEC	TEH	.560	ZBATF	15	H	
71	18	.97	176	DNT		P1	09C	-.63		TEC	TEH	.560	ZBATF	16	H	
73	18	1.18	177	DNT		P1	09H	-.79		TEC	TEH	.560	ZBATF	15	H	
73	18	1.08	175	DNT		P1	09C	-.72		TEC	TEH	.560	ZBATF	15	H	
75	18	1.44	175	DNT		P1	09C	-.69		TEC	TEH	.560	ZBATF	15	H	
66	19	1.00	177	DNT		P1	09H	-.73		TEC	TEH	.560	ZBATF	16	H	
74	19	1.06	177	DNT		P1	09H	-.78		TSC	TEH	.560	ZBATF	16	H	
74	19	2.12	176	DNT		P1	09C	-.68		TSC	TEH	.560	ZBATF	16	H	
76	19	4.93	178	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	15	H	
76	19	5.41	177	DNT		P1	09C	.44		TEC	TEH	.560	ZBATF	15	H	
49	20	1.71	184	DNT		P1	05H	2.26		TEC	TEH	.560	ZBATF	15	H	
77	20	2.20	175	DNT		P1	09H	-.76		TEC	TEH	.560	ZBATF	15	H	
77	20	2.55	176	DNT		P1	09C	-.64		TEC	TEH	.560	ZBATF	15	H	
77	20	1.01	172	DNT		P1	09C	.39		TEC	TEH	.560	ZBATF	15	H	
70	21	2.20	179	DNT		P1	AV1	11.40		TEC	TEH	.560	ZBATF	16	H	
76	21	1.56	176	DNT		P1	09H	-.74		TEC	TEH	.560	ZBATF	15	H	
76	21	1.51	175	DNT		P1	09C	-.62		TEC	TEH	.560	ZBATF	15	H	
78	21	1.82	177	DNT		P1	09H	-.76		TEC	TEH	.560	ZBATF	16	H	
78	21	1.35	173	DNT		P1	09H	.30		TEC	TEH	.560	ZBATF	16	H	
78	21	2.37	177	DNT		P1	09C	-.66		TEC	TEH	.560	ZBATF	16	H	
78	21	1.26	173	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	16	H	
80	21	2.83	175	DNT		P1	09H	-.76		TEC	TEH	.560	ZBATF	15	H	
80	21	.94	174	DNT		P1	09H	.33		TEC	TEH	.560	ZBATF	15	H	
80	21	2.76	175	DNT		P1	09C	-.66		TEC	TEH	.560	ZBATF	15	H	
80	21	1.99	174	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	15	H	
77	22	1.70	174	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	15	H	
79	22	2.90	177	DNT		P1	09H	-.73		TEC	TEH	.560	ZBATF	16	H	
79	22	1.09	173	DNT		P1	09H	.30		TEC	TEH	.560	ZBATF	16	H	
79	22	2.80	175	DNT		P1	09C	-.63		TEC	TEH	.560	ZBATF	16	H	
79	22	1.25	172	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	16	H	
81	22	3.52	176	DNT		P1	09H	-.74		TEC	TEH	.560	ZBATF	15	H	
81	22	3.50	176	DNT		P1	09C	-.67		TEC	TEH	.560	ZBATF	15	H	
81	22	1.39	170	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	15	H	
6	23	1.21	178	DNT		P1	05H	23.44		TEC	TEH	.560	ZBATF	12	H	
76	23	1.87	176	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	16	H	
78	23	2.47	178	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	15	H	
78	23	1.88	175	DNT		P1	09H	.36		TEC	TEH	.560	ZBATF	15	H	
78	23	2.73	176	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	15	H	
78	23	1.24	172	DNT		P1	09C	.47		TEC	TEH	.560	ZBATF	15	H	
80	23	2.59	178	DNT		P1	09H	-.73		TEC	TEH	.560	ZBATF	16	H	
80	23	1.39	173	DNT		P1	09H	.33		TEC	TEH	.560	ZBATF	16	H	
80	23	2.55	177	DNT		P1	09C	-.63		TEC	TEH	.560	ZBATF	16	H	
80	23	1.21	174	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	16	H	

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	• INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
82	23	4.10	177	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	15	H	
82	23	1.39	174	DNT		P1	09H	.31		TEC	TEH	.560	ZBATF	15	H	
82	23	4.16	178	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	15	H	
82	23	1.76	173	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	15	H	
5	24	.95	183	DNT		P1	FBC	11.34		TEC	TEH	.560	ZBATF	12	H	
77	24	.89	174	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	16	H	
79	24	1.58	176	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	15	H	
81	24	2.15	176	DNT		P1	09H	-.73		TEC	TEH	.560	ZBATF	16	H	
81	24	1.04	177	DNT		P1	09C	-.66		TEC	TEH	.560	ZBATF	16	H	
83	24	4.22	177	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	15	H	
83	24	1.29	172	DNT		P1	09H	.33		TEC	TEH	.560	ZBATF	15	H	
83	24	3.00	177	DNT		P1	09C	-.62		TEC	TEH	.560	ZBATF	15	H	
85	24	3.81	177	DNT		P1	09H	-.76		TEC	TEH	.560	ZBATF	15	H	
85	24	1.41	173	DNT		P1	09H	.28		TEC	TEH	.560	ZBATF	15	H	
85	24	3.04	177	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	15	H	
85	24	1.24	170	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	15	H	
78	25	.77	175	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	16	H	
80	25	1.62	176	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	15	H	
80	25	1.47	178	DNT		P1	AV8	34.92		TEC	TEH	.560	ZBATF	15	H	
80	25	1.07	173	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	15	H	
82	25	2.13	177	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	16	H	
82	25	1.25	174	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	16	H	
84	25	3.90	178	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	15	H	
84	25	3.36	176	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	15	H	
84	25	1.62	174	DNT		P1	09C	.47		TEC	TEH	.560	ZBATF	15	H	
86	25	3.80	178	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	15	H	
86	25	1.00	172	DNT		P1	09H	.36		TEC	TEH	.560	ZBATF	15	H	
86	25	3.47	177	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	15	H	
86	25	1.09	172	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	15	H	
77	26	.88	175	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	16	H	
81	26	2.01	176	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	16	H	
83	26	3.55	177	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	15	H	
83	26	1.31	174	DNT		P1	09H	.38		TEC	TEH	.560	ZBATF	15	H	
83	26	1.21	173	DNT		P1	09C	-.63		TEC	TEH	.560	ZBATF	15	H	
85	26	1.97	175	DNT		P1	09H	-.73		TEC	TEH	.560	ZBATF	16	H	
85	26	1.00	171	DNT		P1	09H	.38		TEC	TEH	.560	ZBATF	16	H	
85	26	1.53	175	DNT		P1	09C	-.63		TEC	TEH	.560	ZBATF	16	H	
87	26	3.63	177	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	15	H	
87	26	.88	172	DNT		P1	09H	.33		TEC	TEH	.560	ZBATF	15	H	
87	26	3.49	176	DNT		P1	09C	-.64		TEC	TEH	.560	ZBATF	15	H	
82	27	1.49	176	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	16	H	
82	27	.86	170	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	16	H	
82	27	1.27	178	DNT		P1	07C	12.49		TEC	TEH	.560	ZBATF	16	H	
84	27	2.21	177	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	15	H	
84	27	1.05	171	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	15	H	
84	27	.93	173	DNT		P1	09C	1.19		TEC	TEH	.560	ZBATF	15	H	
86	27	2.51	176	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	16	H	
86	27	1.17	177	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	16	H	
88	27	5.63	178	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	15	H	
88	27	1.45	173	DNT		P1	09H	.36		TEC	TEH	.560	ZBATF	15	H	
88	27	3.09	177	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	15	H	
83	28	1.76	176	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	15	H	
85	28	1.00	175	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	16	H	
85	28	1.01	175	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	16	H	
87	28	1.32	176	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	15	H	
87	28	1.71	175	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	15	H	
87	28	.89	169	DNT		P1	09C	.47		TEC	TEH	.560	ZBATF	15	H	
89	28	1.09	172	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	16	H	
89	28	2.59	177	DNT		P1	09C	-.63		TEC	TEH	.560	ZBATF	16	H	
91	28	2.76	176	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	15	H	
91	28	1.13	170	DNT		P1	09H	.33		TEC	TEH	.560	ZBATF	15	H	
91	28	1.91	176	DNT		P1	09C	-.57		TEC	TEH	.560	ZBATF	15	H	
91	28	1.41	173	DNT		P1	09C	.39		TEC	TEH	.560	ZBATF	15	H	
88	29	2.91	176	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	15	H	
88	29	1.04	174	DNT		P1	09H	.38		TEC	TEH	.560	ZBATF	15	H	
88	29	.65	173	DNT		P1	09C	-.52		TEC	TEH	.560	ZBATF	15	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
90	29	3.05	178	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	16	H	
90	29	1.71	176	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	16	H	
92	29	2.47	177	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	15	H	
92	29	2.67	177	DNT		P1	09C	-.57		TEC	TEH	.560	ZBATF	15	H	
92	29	3.22	177	DNT		P1	09C	.44		TEC	TEH	.560	ZBATF	15	H	
9	30	1.17	180	DNT		P1	07H	20.47		TEH	TEC	.560	ZBATF	35	C	
89	30	.90	176	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	15	H	
91	30	1.61	175	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	16	H	
91	30	.88	171	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	16	H	
91	30	1.50	175	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	16	H	
91	30	1.51	175	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	16	H	
93	30	1.70	175	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	15	H	
93	30	1.17	172	DNT		P1	09H	.33		TEC	TEH	.560	ZBATF	15	H	
93	30	2.47	177	DNT		P1	09C	-.52		TEC	TEH	.560	ZBATF	15	H	
93	30	3.05	175	DNT		P1	09C	.44		TEC	TEH	.560	ZBATF	15	H	
76	31	1.08	173	DNT		P1	AV8	33.17		TEC	TEH	.560	ZBATF	16	H	
82	31	1.81	176	DNT		P1	AV8	17.15		TEC	TEH	.560	ZBATF	15	H	
86	31	.74	178	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	15	H	
88	31	1.70	177	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	16	H	
88	31	1.27	176	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	16	H	
88	31	.94	173	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	16	H	
92	31	1.01	175	DNT		P1	08H	28.63		TEC	TEH	.560	ZBATF	16	H	
92	31	1.77	178	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	16	H	
92	31	2.61	177	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	16	H	
92	31	1.77	174	DNT		P1	09C	.49		TEC	TEH	.560	ZBATF	16	H	
94	31	1.96	175	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	15	H	
94	31	.98	172	DNT		P1	09H	.36		TEC	TEH	.560	ZBATF	15	H	
94	31	4.00	177	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	15	H	
94	31	4.81	177	DNT		P1	09C	.44		TEC	TEH	.560	ZBATF	15	H	
89	32	1.18	174	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	17	H	
91	32	1.72	176	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	18	H	
91	32	1.22	173	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	18	H	
93	32	1.53	183	DNT		P1	02H	23.23		TEC	TEH	.560	ZBATF	17	H	
93	32	2.10	177	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	17	H	
93	32	2.05	178	DNT		P1	09H	.38		TEC	TEH	.560	ZBATF	17	H	
93	32	.89	177	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	17	H	
95	32	2.52	176	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	17	H	
95	32	2.27	178	DNT		P1	09H	.38		TEC	TEH	.560	ZBATF	17	H	
95	32	2.55	175	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	17	H	
95	32	3.10	178	DNT		P1	09C	.49		TEC	TEH	.560	ZBATF	17	H	
90	33	.95	172	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	18	H	
92	33	1.33	175	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	17	H	
92	33	1.32	177	DNT		P1	09H	.41		TEC	TEH	.560	ZBATF	17	H	
92	33	2.39	178	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	17	H	
92	33	2.01	178	DNT		P1	09C	.49		TEC	TEH	.560	ZBATF	17	H	
94	33	1.19	175	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	18	H	
94	33	1.27	172	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	18	H	
94	33	1.81	175	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	18	H	
94	33	2.24	175	DNT		P1	09C	.49		TEC	TEH	.560	ZBATF	18	H	
96	33	1.89	175	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	17	H	
96	33	2.49	177	DNT		P1	09H	.36		TEC	TEH	.560	ZBATF	17	H	
96	33	3.54	176	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	17	H	
96	33	5.09	179	DNT		P1	09C	.49		TEC	TEH	.560	ZBATF	17	H	
91	34	1.00	174	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	18	H	
93	34	1.05	173	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	17	H	
93	34	.79	173	DNT		P1	09H	.53		TEC	TEH	.560	ZBATF	17	H	
93	34	1.82	175	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	17	H	
93	34	1.46	177	DNT		P1	09C	.52		TEC	TEH	.560	ZBATF	17	H	
95	34	1.15	174	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	18	H	
95	34	1.68	176	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	18	H	
95	34	2.16	175	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	18	H	
95	34	3.38	176	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	18	H	
97	34	2.08	176	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	17	H	
97	34	2.53	178	DNT		P1	09H	.38		TEC	TEH	.560	ZBATF	17	H	
97	34	4.16	177	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	17	H	
97	34	5.37	179	DNT		P1	09C	.49		TEC	TEH	.560	ZBATF	17	H	
18	35	1.23	184	DNT		P1	02C	22.36		TEC	TEH	.560	ZBATF	13	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
90	35	.87	175	DNT		P1	09C	-.57		TEC	TEH	.560	ZBATF	17	H	
92	35	1.56	176	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	18	H	
94	35	.94	173	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	17	H	
94	35	2.87	177	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	17	H	
94	35	1.59	177	DNT		P1	09C	.49		TEC	TEH	.560	ZBATF	17	H	
96	35	1.51	175	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	18	H	
96	35	1.46	175	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	18	H	
96	35	2.26	176	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	18	H	
96	35	3.55	177	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	18	H	
98	35	2.74	177	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	17	H	
98	35	2.53	178	DNT		P1	09H	.36		TEC	TEH	.560	ZBATF	17	H	
98	35	2.98	177	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	17	H	
7	36	2.27	183	DNT		P1	08H	8.59		TEC	TEH	.560	ZBATF	13	H	
43	36	2.83	178	DNT		P1	09C	.62		TEC	TEH	.560	ZBATF	14	H	
93	36	.95	174	DNT		P1	09H	-.56		TEC	TEH	.560	ZBATF	17	H	
93	36	1.55	174	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	17	H	
95	36	1.28	175	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	18	H	
95	36	3.19	177	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	18	H	
95	36	1.80	176	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	18	H	
97	36	2.40	176	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	17	H	
97	36	.98	176	DNT		P1	09H	.46		TEC	TEH	.560	ZBATF	17	H	
97	36	3.40	176	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	17	H	
97	36	3.86	177	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	17	H	
99	36	3.34	177	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	17	H	
99	36	1.81	177	DNT		P1	09H	.36		TEC	TEH	.560	ZBATF	17	H	
99	36	4.90	177	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	17	H	
99	36	5.33	179	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	17	H	
94	37	1.04	174	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	18	H	
94	37	1.37	174	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	18	H	
96	37	2.22	176	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	17	H	
96	37	1.29	175	DNT		P1	09H	.38		TEC	TEH	.560	ZBATF	17	H	
96	37	3.47	177	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	17	H	
96	37	2.85	178	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	17	H	
98	37	2.80	177	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	18	H	
98	37	1.06	173	DNT		P1	09H	.38		TEC	TEH	.560	ZBATF	18	H	
98	37	4.19	176	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	18	H	
98	37	3.86	177	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	18	H	
100	37	3.57	177	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	17	H	
100	37	1.48	173	DNT		P1	09H	.38		TEC	TEH	.560	ZBATF	17	H	
100	37	5.15	177	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	17	H	
100	37	3.53	178	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	17	H	
93	38	1.36	176	DNT		P1	09C	-.49		TEC	TEH	.560	ZBATF	17	H	
95	38	1.57	175	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	18	H	
95	38	.74	173	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	18	H	
95	38	3.27	176	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	18	H	
95	38	1.74	175	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	18	H	
97	38	1.77	175	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	17	H	
97	38	.76	172	DNT		P1	09H	.41		TEC	TEH	.560	ZBATF	17	H	
97	38	3.57	178	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	17	H	
97	38	1.85	175	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	17	H	
99	38	3.06	176	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	18	H	
99	38	.95	169	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	18	H	
99	38	3.87	175	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	18	H	
99	38	2.63	174	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	18	H	
101	38	4.68	177	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	17	H	
101	38	1.81	175	DNT		P1	09H	.36		TEC	TEH	.560	ZBATF	17	H	
101	38	5.44	177	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	17	H	
101	38	3.50	177	DNT		P1	09C	.49		TEC	TEH	.560	ZBATF	17	H	
50	39	1.13	179	DNT		P1	07H	-.43		TEC	TEH	.560	ZBATF	17	H	
94	39	2.24	174	DNT		P1	09C	-.48		TEC	TEH	.560	ZBATF	17	H	
94	39	1.22	174	DNT		P1	09C	.57		TEC	TEH	.560	ZBATF	17	H	
96	39	1.01	174	DNT		P1	09H	-.60		TEC	TEH	.560	ZBATF	18	H	
96	39	3.48	178	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	18	H	
96	39	2.36	176	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	18	H	
98	39	1.49	175	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	17	H	
98	39	4.39	178	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	17	H	
98	39	1.94	178	DNT		P1	09C	.57		TEC	TEH	.560	ZBATF	17	H	

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
100	39	2.57	176	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	18	H	
100	39	1.55	173	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	18	H	
100	39	4.90	176	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	18	H	
100	39	3.84	177	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	18	H	
102	39	4.00	178	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	17	H	
102	39	1.04	172	DNT		P1	09H	.38		TEC	TEH	.560	ZBATF	17	H	
102	39	7.25	179	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	17	H	
102	39	5.21	179	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	17	H	
95	40	1.20	172	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	20	H	
97	40	2.47	177	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	19	H	
97	40	3.16	178	DNT		P1	09C	-.46		TEC	TEH	.560	ZBATF	19	H	
97	40	1.47	177	DNT		P1	09C	.57		TEC	TEH	.560	ZBATF	19	H	
97	40	1.10	177	DNT		P1	08C	9.74		TEC	TEH	.560	ZBATF	19	H	
99	40	1.73	174	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	20	H	
99	40	3.74	179	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	20	H	
99	40	2.17	176	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	20	H	
101	40	2.72	178	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	19	H	
101	40	1.46	174	DNT		P1	09H	.46		TEC	TEH	.560	ZBATF	19	H	
101	40	4.80	179	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	19	H	
101	40	3.10	178	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	19	H	
103	40	5.38	175	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	48	H	
103	40	1.62	174	DNT		P1	09H	.36		TEC	TEH	.560	ZBATF	48	H	
103	40	3.69	177	DNT		P1	09C	-.55		TEC	TEH	.560	ZBATF	48	H	
103	40	2.10	175	DNT		P1	09C	.44		TEC	TEH	.560	ZBATF	48	H	
103	40	1.40	170	DNT		P1	07C	.31		TEC	TEH	.560	ZBATF	48	H	
96	41	1.90	178	DNT		P1	09C	-.49		TEC	TEH	.560	ZBATF	19	H	
96	41	.94	174	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	19	H	
98	41	1.07	174	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	20	H	
100	41	1.61	175	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	48	H	
100	41	2.81	178	DNT		P1	09C	-.47		TEC	TEH	.560	ZBATF	48	H	
100	41	1.91	176	DNT		P1	09C	.52		TEC	TEH	.560	ZBATF	48	H	
102	41	2.73	177	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	20	H	
102	41	1.77	178	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	20	H	
102	41	2.59	177	DNT		P1	09C	-.63		TEC	TEH	.560	ZBATF	20	H	
102	41	.98	171	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	20	H	
104	41	3.81	178	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	19	H	
104	41	1.71	176	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	19	H	
104	41	4.22	178	DNT		P1	09C	-.46		TEC	TEH	.560	ZBATF	19	H	
104	41	2.24	175	DNT		P1	09C	.49		TEC	TEH	.560	ZBATF	19	H	
59	42	1.78	173	DNT		P1	08C	3.87		TEC	TEH	.560	ZBATF	20	H	
101	42	1.49	173	DNT		P1	09H	-.62		TEC	TEH	.560	ZBATF	48	H	
101	42	.78	172	DNT		P1	09H	.41		TEC	TEH	.560	ZBATF	48	H	
101	42	2.25	175	DNT		P1	09C	-.49		TEC	TEH	.560	ZBATF	48	H	
103	42	2.49	177	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	20	H	
103	42	1.13	175	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	20	H	
103	42	1.64	175	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	20	H	
103	42	.90	170	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	20	H	
105	42	2.82	178	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	19	H	
105	42	2.14	179	DNT		P1	09H	.41		TEC	TEH	.560	ZBATF	19	H	
105	42	2.87	179	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	19	H	
105	42	1.56	175	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	19	H	
100	43	1.53	176	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	20	H	
102	43	2.06	178	DNT		P1	09C	-.44		TEC	TEH	.560	ZBATF	19	H	
102	43	1.30	176	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	19	H	
104	43	1.36	175	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	20	H	
104	43	1.16	175	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	20	H	
106	43	2.21	175	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	48	H	
106	43	1.70	175	DNT		P1	09H	.33		TEC	TEH	.560	ZBATF	48	H	
106	43	3.85	174	DNT		P1	09C	-.55		TEC	TEH	.560	ZBATF	48	H	
106	43	2.67	177	DNT		P1	09C	.50		TEC	TEH	.560	ZBATF	48	H	
103	44	1.69	175	DNT		P1	09C	-.50		TEC	TEH	.560	ZBATF	22	H	
105	44	1.00	175	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	21	H	
105	44	1.46	173	DNT		P1	09C	-.50		TEC	TEH	.560	ZBATF	21	H	
105	44	1.46	175	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	21	H	
107	44	.99	178	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	21	H	
107	44	.85	169	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	21	H	
107	44	3.61	178	DNT		P1	09C	-.50		TEC	TEH	.560	ZBATF	21	H	
107	44	3.83	178	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	21	H	
104	45	1.27	176	DNT		P1	09C	-.48		TEC	TEH	.560	ZBATF	21	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
104	45	1.28	176	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	21	H	
106	45	1.86	174	DNT		P1	09H	-.60		TEC	TEH	.560	ZBATF	22	H	
106	45	1.81	178	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	22	H	
106	45	1.44	173	DNT		P1	09C	-.50		TEC	TEH	.560	ZBATF	22	H	
106	45	1.22	174	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	22	H	
108	45	2.22	174	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	21	H	
108	45	3.92	178	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	21	H	
108	45	1.85	176	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	21	H	
108	45	1.64	174	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	21	H	
59	46	1.10	187	DNT		P1	06H	31.59		TEC	TEH	.560	ZBATF	21	H	
105	46	.88	176	DNT		P1	09C	-.48		TEC	TEH	.560	ZBATF	21	H	
105	46	.90	175	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	21	H	
107	46	1.16	173	DNT		P1	09H	-.61		TEC	TEH	.560	ZBATF	21	H	
107	46	1.64	175	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	21	H	
107	46	1.01	176	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	21	H	
94	47	1.25	183	DNT		P1	08C	15.74		TEC	TEH	.560	ZBATF	21	H	
106	47	1.56	174	DNT		P1	09C	-.48		TEC	TEH	.560	ZBATF	21	H	
106	47	2.26	178	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	21	H	
108	47	2.40	176	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	21	H	
108	47	1.54	173	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	21	H	
108	47	2.78	178	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	21	H	
45	48	1.28	179	DNT		P1	04C	-.58		TEC	TEH	.560	ZBATF	3	H	
93	48	1.33	182	DNT		P1	05C	4.36		TEC	TEH	.560	ZBATF	23	H	
107	48	1.13	173	DNT		P1	09H	.38		TEC	TEH	.560	ZBATF	24	H	
107	48	1.57	174	DNT		P1	09C	-.48		TEC	TEH	.560	ZBATF	24	H	
107	48	3.12	178	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	24	H	
109	48	1.20	173	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	23	H	
109	48	2.91	177	DNT		P1	09H	.41		TEC	TEH	.560	ZBATF	23	H	
109	48	2.25	176	DNT		P1	09C	-.49		TEC	TEH	.560	ZBATF	23	H	
109	48	5.38	177	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	23	H	
98	49	1.16	171	DNT		P1	07H	19.16		TEC	TEH	.560	ZBATF	23	H	
98	49	1.15	173	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	23	H	
106	49	.98	170	DNT		P1	09H	-.58		TSC	TEH	.560	ZBATF	23	H	
106	49	2.26	176	DNT		P1	09H	.46		TSC	TEH	.560	ZBATF	23	H	
106	49	.84	173	DNT		P1	09C	-.41		TSC	TEH	.560	ZBATF	23	H	
106	49	1.89	175	DNT		P1	09C	.56		TSC	TEH	.560	ZBATF	23	H	
106	49	.70	171	DNT		P1	09H	-.58		TSC	TEH	.560	ZBATF	51	H	
106	49	2.23	178	DNT		P1	09H	.45		TSC	TEH	.560	ZBATF	51	H	
106	49	.97	172	DNT		P1	09C	-.40		TSC	TEH	.560	ZBATF	51	H	
106	49	1.51	179	DNT		P1	09C	.51		TSC	TEH	.560	ZBATF	51	H	
108	49	1.22	174	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	24	H	
108	49	2.46	174	DNT		P1	09C	-.48		TEC	TEH	.560	ZBATF	24	H	
108	49	4.43	177	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	24	H	
110	49	2.68	175	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	23	H	
110	49	4.88	177	DNT		P1	09H	.41		TEC	TEH	.560	ZBATF	23	H	
110	49	3.26	175	DNT		P1	09C	-.49		TEC	TEH	.560	ZBATF	23	H	
110	49	6.06	177	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	23	H	
15	50	1.22	182	DNT		P1	02H	24.73		TEC	TEH	.560	ZBATF	5	H	
61	50	2.27	182	DNT		P1	03H	32.25		TEC	TEH	.560	ZBATF	23	H	
105	50	1.31	176	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	23	H	
107	50	1.10	174	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	24	H	
107	50	1.03	172	DNT		P1	09C	-.48		TEC	TEH	.560	ZBATF	24	H	
107	50	1.79	175	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	24	H	
109	50	2.26	175	DNT		P1	09H	-.58		TEC	TEH	.560	ZBATF	23	H	
109	50	4.48	179	DNT		P1	09H	.46		TEC	TEH	.560	ZBATF	23	H	
109	50	1.34	174	DNT		P1	09C	-.49		TEC	TEH	.560	ZBATF	23	H	
109	50	3.14	177	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	23	H	
111	50	2.44	175	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	23	H	
111	50	4.37	178	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	23	H	
111	50	3.60	175	DNT		P1	09C	-.49		TEC	TEH	.560	ZBATF	23	H	
111	50	1.46	172	DNT		P1	09C	.00		TEC	TEH	.560	ZBATF	23	H	
111	50	6.51	177	DNT		P1	09C	.49		TEC	TEH	.560	ZBATF	23	H	
106	51	1.10	171	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	23	H	
108	51	1.78	176	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	24	H	
108	51	1.17	174	DNT		P1	09C	-.46		TEC	TEH	.560	ZBATF	24	H	
108	51	2.64	177	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	24	H	
110	51	2.38	173	DNT		P1	09H	-.61		TEC	TEH	.560	ZBATF	23	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
110	51	5.30	178	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	23	H	
110	51	1.95	176	DNT		P1	09C	-.49		TEC	TEH	.560	ZBATF	23	H	
110	51	3.95	176	DNT		P1	09C	.49		TEC	TEH	.560	ZBATF	23	H	
105	52	1.48	178	DNT		P1	09C	.59		TEC	TEH	.560	ZBATF	23	H	
107	52	1.70	175	DNT		P1	09H	.45		TEC	TEH	.560	ZBATF	24	H	
107	52	1.55	175	DNT		P1	09C	.59		TEC	TEH	.560	ZBATF	24	H	
109	52	1.68	175	DNT		P1	09H	-.59		TEC	TEH	.560	ZBATF	23	H	
109	52	5.23	179	DNT		P1	09H	.59		TEC	TEH	.560	ZBATF	23	H	
109	52	2.72	178	DNT		P1	09C	-.42		TEC	TEH	.560	ZBATF	23	H	
109	52	6.65	178	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	23	H	
111	52	2.47	174	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	23	H	
111	52	4.57	178	DNT		P1	09H	.41		TEC	TEH	.560	ZBATF	23	H	
111	52	3.12	176	DNT		P1	09C	-.44		TEC	TEH	.560	ZBATF	23	H	
111	52	7.40	177	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	23	H	
98	53	2.07	176	DNT		P1	08C	11.91		TEC	TEH	.560	ZBATF	24	H	
104	53	1.05	179	DNT		P1	09C	.61		TEC	TEH	.560	ZBATF	23	H	
106	53	1.06	175	DNT		P1	09H	.48		TEC	TEH	.560	ZBATF	24	H	
106	53	1.02	172	DNT		P1	09C	-.43		TEC	TEH	.560	ZBATF	24	H	
106	53	1.84	177	DNT		P1	09C	.64		TEC	TEH	.560	ZBATF	24	H	
108	53	1.41	176	DNT		P1	09H	-.56		TEC	TEH	.560	ZBATF	23	H	
108	53	3.74	179	DNT		P1	09H	.48		TEC	TEH	.560	ZBATF	23	H	
108	53	1.20	176	DNT		P1	09C	-.42		TEC	TEH	.560	ZBATF	23	H	
108	53	3.14	177	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	23	H	
110	53	2.93	175	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	24	H	
110	53	4.35	177	DNT		P1	09H	.45		TEC	TEH	.560	ZBATF	24	H	
110	53	2.59	175	DNT		P1	09C	-.46		TEC	TEH	.560	ZBATF	24	H	
110	53	4.18	177	DNT		P1	09C	.58		TEC	TEH	.560	ZBATF	24	H	
112	53	1.46	172	DNT		P1	08H	22.36		TEC	TEH	.560	ZBATF	23	H	
112	53	5.76	177	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	23	H	
112	53	8.29	179	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	23	H	
112	53	5.77	177	DNT		P1	09C	-.52		TEC	TEH	.560	ZBATF	23	H	
112	53	10.50	177	DNT		P1	09C	.59		TEC	TEH	.560	ZBATF	23	H	
112	53	2.10	175	DNT		P1	08C	14.27		TEC	TEH	.560	ZBATF	23	H	
112	53	1.51	172	DNT		P1	08C	20.23		TEC	TEH	.560	ZBATF	23	H	
63	54	1.02	182	DNT		P1	08H	27.82		TEC	TEH	.560	ZBATF	24	H	
107	54	1.17	173	DNT		P1	09H	.48		TEC	TEH	.560	ZBATF	23	H	
107	54	1.55	176	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	23	H	
109	54	1.63	177	DNT		P1	09H	.46		TEC	TEH	.560	ZBATF	24	H	
109	54	.94	174	DNT		P1	09C	-.48		TEC	TEH	.560	ZBATF	24	H	
109	54	1.94	176	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	24	H	
111	54	1.63	173	DNT		P1	09H	-.61		TSC	TEH	.560	ZBATF	23	H	
111	54	2.67	176	DNT		P1	09H	.43		TSC	TEH	.560	ZBATF	23	H	
111	54	2.80	178	DNT		P1	09C	-.47		TSC	TEH	.560	ZBATF	23	H	
111	54	4.62	177	DNT		P1	09C	.54		TSC	TEH	.560	ZBATF	23	H	
111	54	2.01	174	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	48	H	
111	54	3.09	175	DNT		P1	09H	.41		TEC	TEH	.560	ZBATF	48	H	
111	54	3.70	176	DNT		P1	09C	-.45		TEC	TEH	.560	ZBATF	48	H	
111	54	4.28	177	DNT		P1	09C	.52		TEC	TEH	.560	ZBATF	48	H	
113	54	2.35	176	DNT		P1	09H	-.64		TSC	TEH	.560	ZBATF	23	H	
113	54	3.62	177	DNT		P1	09H	.41		TSC	TEH	.560	ZBATF	23	H	
113	54	3.56	177	DNT		P1	09C	-.49		TSC	TEH	.560	ZBATF	23	H	
113	54	5.33	177	DNT		P1	09C	.49		TSC	TEH	.560	ZBATF	23	H	
113	54	1.15	171	DNT		P1	08C	8.90		TSC	TEH	.560	ZBATF	23	H	
113	54	2.04	178	DNT		P1	09H	-.72		TEC	TEH	.560	ZBATF	48	H	
113	54	4.21	176	DNT		P1	09H	.36		TEC	TEH	.560	ZBATF	48	H	
113	54	5.00	175	DNT		P1	09C	-.49		TEC	TEH	.560	ZBATF	48	H	
113	54	4.57	178	DNT		P1	09C	.49		TEC	TEH	.560	ZBATF	48	H	
28	55	1.60	179	DNT		P1	03C	11.98		TEC	TEH	.560	ZBATF	4	H	
36	55	1.11	180	DNT		P1	06C	20.66		TEC	TEH	.560	ZBATF	4	H	
108	55	1.14	180	DNT		P1	09C	-.39		TEC	TEH	.560	ZBATF	25	H	
108	55	3.16	179	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	25	H	
110	55	1.03	174	DNT		P1	09H	-.58		TEC	TEH	.560	ZBATF	26	H	
110	55	1.19	178	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	26	H	
110	55	2.26	177	DNT		P1	09C	-.43		TEC	TEH	.560	ZBATF	26	H	
110	55	2.60	179	DNT		P1	09C	.59		TEC	TEH	.560	ZBATF	26	H	
112	55	3.11	177	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	25	H	
112	55	4.02	178	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	25	H	
112	55	2.64	178	DNT		P1	09C	-.44		TEC	TEH	.560	ZBATF	25	H	
112	55	1.27	179	DNT		P1	09C	.00		TEC	TEH	.560	ZBATF	25	H	
112	55	4.56	178	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	25	H	
15	56	2.43	177	DNT		P1	03H	14.31		TEC	TEH	.560	ZBATF	3	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM	*
27	56	1.11	185	DNT		P1	06H	30.92		TEC	TEH	.560	ZBATF	3	H		
109	56	1.77	177	DNT		P1	09C	-.41		TEC	TEH	.560	ZBATF	25	H		
109	56	4.88	178	DNT		P1	09C	.59		TEC	TEH	.560	ZBATF	25	H		
111	56	1.56	177	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	26	H		
111	56	1.36	178	DNT		P1	09H	.48		TEC	TEH	.560	ZBATF	26	H		
111	56	2.65	178	DNT		P1	09C	-.43		TEC	TEH	.560	ZBATF	26	H		
111	56	2.67	180	DNT		P1	09C	.58		TEC	TEH	.560	ZBATF	26	H		
113	56	2.73	177	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	25	H		
113	56	3.08	177	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	25	H		
113	56	3.38	180	DNT		P1	09C	-.47		TEC	TEH	.560	ZBATF	25	H		
113	56	4.34	178	DNT		P1	09C	.49		TEC	TEH	.560	ZBATF	25	H		
90	57	1.31	182	DNT		P1	FBC	-.60		TEC	TEH	.560	ZBATF	25	H		
108	57	1.12	175	DNT		P1	09C	-.43		TEC	TEH	.560	ZBATF	26	H		
110	57	.96	177	DNT		P1	09C	-.42		TEC	TEH	.560	ZBATF	25	H		
110	57	1.23	180	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	25	H		
112	57	.91	175	DNT		P1	09H	-.60		TEC	TEH	.560	ZBATF	26	H		
112	57	1.93	177	DNT		P1	09C	-.48		TEC	TEH	.560	ZBATF	26	H		
112	57	1.63	175	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	26	H		
114	57	2.03	175	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	25	H		
114	57	1.79	176	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	25	H		
114	57	2.26	176	DNT		P1	09C	-.52		TEC	TEH	.560	ZBATF	25	H		
114	57	1.90	176	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	25	H		
1	58	1.03	177	DNT		P1	04C	1.67		09H	TEC	.560	ZBATF	6	C		
87	58	1.46	183	DNT		P1	04H	2.57		TEC	TEH	.560	ZBATF	26	H		
111	58	1.12	177	DNT		P1	09H	-.58		TEC	TEH	.560	ZBATF	26	H		
111	58	2.40	177	DNT		P1	09H	.45		TEC	TEH	.560	ZBATF	26	H		
111	58	1.07	177	DNT		P1	09C	-.46		TEC	TEH	.560	ZBATF	26	H		
111	58	1.46	178	DNT		P1	09C	.58		TEC	TEH	.560	ZBATF	26	H		
111	58	1.02	175	DNT		P1	08C	25.38		TEC	TEH	.560	ZBATF	26	H		
113	58	.99	177	DNT		P1	09H	-.58		TEC	TEH	.560	ZBATF	25	H		
113	58	1.06	177	DNT		P1	09H	.46		TEC	TEH	.560	ZBATF	25	H		
113	58	.98	179	DNT		P1	09C	-.49		TEC	TEH	.560	ZBATF	25	H		
113	58	1.01	172	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	25	H		
74	59	.95	187	DNT		P1	03H	18.09		TEC	TEH	.560	ZBATF	25	H		
112	59	2.86	183	DNT		P1	01H	13.92		TEC	TEH	.560	ZBATF	26	H		
112	59	.91	176	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	26	H		
112	59	1.38	176	DNT		P1	09H	.58		TEC	TEH	.560	ZBATF	26	H		
112	59	1.14	175	DNT		P1	09C	-.46		TEC	TEH	.560	ZBATF	26	H		
114	59	1.09	175	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	25	H		
114	59	1.26	176	DNT		P1	09H	.46		TEC	TEH	.560	ZBATF	25	H		
115	60	1.14	173	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	25	H		
115	60	1.80	175	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	25	H		
115	60	1.35	173	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	25	H		
21	62	1.16	183	DNT		P1	01C	6.31		TEC	TEH	.560	ZBATF	5	H		
63	62	7.32	178	DNT		P1	08H	31.22		TEC	TEH	.560	ZBATF	28	H		
63	62	1.54	175	DNT		P1	08H	35.53		TEC	TEH	.560	ZBATF	28	H		
63	62	2.04	177	DNT		P1	08C	33.06		TEC	TEH	.560	ZBATF	28	H		
69	62	1.20	182	DNT		P1	03H	16.59		TEC	TEH	.560	ZBATF	27	H		
85	62	1.01	170	DNT		P1	08C	9.49		TEC	TEH	.560	ZBATF	27	H		
85	62	1.03	173	DNT		P1	08C	29.41		TEC	TEH	.560	ZBATF	27	H		
115	62	1.04	172	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	27	H		
26	65	2.25	181	DNT		P1	03C	26.48		TEC	TEH	.560	ZBATF	8	H		
56	65	1.44	184	DNT		P1	TSC	8.27		TEC	TEH	.560	ZBATF	28	H		
94	65	1.38	186	DNT		P1	03H	33.75		TEC	TEH	.560	ZBATF	27	H		
115	66	.73	172	DNT		P1	09H	.51		TEC	TEH	.560	ZBATF	27	H		
84	67	.99	184	DNT		P1	08H	14.93		TEC	TEH	.560	ZBATF	30	H		
94	67	1.43	184	DNT		P1	07H	.23		TEC	TEH	.560	ZBATF	29	H		
56	69	1.11	180	DNT		P1	FBH	9.63		TEC	TEH	.560	ZBATF	30	H		
88	69	1.05	181	DNT		P1	07C	.79		TEC	TEH	.560	ZBATF	30	H		
17	70	1.25	184	DNT		P1	TSH	16.90		TEC	TEH	.560	ZBATF	7	H		
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM	

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	*ENDT	PDIA	PTYPE	CAL	L	COM
90	71	.97	186	DNT		P1	08C	.34		TSC	TEH	.560	ZBATF	29	H	
90	71	1.03	183	DNT		P1	08C	.58		TEC	TEH	.560	ZBATF	48	H	
95	72	1.09	183	DNT		P1	FBC	14.99		TEC	TEH	.560	ZBATF	30	H	
37	74	1.91	181	DNT		P1	TSH	9.79		TEC	TEH	.560	ZBATF	43	H	
47	74	1.43	182	DNT		P1	04C	20.03		TEC	TEH	.560	ZBATF	32	H	
115	74	2.47	183	DNT		P1	AV8	17.03		TEC	TEH	.560	ZBATF	31	H	
40	75	1.11	171	DNT		P1	08C	38.03		TEC	TEH	.560	ZBATF	42	H	
5	76	1.00	183	DNT		P1	08H	37.70		TEC	TEH	.560	ZBATF	43	H	
105	76	1.67	188	DNT		P1	08H	24.28		TEC	TEH	.560	ZBATF	31	H	
44	77	2.63	175	DNT		P1	08H	31.62		TEC	TEH	.560	ZBATF	42	H	
44	77	1.69	176	DNT		P1	08H	32.26		TEC	TEH	.560	ZBATF	42	H	
44	77	1.67	176	DNT		P1	08H	34.71		TEC	TEH	.560	ZBATF	42	H	
44	77	.84	171	DNT		P1	09H	.59		TEC	TEH	.560	ZBATF	42	H	
44	77	2.02	173	DNT		P1	09C	-.29		TEC	TEH	.560	ZBATF	42	H	
72	77	1.96	177	DNT		P1	08C	30.27		TEC	TEH	.560	ZBATF	32	H	Result of History Review
90	79	1.39	175	DNT		P1	01C	21.34		TEC	TEH	.560	ZBATF	33	H	
4	81	2.60	182	DNT		P1	07C	24.05		09H	TEC	.560	ZBACS	33	C	
30	81	1.31	184	DNT		P1	02C	23.37		TEC	TEH	.560	ZBATF	44	H	
65	82	1.09	174	DNT		P1	08C	25.59		TEC	TEH	.560	ZBATF	34	H	
32	83	1.01	171	DNT		P1	FBH	14.87		TEC	TEH	.560	ZBATF	47	H	
62	83	1.65	173	DNT		P1	08C	18.39		TEC	TEH	.560	ZBATF	33	H	
62	83	.87	176	DNT		P1	08C	32.21		TEC	TEH	.560	ZBATF	33	H	
100	85	1.13	175	DNT		P1	02C	6.48		TEC	TEH	.560	ZBATF	48	H	
112	85	1.04	171	DNT		P1	09H	.33		TEC	TEH	.560	ZBATF	48	H	
114	85	1.35	173	DNT		P1	09C	-.52		TEC	TEH	.560	ZBATF	48	H	
114	85	1.56	176	DNT		P1	09C	.47		TEC	TEH	.560	ZBATF	48	H	
47	86	1.17	184	DNT		P1	05C	9.14		TEH	TEC	.560	ZBATF	31	C	
67	86	2.53	179	DNT		P1	04H	19.70		TEH	TEC	.560	ZBATF	30	C	
101	86	2.22	184	DNT		P1	06H	29.89		TEH	TEC	.560	ZBATF	31	C	
111	86	2.15	184	DNT		P1	03C	14.90		TEH	TEC	.560	ZBATF	31	C	
111	86	3.43	184	DNT		P1	02C	33.32		TEH	TEC	.560	ZBATF	31	C	
113	86	1.86	174	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	31	C	
61	88	1.13	181	DNT		P1	08H	6.31		TEH	TEC	.560	ZBATF	30	C	
109	88	1.48	177	DNT		P1	09C	.42		TEH	TEC	.560	ZBATF	31	C	
113	88	1.01	172	DNT		P1	09H	-.59		TEH	TEC	.560	ZBATF	30	C	
113	88	1.90	173	DNT		P1	09H	.51		TEH	TEC	.560	ZBATF	30	C	
34	89	1.44	182	DNT		P1	05C	10.95		TEC	TEH	.560	ZBATF	47	H	
52	89	1.52	181	DNT		P1	TSC	14.82		TEH	TEC	.560	ZBATF	30	C	
76	89	1.76	182	DNT		P1	08H	12.99		TEH	TEC	.560	ZBATF	30	C	
92	89	1.35	179	DNT		P1	05C	1.87		TEH	TEC	.560	ZBATF	30	C	
96	89	2.18	179	DNT		P1	07H	.33		TEH	TEC	.560	ZBATF	30	C	
110	89	1.70	174	DNT		P1	09C	.36		TEH	TEC	.560	ZBATF	30	C	
112	89	1.58	177	DNT		P1	09H	.47		TEH	TEC	.560	ZBATF	31	C	
21	90	1.04	180	DNT		P1	01C	16.13		TEC	TEH	.560	ZBATF	46	H	
77	90	1.65	182	DNT		P1	05H	28.22		TEH	TEC	.560	ZBATF	31	C	
87	90	1.03	179	DNT		P1	06C	15.68		TEH	TEC	.560	ZBATF	30	C	
109	90	1.14	173	DNT		P1	09C	.39		TEH	TEC	.560	ZBATF	31	C	
86	91	1.05	183	DNT		P1	07H	33.79		TEH	TEC	.560	ZBATF	31	C	
5	92	1.22	185	DNT		P1	TSC	.79		TEC	TEH	.560	ZBATF	46	H	
19	92	1.47	182	DNT		P1	07C	7.40		TEC	TEH	.560	ZBATF	46	H	
19	92	1.02	171	DNT		P1	07C	8.17		TEC	TEH	.560	ZBATF	46	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	*LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L COM
79	92	1.07	181	DNT		P1	02C	3.40		TEH	TEC	.560	ZBATF	28	C|
111	92	1.26	177	DNT		P1	09C	.36		TEH	TEC	.560	ZBATF	28	C|
84	93	1.62	178	DNT		P1	TSC	6.36		TEH	TEC	.560	ZBATF	28	C|
110	93	1.24	175	DNT		P1	09C	.36		TEH	TEC	.560	ZBATF	28	C|
41	94	1.72	177	DNT		P1	08H	30.47		TEH	TEC	.560	ZBATF	18	C|
95	94	1.03	182	DNT		P1	05H	9.29		TEH	TEC	.560	ZBATF	29	C|
97	94	1.34	179	DNT		P1	05H	34.05		TEH	TEC	.560	ZBATF	28	C|
95	96	1.46	182	DNT		P1	03C	18.47		TEH	TEC	.560	ZBATF	28	C|
32	97	1.32	179	DNT		P1	04C	7.59		TEH	TEC	.560	ZBATF	17	C|
100	97	1.93	180	DNT		P1	06H	1.72		TEH	TEC	.560	ZBATF	28	C|
53	98	1.26	183	DNT		P1	06C	8.83		TEH	TEC	.560	ZBATF	29	C|
57	98	1.06	186	DNT		P1	07H	30.72		TEH	TEC	.560	ZBATF	29	C|
84	99	5.84	176	DNT		P1	07H	7.44		TEH	TEC	.560	ZBATF	26	C|
3	100	1.65	185	DNT		P1	07C	10.08		09H	TEC	.560	ZBATF	8	C|
101	102	1.33	176	DNT		P1	09C	-.67		TEH	TEC	.560	ZBATF	27	C|
100	103	1.42	173	DNT		P1	09C	-.70		TEH	TEC	.560	ZBATF	26	C|
3	104	1.30	174	DNT		P1	07H	-.77		09H	TEH	.560	ZBATF	49	H|
95	104	1.75	183	DNT		P1	02C	-.65		TEH	TEC	.560	ZBATF	27	C|
99	104	1.07	177	DNT		P1	09C	-.68		TEH	TEC	.560	ZBATF	27	C|
99	104	1.00	173	DNT		P1	09C	.39		TEH	TEC	.560	ZBATF	27	C|
101	104	2.04	173	DNT		P1	09C	-.67		TEH	TEC	.560	ZBATF	26	C|
98	105	1.03	172	DNT		P1	09C	.39		TEH	TEC	.560	ZBATF	27	C|
100	105	1.68	173	DNT		P1	09C	-.72		TEH	TEC	.560	ZBATF	26	C|
100	105	1.10	171	DNT		P1	09C	.38		TEH	TEC	.560	ZBATF	26	C|
29	106	1.43	184	DNT		P1	04C	25.50		TEH	TEC	.560	ZBATF	16	C|
39	106	1.60	183	DNT		P1	07C	24.52		TEH	TEC	.560	ZBATF	16	C|
87	106	1.56	175	DNT		P1	08C	26.73		TEH	TEC	.560	ZBATF	26	C|
89	106	1.01	175	DNT		P1	08C	35.23		TEH	TEC	.560	ZBATF	27	C|
99	106	1.31	172	DNT		P1	09C	-.69		TEH	TEC	.560	ZBATF	24	C|
62	107	1.14	165	DNT		P1	07H	36.13		TEH	TEC	.560	ZBATF	24	C|
62	107	1.82	169	DNT		P1	07H	37.26		TEH	TEC	.560	ZBATF	24	C|
80	107	1.07	181	DNT		P1	05H	35.18		TEH	TEC	.560	ZBATF	25	C|
96	107	1.91	178	DNT		P1	09H	-.47		TEH	TEC	.560	ZBATF	25	C|
96	107	1.79	175	DNT		P1	09H	.58		TEH	TEC	.560	ZBATF	25	C|
21	108	1.41	181	DNT		P1	07H	-1.14		TEH	TEC	.560	ZBATF	16	C|
59	108	1.54	174	DNT		P1	08H	36.58		TEH	TEC	.560	ZBATF	25	C|
61	108	1.13	170	DNT		P1	08C	32.61		TEH	TEC	.560	ZBATF	24	C|
58	109	1.16	182	DNT		P1	06H	20.75		TEH	TEC	.560	ZBATF	25	C|
17	110	1.25	181	DNT		P1	04C	26.90		TEH	TEC	.560	ZBATF	16	C|
95	110	1.18	171	DNT		P1	09C	-.69		TEH	TEC	.560	ZBATF	24	C|
95	110	1.56	173	DNT		P1	09C	.38		TEH	TEC	.560	ZBATF	24	C|
32	111	1.02	176	DNT		P1	02H	11.10		TEH	TEC	.560	ZBATF	15	C|
92	111	1.01	182	DNT		P1	08H	.60		TEH	TEC	.560	ZBATF	25	C|
94	111	1.37	173	DNT		P1	09C	-.72		TEH	TEC	.560	ZBATF	24	C|
94	111	1.58	173	DNT		P1	09C	.36		TEH	TEC	.560	ZBATF	24	C|
77	112	1.18	168	DNT		P1	08C	34.92		TEH	TEC	.560	ZBATF	24	C|
77	112	1.35	167	DNT		P1	08C	35.90		TEH	TEC	.560	ZBATF	24	C|
20	113	1.33	181	DNT		P1	06C	10.47		TEH	TEC	.560	ZBATF	15	C|
37	114	1.29	179	DNT		P1	01H	8.32		TEH	TEC	.560	ZBATF	15	C|
71	114	1.21	171	DNT		P1	08H	24.35		TEH	TEC	.560	ZBATF	22	C|
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
87	114	1.80	174	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	22	C	
87	114	4.04	177	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	22	C	
87	114	1.38	169	DNT		P1	08C	37.35		TEH	TEC	.560	ZBATF	22	C	
87	114	4.13	177	DNT		P1	07C	3.17		TEH	TEC	.560	ZBATF	22	C	
89	114	1.03	177	DNT		P1	09C	-.68		TEH	TEC	.560	ZBATF	23	C	
38	115	1.26	183	DNT		P1	02C	29.70		TEH	TEC	.560	ZBATF	14	C	
43	116	1.11	177	DNT		P1	08C	32.86		TEH	TEC	.560	ZBATF	13	C	
17	118	3.91	173	DNT		P1	TSC	8.99		TEH	TEC	.560	ZBATF	13	C	
17	118	1.29	171	DNT		P1	TSC	9.55		TEH	TEC	.560	ZBATF	13	C	
17	118	2.98	173	DNT		P1	TSC	10.06		TEH	TEC	.560	ZBATF	13	C	
17	118	.96	169	DNT		P1	TSC	10.47		TEH	TEC	.560	ZBATF	13	C	
83	118	1.05	175	DNT		P1	09C	-.70		TEH	TEC	.560	ZBATF	21	C	
85	118	1.62	172	DNT		P1	09C	-.72		TEH	TEC	.560	ZBATF	19	C	
24	119	1.37	181	DNT		P1	02H	15.69		TEH	TEC	.560	ZBATF	14	C	
82	119	1.00	171	DNT		P1	09C	-.72		TEH	TEC	.560	ZBATF	19	C	
45	124	1.42	171	DNT		P1	08H	35.48		TEH	TEC	.560	ZBATF	13	C	
34	125	1.45	179	DNT		P1	08H	7.27		TEH	TEC	.560	ZBATF	14	C	
36	125	1.41	183	DNT		P1	TSH	2.60		TEH	TEC	.560	ZBATF	14	C	
17	126	1.12	180	DNT		P1	08H	20.90		TEH	TEC	.560	ZBATF	13	C	
39	126	1.76	173	DNT		P1	08H	26.89		TEH	TEC	.560	ZBATF	13	C	
22	131	1.26	182	DNT		P1	07C	12.28		TEH	TEC	.560	ZBATF	10	C	
30	131	1.28	184	DNT		P1	03H	.77		TEH	TEC	.560	ZBATF	10	C	
44	131	1.41	179	DNT		P1	05C	22.41		TEH	TEC	.560	ZBATF	10	C	
51	132	1.29	179	DNT		P1	07C	1.21		TEH	TEC	.560	ZBATF	9	C	
2	133	2.76	183	DNT		P1	01H	27.93		09H	TEH	.560	ZBATF	2	H	
24	133	1.26	179	DNT		P1	08H	11.67		TEH	TEC	.560	ZBATF	10	C	
44	133	1.05	181	DNT		P1	06H	1.81		TEH	TEC	.560	ZBATF	10	C	
49	134	1.31	171	DNT		P1	09H	.69		TEH	TEC	.560	ZBATF	9	C	
20	135	1.46	173	DNT		P1	08H	36.63		TEH	TEC	.560	ZBATF	10	C	
20	135	1.32	172	DNT		P1	09H	-.36		TEH	TEC	.560	ZBATF	10	C	
26	137	2.16	185	DNT		P1	03H	15.78		TEH	TEC	.560	ZBATF	12	C	
9	138	1.02	178	DNT		P1	01C	-.05		TEH	TEC	.560	ZBATF	11	C	
9	138	2.24	179	DNT		P1	FBC	13.58		TEH	TEC	.560	ZBATF	11	C	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

Tubes: 319 Records: 660

SG - A ION-QUANTIFIABLE SIGNALS

Shearon Harris RFO11 CQL D75

X 62 TUBE WITH NON-QUANTIFIABLE SIGNAL

* 4 STAY

▫ 1 PLUGGED TUBE

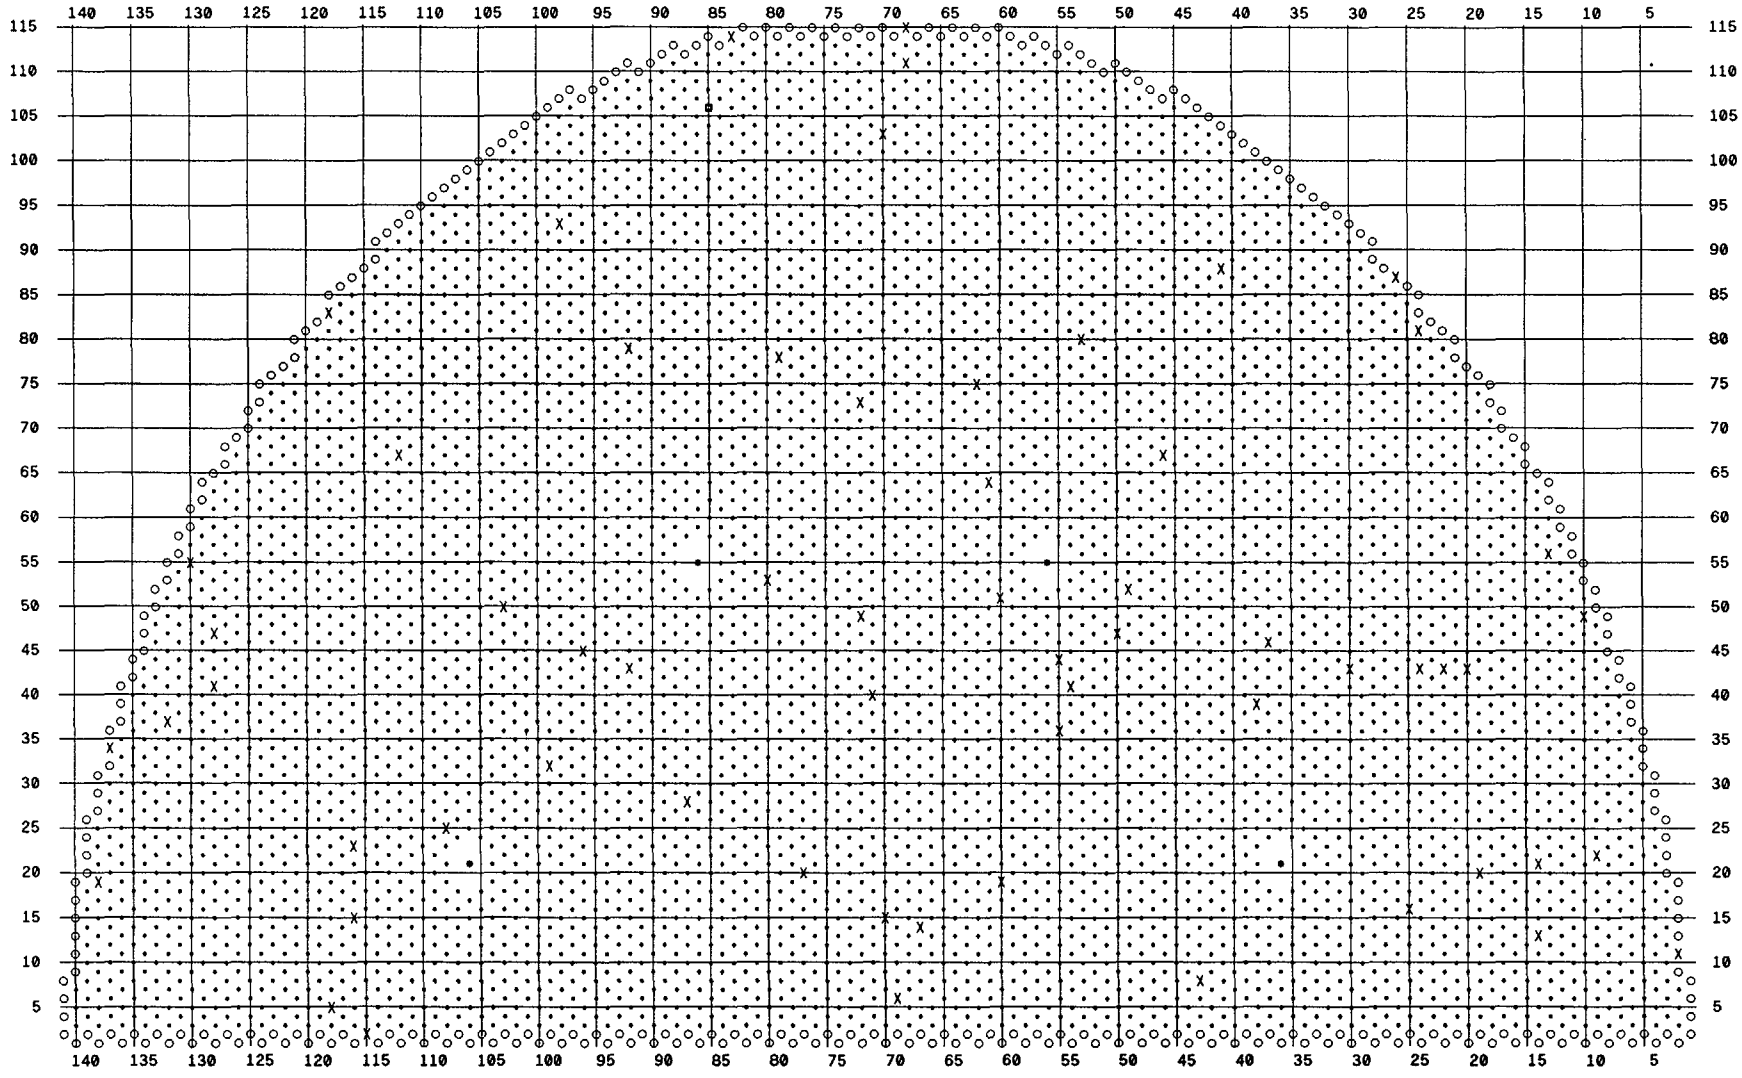

Westinghouse Electric Company LLC - NSBU ST2000 05/07/2003 22:15:26

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	I	CRLEN	CEG	BEGT	ENDT	PDIA	PTYPE	CAL	L COM
11	2	.05	80	NQS		P1	01H	35.66					TEC	TEH	.560	ZBATF	40	H|Result of Senior/History Analyst Review|
22	9	.24	24	NQS		P1	07H	32.32					TEC	TEH	.560	ZBATF	41	H|Result of Senior/History Analyst Review|
49	10	.20	27	NQS		P1	AV2	10.75					TEC	TEH	.560	ZBATF	41	H|Result of Senior/History Analyst Review|
56	13	.06	30	NQS		P1	03C	20.96					TEC	TEH	.560	ZBATF	40	H|Result of Senior/History Analyst Review|
13	14	.14	35	NQS		P1	07C	20.44					TEC	TEH	.560	ZBATF	10	H|Result of Senior/History Analyst Review|
21	14	.10	135	NQS		P1	06C	14.03					TEC	TEH	.560	ZBATF	10	H|Result of Senior/History Analyst Review|
20	19	.32	165	NQS		P1	08H	35.72					TEC	TEH	.560	ZBATF	9	H|Result of Senior/History Analyst Review|
43	20	.39	6	NQS		P1	08H	28.77					TEC	TEH	.560	ZBATF	11	H|Result of Senior/History Analyst Review|
43	22	.58	5	NQS		P1	08H	28.49					TEC	TEH	.560	ZBATF	11	H|Result of Senior/History Analyst Review|
43	24	.35	12	NQS		P1	08H	28.23					TEC	TEH	.560	ZBATF	11	H|Result of Senior/History Analyst Review|
81	24	.19	126	NQS		P1	06H	22.45					TEC	TEH	.560	ZBATF	16	H|Result of Senior/History Analyst Review|
16	25	.57	5	NQS		P1	02C	36.87					TEC	TEH	.560	ZBATF	11	H|Result of Senior/History Analyst Review|
87	26	.22	6	NQS		P1	03H	21.68					TEC	TEH	.560	ZBATF	15	H|Result of Senior/History Analyst Review|
43	30	.46	5	NQS		P1	08H	28.05					TEC	TEH	.560	ZBATF	11	H|Result of Senior/History Analyst Review|
46	37	.06	69	NQS		P1	TSH	15.11					TEC	TEH	.560	ZBATF	18	H|Result of Senior/History Analyst Review|
39	38	.04	84	NQS		P1	05C	25.58					TEC	TEH	.560	ZBATF	13	H|Result of Senior/History Analyst Review|
88	41	.07	150	NQS		P1	05C	16.20					TEC	TEH	.560	ZBATF	19	H|Result of Senior/History Analyst Review|
8	43	.30	7	NQS		P1	08H	9.18					TEC	TEH	.560	ZBATF	13	H|Result of Senior/History Analyst Review|
67	46	.09	34	NQS		P1	03H	36.07					TEC	TEH	.560	ZBATF	21	H|Result of Senior/History Analyst Review|
52	49	.05	110	NQS		P1	06H	33.52					TEC	TEH	.560	ZBATF	24	H|Result of Senior/History Analyst Review|
47	50	.11	147	NQS		P1	05H	4.24					TEC	TEH	.560	ZBATF	24	H|Result of Senior/History Analyst Review|
80	53	.09	66	NQS		P1	07C	1.56					TEC	TEH	.560	ZBATF	23	H|Result of Senior/History Analyst Review|
41	54	.10	92	NQS		P1	08C	11.39					TEC	TEH	.560	ZBATF	3	H|Result of Senior/History Analyst Review|
36	55	.16	25	NQS		P1	08H	1.38					TEC	TEH	.560	ZBATF	4	H|Result of Senior/History Analyst Review|
44	55	.09	39	NQS		P1	FBH	15.76					TEC	TEH	.560	ZBATF	4	H|Result of Senior/History Analyst Review|
19	60	.08	133	NQS		P1	04C	27.17					TEC	TEH	.560	ZBATF	5	H|Result of Senior/History Analyst Review|
51	60	.14	67	NQS		P1	07C	22.85					TEC	TEH	.560	ZBATF	26	H|Result of Senior/History Analyst Review|
64	61	.19	79	NQS		P1	02C	12.64					TEC	TEH	.560	ZBATF	28	H|Result of Senior/History Analyst Review|
75	62	.09	35	NQS		P1	03C	35.82					TEC	TEH	.560	ZBATF	28	H|Result of Senior/History Analyst Review|
14	67	.12	24	NQS		P1	04C	3.28					TEC	TEH	.560	ZBATF	8	H|Result of Senior/History Analyst Review|
111	68	.10	139	NQS		P1	01H	22.92					TEC	TEH	.560	ZBATF	30	H|Result of Senior/History Analyst Review|
115	68	.14	70	NQS		P1	07H	8.22					TEC	TEH	.560	ZBATF	29	H|Result of Senior/History Analyst Review|
6	69	.13	60	NQS		P1	TSC	18.78					TEC	TEH	.560	ZBATF	4	H|Result of Senior/History Analyst Review|
15	70	.12	114	NQS		P1	08C	27.61					TEC	TEH	.560	ZBATF	8	H|Result of Senior/History Analyst Review|
103	70	.11	140	NQS		P1	AV5	16.66					TEC	TEH	.560	ZBATF	30	H|Result of Senior/History Analyst Review|
40	71	.06	99	NQS		P1	02C	17.88					TEC	TEH	.560	ZBATF	42	H|Result of Senior/History Analyst Review|
40	71	.11	0	NQS		P1	02C	18.21					TEC	TEH	.560	ZBATF	42	H|Result of Senior/History Analyst Review|
49	72	.07	150	NQS		P1	08H	8.85					TEC	TEH	.560	ZBATF	29	H|Result of Senior/History Analyst Review|
73	72	.12	30	NQS		P1	08H	32.18					TEC	TEH	.560	ZBATF	29	H|Result of Senior/History Analyst Review|
20	77	.14	128	NQS		P1	06H	3.51					TEC	TEH	.560	ZBATF	42	H|Result of Senior/History Analyst Review|
78	79	.08	41	NQS		P1	03H	6.41					TEC	TEH	.560	ZBATF	33	H|Result of Senior/History Analyst Review|
53	80	.12	24	NQS		P1	08H	13.19					TEC	TEH	.560	ZBATF	33	H|Result of Senior/History Analyst Review|
114	83	.06	62	NQS		P1	01C	5.54					TEC	TEH	.560	ZBATF	33	H|Result of Senior/History Analyst Review|
28	87	.16	18	NQS		P1	01H	8.84					TEC	TEH	.560	ZBATF	47	H|Result of Senior/History Analyst Review|
43	92	.10	49	NQS		P1	08H	33.46					TEC	TEH	.560	ZBATF	47	H|Result of Senior/History Analyst Review|
79	92	.15	96	NQS		P1	05H	25.61					TEH	TEC	.560	ZBATF	28	C|Result of Senior/History Analyst Review|
45	96	.06	67	NQS		P1	05H	20.38					TEH	TEC	.560	ZBATF	18	C|Result of History Review
93	98	.07	78	NQS		P1	TSC	16.62					TEH	TEC	.560	ZBATF	29	C|Result of Senior/History Analyst Review|
32	99	.11	107	NQS		P1	02H	30.92					TEH	TEC	.560	ZBATF	17	C|Result of Senior/History Analyst Review|
50	103	.12	75	NQS		P1	02C	17.23					TEH	TEC	.560	ZBATF	27	C|Result of Senior/History Analyst Review|
25	108	.06	67	NQS		P1	07C	12.75					TEH	TEC	.560	ZBATF	16	C|Result of Senior/History Analyst Review|
67	112	.04	83	NQS		P1	TSH	1.59					TEH	TEC	.560	ZBATF	25	C|Result of Senior/History Analyst Review|
2	115	.15	32	NQS		P1	02H	28.82					09H	TEH	.560	ZBATF	2	H|Result of Senior/History Analyst Review|
15	116	.11	76	NQS		P1	06H	20.38					TEH	TEC	.560	ZBATF	15	C|Result of Senior/History Analyst Review|
23	116	.16	31	NQS		P1	FBH	14.83					TEH	TEC	.560	ZBATF	15	C|Result of Senior/History Analyst Review|
23	116	.14	8	NQS		P1	03H	19.65					TEH	TEC	.560	ZBATF	15	C|Result of Senior/History Analyst Review|
5	118	.07	107	NQS		P1	02H	18.15					TEH	TEC	.560	ZBATF	13	C|Result of Senior/History Analyst Review|
83	118	.09	63	NQS		P1	08C	8.06					TEH	TEC	.560	ZBATF	21	C|Result of Senior/History Analyst Review|
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	I	CRLEN	CEG	BEGT	ENDT	PDIA	PTYPE	CAL	L COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	I	CRLEN	CEG	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
41	128	.09	35	NQS		P1	05H	4.23					TEH	TEC	.560	ZBATF	13	C	Result of Senior/History Analyst Review
47	128	.09	32	NQS		P1	04H	21.96					TEH	TEC	.560	ZBATF	20	C	Result of Senior/History Analyst Review
55	130	.14	49	NQS		P1	FBH	4.31					TEH	TEC	.560	ZBATF	9	C	Result of Senior/History Analyst Review
37	132	.12	92	NQS		P1	F8C	6.80					TEH	TEC	.560	ZBATF	9	C	Result of Senior/History Analyst Review
34	137	.09	120	NQS		P1	02H	35.15					TEH	TEC	.560	ZBATF	10	C	Result of History Review
19	138	.12	120	NQS		P1	TSC	15.91					TEH	TEC	.560	ZBATF	11	C	Result of Senior/History Analyst Review
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	I	CRLEN	CEG	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

SG - A ERMEABILITY VARIATIONS

Shearon Harris RFO11 CQL D75

X 1 TUBE WITH PEMEABILITY VARIATION

* 4 STAY

▫ 1 PLUGGED TUBE

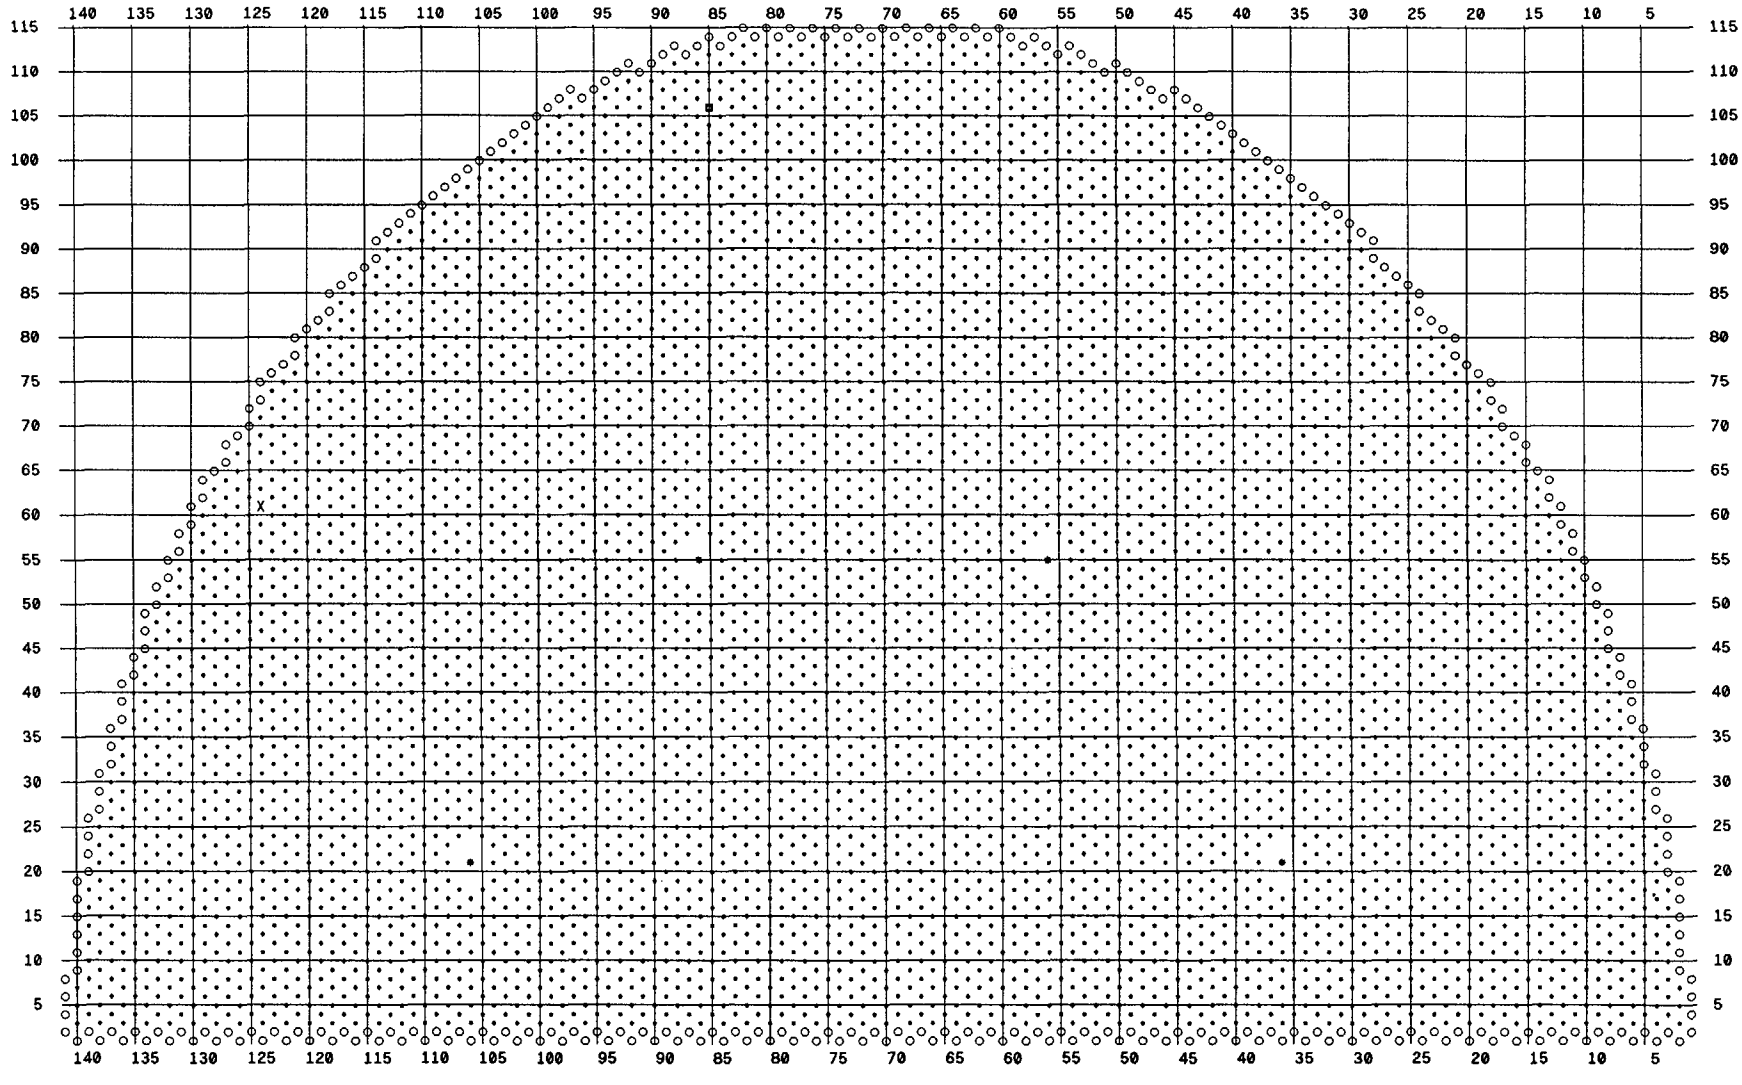

Westinghouse Electric Company LLC - NSBU ST2000 05/07/2003 22:26:52

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
61	124	.31	98	PVN		1	TSH	.00	457.44	TEC	TEH	.560	ZBATF	48	H	Result of Senior/History Analyst Review
61	124															Tube Noise

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

SG - B DENTS

Shearon Harris RFO11 CQL D75

X 634 TUBE WITH DENT

* 4 STAY

▫ 1 PLUGGED TUBE

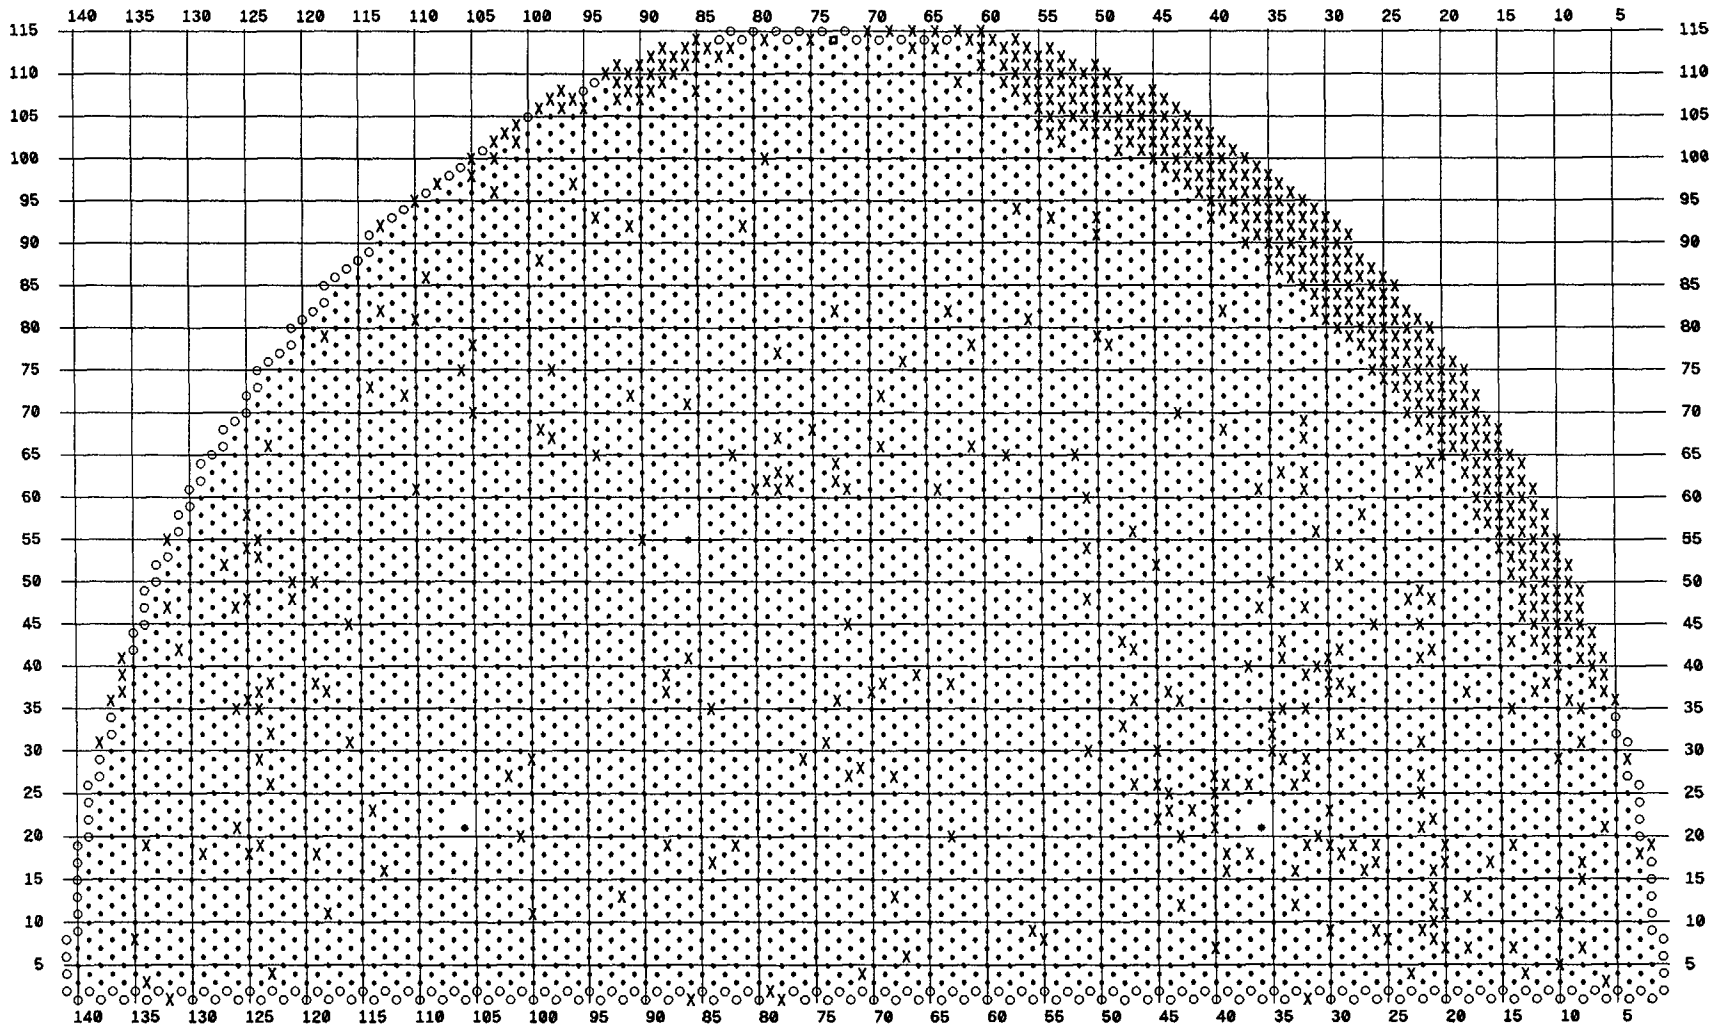

Westinghouse Electric Company LLC - NSBU ST2000 05/08/2003 00:52:23

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
19	2	1.00	172	DNT		P1	09H	-.73		TEC	TEH	.560	ZBATF	34	H	
18	3	1.09	173	DNT		P1	09H	-.65		TEC	TEH	.560	ZBATF	35	H	
29	4	1.02	174	DNT		P1	09C	-.89		TEC	TEH	.560	ZBATF	35	H	
29	4	1.27	182	DNT		P1	08C	18.56		TEC	TEH	.560	ZBATF	35	H	
36	5	1.61	174	DNT		P1	09H	-.97		TEC	TEH	.560	ZBATF	34	H	
3	6	1.00	182	DNT		P1	04H	33.96		09H	TEH	.560	ZBATF	36	H	
21	6	.84	180	DNT		P1	05C	22.02		TEC	TEH	.560	ZBATF	34	H	
37	6	.96	173	DNT		P1	09H	-.81		TEC	TEH	.560	ZBATF	34	H	
37	6	1.83	173	DNT		P1	09C	-.78		TEC	TEH	.560	ZBATF	34	H	
39	6	1.20	175	DNT		P1	09H	-.91		TEC	TEH	.560	ZBATF	35	H	
39	6	1.63	174	DNT		P1	09C	-.78		TEC	TEH	.560	ZBATF	35	H	
41	6	1.75	174	DNT		P1	09H	-.92		TEC	TEH	.560	ZBATF	34	H	
41	6	2.17	174	DNT		P1	09C	-.79		TEC	TEH	.560	ZBATF	34	H	
38	7	1.04	172	DNT		P1	09C	-.78		TEC	TEH	.560	ZBATF	35	H	
40	7	1.26	174	DNT		P1	09H	-.89		TEC	TEH	.560	ZBATF	34	H	
40	7	.93	173	DNT		P1	09C	-.73		TEC	TEH	.560	ZBATF	34	H	
42	7	3.55	174	DNT		P1	09C	-.86		TEC	TEH	.560	ZBATF	35	H	
44	7	2.95	175	DNT		P1	09C	-.66		TEC	TEH	.560	ZBATF	34	H	
7	8	1.86	175	DNT		P1	08C	10.53		TEC	TEH	.560	ZBATF	35	H	
15	8	1.45	173	DNT		P1	08C	31.79		TEC	TEH	.560	ZBATF	35	H	
17	8	1.11	171	DNT		P1	08C	36.59		TEC	TEH	.560	ZBATF	34	H	
31	8	1.09	174	DNT		P1	09C	-.78		TEC	TEH	.560	ZBATF	35	H	
35	8	.51	167	DNT		P1	08H	26.37		TEC	TEH	.560	ZBATF	35	H	
35	8	1.22	175	DNT		P1	09C	-.78		TEC	TEH	.560	ZBATF	35	H	
41	8	1.22	174	DNT		P1	08H	25.61		TEC	TEH	.560	ZBATF	34	H	
41	8	2.37	175	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	34	H	
43	8	1.52	175	DNT		P1	09H	-.86		TEC	TEH	.560	ZBATF	35	H	
43	8	1.74	174	DNT		P1	09C	-.78		TEC	TEH	.560	ZBATF	35	H	
45	8	3.05	175	DNT		P1	09C	-.80		TEC	TEH	.560	ZBATF	34	H	
47	8	.99	172	DNT		P1	09H	-.86		TEC	TEH	.560	ZBATF	35	H	
47	8	4.17	175	DNT		P1	09C	-.83		TEC	TEH	.560	ZBATF	35	H	
49	8	1.98	175	DNT		P1	09H	-.92		TEC	TEH	.560	ZBATF	34	H	
49	8	4.28	177	DNT		P1	09C	-.66		TEC	TEH	.560	ZBATF	34	H	
49	8	1.56	173	DNT		P1	09C	.28		TEC	TEH	.560	ZBATF	34	H	
36	9	1.06	172	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	34	H	
44	9	1.29	175	DNT		P1	09H	-.89		TEC	TEH	.560	ZBATF	34	H	
44	9	1.15	172	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	34	H	
46	9	1.21	173	DNT		P1	09H	-.91		TEC	TEH	.560	ZBATF	35	H	
46	9	2.78	174	DNT		P1	09C	-.78		TEC	TEH	.560	ZBATF	35	H	
48	9	1.29	172	DNT		P1	09H	-.91		TEC	TEH	.560	ZBATF	34	H	
48	9	2.82	174	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	34	H	
50	9	2.25	174	DNT		P1	09H	-.91		TEC	TEH	.560	ZBATF	35	H	
50	9	2.71	175	DNT		P1	09C	-.78		TEC	TEH	.560	ZBATF	35	H	
52	9	1.05	182	DNT		P1	05H	5.31		TEC	TEH	.560	ZBATF	34	H	
52	9	3.99	176	DNT		P1	09H	-.92		TEC	TEH	.560	ZBATF	34	H	
52	9	4.47	176	DNT		P1	09C	-.73		TEC	TEH	.560	ZBATF	34	H	
52	9	1.23	174	DNT		P1	09C	.31		TEC	TEH	.560	ZBATF	34	H	
52	9	1.05	170	DNT		P1	03C	26.52		TEC	TEH	.560	ZBATF	34	H	
5	10	2.66	182	DNT		P1	TSC	11.16		TEC	TEH	.560	ZBATF	35	H	
11	10	1.48	180	DNT		P1	01H	6.34		TEC	TEH	.560	ZBATF	34	H	
29	10	1.34	175	DNT		P1	09C	-.62		TEC	TEH	.560	ZBATF	35	H	
39	10	1.01	172	DNT		P1	09C	-.71		TEC	TEH	.560	ZBATF	34	H	
41	10	2.23	176	DNT		P1	09C	-.78		TEC	TEH	.560	ZBATF	35	H	
43	10	.94	175	DNT		P1	09H	-.78		TEC	TEH	.560	ZBATF	34	H	
43	10	1.27	173	DNT		P1	09C	-.66		TEC	TEH	.560	ZBATF	34	H	
45	10	1.02	171	DNT		P1	08H	36.21		TEC	TEH	.560	ZBATF	35	H	
45	10	1.55	174	DNT		P1	08H	37.51		TEC	TEH	.560	ZBATF	35	H	
45	10	2.29	177	DNT		P1	09H	-.83		TEC	TEH	.560	ZBATF	35	H	
45	10	1.06	174	DNT		P1	09C	-.73		TEC	TEH	.560	ZBATF	35	H	
47	10	1.84	174	DNT		P1	09C	-.77		TEC	TEH	.560	ZBATF	34	H	
49	10	1.46	173	DNT		P1	09H	-.88		TEC	TEH	.560	ZBATF	35	H	
49	10	2.20	174	DNT		P1	09C	-.75		TEC	TEH	.560	ZBATF	35	H	
51	10	1.30	179	DNT		P1	03H	19.67		TEC	TEH	.560	ZBATF	34	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
51	10	2.77	175	DNT		P1	09H	-.89		TEC	TEH	.560	ZBATF	34	H	
51	10	3.93	174	DNT		P1	09C	-.73		TEC	TEH	.560	ZBATF	34	H	
53	10	3.65	176	DNT		P1	09H	-.88		TEC	TEH	.560	ZBATF	35	H	
53	10	1.00	173	DNT		P1	09H	.26		TEC	TEH	.560	ZBATF	35	H	
53	10	3.96	176	DNT		P1	09C	-.75		TEC	TEH	.560	ZBATF	35	H	
55	10	1.25	170	DNT		P1	08H	37.58		TEC	TEH	.560	ZBATF	34	H	
55	10	3.28	175	DNT		P1	09H	-.89		TEC	TEH	.560	ZBATF	34	H	
55	10	5.01	174	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	34	H	
55	10	1.81	173	DNT		P1	09C	.33		TEC	TEH	.560	ZBATF	34	H	
38	11	.69	175	DNT		P1	09C	-.86		TEC	TEH	.560	ZBATF	35	H	
42	11	1.00	173	DNT		P1	09C	-.73		TEC	TEH	.560	ZBATF	35	H	
44	11	1.41	173	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	34	H	
46	11	1.35	173	DNT		P1	09H	-.86		TEC	TEH	.560	ZBATF	35	H	
46	11	.95	180	DNT		P1	09C	-.78		TEC	TEH	.560	ZBATF	35	H	
48	11	1.07	173	DNT		P1	09H	-.81		TEC	TEH	.560	ZBATF	34	H	
48	11	2.10	174	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	34	H	
50	11	1.46	171	DNT		P1	09H	-.86		TEC	TEH	.560	ZBATF	35	H	
50	11	1.43	172	DNT		P1	09C	-.78		TEC	TEH	.560	ZBATF	35	H	
52	11	1.94	174	DNT		P1	09H	-.86		TEC	TEH	.560	ZBATF	34	H	
52	11	4.34	175	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	34	H	
54	11	4.48	178	DNT		P1	09H	-.85		TEC	TEH	.560	ZBATF	35	H	
54	11	.87	174	DNT		P1	09H	.26		TEC	TEH	.560	ZBATF	35	H	
54	11	5.59	178	DNT		P1	09C	-.73		TEC	TEH	.560	ZBATF	35	H	
54	11	1.17	172	DNT		P1	09C	.34		TEC	TEH	.560	ZBATF	35	H	
56	11	3.09	176	DNT		P1	09H	-.89		TEC	TEH	.560	ZBATF	34	H	
56	11	1.03	171	DNT		P1	09H	.16		TEC	TEH	.560	ZBATF	34	H	
56	11	3.96	175	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	34	H	
56	11	1.47	167	DNT		P1	09C	.39		TEC	TEH	.560	ZBATF	34	H	
58	11	4.64	177	DNT		P1	09H	-.86		TEC	TEH	.560	ZBATF	34	H	
58	11	1.35	172	DNT		P1	09H	.16		TEC	TEH	.560	ZBATF	34	H	
58	11	5.61	176	DNT		P1	09C	-.73		TEC	TEH	.560	ZBATF	34	H	
58	11	2.14	170	DNT		P1	09C	.36		TEC	TEH	.560	ZBATF	34	H	
37	12	1.14	180	DNT		P1	08C	12.05		TEC	TEH	.560	ZBATF	35	H	
43	12	1.46	176	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	35	H	
45	12	1.56	173	DNT		P1	09C	-.71		TEC	TEH	.560	ZBATF	34	H	
47	12	1.70	173	DNT		P1	09C	-.73		TEC	TEH	.560	ZBATF	35	H	
49	12	1.67	174	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	34	H	
51	12	2.31	176	DNT		P1	09H	-.83		TEC	TEH	.560	ZBATF	35	H	
51	12	3.18	175	DNT		P1	09C	-.75		TEC	TEH	.560	ZBATF	35	H	
53	12	1.81	175	DNT		P1	09H	-.81		TEC	TEH	.560	ZBATF	34	H	
53	12	4.29	175	DNT		P1	09C	-.71		TEC	TEH	.560	ZBATF	34	H	
55	12	2.30	176	DNT		P1	09H	-.86		TEC	TEH	.560	ZBATF	35	H	
55	12	4.21	176	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	35	H	
57	12	3.39	175	DNT		P1	09H	-.83		TEC	TEH	.560	ZBATF	34	H	
57	12	5.32	176	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	34	H	
59	12	5.68	178	DNT		P1	09H	-.86		TEC	TEH	.560	ZBATF	35	H	
59	12	4.59	177	DNT		P1	09C	-.73		TEC	TEH	.560	ZBATF	35	H	
61	12	4.38	177	DNT		P1	09H	-.86		TEC	TEH	.560	ZBATF	34	H	
61	12	1.72	172	DNT		P1	09H	.22		TEC	TEH	.560	ZBATF	34	H	
61	12	5.89	176	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	34	H	
61	12	1.55	170	DNT		P1	09C	.36		TEC	TEH	.560	ZBATF	34	H	
4	13	2.38	180	DNT		P1	04C	37.55		08H	TEC	.560	ZBACS	40	C	
46	13	1.35	174	DNT		P1	09C	-.73		TEC	TEH	.560	ZBATF	35	H	
48	13	1.22	172	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	35	H	
50	13	1.18	174	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	35	H	
52	13	4.28	177	DNT		P1	09C	-.65		TEC	TEH	.560	ZBATF	35	H	
54	13	2.26	175	DNT		P1	09H	-.83		TEC	TEH	.560	ZBATF	35	H	
54	13	2.31	174	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	35	H	
56	13	3.59	177	DNT		P1	09H	-.83		TEC	TEH	.560	ZBATF	35	H	
56	13	3.31	176	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	35	H	
58	13	3.87	177	DNT		P1	09H	-.85		TEC	TEH	.560	ZBATF	35	H	
58	13	3.82	177	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	35	H	
60	13	5.20	179	DNT		P1	09H	-.85		TEC	TEH	.560	ZBATF	35	H	
60	13	7.03	177	DNT		P1	09C	-.67		TEC	TEH	.560	ZBATF	35	H	
62	13	1.31	182	DNT		P1	01H	25.06		TEC	TEH	.560	ZBATF	35	H	
62	13	7.02	179	DNT		P1	09H	-.85		TEC	TEH	.560	ZBATF	35	H	
62	13	1.50	174	DNT		P1	09H	.23		TEC	TEH	.560	ZBATF	35	H	
62	13	6.44	177	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	35	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
62	13	1.09	175	DNT		P1	09C	.40		TEC	TEH	.560	ZBATF	35	H	
64	13	6.62	178	DNT		P1	09H	-.85		TEC	TEH	.560	ZBATF	35	H	
64	13	1.53	175	DNT		P1	09H	.18		TEC	TEH	.560	ZBATF	35	H	
64	13	6.42	176	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	35	H	
64	13	1.20	174	DNT		P1	09C	.37		TEC	TEH	.560	ZBATF	35	H	
7	14	1.34	177	DNT		P1	08H	27.46		TEH	TEC	.560	ZBATF	16	C	
19	14	1.34	177	DNT		P1	08H	33.97		TEH	TEC	.560	ZBATF	16	C	
19	14	1.47	179	DNT		P1	08C	37.71		TEH	TEC	.560	ZBATF	16	C	
35	14	1.26	174	DNT		P1	01C	3.95		TEH	TEC	.560	ZBATF	16	C	
43	14	.66	180	DNT		P1	09C	-.70		TEH	TEC	.560	ZBATF	16	C	
51	14	1.07	174	DNT		P1	09H	-.77		TEH	TEC	.560	ZBATF	29	C	
51	14	1.30	176	DNT		P1	09C	-.76		TEH	TEC	.560	ZBATF	29	C	
53	14	2.00	177	DNT		P1	09C	-.77		TEH	TEC	.560	ZBATF	30	C	
55	14	.72	174	DNT		P1	09H	-.96		TEH	TEC	.560	ZBATF	29	C	
55	14	2.05	179	DNT		P1	09C	-.76		TEH	TEC	.560	ZBATF	29	C	
57	14	1.43	177	DNT		P1	09H	-.70		TEH	TEC	.560	ZBATF	30	C	
57	14	2.26	176	DNT		P1	09C	-.77		TEH	TEC	.560	ZBATF	30	C	
59	14	2.78	179	DNT		P1	09H	-.74		TEH	TEC	.560	ZBATF	29	C	
59	14	3.32	179	DNT		P1	09C	-.74		TEH	TEC	.560	ZBATF	29	C	
61	14	3.59	178	DNT		P1	09H	-.72		TEH	TEC	.560	ZBATF	30	C	
61	14	5.02	179	DNT		P1	09C	-.77		TEH	TEC	.560	ZBATF	30	C	
63	14	4.28	180	DNT		P1	09H	-.77		TEH	TEC	.560	ZBATF	29	C	
63	14	.74	172	DNT		P1	09H	.34		TEH	TEC	.560	ZBATF	29	C	
63	14	3.14	179	DNT		P1	09C	-.79		TEH	TEC	.560	ZBATF	29	C	
65	14	1.87	175	DNT		P1	09H	-.24		TEC	TEH	.560	ZBATF	45	H	
65	14	1.22	173	DNT		P1	09H	.24		TEC	TEH	.560	ZBATF	45	H	
65	14	4.29	174	DNT		P1	09C	-.69		TEC	TEH	.560	ZBATF	45	H	
54	15	1.50	178	DNT		P1	09C	-.76		TEH	TEC	.560	ZBATF	29	C	
56	15	.86	175	DNT		P1	09H	-.72		TEH	TEC	.560	ZBATF	30	C	
56	15	2.55	177	DNT		P1	09C	-.74		TEH	TEC	.560	ZBATF	30	C	
58	15	1.36	178	DNT		P1	09H	-.74		TEH	TEC	.560	ZBATF	29	C	
58	15	2.02	179	DNT		P1	09C	-.76		TEH	TEC	.560	ZBATF	29	C	
60	15	2.16	178	DNT		P1	09H	-.70		TEH	TEC	.560	ZBATF	30	C	
60	15	2.71	177	DNT		P1	09C	-.75		TEH	TEC	.560	ZBATF	30	C	
62	15	3.06	179	DNT		P1	09H	-.71		TEH	TEC	.560	ZBATF	29	C	
62	15	2.82	180	DNT		P1	09C	-.76		TEH	TEC	.560	ZBATF	29	C	
64	15	4.62	179	DNT		P1	09H	-.70		TEH	TEC	.560	ZBATF	30	C	
64	15	.88	176	DNT		P1	09H	.37		TEH	TEC	.560	ZBATF	30	C	
64	15	4.22	178	DNT		P1	09C	-.74		TEH	TEC	.560	ZBATF	30	C	
66	15	5.49	180	DNT		P1	09H	-.74		TEH	TEC	.560	ZBATF	29	C	
66	15	1.24	176	DNT		P1	09H	.39		TEH	TEC	.560	ZBATF	29	C	
66	15	4.54	180	DNT		P1	09C	-.76		TEH	TEC	.560	ZBATF	29	C	
68	15	5.88	179	DNT		P1	09H	-.72		TEH	TEC	.560	ZBATF	30	C	
68	15	1.78	177	DNT		P1	09H	.34		TEH	TEC	.560	ZBATF	30	C	
68	15	2.38	178	DNT		P1	09C	-.80		TEH	TEC	.560	ZBATF	30	C	
17	16	1.26	175	DNT		P1	08H	31.81		TEH	TEC	.560	ZBATF	16	C	
17	16	1.68	175	DNT		P1	08H	33.29		TEH	TEC	.560	ZBATF	16	C	
57	16	1.67	177	DNT		P1	09C	-.74		TEH	TEC	.560	ZBATF	30	C	
59	16	.94	176	DNT		P1	09C	-.73		TEH	TEC	.560	ZBATF	29	C	
61	16	1.17	177	DNT		P1	09H	-.70		TEH	TEC	.560	ZBATF	30	C	
61	16	2.95	178	DNT		P1	09C	-.72		TEH	TEC	.560	ZBATF	30	C	
63	16	3.19	179	DNT		P1	09H	-.71		TEH	TEC	.560	ZBATF	29	C	
63	16	1.54	178	DNT		P1	09C	-.76		TEH	TEC	.560	ZBATF	29	C	
65	16	3.63	178	DNT		P1	09H	-.67		TEH	TEC	.560	ZBATF	30	C	
65	16	3.68	179	DNT		P1	09C	-.72		TEH	TEC	.560	ZBATF	30	C	
67	16	5.60	180	DNT		P1	09H	-.71		TEH	TEC	.560	ZBATF	29	C	
67	16	.92	175	DNT		P1	09H	.53		TEH	TEC	.560	ZBATF	29	C	
67	16	5.22	181	DNT		P1	09C	-.73		TEH	TEC	.560	ZBATF	29	C	
67	16	.62	171	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	29	C	
69	16	7.26	179	DNT		P1	09H	-.69		TEH	TEC	.560	ZBATF	30	C	
69	16	1.81	180	DNT		P1	09H	.28		TEH	TEC	.560	ZBATF	30	C	
69	16	7.15	178	DNT		P1	09C	-.75		TEH	TEC	.560	ZBATF	30	C	
69	16	1.34	176	DNT		P1	09C	.30		TEH	TEC	.560	ZBATF	30	C	
58	17	3.16	179	DNT		P1	08C	34.95		TEH	TEC	.560	ZBATF	29	C	
58	17	2.23	177	DNT		P1	08C	35.42		TEH	TEC	.560	ZBATF	29	C	
60	17	.93	177	DNT		P1	09H	-.64		TEH	TEC	.560	ZBATF	30	C	
60	17	1.59	178	DNT		P1	09C	-.69		TEH	TEC	.560	ZBATF	30	C	
62	17	1.27	176	DNT		P1	09H	-.74		TEH	TEC	.560	ZBATF	29	C	
62	17	1.43	177	DNT		P1	09C	-.73		TEH	TEC	.560	ZBATF	29	C	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
64	17	2.02	179	DNT		P1	09H	-.67		TEH	TEC	.560	ZBATF	30	C	
64	17	2.04	178	DNT		P1	09C	-.74		TEH	TEC	.560	ZBATF	30	C	
66	17	3.61	179	DNT		P1	09H	-.71		TEH	TEC	.560	ZBATF	29	C	
66	17	2.51	180	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	29	C	
66	17	1.06	176	DNT		P1	06C	15.17		TEH	TEC	.560	ZBATF	29	C	
68	17	5.10	179	DNT		P1	09H	-.69		TEH	TEC	.560	ZBATF	30	C	
68	17	4.20	178	DNT		P1	09C	-.72		TEH	TEC	.560	ZBATF	30	C	
70	17	6.05	180	DNT		P1	09H	-.71		TEH	TEC	.560	ZBATF	29	C	
70	17	1.17	176	DNT		P1	09H	.39		TEH	TEC	.560	ZBATF	29	C	
70	17	5.75	181	DNT		P1	09C	-.74		TEH	TEC	.560	ZBATF	29	C	
70	17	1.59	176	DNT		P1	09C	.33		TEH	TEC	.560	ZBATF	29	C	
72	17	7.45	180	DNT		P1	09H	-.70		TEH	TEC	.560	ZBATF	30	C	
72	17	2.02	180	DNT		P1	09H	.37		TEH	TEC	.560	ZBATF	30	C	
72	17	6.72	180	DNT		P1	09C	-.74		TEH	TEC	.560	ZBATF	30	C	
72	17	2.20	179	DNT		P1	09C	.30		TEH	TEC	.560	ZBATF	30	C	
7	18	.87	184	DNT		P1	07C	24.85		TEH	TEC	.560	ZBATF	16	C	
13	18	.71	186	DNT		P1	08C	.70		TEH	TEC	.560	ZBATF	16	C	
37	18	1.24	176	DNT		P1	08H	31.73		TEH	TEC	.560	ZBATF	16	C	
37	18	2.41	176	DNT		P1	08H	32.68		TEH	TEC	.560	ZBATF	16	C	
37	18	1.63	177	DNT		P1	08H	36.34		TEH	TEC	.560	ZBATF	16	C	
37	18	1.41	175	DNT		P1	08H	37.56		TEH	TEC	.560	ZBATF	16	C	
37	18	2.97	180	DNT		P1	08C	34.95		TEH	TEC	.560	ZBATF	16	C	
63	18	1.02	176	DNT		P1	09H	-.67		TEH	TEC	.560	ZBATF	30	C	
63	18	1.85	178	DNT		P1	09C	-.69		TEH	TEC	.560	ZBATF	30	C	
65	18	1.37	176	DNT		P1	09H	-.69		TEH	TEC	.560	ZBATF	29	C	
65	18	1.30	177	DNT		P1	09C	-.68		TEH	TEC	.560	ZBATF	29	C	
67	18	2.62	178	DNT		P1	09H	-.64		TEH	TEC	.560	ZBATF	30	C	
67	18	2.90	177	DNT		P1	09C	-.72		TEH	TEC	.560	ZBATF	30	C	
69	18	4.90	180	DNT		P1	09H	-.69		TEH	TEC	.560	ZBATF	29	C	
69	18	.97	175	DNT		P1	09H	.39		TEH	TEC	.560	ZBATF	29	C	
69	18	3.16	180	DNT		P1	09C	-.74		TEH	TEC	.560	ZBATF	29	C	
69	18	.79	173	DNT		P1	09C	.35		TEH	TEC	.560	ZBATF	29	C	
71	18	6.73	180	DNT		P1	09H	-.67		TEH	TEC	.560	ZBATF	30	C	
71	18	1.21	177	DNT		P1	09H	.40		TEH	TEC	.560	ZBATF	30	C	
71	18	6.58	180	DNT		P1	09C	-.74		TEH	TEC	.560	ZBATF	30	C	
71	18	1.19	177	DNT		P1	09C	.30		TEH	TEC	.560	ZBATF	30	C	
73	18	6.97	180	DNT		P1	09H	-.71		TEH	TEC	.560	ZBATF	29	C	
73	18	1.66	179	DNT		P1	09H	.36		TEH	TEC	.560	ZBATF	29	C	
73	18	5.78	180	DNT		P1	09C	-.74		TEH	TEC	.560	ZBATF	29	C	
73	18	2.82	178	DNT		P1	09C	.30		TEH	TEC	.560	ZBATF	29	C	
75	18	6.93	179	DNT		P1	09H	-.70		TEH	TEC	.560	ZBATF	30	C	
75	18	3.13	182	DNT		P1	09H	.34		TEH	TEC	.560	ZBATF	30	C	
75	18	5.96	178	DNT		P1	09C	-.75		TEH	TEC	.560	ZBATF	30	C	
75	18	4.47	180	DNT		P1	09C	.28		TEH	TEC	.560	ZBATF	30	C	
66	19	1.63	176	DNT		P1	09H	-.68		TEH	TEC	.560	ZBATF	29	C	
66	19	.91	179	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	29	C	
68	19	1.93	177	DNT		P1	09H	-.75		TEH	TEC	.560	ZBATF	30	C	
68	19	3.86	179	DNT		P1	09C	-.72		TEH	TEC	.560	ZBATF	30	C	
70	19	.82	180	DNT		P1	07H	14.47		TEH	TEC	.560	ZBATF	29	C	
70	19	3.39	179	DNT		P1	09H	-.68		TEH	TEC	.560	ZBATF	29	C	
70	19	3.35	180	DNT		P1	09C	-.68		TEH	TEC	.560	ZBATF	29	C	
70	19	.81	172	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	29	C	
72	19	5.02	179	DNT		P1	09H	-.64		TEH	TEC	.560	ZBATF	30	C	
72	19	.68	173	DNT		P1	09H	.40		TEH	TEC	.560	ZBATF	30	C	
72	19	6.53	179	DNT		P1	09C	-.74		TEH	TEC	.560	ZBATF	30	C	
72	19	1.08	175	DNT		P1	09C	.33		TEH	TEC	.560	ZBATF	30	C	
74	19	6.66	180	DNT		P1	09H	-.68		TEH	TEC	.560	ZBATF	29	C	
74	19	2.36	178	DNT		P1	09H	.42		TEH	TEC	.560	ZBATF	29	C	
74	19	5.19	180	DNT		P1	09C	-.74		TEH	TEC	.560	ZBATF	29	C	
74	19	3.48	178	DNT		P1	09C	.33		TEH	TEC	.560	ZBATF	29	C	
76	19	7.63	178	DNT		P1	09H	-.64		TEH	TEC	.560	ZBATF	30	C	
76	19	3.16	181	DNT		P1	09H	.40		TEH	TEC	.560	ZBATF	30	C	
76	19	7.61	179	DNT		P1	09C	-.74		TEH	TEC	.560	ZBATF	30	C	
76	19	4.89	179	DNT		P1	09C	.30		TEH	TEC	.560	ZBATF	30	C	
7	20	1.48	178	DNT		P1	08C	32.99		TEH	TEC	.560	ZBATF	16	C	
7	20	1.45	181	DNT		P1	08C	35.12		TEH	TEC	.560	ZBATF	16	C	
7	20	1.56	178	DNT		P1	08C	35.66		TEH	TEC	.560	ZBATF	16	C	
7	20	.94	173	DNT		P1	08C	36.69		TEH	TEC	.560	ZBATF	16	C	
11	20	2.43	179	DNT		P1	09C	.16		TEH	TEC	.560	ZBATF	16	C	
17	20	1.80	175	DNT		P1	08H	35.90		TEH	TEC	.560	ZBATF	16	C	
17	20	1.49	179	DNT		P1	08C	35.58		TEH	TEC	.560	ZBATF	16	C	
19	20	.95	182	DNT		P1	05H	-.13		TEH	TEC	.560	ZBATF	16	C	
65	20	1.80	182	DNT		P1	05H	34.32		TEH	TEC	.560	ZBATF	30	C	
67	20	1.10	177	DNT		P1	09H	-.63		TEH	TEC	.560	ZBATF	29	C	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
67	20	1.76	179	DNT		P1	09C	-.71		TEH	TEC	.560	ZBATF	29	C	
69	20	1.86	179	DNT		P1	09H	-.64		TEH	TEC	.560	ZBATF	30	C	
69	20	2.80	177	DNT		P1	09C	-.69		TEH	TEC	.560	ZBATF	30	C	
71	20	3.47	180	DNT		P1	09H	-.66		TEH	TEC	.560	ZBATF	29	C	
71	20	1.06	176	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	29	C	
71	20	2.90	180	DNT		P1	09C	-.68		TEH	TEC	.560	ZBATF	29	C	
71	20	.99	174	DNT		P1	09C	.43		TEH	TEC	.560	ZBATF	29	C	
73	20	1.48	183	DNT		P1	05H	35.38		TEH	TEC	.560	ZBATF	30	C	
73	20	5.06	179	DNT		P1	09H	-.64		TEH	TEC	.560	ZBATF	30	C	
73	20	.96	175	DNT		P1	09H	.43		TEH	TEC	.560	ZBATF	30	C	
73	20	4.92	178	DNT		P1	09C	-.72		TEH	TEC	.560	ZBATF	30	C	
73	20	1.75	177	DNT		P1	09C	.33		TEH	TEC	.560	ZBATF	30	C	
75	20	6.03	180	DNT		P1	09H	-.66		TEH	TEC	.560	ZBATF	29	C	
75	20	2.14	177	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	29	C	
75	20	4.42	179	DNT		P1	09C	-.74		TEH	TEC	.560	ZBATF	29	C	
75	20	3.13	178	DNT		P1	09C	.35		TEH	TEC	.560	ZBATF	29	C	
77	20	8.26	179	DNT		P1	09H	-.64		TEH	TEC	.560	ZBATF	30	C	
77	20	4.12	181	DNT		P1	09H	.40		TEH	TEC	.560	ZBATF	30	C	
77	20	6.70	179	DNT		P1	09C	-.72		TEH	TEC	.560	ZBATF	30	C	
77	20	4.77	180	DNT		P1	09C	.33		TEH	TEC	.560	ZBATF	30	C	
8	21	.97	177	DNT		P1	08H	23.51		TEH	TEC	.560	ZBATF	16	C	
10	21	2.05	176	DNT		P1	08C	19.75		TEH	TEC	.560	ZBATF	17	C	
12	21	2.33	177	DNT		P1	08C	22.74		TEH	TEC	.560	ZBATF	17	C	
12	21	1.26	177	DNT		P1	08C	24.05		TEH	TEC	.560	ZBATF	17	C	
12	21	1.97	180	DNT		P1	08C	26.55		TEH	TEC	.560	ZBATF	17	C	
12	21	1.68	175	DNT		P1	08C	27.53		TEH	TEC	.560	ZBATF	17	C	
12	21	1.29	176	DNT		P1	08C	29.15		TEH	TEC	.560	ZBATF	17	C	
14	21	1.06	176	DNT		P1	08C	32.43		TEH	TEC	.560	ZBATF	17	C	
16	21	1.35	177	DNT		P1	08C	35.34		TEH	TEC	.560	ZBATF	17	C	
16	21	1.63	178	DNT		P1	08C	37.68		TEH	TEC	.560	ZBATF	17	C	
22	21	4.83	181	DNT		P1	09C	-.64		TEH	TEC	.560	ZBATF	17	C	
22	21	1.03	176	DNT		P1	08C	34.85		TEH	TEC	.560	ZBATF	17	C	
22	21	2.00	179	DNT		P1	08C	35.83		TEH	TEC	.560	ZBATF	17	C	
42	21	1.12	175	DNT		P1	09H	-.59		TEH	TEC	.560	ZBATF	17	C	
48	21	1.06	179	DNT		P1	08H	24.01		TEH	TEC	.560	ZBATF	30	C	
48	21	1.72	177	DNT		P1	08C	34.32		TEH	TEC	.560	ZBATF	30	C	
64	21	1.19	176	DNT		P1	08C	1.24		TEH	TEC	.560	ZBATF	30	C	
64	21	1.23	175	DNT		P1	08C	33.64		TEH	TEC	.560	ZBATF	30	C	
68	21	.75	176	DNT		P1	09H	-.64		TEH	TEC	.560	ZBATF	30	C	
70	21	2.10	177	DNT		P1	09H	-.63		TEH	TEC	.560	ZBATF	29	C	
70	21	1.90	179	DNT		P1	09C	-.68		TEH	TEC	.560	ZBATF	29	C	
72	21	2.83	179	DNT		P1	09H	-.61		TEH	TEC	.560	ZBATF	30	C	
72	21	.58	174	DNT		P1	09H	.43		TEH	TEC	.560	ZBATF	30	C	
72	21	4.76	179	DNT		P1	09C	-.69		TEH	TEC	.560	ZBATF	30	C	
72	21	2.55	179	DNT		P1	09C	.36		TEH	TEC	.560	ZBATF	30	C	
74	21	3.85	180	DNT		P1	09H	-.66		TEH	TEC	.560	ZBATF	29	C	
74	21	1.69	177	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	29	C	
74	21	3.58	180	DNT		P1	09C	-.73		TEH	TEC	.560	ZBATF	29	C	
74	21	1.69	175	DNT		P1	09C	.35		TEH	TEC	.560	ZBATF	29	C	
76	21	6.04	178	DNT		P1	09H	-.64		TEH	TEC	.560	ZBATF	30	C	
76	21	2.54	179	DNT		P1	09H	.40		TEH	TEC	.560	ZBATF	30	C	
76	21	8.04	179	DNT		P1	09C	-.75		TEH	TEC	.560	ZBATF	30	C	
76	21	4.68	180	DNT		P1	09C	.36		TEH	TEC	.560	ZBATF	30	C	
78	21	7.73	180	DNT		P1	09H	-.69		TEH	TEC	.560	ZBATF	29	C	
78	21	4.59	179	DNT		P1	09H	.42		TEH	TEC	.560	ZBATF	29	C	
78	21	6.04	179	DNT		P1	09C	-.73		TEH	TEC	.560	ZBATF	29	C	
78	21	5.65	179	DNT		P1	09C	.38		TEH	TEC	.560	ZBATF	29	C	
80	21	10.18	179	DNT		P1	09H	-.67		TEH	TEC	.560	ZBATF	30	C	
80	21	6.20	181	DNT		P1	09H	.40		TEH	TEC	.560	ZBATF	30	C	
80	21	9.51	179	DNT		P1	09C	-.72		TEH	TEC	.560	ZBATF	30	C	
80	21	7.99	179	DNT		P1	09C	.30		TEH	TEC	.560	ZBATF	30	C	
9	22	.81	172	DNT		P1	08H	36.61		TEH	TEC	.560	ZBATF	16	C	
21	22	.71	172	DNT		P1	09H	.17		TEH	TEC	.560	ZBATF	16	C	
21	22	1.42	176	DNT		P1	09C	-.65		TEH	TEC	.560	ZBATF	16	C	
25	22	1.97	179	DNT		P1	09C	-.38		TEH	TEC	.560	ZBATF	16	C	
25	22	1.47	179	DNT		P1	08C	37.01		TEH	TEC	.560	ZBATF	16	C	
27	22	.92	173	DNT		P1	08H	37.89		TEH	TEC	.560	ZBATF	16	C	
31	22	1.02	174	DNT		P1	08H	37.37		TEH	TEC	.560	ZBATF	16	C	
31	22	.90	177	DNT		P1	08C	35.07		TEH	TEC	.560	ZBATF	16	C	
31	22	1.17	175	DNT		P1	08C	37.66		TEH	TEC	.560	ZBATF	16	C	
41	22	.96	176	DNT		P1	08H	26.35		TEH	TEC	.560	ZBATF	16	C	
41	22	2.51	178	DNT		P1	08H	31.08		TEH	TEC	.560	ZBATF	16	C	
41	22	1.28	177	DNT		P1	08H	34.38		TEH	TEC	.560	ZBATF	16	C	

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
45	22	.83	173	DNT		P1	08H	12.29		TEH	TEC	.560	ZBATF	16	C	
45	22	1.29	179	DNT		P1	08H	13.33		TEH	TEC	.560	ZBATF	16	C	
45	22	.97	175	DNT		P1	08H	17.87		TEH	TEC	.560	ZBATF	16	C	
45	22	1.44	177	DNT		P1	08H	20.56		TEH	TEC	.560	ZBATF	16	C	
45	22	1.00	180	DNT		P1	08H	30.98		TEH	TEC	.560	ZBATF	16	C	
45	22	1.41	177	DNT		P1	08H	32.88		TEH	TEC	.560	ZBATF	16	C	
45	22	.98	180	DNT		P1	08H	35.52		TEH	TEC	.560	ZBATF	16	C	
45	22	1.25	178	DNT		P1	09C	-.67		TEH	TEC	.560	ZBATF	16	C	
45	22	.87	175	DNT		P1	08C	17.52		TEH	TEC	.560	ZBATF	16	C	
45	22	1.49	178	DNT		P1	08C	32.21		TEH	TEC	.560	ZBATF	16	C	
45	22	.88	177	DNT		P1	08C	37.88		TEH	TEC	.560	ZBATF	16	C	
49	22	.99	181	DNT		P1	08H	15.75		TEH	TEC	.560	ZBATF	30	C	
49	22	5.06	179	DNT		P1	09H	.51		TEH	TEC	.560	ZBATF	30	C	
63	22	1.66	182	DNT		P1	02C	19.68		TEH	TEC	.560	ZBATF	29	C	
69	22	.75	176	DNT		P1	09H	-.58		TEH	TEC	.560	ZBATF	30	C	
69	22	.96	179	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	30	C	
71	22	2.70	178	DNT		P1	09H	-.60		TEH	TEC	.560	ZBATF	29	C	
71	22	.88	175	DNT		P1	09H	.42		TEH	TEC	.560	ZBATF	29	C	
71	22	1.47	177	DNT		P1	09C	-.68		TEH	TEC	.560	ZBATF	29	C	
73	22	1.56	176	DNT		P1	09H	-.61		TEH	TEC	.560	ZBATF	30	C	
73	22	.77	175	DNT		P1	09H	.43		TEH	TEC	.560	ZBATF	30	C	
73	22	4.28	180	DNT		P1	09C	-.69		TEH	TEC	.560	ZBATF	30	C	
73	22	.88	175	DNT		P1	09C	.39		TEH	TEC	.560	ZBATF	30	C	
75	22	3.07	178	DNT		P1	09H	-.66		TEH	TEC	.560	ZBATF	29	C	
75	22	1.42	177	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	29	C	
75	22	3.86	178	DNT		P1	09C	-.71		TEH	TEC	.560	ZBATF	29	C	
75	22	1.82	177	DNT		P1	09C	.38		TEH	TEC	.560	ZBATF	29	C	
77	22	7.10	179	DNT		P1	09H	-.61		TEH	TEC	.560	ZBATF	30	C	
77	22	2.30	180	DNT		P1	09H	.42		TEH	TEC	.560	ZBATF	30	C	
77	22	7.08	180	DNT		P1	09C	-.72		TEH	TEC	.560	ZBATF	30	C	
77	22	3.79	179	DNT		P1	09C	.36		TEH	TEC	.560	ZBATF	30	C	
77	22	.82	181	DNT		P1	03C	-.52		TEH	TEC	.560	ZBATF	30	C	
79	22	8.14	179	DNT		P1	09H	-.66		TEH	TEC	.560	ZBATF	29	C	
79	22	4.10	179	DNT		P1	09H	.44		TEH	TEC	.560	ZBATF	29	C	
79	22	7.41	180	DNT		P1	09C	-.73		TEH	TEC	.560	ZBATF	29	C	
79	22	4.82	178	DNT		P1	09C	.35		TEH	TEC	.560	ZBATF	29	C	
81	22	1.75	185	DNT		P1	03H	28.29		TEH	TEC	.560	ZBATF	30	C	
81	22	10.24	179	DNT		P1	09H	-.64		TEH	TEC	.560	ZBATF	30	C	
81	22	6.70	182	DNT		P1	09H	.42		TEH	TEC	.560	ZBATF	30	C	
81	22	8.47	178	DNT		P1	09C	-.74		TEH	TEC	.560	ZBATF	30	C	
81	22	5.70	179	DNT		P1	09C	.30		TEH	TEC	.560	ZBATF	30	C	
4	23	.89	182	DNT		P1	06H	25.59		09H	TEH	.560	ZBATF	3	H	
48	23	1.24	177	DNT		P1	08H	37.86		TEH	TEC	.560	ZBATF	30	C	
70	23	1.08	179	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	29	C	
72	23	2.72	178	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	30	C	
72	23	.95	175	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	30	C	
74	23	2.39	177	DNT		P1	09H	-.60		TEH	TEC	.560	ZBATF	29	C	
74	23	.69	170	DNT		P1	09H	.36		TEH	TEC	.560	ZBATF	29	C	
74	23	2.80	179	DNT		P1	09C	-.68		TEH	TEC	.560	ZBATF	29	C	
76	23	4.22	177	DNT		P1	09H	-.61		TEH	TEC	.560	ZBATF	30	C	
76	23	1.61	178	DNT		P1	09H	.42		TEH	TEC	.560	ZBATF	30	C	
76	23	5.66	179	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	30	C	
76	23	2.55	179	DNT		P1	09C	.39		TEH	TEC	.560	ZBATF	30	C	
78	23	6.45	180	DNT		P1	09H	-.60		TEH	TEC	.560	ZBATF	29	C	
78	23	2.69	179	DNT		P1	09H	.47		TEH	TEC	.560	ZBATF	29	C	
78	23	5.94	181	DNT		P1	09C	-.71		TEH	TEC	.560	ZBATF	29	C	
78	23	3.87	178	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	29	C	
80	23	8.11	179	DNT		P1	09H	-.61		TEH	TEC	.560	ZBATF	30	C	
80	23	3.02	179	DNT		P1	09H	.42		TEH	TEC	.560	ZBATF	30	C	
80	23	8.89	179	DNT		P1	09C	-.72		TEH	TEC	.560	ZBATF	30	C	
80	23	4.72	180	DNT		P1	09C	.33		TEH	TEC	.560	ZBATF	30	C	
82	23	9.56	179	DNT		P1	09H	-.67		TEH	TEC	.560	ZBATF	30	C	
82	23	4.46	181	DNT		P1	09H	.42		TEH	TEC	.560	ZBATF	30	C	
82	23	11.33	178	DNT		P1	09C	-.72		TEH	TEC	.560	ZBATF	30	C	
82	23	5.58	179	DNT		P1	09C	.36		TEH	TEC	.560	ZBATF	30	C	
73	24	2.69	177	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	30	C	
73	24	.92	175	DNT		P1	09C	.39		TEH	TEC	.560	ZBATF	30	C	
75	24	1.35	177	DNT		P1	09H	-.61		TEH	TEC	.560	ZBATF	29	C	
75	24	1.49	176	DNT		P1	09C	-.65		TEH	TEC	.560	ZBATF	29	C	
75	24	1.01	173	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	29	C	
77	24	4.76	179	DNT		P1	09H	-.58		TEH	TEC	.560	ZBATF	30	C	
77	24	1.52	178	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	30	C	
77	24	5.30	180	DNT		P1	09C	-.69		TEH	TEC	.560	ZBATF	30	C	
77	24	1.50	180	DNT		P1	09C	.36		TEH	TEC	.560	ZBATF	30	C	
79	24	6.53	179	DNT		P1	09H	-.60		TEH	TEC	.560	ZBATF	29	C	
79	24	2.79	178	DNT		P1	09H	.47		TEH	TEC	.560	ZBATF	29	C	
79	24	5.91	180	DNT		P1	09C	-.71		TEH	TEC	.560	ZBATF	29	C	
79-	24	2.54	177	DNT		P1	09C	.38		TEH	TEC	.560	ZBATF	29	C	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
81	24	8.76	179	DNT		P1	09H	-.64		TEH	TEC	.560	ZBATF	30	C	
81	24	3.13	180	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	30	C	
81	24	8.77	180	DNT		P1	09C	-.72		TEH	TEC	.560	ZBATF	30	C	
81	24	4.09	179	DNT		P1	09C	.33		TEH	TEC	.560	ZBATF	30	C	
83	24	9.49	179	DNT		P1	09H	-.66		TEH	TEC	.560	ZBATF	29	C	
83	24	4.22	179	DNT		P1	09H	.42		TEH	TEC	.560	ZBATF	29	C	
83	24	7.96	179	DNT		P1	09C	-.76		TEH	TEC	.560	ZBATF	29	C	
83	24	5.41	178	DNT		P1	09C	.35		TEH	TEC	.560	ZBATF	29	C	
85	24	9.39	179	DNT		P1	09H	-.67		TEH	TEC	.560	ZBATF	30	C	
85	24	4.34	180	DNT		P1	09H	.42		TEH	TEC	.560	ZBATF	30	C	
85	24	12.38	179	DNT		P1	09C	-.75		TEH	TEC	.560	ZBATF	30	C	
85	24	6.29	179	DNT		P1	09C	.33		TEH	TEC	.560	ZBATF	30	C	
8	25	1.19	182	DNT		P1	01H	16.14		TEH	TEC	.560	ZBATF	15	C	
74	25	1.39	178	DNT		P1	09H	-.55		TEH	TEC	.560	ZBATF	29	C	
74	25	.76	177	DNT		P1	09C	-.57		TEH	TEC	.560	ZBATF	29	C	
76	25	1.56	177	DNT		P1	09H	-.56		TEH	TEC	.560	ZBATF	30	C	
76	25	.77	176	DNT		P1	09H	.43		TEH	TEC	.560	ZBATF	30	C	
76	25	2.72	177	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	30	C	
76	25	.79	173	DNT		P1	09C	.39		TEH	TEC	.560	ZBATF	30	C	
78	25	2.90	178	DNT		P1	09H	-.60		TEH	TEC	.560	ZBATF	29	C	
78	25	1.56	176	DNT		P1	09H	.44		TEH	TEC	.560	ZBATF	29	C	
78	25	4.35	180	DNT		P1	09C	-.68		TEH	TEC	.560	ZBATF	29	C	
78	25	.89	174	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	29	C	
80	25	4.91	178	DNT		P1	09H	-.61		TEH	TEC	.560	ZBATF	30	C	
80	25	1.54	178	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	30	C	
80	25	8.05	179	DNT		P1	09C	-.69		TEH	TEC	.560	ZBATF	30	C	
80	25	1.73	177	DNT		P1	09C	.36		TEH	TEC	.560	ZBATF	30	C	
82	25	7.24	180	DNT		P1	09H	-.63		TEH	TEC	.560	ZBATF	29	C	
82	25	3.84	180	DNT		P1	09H	.44		TEH	TEC	.560	ZBATF	29	C	
82	25	6.74	181	DNT		P1	09C	-.71		TEH	TEC	.560	ZBATF	29	C	
82	25	2.27	176	DNT		P1	09C	.38		TEH	TEC	.560	ZBATF	29	C	
84	25	10.38	179	DNT		P1	09H	-.64		TEH	TEC	.560	ZBATF	30	C	
84	25	4.84	181	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	30	C	
84	25	11.19	178	DNT		P1	09C	-.72		TEH	TEC	.560	ZBATF	30	C	
84	25	3.84	178	DNT		P1	09C	.36		TEH	TEC	.560	ZBATF	30	C	
86	25	10.45	179	DNT		P1	09H	-.67		TEH	TEC	.560	ZBATF	30	C	
86	25	3.60	180	DNT		P1	09H	.42		TEH	TEC	.560	ZBATF	30	C	
86	25	11.62	179	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	30	C	
86	25	5.55	180	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	30	C	
9	26	.97	171	DNT		P1	08H	33.12		TEH	TEC	.560	ZBATF	14	C	
17	26	.99	172	DNT		P1	08C	31.38		TEH	TEC	.560	ZBATF	14	C	
19	26	.63	173	DNT		P1	08H	36.26		TEH	TEC	.560	ZBATF	14	C	
19	26	2.53	178	DNT		P1	09C	-1.00		TEH	TEC	.560	ZBATF	14	C	
19	26	3.04	177	DNT		P1	09C	-.03		TEH	TEC	.560	ZBATF	14	C	
19	26	3.04	177	DNT		P1	09C	.03		TEH	TEC	.560	ZBATF	14	C	
19	26	3.04	177	DNT		P1	09C	.13		TEH	TEC	.560	ZBATF	14	C	
19	26	2.31	176	DNT		P1	08C	33.22		TEH	TEC	.560	ZBATF	14	C	
19	26	1.66	176	DNT		P1	08C	34.65		TEH	TEC	.560	ZBATF	14	C	
19	26	3.87	177	DNT		P1	08C	35.83		TEH	TEC	.560	ZBATF	14	C	
19	26	3.87	177	DNT		P1	08C	35.86		TEH	TEC	.560	ZBATF	14	C	
19	26	2.84	178	DNT		P1	08C	37.45		TEH	TEC	.560	ZBATF	14	C	
45	26	1.55	172	DNT		P1	09C	-.40		TEH	TEC	.560	ZBATF	14	C	
75	26	1.94	178	DNT		P1	09H	-.53		TEH	TEC	.560	ZBATF	30	C	
75	26	.57	177	DNT		P1	09H	.48		TEH	TEC	.560	ZBATF	30	C	
75	26	1.70	177	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	30	C	
77	26	2.04	178	DNT		P1	09H	-.55		TEH	TEC	.560	ZBATF	29	C	
77	26	.87	174	DNT		P1	09H	.47		TEH	TEC	.560	ZBATF	29	C	
77	26	1.02	176	DNT		P1	09C	-.65		TEH	TEC	.560	ZBATF	29	C	
79	26	3.14	178	DNT		P1	09H	-.58		TEH	TEC	.560	ZBATF	30	C	
79	26	.90	176	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	30	C	
79	26	3.43	177	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	30	C	
79	26	.91	176	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	30	C	
81	26	4.14	180	DNT		P1	09H	-.61		TEH	TEC	.560	ZBATF	29	C	
81	26	1.46	176	DNT		P1	09H	.47		TEH	TEC	.560	ZBATF	29	C	
81	26	4.59	180	DNT		P1	09C	-.68		TEH	TEC	.560	ZBATF	29	C	
81	26	1.21	176	DNT		P1	09C	.38		TEH	TEC	.560	ZBATF	29	C	
83	26	7.51	179	DNT		P1	09H	-.56		TEH	TEC	.560	ZBATF	30	C	
83	26	2.13	177	DNT		P1	09H	.48		TEH	TEC	.560	ZBATF	30	C	
83	26	8.86	180	DNT		P1	09C	-.69		TEH	TEC	.560	ZBATF	30	C	
83	26	2.09	177	DNT		P1	09C	.36		TEH	TEC	.560	ZBATF	30	C	
85	26	8.62	179	DNT		P1	09H	-.58		TEH	TEC	.560	ZBATF	29	C	
85	26	5.49	180	DNT		P1	09H	.47		TEH	TEC	.560	ZBATF	29	C	
85	26	6.37	181	DNT		P1	09C	-.71		TEH	TEC	.560	ZBATF	29	C	
85	26	2.77	175	DNT		P1	09C	.35		TEH	TEC	.560	ZBATF	29	C	
87	26	10.70	178	DNT		P1	09H	-.64		TEH	TEC	.560	ZBATF	30	C	
87	26	4.02	181	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	30	C	
87	26	10.30	179	DNT		P1	09C	-.69		TEH	TEC	.560	ZBATF	30	C	
87	26	5.19	179	DNT		P1	09C	.36		TEH	TEC	.560	ZBATF	30	C	
16	27	.80	173	DNT		P1	08H	36.81		TEH	TEC	.560	ZBATF	15	C	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
58	27	.72	172	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	29	C	
58	27	.98	174	DNT		P1	09C	-.27		TEH	TEC	.560	ZBATF	29	C	
78	27	.81	175	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	29	C	
78	27	1.31	178	DNT		P1	09C	-.65		TEH	TEC	.560	ZBATF	29	C	
80	27	.80	174	DNT		P1	09H	-.58		TEH	TEC	.560	ZBATF	30	C	
80	27	4.25	180	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	30	C	
80	27	1.34	177	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	30	C	
82	27	3.46	179	DNT		P1	09H	-.58		TEH	TEC	.560	ZBATF	29	C	
82	27	1.17	176	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	29	C	
82	27	5.77	181	DNT		P1	09C	-.68		TEH	TEC	.560	ZBATF	29	C	
82	27	2.24	179	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	29	C	
84	27	4.96	179	DNT		P1	09H	-.59		TEH	TEC	.560	ZBATF	30	C	
84	27	1.58	178	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	30	C	
84	27	8.58	180	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	30	C	
84	27	1.97	178	DNT		P1	09C	.39		TEH	TEC	.560	ZBATF	30	C	
86	27	8.24	180	DNT		P1	09H	-.58		TEH	TEC	.560	ZBATF	29	C	
86	27	4.85	180	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	29	C	
86	27	7.06	180	DNT		P1	09C	-.68		TEH	TEC	.560	ZBATF	29	C	
86	27	2.93	176	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	29	C	
88	27	9.54	179	DNT		P1	09H	-.62		TEH	TEC	.560	ZBATF	30	C	
88	27	3.34	179	DNT		P1	09H	.42		TEH	TEC	.560	ZBATF	30	C	
88	27	12.01	178	DNT		P1	09C	-.72		TEH	TEC	.560	ZBATF	30	C	
88	27	6.49	179	DNT		P1	09C	.36		TEH	TEC	.560	ZBATF	30	C	
19	28	.82	173	DNT		P1	08H	34.79		TEH	TEC	.560	ZBATF	14	C	
19	28	1.13	173	DNT		P1	08H	37.57		TEH	TEC	.560	ZBATF	14	C	
19	28	.96	173	DNT		P1	09H	-.27		TEH	TEC	.560	ZBATF	14	C	
37	28	1.33	175	DNT		P1	08C	37.55		TEH	TEC	.560	ZBATF	14	C	
79	28	1.78	177	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	30	C	
81	28	.90	178	DNT		P1	09H	-.72		TEH	TEC	.560	ZBATF	29	C	
81	28	2.43	178	DNT		P1	09C	-.65		TEH	TEC	.560	ZBATF	29	C	
81	28	.81	174	DNT		P1	09C	.43		TEH	TEC	.560	ZBATF	29	C	
83	28	2.90	179	DNT		P1	09H	-.53		TEH	TEC	.560	ZBATF	30	C	
83	28	1.42	178	DNT		P1	09H	.51		TEH	TEC	.560	ZBATF	30	C	
83	28	5.36	180	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	30	C	
83	28	1.34	178	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	30	C	
85	28	4.38	179	DNT		P1	09H	-.52		TEH	TEC	.560	ZBATF	29	C	
85	28	2.28	177	DNT		P1	09H	.47		TEH	TEC	.560	ZBATF	29	C	
85	28	6.32	180	DNT		P1	09C	-.70		TEH	TEC	.560	ZBATF	29	C	
85	28	2.00	177	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	29	C	
87	28	8.90	180	DNT		P1	09H	-.56		TEH	TEC	.560	ZBATF	30	C	
87	28	4.11	182	DNT		P1	09H	.48		TEH	TEC	.560	ZBATF	30	C	
87	28	8.63	180	DNT		P1	09C	-.69		TEH	TEC	.560	ZBATF	30	C	
87	28	4.16	179	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	30	C	
89	28	6.79	179	DNT		P1	09H	-.60		TEH	TEC	.560	ZBATF	29	C	
89	28	3.35	178	DNT		P1	09H	.47		TEH	TEC	.560	ZBATF	29	C	
89	28	6.98	180	DNT		P1	09C	-.73		TEH	TEC	.560	ZBATF	29	C	
89	28	4.09	178	DNT		P1	09C	.38		TEH	TEC	.560	ZBATF	29	C	
91	28	8.16	180	DNT		P1	09H	-.61		TEH	TEC	.560	ZBATF	30	C	
91	28	5.82	181	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	30	C	
91	28	10.31	178	DNT		P1	09C	-.71		TEH	TEC	.560	ZBATF	30	C	
91	28	5.25	179	DNT		P1	09C	.47		TEH	TEC	.560	ZBATF	30	C	
18	29	1.06	173	DNT		P1	09H	-.31		TEH	TEC	.560	ZBATF	15	C	
32	29	.95	172	DNT		P1	09C	-.11		TEH	TEC	.560	ZBATF	15	C	
38	29	.91	174	DNT		P1	09C	-.39		TEH	TEC	.560	ZBATF	15	C	
42	29	1.12	182	DNT		P1	01H	21.30		TEH	TEC	.560	ZBATF	15	C	
52	29	.85	173	DNT		P1	08H	22.19		TEH	TEC	.560	ZBATF	28	C	
52	29	.93	175	DNT		P1	08H	35.79		TEH	TEC	.560	ZBATF	28	C	
80	29	1.23	176	DNT		P1	09H	-.53		TEH	TEC	.560	ZBATF	28	C	
80	29	1.82	178	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	28	C	
82	29	1.54	177	DNT		P1	09H	-.58		TEH	TEC	.560	ZBATF	27	C	
82	29	.55	172	DNT		P1	09H	.44		TEH	TEC	.560	ZBATF	27	C	
82	29	1.54	177	DNT		P1	09C	-.60		TEH	TEC	.560	ZBATF	27	C	
84	29	1.67	175	DNT		P1	09H	-.56		TEH	TEC	.560	ZBATF	28	C	
84	29	.92	176	DNT		P1	09H	.48		TEH	TEC	.560	ZBATF	28	C	
84	29	5.24	179	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	28	C	
84	29	1.03	177	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	28	C	
86	29	2.94	177	DNT		P1	09H	-.55		TEH	TEC	.560	ZBATF	27	C	
86	29	1.34	175	DNT		P1	09H	.47		TEH	TEC	.560	ZBATF	27	C	
86	29	4.82	179	DNT		P1	09C	-.65		TEH	TEC	.560	ZBATF	27	C	
86	29	2.20	177	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	27	C	
88	29	7.67	177	DNT		P1	09H	-.59		TEH	TEC	.560	ZBATF	28	C	
88	29	4.10	180	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	28	C	
88	29	9.49	178	DNT		P1	09C	-.69		TEH	TEC	.560	ZBATF	28	C	
88	29	3.06	178	DNT		P1	09C	.39		TEH	TEC	.560	ZBATF	28	C	

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
90	29	6.27	178	DNT		P1	09H	-.61		TEH	TEC	.560	ZBATF	27	C	
90	29	4.03	178	DNT		P1	09H	.47		TEH	TEC	.560	ZBATF	27	C	
90	29	7.02	179	DNT		P1	09C	-.68		TEH	TEC	.560	ZBATF	27	C	
90	29	4.84	178	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	27	C	
92	29	1.65	184	DNT		P1	02H	35.80		TEH	TEC	.560	ZBATF	28	C	
92	29	8.87	177	DNT		P1	09H	-.64		TEH	TEC	.560	ZBATF	28	C	
92	29	4.81	180	DNT		P1	09H	.42		TEH	TEC	.560	ZBATF	28	C	
92	29	12.42	177	DNT		P1	09C	-.69		TEH	TEC	.560	ZBATF	28	C	
92	29	8.16	179	DNT		P1	09C	.36		TEH	TEC	.560	ZBATF	28	C	
9	30	.66	180	DNT		P1	02H	.61		TEH	TEC	.560	ZBATF	14	C	
19	30	1.87	174	DNT		P1	08H	34.60		TEH	TEC	.560	ZBATF	14	C	
19	30	1.72	175	DNT		P1	08H	36.61		TEH	TEC	.560	ZBATF	14	C	
19	30	1.04	171	DNT		P1	08H	37.21		TEH	TEC	.560	ZBATF	14	C	
19	30	2.22	174	DNT		P1	08H	37.73		TEH	TEC	.560	ZBATF	14	C	
19	30	1.06	174	DNT		P1	09H	-.14		TEH	TEC	.560	ZBATF	14	C	
19	30	.84	172	DNT		P1	09C	-.62		TEH	TEC	.560	ZBATF	14	C	
19	30	1.18	177	DNT		P1	09C	.51		TEH	TEC	.560	ZBATF	14	C	
19	30	1.60	175	DNT		P1	08C	35.77		TEH	TEC	.560	ZBATF	14	C	
23	30	.98	171	DNT		P1	09H	-.46		TEH	TEC	.560	ZBATF	14	C	
37	30	1.11	173	DNT		P1	08H	37.43		TEH	TEC	.560	ZBATF	14	C	
39	30	.74	174	DNT		P1	08H	25.76		TEH	TEC	.560	ZBATF	14	C	
39	30	1.51	175	DNT		P1	08H	36.27		TEH	TEC	.560	ZBATF	14	C	
39	30	.98	173	DNT		P1	09H	-.22		TEH	TEC	.560	ZBATF	14	C	
41	30	.85	172	DNT		P1	08H	28.36		TEH	TEC	.560	ZBATF	14	C	
41	30	.79	172	DNT		P1	08H	36.50		TEH	TEC	.560	ZBATF	14	C	
41	30	.88	175	DNT		P1	08C	37.82		TEH	TEC	.560	ZBATF	14	C	
81	30	1.65	175	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	28	C	
83	30	1.48	177	DNT		P1	09H	-.52		TEH	TEC	.560	ZBATF	27	C	
83	30	2.41	178	DNT		P1	09C	-.62		TEH	TEC	.560	ZBATF	27	C	
83	30	.94	176	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	27	C	
85	30	1.08	177	DNT		P1	09H	-.56		TEH	TEC	.560	ZBATF	28	C	
85	30	2.96	177	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	28	C	
85	30	1.23	175	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	28	C	
87	30	4.66	178	DNT		P1	09H	-.52		TEH	TEC	.560	ZBATF	27	C	
87	30	2.66	179	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	27	C	
87	30	4.88	180	DNT		P1	09C	-.60		TEH	TEC	.560	ZBATF	27	C	
87	30	2.04	178	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	27	C	
89	30	5.22	176	DNT		P1	09H	-.56		TEH	TEC	.560	ZBATF	28	C	
89	30	2.76	179	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	28	C	
89	30	6.72	178	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	28	C	
89	30	3.95	179	DNT		P1	09C	.52		TEH	TEC	.560	ZBATF	28	C	
91	30	1.57	175	DNT		P1	08H	32.49		TEH	TEC	.560	ZBATF	27	C	
91	30	6.74	179	DNT		P1	09H	-.55		TEH	TEC	.560	ZBATF	27	C	
91	30	7.30	179	DNT		P1	09H	.47		TEH	TEC	.560	ZBATF	27	C	
91	30	5.64	179	DNT		P1	09C	-.54		TEH	TEC	.560	ZBATF	27	C	
91	30	4.89	177	DNT		P1	09C	.43		TEH	TEC	.560	ZBATF	27	C	
93	30	8.91	177	DNT		P1	09H	-.64		TEH	TEC	.560	ZBATF	28	C	
93	30	7.99	179	DNT		P1	09H	.42		TEH	TEC	.560	ZBATF	28	C	
93	30	9.35	179	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	28	C	
93	30	6.99	178	DNT		P1	09C	.39		TEH	TEC	.560	ZBATF	28	C	
20	31	.96	177	DNT		P1	08H	38.07		TEH	TEC	.560	ZBATF	15	C	
40	31	.96	173	DNT		P1	08C	36.95		TEH	TEC	.560	ZBATF	15	C	
56	31	.90	173	DNT		P1	08C	31.26		TEH	TEC	.560	ZBATF	27	C	
82	31	1.83	176	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	28	C	
84	31	1.35	177	DNT		P1	09C	-.62		TEH	TEC	.560	ZBATF	27	C	
84	31	1.18	177	DNT		P1	09C	.43		TEH	TEC	.560	ZBATF	27	C	
86	31	3.18	177	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	28	C	
86	31	1.05	175	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	28	C	
88	31	2.66	176	DNT		P1	09H	-.52		TEH	TEC	.560	ZBATF	27	C	
88	31	1.06	174	DNT		P1	09H	.47		TEH	TEC	.560	ZBATF	27	C	
88	31	4.18	178	DNT		P1	09C	-.62		TEH	TEC	.560	ZBATF	27	C	
88	31	3.31	178	DNT		P1	09C	.43		TEH	TEC	.560	ZBATF	27	C	
90	31	5.70	178	DNT		P1	09H	-.56		TEH	TEC	.560	ZBATF	28	C	
90	31	2.95	180	DNT		P1	09H	.48		TEH	TEC	.560	ZBATF	28	C	
90	31	8.37	179	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	28	C	
90	31	5.88	179	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	28	C	
92	31	5.65	178	DNT		P1	09H	-.58		TEH	TEC	.560	ZBATF	27	C	
92	31	4.28	178	DNT		P1	09H	.47		TEH	TEC	.560	ZBATF	27	C	
92	31	5.10	178	DNT		P1	09C	-.65		TEH	TEC	.560	ZBATF	27	C	
92	31	5.25	178	DNT		P1	09C	.43		TEH	TEC	.560	ZBATF	27	C	
94	31	8.51	178	DNT		P1	09H	-.59		TEH	TEC	.560	ZBATF	28	C	
94	31	6.24	180	DNT		P1	09H	.42		TEH	TEC	.560	ZBATF	28	C	
94	31	9.78	178	DNT		P1	09C	-.69		TEH	TEC	.560	ZBATF	28	C	
94	31	9.56	179	DNT		P1	09C	.36		TEH	TEC	.560	ZBATF	28	C	
1	32	1.08	180	DNT		P1	02H	14.97		09H	TEH	.560	ZBATF	2	H	

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
19	32	1.78	171	DNT		P1	08H	37.66		TEH	TEC	.560	ZBATF	14	C	
19	32	1.30	174	DNT		P1	09H	.03		TEH	TEC	.560	ZBATF	14	C	
19	32	.97	173	DNT		P1	09C	-.57		TEH	TEC	.560	ZBATF	14	C	
27	32	.99	169	DNT		P1	09C	-.68		TEH	TEC	.560	ZBATF	14	C	
29	32	.99	174	DNT		P1	08C	35.06		TEH	TEC	.560	ZBATF	14	C	
35	32	1.13	172	DNT		P1	08H	37.56		TEH	TEC	.560	ZBATF	14	C	
35	32	.86	173	DNT		P1	08C	30.06		TEH	TEC	.560	ZBATF	14	C	
35	32	.81	171	DNT		P1	08C	33.26		TEH	TEC	.560	ZBATF	14	C	
35	32	1.77	175	DNT		P1	08C	36.48		TEH	TEC	.560	ZBATF	14	C	
39	32	.97	175	DNT		P1	08H	35.90		TEH	TEC	.560	ZBATF	14	C	
39	32	.84	174	DNT		P1	08C	32.17		TEH	TEC	.560	ZBATF	14	C	
39	32	.93	174	DNT		P1	08C	37.47		TEH	TEC	.560	ZBATF	14	C	
47	32	1.15	172	DNT		P1	08C	34.47		TEH	TEC	.560	ZBATF	27	C	
47	32	1.00	182	DNT		P1	03C	5.39		TEH	TEC	.560	ZBATF	27	C	
61	32	.75	175	DNT		P1	09C	.58		TEH	TEC	.560	ZBATF	28	C	
63	32	2.21	177	DNT		P1	08H	26.52		TEH	TEC	.560	ZBATF	27	C	
67	32	1.05	181	DNT		P1	01C	12.11		TEH	TEC	.560	ZBATF	27	C	
69	32	1.22	182	DNT		P1	TSC	18.56		TEH	TEC	.560	ZBATF	28	C	
85	32	1.96	177	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	28	C	
85	32	.79	182	DNT		P1	09C	.52		TEH	TEC	.560	ZBATF	28	C	
87	32	1.34	175	DNT		P1	09H	-.52		TEH	TEC	.560	ZBATF	27	C	
87	32	.93	174	DNT		P1	09H	.44		TEH	TEC	.560	ZBATF	27	C	
87	32	1.45	175	DNT		P1	09C	-.60		TEH	TEC	.560	ZBATF	27	C	
87	32	1.13	175	DNT		P1	09C	.43		TEH	TEC	.560	ZBATF	27	C	
89	32	4.31	177	DNT		P1	09H	-.51		TEH	TEC	.560	ZBATF	28	C	
89	32	2.17	179	DNT		P1	09H	.48		TEH	TEC	.560	ZBATF	28	C	
89	32	4.47	177	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	28	C	
89	32	1.38	176	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	28	C	
91	32	4.02	178	DNT		P1	09H	-.55		TEH	TEC	.560	ZBATF	27	C	
91	32	3.90	178	DNT		P1	09H	.47		TEH	TEC	.560	ZBATF	27	C	
91	32	3.86	177	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	27	C	
91	32	3.59	178	DNT		P1	09C	.43		TEH	TEC	.560	ZBATF	27	C	
93	32	8.74	177	DNT		P1	09H	-.54		TEH	TEC	.560	ZBATF	28	C	
93	32	8.28	180	DNT		P1	09H	.48		TEH	TEC	.560	ZBATF	28	C	
93	32	6.54	179	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	28	C	
93	32	5.79	179	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	28	C	
93	32	1.15	171	DNT		P1	08C	.39		TEH	TEC	.560	ZBATF	28	C	
95	32	9.77	177	DNT		P1	09H	-.59		TEH	TEC	.560	ZBATF	28	C	
95	32	7.91	181	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	28	C	
95	32	7.39	180	DNT		P1	09C	-.69		TEH	TEC	.560	ZBATF	28	C	
95	32	5.93	178	DNT		P1	09C	.36		TEH	TEC	.560	ZBATF	28	C	
12	33	2.01	176	DNT		P1	09C	-.23		TEH	TEC	.560	ZBATF	15	C	
16	33	3.89	183	DNT		P1	09H	3.92		TEH	TEC	.560	ZBATF	15	C	
16	33	1.79	175	DNT		P1	08C	31.98		TEH	TEC	.560	ZBATF	15	C	
16	33	1.85	176	DNT		P1	08C	34.37		TEH	TEC	.560	ZBATF	15	C	
16	33	1.51	177	DNT		P1	08C	35.86		TEH	TEC	.560	ZBATF	15	C	
16	33	1.12	172	DNT		P1	08C	37.66		TEH	TEC	.560	ZBATF	15	C	
26	33	.91	172	DNT		P1	09C	-.56		TEH	TEC	.560	ZBATF	15	C	
86	33	.73	173	DNT		P1	09C	-.62		TEH	TEC	.560	ZBATF	27	C	
86	33	.71	174	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	27	C	
88	33	2.14	178	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	28	C	
88	33	1.01	176	DNT		P1	09H	.54		TEH	TEC	.560	ZBATF	28	C	
88	33	2.52	177	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	28	C	
88	33	1.41	178	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	28	C	
90	33	3.29	178	DNT		P1	09H	-.52		TEH	TEC	.560	ZBATF	27	C	
90	33	2.00	176	DNT		P1	09H	.47		TEH	TEC	.560	ZBATF	27	C	
90	33	3.09	178	DNT		P1	09C	-.60		TEH	TEC	.560	ZBATF	27	C	
90	33	2.45	178	DNT		P1	09C	.43		TEH	TEC	.560	ZBATF	27	C	
92	33	6.03	177	DNT		P1	09H	-.58		TEH	TEC	.560	ZBATF	28	C	
92	33	4.26	180	DNT		P1	09H	.48		TEH	TEC	.560	ZBATF	28	C	
92	33	5.26	178	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	28	C	
92	33	3.54	180	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	28	C	
94	33	6.14	178	DNT		P1	09H	-.55		TEH	TEC	.560	ZBATF	27	C	
94	33	7.24	179	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	27	C	
94	33	4.21	178	DNT		P1	09C	-.68		TEH	TEC	.560	ZBATF	27	C	
94	33	5.81	178	DNT		P1	09C	.43		TEH	TEC	.560	ZBATF	27	C	
96	33	9.74	177	DNT		P1	09H	-.59		TEH	TEC	.560	ZBATF	28	C	
96	33	8.99	181	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	28	C	
96	33	6.33	178	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	28	C	
96	33	7.52	180	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	28	C	
29	34	2.68	176	DNT		P1	09C	-.59		TEH	TEC	.560	ZBATF	14	C	
29	34	2.31	179	DNT		P1	09C	.51		TEH	TEC	.560	ZBATF	14	C	
35	34	.80	173	DNT		P1	08H	38.06		TEH	TEC	.560	ZBATF	14	C	
35	34	1.32	174	DNT		P1	08C	36.31		TEH	TEC	.560	ZBATF	14	C	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L COM
41	34	.83	174	DNT		P1	08H	33.56		TEH	TEC	.560	ZBATF	14	C
41	34	.73	174	DNT		P1	08H	36.66		TEH	TEC	.560	ZBATF	14	C
41	34	.86	176	DNT		P1	08C	37.50		TEH	TEC	.560	ZBATF	14	C
43	34	1.50	176	DNT		P1	08H	34.61		TEH	TEC	.560	ZBATF	14	C
43	34	1.06	176	DNT		P1	09C	-.78		TEH	TEC	.560	ZBATF	14	C
43	34	.74	172	DNT		P1	08C	34.79		TEH	TEC	.560	ZBATF	14	C
63	34	1.12	173	DNT		P1	08H	32.92		TEH	TEC	.560	ZBATF	27	C
87	34	.89	177	DNT		P1	09H	-.55		TEH	TEC	.560	ZBATF	27	C
87	34	1.04	175	DNT		P1	09C	-.62		TEH	TEC	.560	ZBATF	27	C
89	34	2.11	178	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	28	C
89	34	1.05	177	DNT		P1	09H	.54		TEH	TEC	.560	ZBATF	28	C
89	34	3.08	177	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	28	C
89	34	2.07	177	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	28	C
91	34	2.92	178	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	27	C
91	34	2.70	177	DNT		P1	09H	.52		TEH	TEC	.560	ZBATF	27	C
91	34	2.37	176	DNT		P1	09C	-.60		TEH	TEC	.560	ZBATF	27	C
91	34	2.68	177	DNT		P1	09C	.43		TEH	TEC	.560	ZBATF	27	C
93	34	6.59	178	DNT		P1	09H	-.53		TEH	TEC	.560	ZBATF	28	C
93	34	5.12	180	DNT		P1	09H	.48		TEH	TEC	.560	ZBATF	28	C
93	34	6.09	177	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	28	C
93	34	3.96	179	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	28	C
95	34	6.28	178	DNT		P1	09H	-.52		TEH	TEC	.560	ZBATF	27	C
95	34	8.07	178	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	27	C
95	34	5.01	178	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	27	C
95	34	7.69	177	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	27	C
97	34	9.63	177	DNT		P1	09H	-.70		TEH	TEC	.560	ZBATF	28	C
97	34	9.99	181	DNT		P1	09H	.48		TEH	TEC	.560	ZBATF	28	C
97	34	6.76	179	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	28	C
97	34	9.47	179	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	28	C
30	35	1.01	172	DNT		P1	08H	33.43		TEH	TEC	.560	ZBATF	14	C
30	35	1.02	172	DNT		P1	09C	-.62		TEH	TEC	.560	ZBATF	14	C
32	35	.74	173	DNT		P1	09H	-.27		TEH	TEC	.560	ZBATF	14	C
34	35	.85	174	DNT		P1	08C	35.15		TEH	TEC	.560	ZBATF	14	C
50	35	1.39	175	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	28	C
88	35	.76	173	DNT		P1	09C	-.60		TEH	TEC	.560	ZBATF	27	C
88	35	.74	175	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	27	C
90	35	1.90	177	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	28	C
90	35	2.58	176	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	28	C
90	35	2.06	179	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	28	C
92	35	2.36	178	DNT		P1	09H	-.52		TEH	TEC	.560	ZBATF	27	C
92	35	1.47	177	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	27	C
92	35	2.27	178	DNT		P1	09C	-.62		TEH	TEC	.560	ZBATF	27	C
92	35	2.34	177	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	27	C
94	35	5.30	177	DNT		P1	09H	-.53		TEH	TEC	.560	ZBATF	28	C
94	35	4.90	181	DNT		P1	09H	.48		TEH	TEC	.560	ZBATF	28	C
94	35	5.03	178	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	28	C
94	35	4.39	180	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	28	C
96	35	6.58	179	DNT		P1	09H	-.58		TEH	TEC	.560	ZBATF	27	C
96	35	6.95	179	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	27	C
96	35	4.49	179	DNT		P1	09C	-.65		TEH	TEC	.560	ZBATF	27	C
96	35	6.20	178	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	27	C
98	35	9.17	178	DNT		P1	09H	-.70		TEH	TEC	.560	ZBATF	28	C
98	35	6.47	180	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	28	C
98	35	6.86	178	DNT		P1	09C	-.69		TEH	TEC	.560	ZBATF	28	C
98	35	7.58	179	DNT		P1	09C	.39		TEH	TEC	.560	ZBATF	28	C
47	36	.82	181	DNT		P1	04H	33.21		TEH	TEC	.560	ZBATF	27	C
61	36	.73	174	DNT		P1	09C	.58		TEH	TEC	.560	ZBATF	28	C
91	36	1.50	177	DNT		P1	09H	-.49		TEH	TEC	.560	ZBATF	27	C
91	36	1.61	177	DNT		P1	09H	.52		TEH	TEC	.560	ZBATF	27	C
91	36	1.37	176	DNT		P1	09C	-.57		TEH	TEC	.560	ZBATF	27	C
91	36	.97	175	DNT		P1	09C	.49		TEH	TEC	.560	ZBATF	27	C
93	36	4.46	178	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	28	C
93	36	3.89	180	DNT		P1	09H	.53		TEH	TEC	.560	ZBATF	28	C
93	36	3.65	177	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	28	C
93	36	2.13	178	DNT		P1	09C	.47		TEH	TEC	.560	ZBATF	28	C
95	36	5.17	179	DNT		P1	09H	-.52		TEH	TEC	.560	ZBATF	27	C
95	36	5.82	178	DNT		P1	09H	.52		TEH	TEC	.560	ZBATF	27	C
95	36	3.53	177	DNT		P1	09C	-.62		TEH	TEC	.560	ZBATF	27	C
95	36	3.35	178	DNT		P1	09C	.43		TEH	TEC	.560	ZBATF	27	C
97	36	6.93	178	DNT		P1	09H	-.67		TEH	TEC	.560	ZBATF	28	C
97	36	5.81	180	DNT		P1	09H	.48		TEH	TEC	.560	ZBATF	28	C
97	36	6.74	180	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	28	C
97	36	5.18	179	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	28	C
99	36	9.50	178	DNT		P1	09H	-.56		TEH	TEC	.560	ZBATF	28	C
99	36	8.50	180	DNT		P1	09H	.48		TEH	TEC	.560	ZBATF	28	C
99	36	5.87	179	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	28	C
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
99	36	3.89	178	DNT		P1	09C	.36		TEH	TEC	.560	ZBATF	28	C	
18	37	.77	175	DNT		P1	08C	.70		TEH	TEC	.560	ZBATF	12	C	
26	37	.71	172	DNT		P1	09C	-.62		TEH	TEC	.560	ZBATF	12	C	
40	37	1.23	175	DNT		P1	08H	30.18		TEH	TEC	.560	ZBATF	12	C	
90	37	.75	174	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	27	C	
90	37	.89	175	DNT		P1	09C	-.54		TEH	TEC	.560	ZBATF	27	C	
90	37	1.07	176	DNT		P1	09C	.52		TEH	TEC	.560	ZBATF	27	C	
92	37	1.94	178	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	28	C	
92	37	1.54	178	DNT		P1	09H	.56		TEH	TEC	.560	ZBATF	28	C	
92	37	2.51	176	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	28	C	
92	37	2.66	179	DNT		P1	09C	.47		TEH	TEC	.560	ZBATF	28	C	
94	37	3.42	179	DNT		P1	09H	-.49		TEH	TEC	.560	ZBATF	27	C	
94	37	1.83	176	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	27	C	
94	37	3.32	178	DNT		P1	09C	-.57		TEH	TEC	.560	ZBATF	27	C	
94	37	4.18	178	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	27	C	
96	37	5.26	178	DNT		P1	09H	-.53		TEH	TEC	.560	ZBATF	28	C	
96	37	4.23	181	DNT		P1	09H	.53		TEH	TEC	.560	ZBATF	28	C	
96	37	7.14	179	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	28	C	
96	37	4.42	179	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	28	C	
98	37	6.29	179	DNT		P1	09H	-.52		TEH	TEC	.560	ZBATF	27	C	
98	37	5.57	178	DNT		P1	09H	.49		TEH	TEC	.560	ZBATF	27	C	
98	37	5.71	179	DNT		P1	09C	-.65		TEH	TEC	.560	ZBATF	27	C	
98	37	6.49	178	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	27	C	
100	37	10.40	178	DNT		P1	09H	-.58		TEH	TEC	.560	ZBATF	28	C	
100	37	7.69	181	DNT		P1	09H	.48		TEH	TEC	.560	ZBATF	28	C	
100	37	10.15	178	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	28	C	
100	37	8.09	179	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	28	C	
93	38	2.15	179	DNT		P1	09H	-.47		TEH	TEC	.560	ZBATF	28	C	
93	38	1.67	177	DNT		P1	09H	.56		TEH	TEC	.560	ZBATF	28	C	
93	38	2.54	176	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	28	C	
93	38	1.28	175	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	28	C	
95	38	4.65	179	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	27	C	
95	38	4.91	179	DNT		P1	09H	.52		TEH	TEC	.560	ZBATF	27	C	
95	38	2.51	177	DNT		P1	09C	-.62		TEH	TEC	.560	ZBATF	27	C	
95	38	2.72	177	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	27	C	
97	38	7.09	179	DNT		P1	09H	-.52		TEH	TEC	.560	ZBATF	28	C	
97	38	4.33	181	DNT		P1	09H	.51		TEH	TEC	.560	ZBATF	28	C	
97	38	8.06	178	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	28	C	
97	38	4.18	179	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	28	C	
99	38	7.23	179	DNT		P1	09H	-.52		TEH	TEC	.560	ZBATF	27	C	
99	38	4.49	179	DNT		P1	09H	.52		TEH	TEC	.560	ZBATF	27	C	
99	38	5.48	179	DNT		P1	09C	-.70		TEH	TEC	.560	ZBATF	27	C	
99	38	3.28	178	DNT		P1	09C	.43		TEH	TEC	.560	ZBATF	27	C	
101	38	11.60	179	DNT		P1	09H	-.61		TEH	TEC	.560	ZBATF	28	C	
101	38	7.02	181	DNT		P1	09H	.48		TEH	TEC	.560	ZBATF	28	C	
101	38	8.72	179	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	28	C	
101	38	5.99	180	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	28	C	
16	39	1.05	172	DNT		P1	08H	27.82		TEH	TEC	.560	ZBATF	12	C	
18	39	1.73	177	DNT		P1	08H	29.12		TEH	TEC	.560	ZBATF	12	C	
18	39	1.03	176	DNT		P1	08H	30.22		TEH	TEC	.560	ZBATF	12	C	
18	39	2.19	177	DNT		P1	08C	27.43		TEH	TEC	.560	ZBATF	12	C	
18	39	.64	175	DNT		P1	08C	34.91		TEH	TEC	.560	ZBATF	12	C	
18	39	1.82	178	DNT		P1	08C	35.85		TEH	TEC	.560	ZBATF	12	C	
18	39	.68	172	DNT		P1	08C	37.01		TEH	TEC	.560	ZBATF	12	C	
26	39	.91	171	DNT		P1	08H	36.27		TEH	TEC	.560	ZBATF	12	C	
26	39	.69	171	DNT		P1	09C	.30		TEH	TEC	.560	ZBATF	12	C	
68	39	1.43	174	DNT		P1	08H	35.04		TEH	TEC	.560	ZBATF	25	C	
82	39	1.17	184	DNT		P1	02C	16.27		TEH	TEC	.560	ZBATF	26	C	
94	39	2.31	178	DNT		P1	09H	-.48		TEH	TEC	.560	ZBATF	26	C	
94	39	1.07	178	DNT		P1	09H	.54		TEH	TEC	.560	ZBATF	26	C	
94	39	2.24	176	DNT		P1	09C	-.58		TEH	TEC	.560	ZBATF	26	C	
94	39	1.24	177	DNT		P1	09C	.47		TEH	TEC	.560	ZBATF	26	C	
96	39	2.20	177	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	25	C	
96	39	1.51	176	DNT		P1	09H	.52		TEH	TEC	.560	ZBATF	25	C	
96	39	2.93	177	DNT		P1	09C	-.59		TEH	TEC	.560	ZBATF	25	C	
96	39	2.05	176	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	25	C	
98	39	6.03	178	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	26	C	
98	39	4.13	180	DNT		P1	09H	.53		TEH	TEC	.560	ZBATF	26	C	
98	39	5.54	177	DNT		P1	09C	-.64		TEH	TEC	.560	ZBATF	26	C	
98	39	3.23	179	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	26	C	
100	39	6.65	178	DNT		P1	09H	-.52		TEH	TEC	.560	ZBATF	25	C	
100	39	5.08	177	DNT		P1	09H	.52		TEH	TEC	.560	ZBATF	25	C	
100	39	5.45	177	DNT		P1	09C	-.67		TEH	TEC	.560	ZBATF	25	C	
100	39	3.36	176	DNT		P1	09C	.40		TEH	TEC	.560	ZBATF	25	C	
102	39	10.08	177	DNT		P1	09H	-.65		TEH	TEC	.560	ZBATF	26	C	
102	39	5.02	180	DNT		P1	09H	.48		TEH	TEC	.560	ZBATF	26	C	
102	39	7.90	178	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	26	C	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L COM
102	39	3.74	178	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	26	C|
7	40	1.47	174	DNT		P1	09H	-.83		TEH	TEC	.560	ZBATF	13	C|
7	40	1.06	173	DNT		P1	08C	37.49		TEH	TEC	.560	ZBATF	13	C|
21	40	1.38	179	DNT		P1	09C	.45		TEH	TEC	.560	ZBATF	13	C|
23	40	1.57	175	DNT		P1	09H	.14		TEH	TEC	.560	ZBATF	13	C|
23	40	.82	172	DNT		P1	09C	-.59		TEH	TEC	.560	ZBATF	13	C|
25	40	.93	172	DNT		P1	08H	34.64		TEH	TEC	.560	ZBATF	13	C|
25	40	1.03	173	DNT		P1	09H	-.11		TEH	TEC	.560	ZBATF	13	C|
25	40	.94	172	DNT		P1	08C	36.97		TEH	TEC	.560	ZBATF	13	C|
27	40	.87	175	DNT		P1	08H	35.53		TEH	TEC	.560	ZBATF	13	C|
93	40	1.39	173	DNT		P1	09C	-.58		TEH	TEC	.560	ZBATF	26	C|
95	40	1.18	175	DNT		P1	09H	-.52		TEH	TEC	.560	ZBATF	25	C|
95	40	1.72	176	DNT		P1	09C	-.60		TEH	TEC	.560	ZBATF	25	C|
95	40	1.26	176	DNT		P1	09C	.49		TEH	TEC	.560	ZBATF	25	C|
97	40	2.34	178	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	26	C|
97	40	1.07	178	DNT		P1	09H	.51		TEH	TEC	.560	ZBATF	26	C|
97	40	5.72	179	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	26	C|
97	40	1.94	178	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	26	C|
99	40	4.96	178	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	25	C|
99	40	2.54	177	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	25	C|
99	40	5.20	178	DNT		P1	09C	-.65		TEH	TEC	.560	ZBATF	25	C|
99	40	2.56	177	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	25	C|
101	40	8.46	177	DNT		P1	09H	-.61		TEH	TEC	.560	ZBATF	26	C|
101	40	4.76	180	DNT		P1	09H	.51		TEH	TEC	.560	ZBATF	26	C|
101	40	8.18	178	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	26	C|
101	40	2.93	178	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	26	C|
103	40	1.08	179	DNT		P1	01H	27.77		TEH	TEC	.560	ZBATF	26	C|
103	40	9.76	177	DNT		P1	09H	-.56		TEH	TEC	.560	ZBATF	26	C|
103	40	6.22	180	DNT		P1	09H	.48		TEH	TEC	.560	ZBATF	26	C|
103	40	9.40	178	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	26	C|
103	40	3.93	178	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	26	C|
96	41	1.64	177	DNT		P1	09H	-.48		TEH	TEC	.560	ZBATF	26	C|
96	41	1.82	176	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	26	C|
98	41	1.60	176	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	25	C|
98	41	.99	173	DNT		P1	09H	.49		TEH	TEC	.560	ZBATF	25	C|
98	41	1.95	176	DNT		P1	09C	-.60		TEH	TEC	.560	ZBATF	25	C|
98	41	1.93	176	DNT		P1	09C	.49		TEH	TEC	.560	ZBATF	25	C|
100	41	4.83	177	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	26	C|
100	41	2.60	179	DNT		P1	09H	.51		TEH	TEC	.560	ZBATF	26	C|
100	41	5.99	178	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	26	C|
100	41	2.27	177	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	26	C|
102	41	5.96	178	DNT		P1	09H	-.53		TEH	TEC	.560	ZBATF	25	C|
102	41	3.12	177	DNT		P1	09H	.49		TEH	TEC	.560	ZBATF	25	C|
102	41	5.09	177	DNT		P1	09C	-.65		TEH	TEC	.560	ZBATF	25	C|
102	41	2.79	176	DNT		P1	09C	.43		TEH	TEC	.560	ZBATF	25	C|
104	41	8.59	177	DNT		P1	09H	-.67		TEH	TEC	.560	ZBATF	26	C|
104	41	4.47	180	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	26	C|
104	41	8.58	179	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	26	C|
104	41	3.71	179	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	26	C|
23	42	1.02	173	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	13	C|
97	42	1.84	178	DNT		P1	09H	-.48		TEH	TEC	.560	ZBATF	26	C|
97	42	1.77	176	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	26	C|
97	42	.87	178	DNT		P1	09C	.47		TEH	TEC	.560	ZBATF	26	C|
99	42	1.70	175	DNT		P1	09H	-.52		TEH	TEC	.560	ZBATF	25	C|
99	42	.92	173	DNT		P1	09H	.47		TEH	TEC	.560	ZBATF	25	C|
99	42	2.21	175	DNT		P1	09C	-.65		TEH	TEC	.560	ZBATF	25	C|
99	42	1.73	176	DNT		P1	09C	.49		TEH	TEC	.560	ZBATF	25	C|
101	42	4.61	177	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	26	C|
101	42	3.22	179	DNT		P1	09H	.53		TEH	TEC	.560	ZBATF	26	C|
101	42	5.14	179	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	26	C|
101	42	1.70	178	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	26	C|
103	42	6.00	178	DNT		P1	09H	-.49		TEH	TEC	.560	ZBATF	25	C|
103	42	4.45	177	DNT		P1	09H	.49		TEH	TEC	.560	ZBATF	25	C|
103	42	4.64	178	DNT		P1	09C	-.68		TEH	TEC	.560	ZBATF	25	C|
103	42	2.33	177	DNT		P1	09C	.43		TEH	TEC	.560	ZBATF	25	C|
105	42	8.39	177	DNT		P1	09H	-.56		TEH	TEC	.560	ZBATF	26	C|
105	42	5.82	181	DNT		P1	09H	.48		TEH	TEC	.560	ZBATF	26	C|
105	42	8.11	179	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	26	C|
105	42	3.45	179	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	26	C|
12	43	.61	185	DNT		P1	TSH	6.07		TEH	TEC	.560	ZBATF	12	C|
20	43	.88	170	DNT		P1	09C	-.59		TEH	TEC	.560	ZBATF	12	C|
36	43	1.69	176	DNT		P1	08H	35.63		TEH	TEC	.560	ZBATF	12	C|
36	43	.76	168	DNT		P1	09C	-.38		TEH	TEC	.560	ZBATF	12	C|
70	43	.67	176	DNT		P1	08H	33.32		TEH	TEC	.560	ZBATF	26	C|
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
98	43	1.32	176	DNT		P1	09C	-.58		TEH	TEC	.560	ZBATF	23	C	
100	43	2.30	176	DNT		P1	09H	-.47		TEH	TEC	.560	ZBATF	24	C	
100	43	1.00	175	DNT		P1	09H	.49		TEH	TEC	.560	ZBATF	24	C	
100	43	1.13	175	DNT		P1	09C	-.62		TEH	TEC	.560	ZBATF	24	C	
102	43	4.01	177	DNT		P1	09H	-.53		TEH	TEC	.560	ZBATF	23	C	
102	43	2.23	179	DNT		P1	09H	.51		TEH	TEC	.560	ZBATF	23	C	
102	43	3.56	178	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	23	C	
102	43	1.72	179	DNT		P1	09C	.47		TEH	TEC	.560	ZBATF	23	C	
104	43	5.03	177	DNT		P1	09H	-.52		TEH	TEC	.560	ZBATF	24	C	
104	43	4.18	177	DNT		P1	09H	.49		TEH	TEC	.560	ZBATF	24	C	
104	43	3.93	178	DNT		P1	09C	-.68		TEH	TEC	.560	ZBATF	24	C	
104	43	2.50	176	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	24	C	
106	43	7.36	177	DNT		P1	09H	-.55		TEH	TEC	.560	ZBATF	23	C	
106	43	5.71	180	DNT		P1	09H	.48		TEH	TEC	.560	ZBATF	23	C	
106	43	6.19	179	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	23	C	
106	43	3.93	179	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	23	C	
23	44	.90	177	DNT		P1	09C	.67		TEH	TEC	.560	ZBATF	13	C	
25	44	2.44	177	DNT		P1	09C	-.22		TEH	TEC	.560	ZBATF	13	C	
37	44	.87	175	DNT		P1	08H	37.79		TEH	TEC	.560	ZBATF	13	C	
37	44	1.19	174	DNT		P1	09H	.03		TEH	TEC	.560	ZBATF	13	C	
37	44	1.30	175	DNT		P1	08C	34.67		TEH	TEC	.560	ZBATF	13	C	
99	44	1.45	174	DNT		P1	09C	-.60		TEH	TEC	.560	ZBATF	24	C	
101	44	2.30	177	DNT		P1	09H	-.48		TEH	TEC	.560	ZBATF	23	C	
101	44	2.02	176	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	23	C	
101	44	1.51	178	DNT		P1	09C	.47		TEH	TEC	.560	ZBATF	23	C	
103	44	3.61	177	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	24	C	
103	44	2.03	177	DNT		P1	09H	.52		TEH	TEC	.560	ZBATF	24	C	
103	44	3.12	177	DNT		P1	09C	-.60		TEH	TEC	.560	ZBATF	24	C	
103	44	1.58	176	DNT		P1	09C	.49		TEH	TEC	.560	ZBATF	24	C	
105	44	6.85	178	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	23	C	
105	44	4.52	180	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	23	C	
105	44	5.00	180	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	23	C	
105	44	2.87	178	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	23	C	
107	44	8.71	177	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	23	C	
107	44	6.24	181	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	23	C	
107	44	6.95	181	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	23	C	
107	44	4.68	179	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	23	C	
22	45	1.02	173	DNT		P1	09C	-.59		TEH	TEC	.560	ZBATF	12	C	
22	45	.98	171	DNT		P1	09C	-.03		TEH	TEC	.560	ZBATF	12	C	
22	45	1.09	178	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	12	C	
26	45	1.00	172	DNT		P1	09C	-.76		TEH	TEC	.560	ZBATF	12	C	
26	45	1.11	171	DNT		P1	08C	30.06		TEH	TEC	.560	ZBATF	12	C	
26	45	.84	174	DNT		P1	08C	30.71		TEH	TEC	.560	ZBATF	12	C	
30	45	.65	172	DNT		P1	08C	37.88		TEH	TEC	.560	ZBATF	12	C	
52	45	1.21	183	DNT		P1	FBH	14.28		TEH	TEC	.560	ZBATF	23	C	
100	45	1.38	175	DNT		P1	09C	-.58		TEH	TEC	.560	ZBATF	23	C	
102	45	.92	173	DNT		P1	09H	-.55		TEH	TEC	.560	ZBATF	24	C	
102	45	1.13	174	DNT		P1	09C	-.62		TEH	TEC	.560	ZBATF	24	C	
102	45	1.12	175	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	24	C	
104	45	.77	170	DNT		P1	08H	.48		TEH	TEC	.560	ZBATF	23	C	
104	45	3.97	176	DNT		P1	09H	-.48		TEH	TEC	.560	ZBATF	23	C	
104	45	2.82	179	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	23	C	
104	45	3.75	176	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	23	C	
104	45	2.52	179	DNT		P1	09C	.47		TEH	TEC	.560	ZBATF	23	C	
106	45	4.45	177	DNT		P1	09H	-.49		TEH	TEC	.560	ZBATF	24	C	
106	45	4.10	177	DNT		P1	09H	.52		TEH	TEC	.560	ZBATF	24	C	
106	45	2.59	176	DNT		P1	09C	-.62		TEH	TEC	.560	ZBATF	24	C	
106	45	2.88	177	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	24	C	
108	45	6.71	176	DNT		P1	09H	-.53		TEH	TEC	.560	ZBATF	23	C	
108	45	8.40	179	DNT		P1	09H	.45		TEH	TEC	.560	ZBATF	23	C	
108	45	4.99	178	DNT		P1	09C	-.66		TEH	TEC	.560	ZBATF	23	C	
108	45	3.33	179	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	23	C	
101	46	1.04	175	DNT		P1	09H	-.45		TEH	TEC	.560	ZBATF	23	C	
101	46	1.90	176	DNT		P1	09C	-.58		TEH	TEC	.560	ZBATF	23	C	
101	46	1.10	177	DNT		P1	09C	.47		TEH	TEC	.560	ZBATF	23	C	
103	46	1.77	175	DNT		P1	09H	-.47		TEH	TEC	.560	ZBATF	24	C	
103	46	.88	173	DNT		P1	09H	.49		TEH	TEC	.560	ZBATF	24	C	
103	46	1.44	174	DNT		P1	09C	-.62		TEH	TEC	.560	ZBATF	24	C	
103	46	1.71	176	DNT		P1	09C	.49		TEH	TEC	.560	ZBATF	24	C	
105	46	4.53	176	DNT		P1	09H	-.51		TEH	TEC	.560	ZBATF	23	C	
105	46	2.83	180	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	23	C	
105	46	4.33	178	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	23	C	
105	46	1.45	178	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	23	C	
107	46	5.01	176	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	23	C	
107	46	4.73	180	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	23	C	
107	46	3.99	177	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	23	C	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
107	46	3.84	180	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	23	C	
26	47	.70	172	DNT		P1	09H	-.73		TEH	TEC	.560	ZBATF	12	C	
36	47	.80	173	DNT		P1	08H	32.66		TEH	TEC	.560	ZBATF	12	C	
42	47	.79	176	DNT		P1	05H	13.42		TEH	TEC	.560	ZBATF	12	C	
42	47	.66	167	DNT		P1	08H	34.61		TEH	TEC	.560	ZBATF	12	C	
56	47	.84	176	DNT		P1	09H	.57		TEH	TEC	.560	ZBATF	23	C	
102	47	1.10	175	DNT		P1	09H	-.44		TEH	TEC	.560	ZBATF	24	C	
102	47	1.36	174	DNT		P1	09H	.55		TEH	TEC	.560	ZBATF	24	C	
104	47	2.47	175	DNT		P1	09H	-.42		TEH	TEC	.560	ZBATF	23	C	
104	47	1.41	178	DNT		P1	09H	.53		TEH	TEC	.560	ZBATF	23	C	
104	47	1.35	173	DNT		P1	09C	-.58		TEH	TEC	.560	ZBATF	23	C	
104	47	1.43	178	DNT		P1	09C	.47		TEH	TEC	.560	ZBATF	23	C	
106	47	3.98	176	DNT		P1	09H	-.49		TEH	TEC	.560	ZBATF	24	C	
106	47	4.03	177	DNT		P1	09H	.52		TEH	TEC	.560	ZBATF	24	C	
106	47	2.10	175	DNT		P1	09C	-.62		TEH	TEC	.560	ZBATF	24	C	
106	47	1.68	176	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	24	C	
108	47	6.70	177	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	23	C	
108	47	7.83	180	DNT		P1	09H	.53		TEH	TEC	.560	ZBATF	23	C	
108	47	1.95	174	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	23	C	
108	47	2.40	178	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	23	C	
33	48	.92	175	DNT		P1	02H	30.96		TEH	TEC	.560	ZBATF	9	C	
43	48	.82	172	DNT		P1	08H	33.75		TEH	TEC	.560	ZBATF	9	C	
101	48	.91	179	DNT		P1	09H	.53		TEH	TEC	.560	ZBATF	23	C	
103	48	.96	172	DNT		P1	09H	-.52		TEH	TEC	.560	ZBATF	24	C	
103	48	1.05	174	DNT		P1	09H	.55		TEH	TEC	.560	ZBATF	24	C	
105	48	2.85	175	DNT		P1	09H	-.47		TEH	TEC	.560	ZBATF	23	C	
105	48	1.75	179	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	23	C	
105	48	1.55	174	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	23	C	
105	48	1.48	179	DNT		P1	09C	.47		TEH	TEC	.560	ZBATF	23	C	
107	48	.76	170	DNT		P1	08H	.46		TEH	TEC	.560	ZBATF	24	C	
107	48	4.23	176	DNT		P1	09H	-.52		TEH	TEC	.560	ZBATF	24	C	
107	48	5.77	177	DNT		P1	09H	.55		TEH	TEC	.560	ZBATF	24	C	
107	48	2.08	175	DNT		P1	09C	-.62		TEH	TEC	.560	ZBATF	24	C	
107	48	2.23	176	DNT		P1	09C	.49		TEH	TEC	.560	ZBATF	24	C	
109	48	8.20	177	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	23	C	
109	48	11.16	179	DNT		P1	09H	.56		TEH	TEC	.560	ZBATF	23	C	
109	48	3.20	176	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	23	C	
109	48	4.37	180	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	23	C	
78	49	1.13	172	DNT		P1	08H	32.42		TEH	TEC	.560	ZBATF	24	C	
104	49	1.08	173	DNT		P1	09H	-.45		TEH	TEC	.560	ZBATF	23	C	
104	49	1.24	178	DNT		P1	09H	.53		TEH	TEC	.560	ZBATF	23	C	
104	49	1.28	173	DNT		P1	09C	-.58		TEH	TEC	.560	ZBATF	23	C	
106	49	1.68	174	DNT		P1	09H	-.47		TEH	TEC	.560	ZBATF	24	C	
106	49	2.19	176	DNT		P1	09H	.55		TEH	TEC	.560	ZBATF	24	C	
106	49	1.02	173	DNT		P1	09C	-.60		TEH	TEC	.560	ZBATF	24	C	
106	49	2.07	176	DNT		P1	09C	.49		TEH	TEC	.560	ZBATF	24	C	
108	49	.86	171	DNT		P1	08H	.53		TEH	TEC	.560	ZBATF	23	C	
108	49	4.03	175	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	23	C	
108	49	7.04	180	DNT		P1	09H	.53		TEH	TEC	.560	ZBATF	23	C	
108	49	3.34	175	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	23	C	
108	49	3.34	178	DNT		P1	09C	.47		TEH	TEC	.560	ZBATF	23	C	
110	49	6.28	176	DNT		P1	09H	-.51		TEH	TEC	.560	ZBATF	23	C	
110	49	10.34	179	DNT		P1	09H	.53		TEH	TEC	.560	ZBATF	23	C	
110	49	3.07	175	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	23	C	
110	49	3.31	179	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	23	C	
79	50	.73	184	DNT		P1	04C	34.00		TEH	TEC	.560	ZBATF	23	C	
91	50	1.19	181	DNT		P1	05H	17.97		TEH	TEC	.560	ZBATF	23	C	
93	50	1.62	181	DNT		P1	02H	36.53		TEH	TEC	.560	ZBATF	24	C	
103	50	1.75	178	DNT		P1	09H	.56		TEH	TEC	.560	ZBATF	23	C	
105	50	2.15	176	DNT		P1	09H	-.46		TEH	TEC	.560	ZBATF	24	C	
105	50	2.01	175	DNT		P1	09H	.55		TEH	TEC	.560	ZBATF	24	C	
105	50	1.55	174	DNT		P1	09C	-.57		TEH	TEC	.560	ZBATF	24	C	
105	50	1.53	176	DNT		P1	09C	.49		TEH	TEC	.560	ZBATF	24	C	
107	50	4.91	177	DNT		P1	09H	-.47		TEH	TEC	.560	ZBATF	23	C	
107	50	4.37	180	DNT		P1	09H	.56		TEH	TEC	.560	ZBATF	23	C	
107	50	1.60	174	DNT		P1	09C	-.58		TEH	TEC	.560	ZBATF	23	C	
107	50	2.23	179	DNT		P1	09C	.47		TEH	TEC	.560	ZBATF	23	C	
109	50	3.94	175	DNT		P1	09H	-.55		TEH	TEC	.560	ZBATF	24	C	
109	50	5.56	177	DNT		P1	09H	.52		TEH	TEC	.560	ZBATF	24	C	
109	50	1.83	176	DNT		P1	09C	-.60		TEH	TEC	.560	ZBATF	24	C	
109	50	3.40	177	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	24	C	
111	50	6.59	176	DNT		P1	09H	-.53		TEH	TEC	.560	ZBATF	23	C	
111	50	8.91	179	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	23	C	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
111	50	4.24	177	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	23	C	
111	50	3.61	180	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	23	C	
30	51	1.83	175	DNT		P1	09H	-.54		TEH	TEC	.560	ZBATF	8	C	
48	51	1.32	173	DNT		P1	08C	28.67		TEH	TEC	.560	ZBATF	23	C	
54	51	1.85	174	DNT		P1	08C	34.56		TEH	TEC	.560	ZBATF	24	C	
60	51	1.00	175	DNT		P1	08H	34.72		TEH	TEC	.560	ZBATF	23	C	
104	51	1.41	177	DNT		P1	09H	.56		TEH	TEC	.560	ZBACS	42	C	
106	51	3.18	174	DNT		P1	09H	-.45		TEH	TEC	.560	ZBATF	21	C	
106	51	4.24	180	DNT		P1	09H	.56		TEH	TEC	.560	ZBATF	21	C	
106	51	1.59	174	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	21	C	
106	51	1.23	178	DNT		P1	09C	.47		TEH	TEC	.560	ZBATF	21	C	
108	51	3.91	175	DNT		P1	09H	-.52		TEH	TEC	.560	ZBACS	42	C	
108	51	6.34	177	DNT		P1	09H	.58		TEH	TEC	.560	ZBACS	42	C	
108	51	1.54	174	DNT		P1	09C	-.60		TEH	TEC	.560	ZBACS	42	C	
108	51	2.79	177	DNT		P1	09C	.49		TEH	TEC	.560	ZBACS	42	C	
110	51	5.94	176	DNT		P1	09H	-.53		TEH	TEC	.560	ZBATF	21	C	
110	51	9.26	178	DNT		P1	09H	.53		TEH	TEC	.560	ZBATF	21	C	
110	51	3.07	175	DNT		P1	09C	-.64		TEH	TEC	.560	ZBATF	21	C	
110	51	3.62	180	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	21	C	
65	52	1.37	182	DNT		P1	AV3	4.74		TEH	TEC	.560	ZBATF	21	C	
105	52	1.55	177	DNT		P1	09H	-.44		TEH	TEC	.560	ZBATF	21	C	
105	52	1.67	179	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	21	C	
105	52	1.17	175	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	21	C	
105	52	1.38	178	DNT		P1	09C	.50		TEH	TEC	.560	ZBATF	21	C	
107	52	3.80	176	DNT		P1	09H	-.50		TEH	TEC	.560	ZBACS	42	C	
107	52	5.29	178	DNT		P1	09H	.61		TEH	TEC	.560	ZBACS	42	C	
107	52	1.56	175	DNT		P1	09C	-.58		TEH	TEC	.560	ZBACS	42	C	
107	52	2.32	177	DNT		P1	09C	.47		TEH	TEC	.560	ZBACS	42	C	
109	52	.86	173	DNT		P1	08H	.44		TEH	TEC	.560	ZBATF	21	C	
109	52	5.02	176	DNT		P1	09H	-.47		TEH	TEC	.560	ZBATF	21	C	
109	52	6.51	180	DNT		P1	09H	.53		TEH	TEC	.560	ZBATF	21	C	
109	52	3.64	176	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	21	C	
109	52	2.54	179	DNT		P1	09C	.47		TEH	TEC	.560	ZBATF	21	C	
111	52	5.64	176	DNT		P1	09H	-.54		TEH	TEC	.560	ZBATF	21	C	
111	52	7.41	179	DNT		P1	09H	.53		TEH	TEC	.560	ZBATF	21	C	
111	52	4.21	176	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	21	C	
111	52	3.83	179	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	21	C	
102	53	1.22	180	DNT		P1	05C	18.98		TEH	TEC	.560	ZBACS	42	C	
104	53	1.39	174	DNT		P1	09H	-.45		TEH	TEC	.560	ZBATF	21	C	
104	53	1.69	177	DNT		P1	09H	.56		TEH	TEC	.560	ZBATF	21	C	
106	53	1.31	173	DNT		P1	09H	.56		TEH	TEC	.560	ZBACS	42	C	
108	53	3.15	174	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	21	C	
108	53	2.86	179	DNT		P1	09H	.56		TEH	TEC	.560	ZBATF	21	C	
108	53	2.42	176	DNT		P1	09C	-.58		TEH	TEC	.560	ZBATF	21	C	
108	53	2.11	177	DNT		P1	09C	.47		TEH	TEC	.560	ZBATF	21	C	
110	53	5.47	176	DNT		P1	09H	-.55		TSH	TEC	.560	ZBACS	42	C	
110	53	7.62	178	DNT		P1	09H	.56		TSH	TEC	.560	ZBACS	42	C	
110	53	3.27	176	DNT		P1	09C	-.66		TSH	TEC	.560	ZBACS	42	C	
110	53	4.12	177	DNT		P1	09C	.50		TSH	TEC	.560	ZBACS	42	C	
112	53	7.00	176	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	21	C	
112	53	8.46	180	DNT		P1	09H	.53		TEH	TEC	.560	ZBATF	21	C	
112	53	4.23	177	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	21	C	
112	53	4.34	179	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	21	C	
93	54	1.56	182	DNT		P1	06H	10.47		TEH	TEC	.560	ZBATF	21	C	
103	54	.85	176	DNT		P1	09H	.54		TEH	TEC	.560	ZBATF	20	C	
105	54	1.80	176	DNT		P1	09H	-.45		TEH	TEC	.560	ZBATF	21	C	
105	54	1.51	178	DNT		P1	09H	.56		TEH	TEC	.560	ZBATF	21	C	
105	54	1.10	173	DNT		P1	09C	-.55		TEH	TEC	.560	ZBATF	21	C	
105	54	1.03	177	DNT		P1	09C	.55		TEH	TEC	.560	ZBATF	21	C	
107	54	2.04	175	DNT		P1	09H	-.43		TEH	TEC	.560	ZBATF	20	C	
107	54	2.47	177	DNT		P1	09H	.54		TEH	TEC	.560	ZBATF	20	C	
107	54	.98	172	DNT		P1	09C	-.45		TEH	TEC	.560	ZBATF	20	C	
107	54	1.40	177	DNT		P1	09C	.51		TEH	TEC	.560	ZBATF	20	C	
109	54	4.66	176	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	21	C	
109	54	3.72	178	DNT		P1	09H	.56		TEH	TEC	.560	ZBATF	21	C	
109	54	2.03	175	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	21	C	
109	54	2.74	179	DNT		P1	09C	.47		TEH	TEC	.560	ZBATF	21	C	
111	54	6.11	176	DNT		P1	09H	-.55		TSH	TEC	.560	ZBACS	42	C	
111	54	7.48	177	DNT		P1	09H	.58		TSH	TEC	.560	ZBACS	42	C	
111	54	3.94	176	DNT		P1	09C	-.66		TSH	TEC	.560	ZBACS	42	C	
111	54	4.03	177	DNT		P1	09C	.47		TSH	TEC	.560	ZBACS	42	C	
113	54	7.09	177	DNT		P1	09H	-.56		TEH	TEC	.560	ZBATF	21	C	
113	54	6.24	179	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	21	C	
113	54	5.96	178	DNT		P1	09C	-.64		TEH	TEC	.560	ZBATF	21	C	
113	54	6.02	180	DNT		P1	09C	.47		TEH	TEC	.560	ZBATF	21	C	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
8	55	1.14	181	DNT		P1	01C	35.37		TEH	TEC	.560	ZBATF	8	C	
104	55	1.36	175	DNT		P1	09H	-.44		TEH	TEC	.560	ZBATF	21	C	
104	55	.82	174	DNT		P1	09H	.59		TEH	TEC	.560	ZBATF	21	C	
106	55	1.75	175	DNT		P1	09H	-.43		TEH	TEC	.560	ZBATF	20	C	
106	55	3.10	177	DNT		P1	09H	.57		TEH	TEC	.560	ZBATF	20	C	
108	55	2.54	175	DNT		P1	09H	-.47		TEH	TEC	.560	ZBATF	21	C	
108	55	2.67	177	DNT		P1	09H	.56		TEH	TEC	.560	ZBATF	21	C	
110	55	2.76	176	DNT		P1	09H	-.49		TEH	TEC	.560	ZBATF	20	C	
110	55	2.44	176	DNT		P1	09H	.51		TEH	TEC	.560	ZBATF	20	C	
110	55	1.23	175	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	20	C	
110	55	1.38	176	DNT		P1	09C	.45		TEH	TEC	.560	ZBATF	20	C	
112	55	4.45	175	DNT		P1	09H	-.53		TEH	TEC	.560	ZBATF	21	C	
112	55	5.65	179	DNT		P1	09H	.53		TEH	TEC	.560	ZBATF	21	C	
112	55	2.29	176	DNT		P1	09C	-.64		TEH	TEC	.560	ZBATF	21	C	
112	55	2.65	176	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	21	C	
9	56	.94	181	DNT		P1	07C	4.33		TEH	TEC	.560	ZBATF	9	C	
81	56	1.40	181	DNT		P1	06H	20.41		TEH	TEC	.560	ZBATF	21	C	
107	56	1.46	176	DNT		P1	09H	-.43		TEH	TEC	.560	ZBATF	20	C	
107	56	.68	169	DNT		P1	09H	.52		TEH	TEC	.560	ZBATF	20	C	
109	56	2.96	176	DNT		P1	09H	-.47		TEH	TEC	.560	ZBATF	21	C	
109	56	2.18	179	DNT		P1	09H	.56		TEH	TEC	.560	ZBATF	21	C	
109	56	1.61	177	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	21	C	
109	56	1.84	178	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	21	C	
111	56	3.05	175	DNT		P1	09H	-.49		TEH	TEC	.560	ZBATF	20	C	
111	56	3.09	175	DNT		P1	09H	.51		TEH	TEC	.560	ZBATF	20	C	
111	56	1.13	177	DNT		P1	09C	-.64		TEH	TEC	.560	ZBATF	20	C	
111	56	1.35	175	DNT		P1	09C	.45		TEH	TEC	.560	ZBATF	20	C	
113	56	4.69	175	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	21	C	
113	56	4.09	179	DNT		P1	09H	.53		TEH	TEC	.560	ZBATF	21	C	
113	56	3.16	177	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	21	C	
113	56	3.11	177	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	21	C	
94	57	.96	181	DNT		P1	02C	22.99		TEH	TEC	.560	ZBATF	21	C	
108	57	1.23	175	DNT		P1	09H	-.46		TEH	TEC	.560	ZBATF	20	C	
108	57	1.32	171	DNT		P1	09H	.51		TEH	TEC	.560	ZBATF	20	C	
110	57	2.03	174	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	21	C	
110	57	1.31	176	DNT		P1	09H	.59		TEH	TEC	.560	ZBATF	21	C	
110	57	1.12	175	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	21	C	
112	57	2.12	176	DNT		P1	09H	-.49		TEH	TEC	.560	ZBATF	20	C	
112	57	1.56	176	DNT		P1	09H	.54		TEH	TEC	.560	ZBATF	20	C	
112	57	1.18	177	DNT		P1	09C	-.62		TEH	TEC	.560	ZBATF	20	C	
112	57	1.14	175	DNT		P1	09C	.46		TEH	TEC	.560	ZBATF	20	C	
114	57	5.20	176	DNT		P1	09H	-.53		TEH	TEC	.560	ZBATF	21	C	
114	57	3.40	180	DNT		P1	09H	.56		TEH	TEC	.560	ZBATF	21	C	
114	57	2.09	176	DNT		P1	09C	-.64		TEH	TEC	.560	ZBATF	21	C	
114	57	1.57	175	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	21	C	
65	58	1.09	174	DNT		P1	08C	31.58		TEH	TEC	.560	ZBATF	19	C	
109	58	1.67	178	DNT		P1	09H	-.47		TEH	TEC	.560	ZBATF	21	C	
109	58	1.22	176	DNT		P1	09H	.56		TEH	TEC	.560	ZBATF	21	C	
111	58	1.46	176	DNT		P1	09H	-.49		TEH	TEC	.560	ZBATF	20	C	
111	58	1.16	172	DNT		P1	09H	.54		TEH	TEC	.560	ZBATF	20	C	
111	58	1.03	176	DNT		P1	09C	-.59		TEH	TEC	.560	ZBATF	20	C	
113	58	3.29	176	DNT		P1	09H	-.53		TEH	TEC	.560	ZBATF	21	C	
113	58	2.61	177	DNT		P1	09H	.53		TEH	TEC	.560	ZBATF	21	C	
113	58	2.50	177	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	21	C	
113	58	2.24	177	DNT		P1	09C	.44		TEH	TEC	.560	ZBATF	21	C	
114	59	3.57	178	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	32	C	
114	59	2.73	182	DNT		P1	09H	.53		TEH	TEC	.560	ZBATF	32	C	
114	59	2.04	177	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	32	C	
114	59	.93	175	DNT		P1	09C	.50		TEH	TEC	.560	ZBATF	32	C	
111	60	.83	175	DNT		P1	09H	-.47		TEH	TEC	.560	ZBATF	31	C	
111	60	.81	175	DNT		P1	09H	.52		TEH	TEC	.560	ZBATF	31	C	
113	60	2.09	175	DNT		P1	09H	-.47		TEH	TEC	.560	ZBATF	32	C	
113	60	1.66	178	DNT		P1	09H	.56		TEH	TEC	.560	ZBATF	32	C	
113	60	1.04	175	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	32	C	
115	60	4.13	179	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	32	C	
115	60	3.45	180	DNT		P1	09H	.56		TEH	TEC	.560	ZBATF	32	C	
115	60	1.44	176	DNT		P1	09C	-.63		TEH	TEC	.560	ZBATF	32	C	
66	61	2.50	178	DNT		P1	09H	.62		TEH	TEC	.560	ZBATF	32	C	
78	61	1.92	177	DNT		P1	09C	.41		TEH	TEC	.560	ZBATF	32	C	
114	61	1.85	176	DNT		P1	09H	-.45		TEH	TEC	.560	ZBATF	32	C	
114	61	2.60	179	DNT		P1	09H	.56		TEH	TEC	.560	ZBATF	32	C	
114	61	1.34	177	DNT		P1	09C	-.61		TEH	TEC	.560	ZBATF	32	C	

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
109	62	.78	182	DNT		P1	06C	15.06		TEH	TEC	.560	ZBATF	32	C	
115	62	2.05	176	DNT		P1	09H	-.44		TEH	TEC	.560	ZBATF	32	C	
115	62	1.73	177	DNT		P1	09H	.56		TEH	TEC	.560	ZBATF	32	C	
20	63	1.21	175	DNT		P1	06H	7.52		TEH	TEC	.560	ZBATF	10	C	
38	63	.86	174	DNT		P1	08C	35.22		TEH	TEC	.560	ZBATF	10	C	
82	63	1.20	183	DNT		P1	02H	19.40		TEH	TEC	.560	ZBATF	32	C	
61	64	.94	174	DNT		P1	08H	36.98		TEH	TEC	.560	ZBATF	32	C	
113	64	.93	181	DNT		P1	06H	7.19		TEH	TEC	.560	ZBATF	31	C	
115	64	1.43	176	DNT		P1	09H	-.48		TEH	TEC	.560	ZBATF	32	C	
115	64	2.63	179	DNT		P1	09H	.61		TEH	TEC	.560	ZBATF	32	C	
39	66	1.32	181	DNT		P1	FBC	9.62		TEH	TEC	.560	ZBATF	11	C	
113	66	.97	176	DNT		P1	09H	.60		TEH	TEC	.560	ZBATF	31	C	
115	66	1.14	174	DNT		P1	09H	-.43		TEH	TEC	.560	ZBATF	32	C	
115	66	1.08	178	DNT		P1	09H	.61		TEH	TEC	.560	ZBATF	32	C	
6	67	1.55	174	DNT		P1	08C	37.57		TEH	TEC	.560	ZBATF	10	C	
76	67	.71	172	DNT		P1	08H	33.45		TEH	TEC	.560	ZBATF	34	C	
13	68	1.29	173	DNT		P1	09C	-.45		TEH	TEC	.560	ZBATF	11	C	
27	68	2.10	175	DNT		P1	09C	-.78		TEH	TEC	.560	ZBATF	11	C	
115	68	.95	176	DNT		P1	09H	.56		TEH	TEC	.560	ZBATF	34	C	
38	69	2.47	184	DNT		P1	TSH	6.41		TEH	TEC	.560	ZBATF	10	C	
66	69	1.37	180	DNT		P1	07H	24.08		TEH	TEC	.560	ZBATF	33	C	
72	69	1.50	176	DNT		P1	08H	33.01		TEH	TEC	.560	ZBATF	34	C	
37	70	1.27	182	DNT		P1	06H	16.44		TEH	TEC	.560	ZBATF	11	C	
37	70	1.06	172	DNT		P1	08C	32.37		TEH	TEC	.560	ZBATF	11	C	
37	70	.99	171	DNT		P1	08C	36.62		TEH	TEC	.560	ZBATF	11	C	
115	70	.95	177	DNT		P1	09H	.61		TEH	TEC	.560	ZBATF	34	C	
4	71	2.06	182	DNT		P1	08C	18.86		09H	TEC	.560	ZBACS	6	C	
4	71	2.08	183	DNT		P1	08C	18.87		09H	TEC	.560	ZBACS	39	C	
28	71	1.11	172	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	38	H	
27	72	1.04	178	DNT		P1	04C	-.26		TEC	TEH	.560	ZBATF	37	H	
45	72	1.38	175	DNT		P1	08H	29.79		TEC	TEH	.560	ZBATF	38	H	
45	72	1.66	172	DNT		P1	08H	30.30		TEC	TEH	.560	ZBATF	38	H	
45	72	2.61	173	DNT		P1	08H	36.48		TEC	TEH	.560	ZBATF	38	H	
61	72	1.00	170	DNT		P1	08C	30.86		TEH	TEC	.560	ZBATF	33	C	
36	73	1.02	178	DNT		P1	02C	17.66		TEC	TEH	.560	ZBATF	38	H	
62	73	1.08	175	DNT		P1	08H	35.22		TEH	TEC	.560	ZBATF	33	C	
62	73	1.06	175	DNT		P1	08C	31.11		TEH	TEC	.560	ZBATF	33	C	
64	73	.99	177	DNT		P1	08H	36.09		TEH	TEC	.560	ZBATF	34	C	
82	73	1.24	172	DNT		P1	08H	22.50		TEH	TEC	.560	ZBATF	33	C	
31	74	.85	170	DNT		P1	09C	-.24		TEC	TEH	.560	ZBATF	37	H	
68	75	.92	183	DNT		P1	02C	20.67		TEH	TEC	.560	ZBATF	36	C	
114	75	.90	176	DNT		P1	09H	.50		TEH	TEC	.560	ZBATF	36	C	
29	76	.94	184	DNT		P1	04H	36.36		TEC	TEH	.560	ZBATF	38	H	
29	76	1.71	181	DNT		P1	04H	36.61		TEC	TEH	.560	ZBATF	38	H	
62	77	.90	174	DNT		P1	08C	35.83		TEH	TEC	.560	ZBATF	35	C	
1	78	1.12	180	DNT		P1	03C	21.45		08H	TEC	.560	ZBACS	40	C	
61	78	1.04	173	DNT		P1	08H	31.79		TEH	TEC	.560	ZBATF	35	C	
63	78	2.57	178	DNT		P1	08H	32.95		TEH	TEC	.560	ZBATF	36	C	
63	78	1.06	178	DNT		P1	08H	34.53		TEH	TEC	.560	ZBATF	36	C	
63	78	3.18	176	DNT		P1	08C	30.70		TEH	TEC	.560	ZBATF	36	C	
67	78	1.03	172	DNT		P1	08C	29.62		TEH	TEC	.560	ZBATF	36	C	
77	78	.90	182	DNT		P1	07C	14.45		TEH	TEC	.560	ZBATF	35	C	
2	79	2.47	181	DNT		P1	02H	17.53		09H	TEH	.560	ZBATF	42	H	
62	79	1.17	173	DNT		P1	08H	36.32		TEH	TEC	.560	ZBATF	35	C	
100	79	.89	181	DNT		P1	05H	30.18		TEH	TEC	.560	ZBATF	36	C	
114	79	1.34	173	DNT		P1	09H	-.48		TEH	TEC	.560	ZBATF	36	C	
61	80	.81	174	DNT		P1	08C	32.81		TEH	TEC	.560	ZBATF	35	C	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
92	81	.60	184	DNT		P1	02C	19.46		TEH	TEC	.560	ZBATF	37	C	
19	82	.89	179	DNT		P1	07C	25.38		TEC	TEH	.560	ZBATF	37	H	
65	82	3.13	182	DNT		P1	02C	15.52		TEH	TEC	.560	ZBATF	38	C	
113	82	1.29	174	DNT		P1	09H	-.50		TEH	TEC	.560	ZBATF	38	C	
112	83	1.10	179	DNT		P1	09H	-.55		TEH	TEC	.560	ZBATF	37	C	
17	84	1.42	181	DNT		P1	07H	16.59		TEC	TEH	.560	ZBATF	39	H	
35	84	1.15	175	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	40	H	
113	84	2.08	173	DNT		P1	09H	-.65		TEC	TEH	.560	ZBATF	31	H	
108	85	1.06	174	DNT		P1	09H	-.65		TEC	TEH	.560	ZBATF	31	H	
112	85	2.38	176	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	31	H	
114	85	2.46	177	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	31	H	
1	86	1.92	173	DNT		P1	09H	8.20		08H	TEC	.560	ZBACS	40	C	
41	86	1.12	180	DNT		P1	07H	20.46		TEC	TEH	.560	ZBATF	40	H	
71	86	1.45	182	DNT		P1	06C	8.68		TEC	TEH	.560	ZBATF	30	H	
111	86	1.78	176	DNT		P1	09H	-.65		TEC	TEH	.560	ZBATF	30	H	
113	86	2.78	177	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	30	H	
113	86	1.64	176	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	30	H	
110	87	1.00	173	DNT		P1	09H	.41		TEC	TEH	.560	ZBATF	31	H	
112	87	1.95	175	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	31	H	
112	87	1.02	173	DNT		P1	09H	.39		TEC	TEH	.560	ZBATF	31	H	
19	88	1.18	179	DNT		P1	TSC	9.71		TEC	TEH	.560	ZBATF	39	H	
37	88	2.14	171	DNT		P1	08C	23.91		TEC	TEH	.560	ZBATF	40	H	
39	88	1.08	170	DNT		P1	08C	26.14		TEC	TEH	.560	ZBATF	39	H	
109	88	1.52	177	DNT		P1	09H	-.65		TEC	TEH	.560	ZBATF	30	H	
109	88	1.83	177	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	30	H	
111	88	1.11	174	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	30	H	
113	88	2.45	173	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	30	H	
113	88	9.01	178	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	30	H	
113	88	.91	166	DNT		P1	09C	-.41		TEC	TEH	.560	ZBATF	30	H	
113	88	6.35	178	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	30	H	
113	88	1.16	181	DNT		P1	09C	.81		TEC	TEH	.560	ZBATF	30	H	
108	89	1.26	176	DNT		P1	09H	.41		TEC	TEH	.560	ZBATF	31	H	
110	89	1.01	173	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	31	H	
110	89	1.45	174	DNT		P1	09H	.36		TEC	TEH	.560	ZBATF	31	H	
112	89	1.91	176	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	31	H	
112	89	2.18	176	DNT		P1	09H	.36		TEC	TEH	.560	ZBATF	31	H	
55	90	1.77	181	DNT		P1	02C	5.27		TEC	TEH	.560	ZBATF	30	H	
107	90	1.04	175	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	30	H	
109	90	1.05	173	DNT		P1	09H	.38		TEC	TEH	.560	ZBATF	30	H	
111	90	2.02	175	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	30	H	
111	90	2.67	177	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	30	H	
72	91	2.02	183	DNT		P1	04C	34.42		TEC	TEH	.560	ZBATF	31	H	
92	91	.95	183	DNT		P1	02C	18.36		TEC	TEH	.560	ZBATF	31	H	
108	91	1.13	172	DNT		P1	09H	-.65		TEC	TEH	.560	ZBATF	31	H	
108	91	1.32	177	DNT		P1	09H	.44		TEC	TEH	.560	ZBATF	31	H	
110	91	1.28	174	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	31	H	
110	91	1.73	176	DNT		P1	09H	.39		TEC	TEH	.560	ZBATF	31	H	
110	91	1.52	173	DNT		P1	09C	.49		TEC	TEH	.560	ZBATF	31	H	
13	92	.99	176	DNT		P1	01C	13.04		TEC	TEH	.560	ZBATF	39	H	
107	92	1.07	175	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	30	H	
107	92	1.28	174	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	30	H	
109	92	1.27	173	DNT		P1	09H	.38		TEC	TEH	.560	ZBATF	30	H	
109	92	1.35	174	DNT		P1	09C	.43		TEC	TEH	.560	ZBATF	30	H	
111	92	2.17	175	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	30	H	
111	92	3.75	178	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	30	H	
110	93	2.21	177	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	29	H	
65	94	1.03	172	DNT		P1	08H	11.86		TEC	TEH	.560	ZBATF	28	H	
93	94	1.61	180	DNT		P1	02H	.67		TEC	TEH	.560	ZBATF	28	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
106	95	1.22	174	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	29	H	
106	95	1.23	173	DNT		P1	09H	.39		TEC	TEH	.560	ZBATF	29	H	
97	96	1.06	173	DNT		P1	09H	1.29		TEC	TEH	.560	ZBATF	28	H	
107	96	1.34	173	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	28	H	
107	96	2.16	171	DNT		P1	09H	.38		TEC	TEH	.560	ZBATF	28	H	
106	97	1.80	171	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	29	H	
108	97	1.13	173	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	29	H	
108	97	7.45	177	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	29	H	
67	98	1.29	181	DNT		P1	04C	30.69		TEC	TEH	.560	ZBATF	28	H	
67	98	1.82	179	DNT		P1	03C	34.45		TEC	TEH	.560	ZBATF	28	H	
75	98	1.27	169	DNT		P1	08C	26.60		TEC	TEH	.560	ZBATF	28	H	
107	98	1.37	170	DNT		P1	09H	.38		TEC	TEH	.560	ZBATF	28	H	
68	99	2.37	179	DNT		P1	FBC	8.83		TEC	TEH	.560	ZBATF	29	H	
88	99	2.32	180	DNT		P1	06C	8.53		TEC	TEH	.560	ZBATF	29	H	
106	99	3.73	178	DNT		P1	09H	.44		TEC	TEH	.560	ZBATF	29	H	
106	99	4.82	178	DNT		P1	09C	.52		TEC	TEH	.560	ZBATF	29	H	
11	100	1.14	182	DNT		P1	08C	36.10		TEC	TEH	.560	ZBATF	20	H	
29	100	1.06	181	DNT		P1	07H	24.74		TEC	TEH	.560	ZBATF	20	H	
20	101	.83	183	DNT		P1	06H	1.05		TEC	TEH	.560	ZBATF	21	H	
102	101	1.43	171	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	27	H	
104	101	1.69	171	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	27	H	
27	102	1.06	184	DNT		P1	TSC	4.30		TEC	TEH	.560	ZBATF	20	H	
103	102	2.25	175	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	26	H	
96	103	1.20	173	DNT		P1	TSH	4.02		TEC	TEH	.560	ZBATF	27	H	
96	103	1.05	173	DNT		P1	06H	-.08		TEC	TEH	.560	ZBATF	27	H	
100	103	1.05	170	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	27	H	
102	103	1.54	171	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	27	H	
70	105	1.30	177	DNT		P1	08C	27.50		TEC	TEH	.560	ZBATF	27	H	
78	105	1.06	179	DNT		P1	05C	2.01		TEC	TEH	.560	ZBATF	27	H	
98	105	1.25	170	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	27	H	
100	105	1.72	172	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	27	H	
75	106	.99	180	DNT		P1	05H	8.42		TEC	TEH	.560	ZBATF	26	H	
97	108	1.15	174	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	26	H	
86	109	1.36	180	DNT		P1	01H	27.49		TEC	TEH	.560	ZBATF	27	H	
61	110	1.05	188	DNT		P1	07H	30.45		TEC	TEH	.560	ZBATF	26	H	
81	110	2.49	178	DNT		P1	09H	-1.13		TEC	TEH	.560	ZBATF	26	H	
81	110	1.84	177	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	26	H	
81	110	1.48	168	DNT		P1	08C	33.18		TEC	TEH	.560	ZBATF	26	H	
81	110	4.59	178	DNT		P1	08C	34.20		TEC	TEH	.560	ZBATF	26	H	
95	110	1.05	173	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	26	H	
72	111	1.25	183	DNT		P1	01C	31.27		TEC	TEH	.560	ZBATF	27	H	
16	113	1.19	171	DNT		P1	09H	-.42		TEC	TEH	.560	ZBATF	21	H	
82	113	.97	185	DNT		P1	01C	36.05		TEC	TEH	.560	ZBATF	25	H	
92	113	1.00	172	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	25	H	
23	114	.97	183	DNT		P1	02H	29.23		TEC	TEH	.560	ZBATF	20	H	
73	114	3.02	182	DNT		P1	AV6	13.40		TEC	TEH	.560	ZBATF	24	H	
31	116	1.11	184	DNT		P1	08C	-.80		TEC	TEH	.560	ZBATF	22	H	
45	116	3.03	178	DNT		P1	08H	32.28		TEC	TEH	.560	ZBATF	22	H	
11	118	.34	170	DNT		P1	02C	.38		TEC	TEH	.560	ZBATF	22	H	
37	118	.88	175	DNT		P1	08C	36.92		TEC	TEH	.560	ZBATF	22	H	
79	118	1.05	166	DNT		P1	08C	19.93		TEC	TEH	.560	ZBATF	24	H	
18	119	.92	174	DNT		P1	08H	35.99		TEC	TEH	.560	ZBATF	23	H	
38	119	1.39	174	DNT		P1	08C	36.63		TEC	TEH	.560	ZBATF	23	H	
50	119	1.21	182	DNT		P1	TSH	4.70		TEC	TEH	.560	ZBATF	25	H	
48	121	1.19	171	DNT		P1	08C	34.31		TEC	TEH	.560	ZBATF	25	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	•PDIA	PTYPE	CAL	L	COM
50	121	1.11	172	DNT		P1	08C	34.34		TEC	TEH	.560	ZBATF	25	H	
4	123	.73	184	DNT		P1	04C	18.54		09H	TEC	.560	ZBATF	1	C	Result of History Review
4	123	1.08	184	DNT		P1	04C	23.62		09H	TEC	.560	ZBATF	1	C	
26	123	1.93	176	DNT		P1	09C	-1.05		TEC	TEH	.560	ZBATF	23	H	
26	123	.94	174	DNT		P1	08C	33.91		TEC	TEH	.560	ZBATF	23	H	
26	123	1.39	175	DNT		P1	08C	35.80		TEC	TEH	.560	ZBATF	23	H	
26	123	2.97	177	DNT		P1	08C	36.87		TEC	TEH	.560	ZBATF	23	H	
26	123	.78	175	DNT		P1	07C	37.57		TEC	TEH	.560	ZBATF	23	H	
32	123	1.04	174	DNT		P1	02C	21.16		TEC	TEH	.560	ZBATF	23	H	
38	123	1.25	183	DNT		P1	01H	24.84		TEC	TEH	.560	ZBATF	23	H	
38	123	3.99	179	DNT		P1	08C	37.50		TEC	TEH	.560	ZBATF	23	H	
66	123	.63	170	DNT		P1	08C	35.25		TEC	TEH	.560	ZBATF	25	H	
19	124	2.38	178	DNT		P1	08C	30.16		TEC	TEH	.560	ZBATF	22	H	
29	124	.72	172	DNT		P1	08H	36.19		TEC	TEH	.560	ZBATF	22	H	
29	124	.98	177	DNT		P1	08H	37.15		TEC	TEH	.560	ZBATF	22	H	
29	124	1.78	176	DNT		P1	08H	37.54		TEC	TEH	.560	ZBATF	22	H	
35	124	.89	174	DNT		P1	08C	36.56		TEC	TEH	.560	ZBATF	22	H	
37	124	1.06	174	DNT		P1	08H	14.74		TEC	TEH	.560	ZBATF	22	H	
37	124	2.28	176	DNT		P1	08C	7.14		TEC	TEH	.560	ZBATF	22	H	
37	124	.90	174	DNT		P1	08C	13.40		TEC	TEH	.560	ZBATF	22	H	
37	124	1.34	175	DNT		P1	08C	34.68		TEC	TEH	.560	ZBATF	22	H	
37	124	1.45	176	DNT		P1	08C	36.48		TEC	TEH	.560	ZBATF	22	H	
53	124	1.07	174	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	24	H	
55	124	1.30	175	DNT		P1	09C	.63		TEC	TEH	.560	ZBATF	24	H	
18	125	.92	174	DNT		P1	09H	.10		TEC	TEH	.560	ZBATF	23	H	
36	125	2.63	179	DNT		P1	08H	34.77		TEC	TEH	.560	ZBATF	23	H	
48	125	1.07	172	DNT		P1	07C	12.09		TEC	TEH	.560	ZBATF	25	H	
54	125	1.60	175	DNT		P1	08H	34.54		TEC	TEH	.560	ZBATF	25	H	
58	125	1.90	171	DNT		P1	08C	28.85		TEC	TEH	.560	ZBATF	25	H	
21	126	1.90	175	DNT		P1	08H	37.59		TEC	TEH	.560	ZBATF	22	H	
35	126	1.17	175	DNT		P1	08H	31.78		TEC	TEH	.560	ZBATF	22	H	
47	126	2.61	174	DNT		P1	08H	32.27		TEC	TEH	.560	ZBATF	24	H	
47	126	2.86	175	DNT		P1	08H	32.98		TEC	TEH	.560	ZBATF	24	H	
47	126	1.48	174	DNT		P1	08H	34.38		TEC	TEH	.560	ZBATF	24	H	
47	126	1.76	175	DNT		P1	08H	37.37		TEC	TEH	.560	ZBATF	24	H	
52	127	1.04	184	DNT		P1	F8C	11.35		TEC	TEH	.560	ZBATF	25	H	
52	127	1.14	182	DNT		P1	F8C	12.68		TEC	TEH	.560	ZBATF	25	H	
18	129	1.67	182	DNT		P1	02C	30.82		TEC	TEH	.560	ZBATF	14	H	
42	131	1.32	172	DNT		P1	08C	35.07		TEC	TEH	.560	ZBATF	14	H	
1	132	.83	180	DNT		P1	08C	37.38		09H	TEC	.560	ZBACS	4	C	Result of Senior/History Analyst Review
47	132	.92	181	DNT		P1	08C	30.69		TEC	TEH	.560	ZBATF	15	H	
55	132	1.24	182	DNT		P1	01C	10.49		TEC	TEH	.560	ZBATF	14	H	
3	134	1.05	179	DNT		P1	TSC	18.18		09H	TEC	.560	ZBATF	3	C	
19	134	1.24	174	DNT		P1	09C	-.87		TEC	TEH	.560	ZBATF	17	H	
8	135	1.50	180	DNT		P1	04C	31.61		TEC	TEH	.560	ZBATF	17	H	
37	136	.78	172	DNT		P1	09C	.61		TEC	TEH	.560	ZBATF	14	H	
39	136	.81	172	DNT		P1	09C	.34		TEC	TEH	.560	ZBATF	15	H	
41	136	1.30	173	DNT		P1	09C	.69		TEC	TEH	.560	ZBATF	14	H	
36	137	1.42	178	DNT		P1	09C	-.45		TEC	TEH	.560	ZBATF	14	H	
36	137	2.45	177	DNT		P1	09C	.66		TEC	TEH	.560	ZBATF	14	H	
31	138	1.00	172	DNT		P1	09C	.69		TEC	TEH	.560	ZBATF	17	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

SG - B NON-QUANTIFIABLE SIGNALS

Shearon Harris RFO11 CQL D75

X 74 TUBE WITH NON-QUANTIFIABLE SIGNAL

* 4 STAY

▫ 1 PLUGGED TUBE

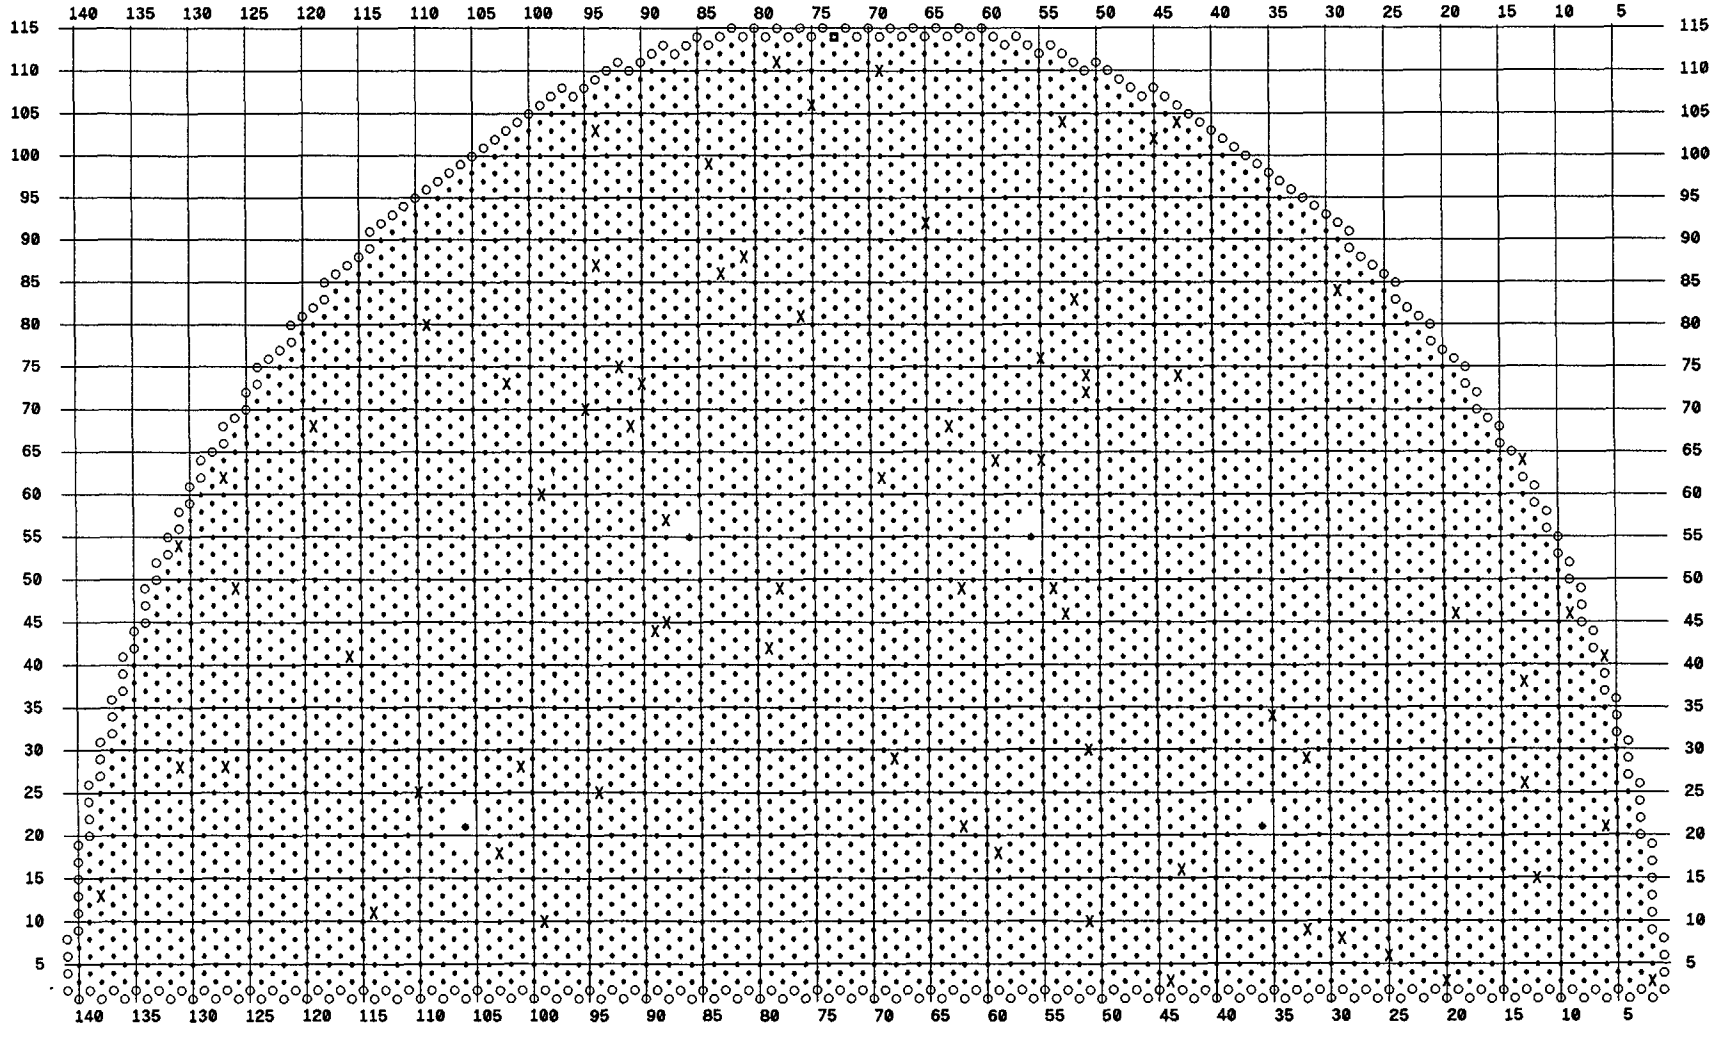

Westinghouse Electric Company LLC - NSBU ST2000 05/08/2003 00:06:43

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	I	CRLEN	CEG	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
3	2	.81	10	NQS		P1	08H	2.74					09H	TEH	.560	ZBATF	36	H	Result of Senior/History Analyst Review
21	6	.34	8	NQS		P1	FBH	11.21					TEC	TEH	.560	ZBATF	34	H	Result of Senior/History Analyst Review
41	6	.47	357	NQS		P1	08H	6.39					TEC	TEH	.560	ZBATF	34	H	Result of Senior/History Analyst Review
46	9	.28	158	NQS		P1	06C	30.88					TEC	TEH	.560	ZBATF	35	H	Result of Senior/History Analyst Review
46	9	.11	166	NQS		P1	04C	13.15					TEC	TEH	.560	ZBATF	35	H	Result of Senior/History Analyst Review
15	12	.08	84	NQS		P1	03H	21.48					TEC	TEH	.560	ZBATF	35	H	Result of Senior/History Analyst Review
15	12	.10	58	NQS		P1	03H	22.33					TEC	TEH	.560	ZBATF	35	H	Result of Senior/History Analyst Review
26	13	.08	139	NQS		P1	03H	32.88					TEC	TEH	.560	ZBATF	35	H	Result of Senior/History Analyst Review
38	13	.07	142	NQS		P1	02H	15.80					TEC	TEH	.560	ZBATF	35	H	Result of Senior/History Analyst Review
64	13	.25	16	NQS		P1	08C	10.62					TEC	TEH	.560	ZBATF	35	H	Result of Senior/History Analyst Review
46	19	1.10	3	NQS		P1	02H	.48	5.21				TEH	TEC	.560	ZBATF	29	C	Result of Senior/History Analyst Review
3	20	.58	170	NQS		P1	07H	25.99					09H	TEH	.560	ZBATF	2	H	Result of Senior/History Analyst Review
6	25	.17	18	NQS		P1	08C	11.33					TEH	TEC	.560	ZBATF	15	C	Result of Senior/History Analyst Review
8	29	.09	104	NQS		P1	02C	10.21					TEH	TEC	.560	ZBATF	15	C	Result of Senior/History Analyst Review
84	29	.33	27	NQS		P1	TSH	13.25					TEH	TEC	.560	ZBATF	28	C	Result of Senior/History Analyst Review
9	32	.08	41	NQS		P1	06H	25.63					TEH	TEC	.560	ZBATF	14	C	Result of Senior/History Analyst Review
29	32	.20	167	NQS		P1	08H	29.00					TEH	TEC	.560	ZBATF	14	C	Result of Senior/History Analyst Review
34	35	.30	152	NQS		P1	08H	34.72					TEH	TEC	.560	ZBATF	14	C	Result of Senior/History Analyst Review
16	43	.42	180	NQS		P1	06H	7.43					TEH	TEC	.560	ZBATF	12	C	Result of Senior/History Analyst Review
74	43	.50	6	NQS		P1	06H	14.24					TEH	TEC	.560	ZBATF	26	C	Result of Senior/History Analyst Review
74	43	.34	5	NQS		P1	07H	13.46					TEH	TEC	.560	ZBATF	26	C	Result of Senior/History Analyst Review
74	43	.64	3	NQS		P1	02C	24.53					TEH	TEC	.560	ZBATF	26	C	Result of Senior/History Analyst Review
104	43	.23	15	NQS		P1	AV2	6.67					TEH	TEC	.560	ZBATF	24	C	Result of Senior/History Analyst Review
3	44	.39	4	NQS		P1	FBH	5.74					09H	TEH	.560	ZBATF	3	H	Result of Senior/History Analyst Review
3	44	.45	5	NQS		P1	01H	27.94					09H	TEH	.560	ZBATF	3	H	Result of Senior/History Analyst Review
3	44	.99	5	NQS		P1	01H	28.61					09H	TEH	.560	ZBATF	3	H	Result of Senior/History Analyst Review
3	44	.53	2	NQS		P1	04H	21.25					09H	TEH	.560	ZBATF	3	H	Result of Senior/History Analyst Review
102	45	.38	6	NQS		P1	01H	21.57					TEH	TEC	.560	ZBATF	24	C	Result of Senior/History Analyst Review
102	45	.41	6	NQS		P1	01H	27.17					TEH	TEC	.560	ZBATF	24	C	Result of Senior/History Analyst Review
102	45	.55	4	NQS		P1	01H	28.51					TEH	TEC	.560	ZBATF	24	C	Result of Senior/History Analyst Review
102	45	.56	2	NQS		P1	01H	28.91					TEH	TEC	.560	ZBATF	24	C	Result of Senior/History Analyst Review
10	51	.67	1	NQS		P1	02C	9.31					TEH	TEC	.560	ZBATF	8	C	Result of Senior/History Analyst Review
30	51	.21	148	NQS		P1	08H	37.38					TEH	TEC	.560	ZBATF	8	C	Result of Senior/History Analyst Review
72	51	.14	156	NQS		P1	04C	32.85					TEH	TEC	.560	ZBATF	23	C	Result of Senior/History Analyst Review
74	51	.56	2	NQS		P1	01H	23.62					TEH	TEC	.560	ZBATF	24	C	Result of Senior/History Analyst Review
83	52	.07	152	NQS		P1	AV3	5.90					TEH	TEC	.560	ZBATF	20	C	Result of Senior/History Analyst Review
46	53	.08	157	NQS		P1	FBC	6.06					TEH	TEC	.560	ZBACS	42	C	Result of Senior/History Analyst Review
104	53	.12	153	NQS		P1	02H	35.31					TEH	TEC	.560	ZBATF	21	C	Result of Senior/History Analyst Review
49	54	.14	108	NQS		P1	TSH	10.00					TEH	TEC	.560	ZBATF	21	C	Result of Senior/History Analyst Review
64	55	.14	35	NQS		P1	AV1	10.82					TEH	TEC	.560	ZBATF	21	C	Result of Senior/History Analyst Review
76	55	1.19	11	NQS		P1	TSH	1.30					TEH	TEC	.560	ZBATF	21	C	Result of Senior/History Analyst Review
18	59	.53	4	NQS		P1	01H	32.40					TEH	TEC	.560	ZBATF	10	C	Result of Senior/History Analyst Review
64	59	.22	162	NQS		P1	TSH	12.93					TEH	TEC	.560	ZBATF	31	C	Result of Senior/History Analyst Review
21	62	.08	101	NQS		P1	03H	26.76					TEH	TEC	.560	ZBATF	11	C	Result of Senior/History Analyst Review
49	62	.07	124	NQS		P1	06H	32.85					TEH	TEC	.560	ZBATF	32	C	Result of Senior/History Analyst Review
68	63	.15	33	NQS		P1	AV8	7.04					TEH	TEC	.560	ZBATF	31	C	Result of Senior/History Analyst Review
92	65	1.27	2	NQS		P1	08H	29.50					TEH	TEC	.560	ZBATF	32	C	Result of Senior/History Analyst Review
29	68	.08	31	NQS		P1	05C	22.37					TEH	TEC	.560	ZBATF	11	C	Result of Senior/History Analyst Review
62	69	.09	28	NQS		P1	06C	6.69					TEH	TEC	.560	ZBATF	33	C	Result of Senior/History Analyst Review
110	69	.06	13	NQS		P1	AV2	18.72					TEH	TEC	.560	ZBATF	33	C	Result of Senior/History Analyst Review
106	75	.09	30	NQS		P1	04H	22.67					TEH	TEC	.560	ZBATF	36	C	Result of Senior/History Analyst Review
81	76	.27	2	NQS		P1	07C	32.31					TEH	TEC	.560	ZBATF	35	C	Result of Senior/History Analyst Review
49	78	.09	11	NQS		P1	02H	8.50					TEH	TEC	.560	ZBATF	35	C	Result of Senior/History Analyst Review
111	78	.09	139	NQS		P1	09H	3.68					TEH	TEC	.560	ZBATF	36	C	Result of Senior/History Analyst Review
42	79	.09	48	NQS		P1	05H	8.96					TEC	TEH	.560	ZBATF	37	H	Result of Senior/History Analyst Review
88	81	.05	110	NQS		P1	06H	14.80					TEH	TEC	.560	ZBATF	37	C	Result of Senior/History Analyst Review
86	83	.07	74	NQS		P1	AV1	11.93					TEH	TEC	.560	ZBATF	38	C	Result of Senior/History Analyst Review
99	84	.13	66	NQS		P1	AV8	3.66					TEC	TEH	.560	ZBATF	30	H	Result of Senior/History Analyst Review
99	84	.04	96	NQS		P1	AV8	4.13					TEC	TEH	.560	ZBATF	30	H	Result of Senior/History Analyst Review
45	88	.08	25	NQS		P1	08H	16.98					TEC	TEH	.560	ZBATF	40	H	Result of Senior/History Analyst Review
57	88	.13	28	NQS		P1	08C	25.17					TEC	TEH	.560	ZBATF	30	H	Result of Senior/History Analyst Review
44	89	.12	123	NQS		P1	08C	12.61					TEC	TEH	.560	ZBATF	40	H	Result of Senior/History Analyst Review
73	90	.08	39	NQS		P1	04H	31.21					TEC	TEH	.560	ZBATF	30	H	Result of Senior/History Analyst Review
73	90	.08	142	NQS		P1	05H	7.69					TEC	TEH	.560	ZBATF	30	H	Result of Senior/History Analyst Review
73	90																		Non-Relevant Response - Non-flaw like in nature
73	90	.09	149	NQS		P1	05H	7.69					TEC	TEH	.560	ZBATF	30	H	Result of Senior/History Analyst Review
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	I	CRLEN	CEG	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	I	CRLEN	CEG	BEGT	ENDT	PDIA	PTYPE	CAL	L COM
73	90	.14	120	NQS		P1	06H	9.80					TEC	TEH	.560	ZBATF	30	H|Result of Senior/History Analyst Review
68	91	.11	38	NQS		P1	05C	15.95					TEC	TEH	.560	ZBATF	31	H|Result of Senior/History Analyst Review
75	92	.12	24	NQS		P1	09H	10.57					TEC	TEH	.560	ZBATF	30	H|Result of Senior/History Analyst Review
25	94	.09	112	NQS		P1	02H	22.89					TEC	TEH	.560	ZBATF	18	H|Result of Senior/History Analyst Review
87	94	.12	37	NQS		P1	08C	27.91					TEC	TEH	.560	ZBATF	28	H|Result of Senior/History Analyst Review
103	94	.23	157	NQS		P1	04H	30.02					TEC	TEH	.560	ZBATF	28	H|Result of Senior/History Analyst Review
70	95	.18	27	NQS		P1	06H	10.01					TEC	TEH	.560	ZBATF	29	H|Result of Senior/History Analyst Review
10	99	.07	30	NQS		P1	TSH	12.14					TEC	TEH	.560	ZBATF	21	H|Result of Senior/History Analyst Review
60	99	.10	43	NQS		P1	03C	25.12					TEC	TEH	.560	ZBATF	29	H|Result of Senior/History Analyst Review
28	101	.14	62	NQS		P1	07C	7.38					TEC	TEH	.560	ZBATF	21	H|Result of Senior/History Analyst Review
73	102	.10	52	NQS		P1	02C	4.13					TEC	TEH	.560	ZBATF	26	H|Result of Senior/History Analyst Review
18	103	.13	94	NQS		P1	03H	16.55					TEC	TEH	.560	ZBATF	21	H|Result of Senior/History Analyst Review
80	109	.06	61	NQS		P1	04H	21.59					TEC	TEH	.560	ZBATF	27	H|Result of Senior/History Analyst Review
25	110	.06	132	NQS		P1	04H	4.33					TEC	TEH	.560	ZBATF	20	H|Result of Senior/History Analyst Review
11	114	1.80	1	NQS		P1	08C	36.92					TEC	TEH	.560	ZBATF	20	H|Result of Senior/History Analyst Review
41	116	.10	22	NQS		P1	07H	30.09					TEC	TEH	.560	ZBATF	22	H|Result of Senior/History Analyst Review
68	119	.09	117	NQS		P1	07C	20.91					TEC	TEH	.560	ZBATF	25	H|Result of Senior/History Analyst Review
49	126	.15	29	NQS		P1	02H	30.43					TEC	TEH	.560	ZBATF	24	H|Result of Senior/History Analyst Review
28	127	.24	7	NQS		P1	05H	23.63					TEC	TEH	.560	ZBATF	23	H|Result of Senior/History Analyst Review
62	127	.14	29	NQS		P1	AV3	17.29					TEC	TEH	.560	ZBATF	25	H|Result of Senior/History Analyst Review
28	131	.63	3	NQS		P1	02H	19.40					TEC	TEH	.560	ZBATF	15	H|Result of Senior/History Analyst Review
54	131	.09	56	NQS		P1	03H	2.98					TEC	TEH	.560	ZBATF	14	H|Result of Senior/History Analyst Review
13	138	.07	82	NQS		P1	05C	3.32					TEC	TEH	.560	ZBATF	17	H|Result of Senior/History Analyst Review
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	I	CRLEN	CEG	BEGT	ENDT	PDIA	PTYPE	CAL	L COM

SG - B PERMEABILITY VARIATIONS

Shearon Harris RFO11 CQL D75

X 2 TUBE WITH PEMEABILITY VARIATION

* 4 STAY

□ 1 PLUGGED TUBE

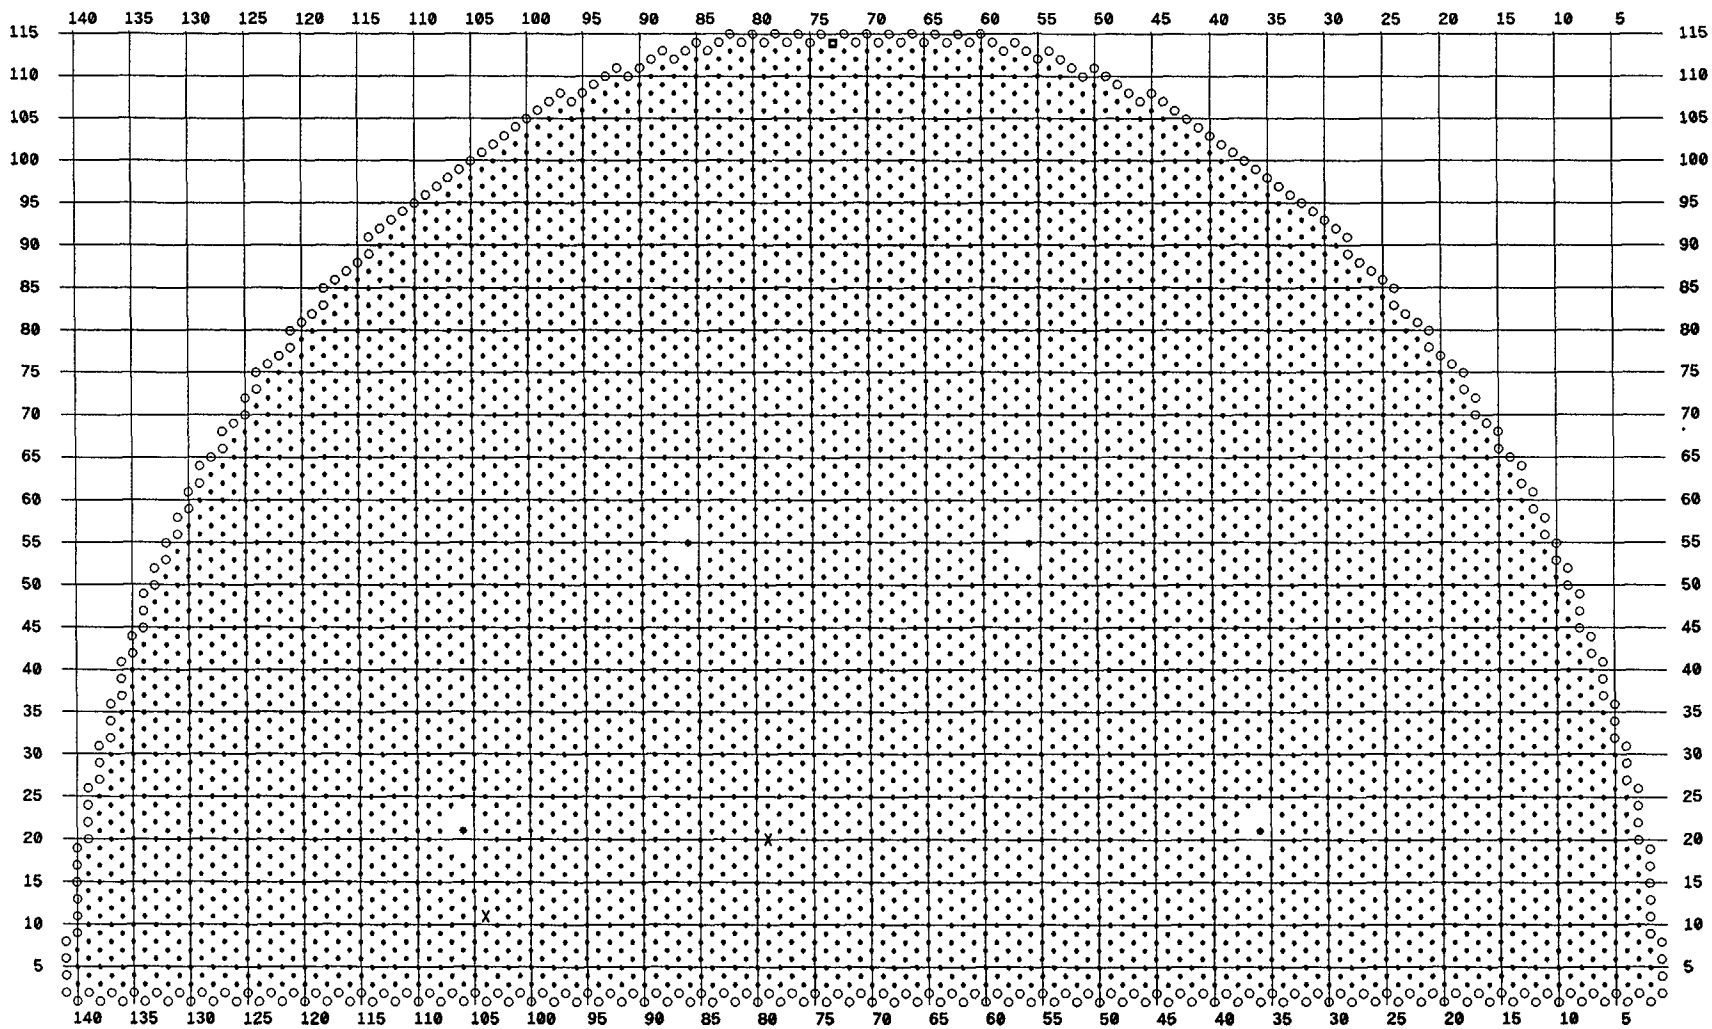

Westinghouse Electric Company LLC - NSBU ST2000 05/08/2003 00:54:24

SG - B Permeability Variations

Shearon Harris 1 RF011 CQL 20030501 05/08/2003 00:29:51

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
20	79	.99	7	PVN		1	TSC	6.00		TEC	TEH	.560	ZBATF	38	H	Result of Senior Analyst Review
11	104	2.06	4	PVN		1	08C	36.82		. TEC	TEH	.560	ZBATF	20	H	Result of Senior Analyst Review
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

Tubes: 2 Records: 2

SG - C DENTS

Shearon Harris RFO11 CQL D75

X 528 TUBE WITH DENT

* 4 STAY

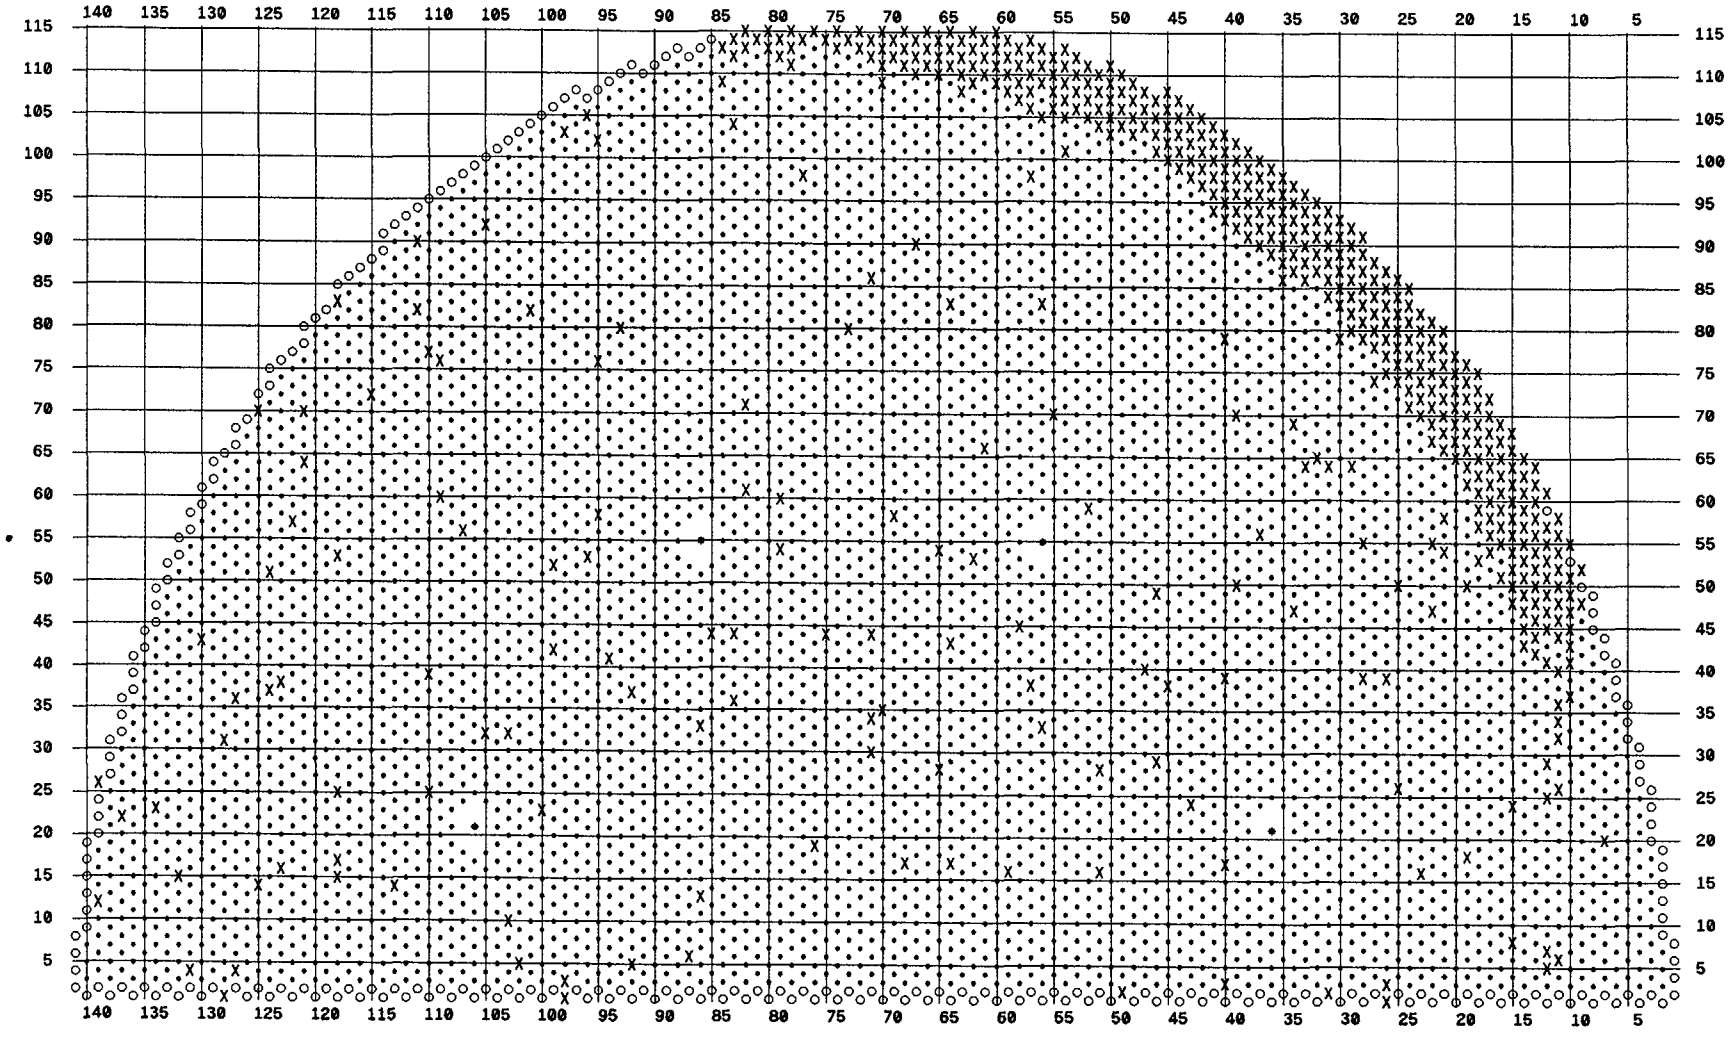

Westinghouse Electric Company LLC - NSBU ST2000 05/08/2003 02:11:04

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
20	7	.83	182	DNT		P1	01H	25.03		TEH	TEC	.560	ZBACS	43	C	
48	9	.85	179	DNT		P1	09C	-.80		TEC	TEH	.560	ZBATF	36	H	
52	9	1.14	181	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	36	H	
37	10	.80	174	DNT		P1	09C	-.87		TEC	TEH	.560	ZBATF	35	H	
41	10	.94	175	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	35	H	
43	10	.78	171	DNT		P1	09C	-.81		TEC	TEH	.560	ZBATF	35	H	
43	10	1.10	176	DNT		P1	03C	16.26		TEC	TEH	.560	ZBATF	35	H	
45	10	.93	183	DNT		P1	FBH	12.36		TEC	TEH	.560	ZBATF	35	H	
47	10	.99	175	DNT		P1	09C	-.79		TEC	TEH	.560	ZBATF	35	H	
49	10	.90	178	DNT		P1	TSH	1.28		TEC	TEH	.560	ZBATF	35	H	
51	10	.85	171	DNT		P1	09C	-.85		TEC	TEH	.560	ZBATF	35	H	
55	10	1.13	174	DNT		P1	09H	-.92		TEC	TEH	.560	ZBATF	35	H	
55	10	1.27	176	DNT		P1	09C	-.84		TEC	TEH	.560	ZBATF	35	H	
6	11	1.20	182	DNT		P1	04H	1.72		TEC	TEH	.560	ZBATF	35	H	
26	11	1.20	178	DNT		P1	TSH	11.97		TEC	TEH	.560	ZBATF	35	H	
32	11	.87	174	DNT		P1	09C	-.79		TEC	TEH	.560	ZBATF	35	H	
34	11	.77	173	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	35	H	
36	11	1.35	182	DNT		P1	02H	29.01		TEC	TEH	.560	ZBATF	35	H	
36	11	.90	174	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	35	H	
40	11	1.03	175	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	35	H	
44	11	1.13	173	DNT		P1	09C	-.79		TEC	TEH	.560	ZBATF	35	H	
46	11	1.22	175	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	35	H	
48	11	1.55	175	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	35	H	
48	11	.97	181	DNT		P1	08C	23.07		TEC	TEH	.560	ZBATF	35	H	
50	11	.92	174	DNT		P1	09C	-.85		TEC	TEH	.560	ZBATF	35	H	
52	11	.96	176	DNT		P1	09H	-.86		TEC	TEH	.560	ZBATF	35	H	
52	11	1.22	176	DNT		P1	09C	-.71		TEC	TEH	.560	ZBATF	35	H	
54	11	1.63	174	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	35	H	
56	11	1.39	174	DNT		P1	09C	-.82		TEC	TEH	.560	ZBATF	35	H	
58	11	.92	173	DNT		P1	09H	-.86		TEC	TEH	.560	ZBATF	35	H	
58	11	1.38	174	DNT		P1	09C	-.79		TEC	TEH	.560	ZBATF	35	H	
5	12	.87	180	DNT		P1	06H	15.18		TEC	TEH	.560	ZBATF	35	H	
7	12	1.13	179	DNT		P1	01H	13.37		TEC	TEH	.560	ZBATF	35	H	
25	12	1.18	181	DNT		P1	08C	10.89		TEC	TEH	.560	ZBATF	35	H	
29	12	1.16	183	DNT		P1	02H	2.29		TEC	TEH	.560	ZBATF	35	H	
41	12	1.00	176	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	35	H	
45	12	1.00	174	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	35	H	
47	12	1.64	174	DNT		P1	09C	-.77		TEC	TEH	.560	ZBATF	35	H	
49	12	1.52	176	DNT		P1	09C	-.77		TEC	TEH	.560	ZBATF	35	H	
51	12	1.18	172	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	35	H	
53	12	.91	175	DNT		P1	09H	-.92		TEC	TEH	.560	ZBATF	35	H	
53	12	1.23	175	DNT		P1	09C	-.77		TEC	TEH	.560	ZBATF	35	H	

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
55	12	.81	173	DNT		P1	09H	-.76		TEC	TEH	.560	ZBATF	35	H	
55	12	1.51	175	DNT		P1	09C	-.77		TEC	TEH	.560	ZBATF	35	H	
57	12	1.44	173	DNT		P1	09C	-.84		TEC	TEH	.560	ZBATF	35	H	
57	12	.98	179	DNT		P1	04C	13.31		TEC	TEH	.560	ZBATF	35	H	
61	12	1.38	173	DNT		P1	09H	-.89		TEC	TEH	.560	ZBATF	35	H	
61	12	1.48	174	DNT		P1	09C	-.79		TEC	TEH	.560	ZBATF	35	H	
42	13	.91	173	DNT		P1	09C	-.82		TEC	TEH	.560	ZBATF	35	H	
44	13	1.17	174	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	35	H	
46	13	1.82	176	DNT		P1	09C	-.71		TEC	TEH	.560	ZBATF	35	H	
48	13	1.39	175	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	35	H	
50	13	1.55	176	DNT		P1	09C	-.71		TEC	TEH	.560	ZBATF	35	H	
52	13	1.74	174	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	35	H	
54	13	1.86	176	DNT		P1	09H	-.84		TEC	TEH	.560	ZBATF	35	H	
54	13	2.73	177	DNT		P1	09C	-.71		TEC	TEH	.560	ZBATF	35	H	
56	13	1.06	173	DNT		P1	09H	-.86		TEC	TEH	.560	ZBATF	35	H	
56	13	1.94	175	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	35	H	
58	13	1.07	175	DNT		P1	09H	-.86		TEC	TEH	.560	ZBATF	35	H	
58	13	2.73	176	DNT		P1	09C	-.79		TEC	TEH	.560	ZBATF	35	H	
60	13	3.15	177	DNT		P1	09H	-.89		TEC	TEH	.560	ZBATF	35	H	
60	13	2.00	175	DNT		P1	09C	-.79		TEC	TEH	.560	ZBATF	35	H	
62	13	1.13	176	DNT		P1	09H	-.92		TEC	TEH	.560	ZBATF	35	H	
62	13	1.98	174	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	35	H	
64	13	1.79	174	DNT		P1	09H	-.92		TEC	TEH	.560	ZBATF	35	H	
64	13	1.24	173	DNT		P1	09C	-.77		TEC	TEH	.560	ZBATF	35	H	
43	14	1.62	175	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	10	H	
45	14	1.17	175	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	10	H	
47	14	1.13	174	DNT		P1	09C	-.71		TEC	TEH	.560	ZBATF	15	H	
49	14	1.70	174	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	14	H	
51	14	1.55	175	DNT		P1	09C	-.71		TEC	TEH	.560	ZBATF	15	H	
53	14	.88	176	DNT		P1	09H	-.90		TEC	TEH	.560	ZBATF	14	H	
53	14	1.84	175	DNT		P1	09C	-.72		TEC	TEH	.560	ZBATF	14	H	
55	14	1.16	174	DNT		P1	09C	-.73		TEC	TEH	.560	ZBATF	15	H	
57	14	1.17	174	DNT		P1	09H	-.85		TEC	TEH	.560	ZBATF	14	H	
57	14	1.69	174	DNT		P1	09C	-.77		TEC	TEH	.560	ZBATF	14	H	
59	14	1.23	174	DNT		P1	09H	-.84		TEC	TEH	.560	ZBATF	15	H	
59	14	1.41	174	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	15	H	
61	14	1.33	176	DNT		P1	09H	-.87		TEC	TEH	.560	ZBATF	14	H	
61	14	1.68	174	DNT		P1	09C	-.77		TEC	TEH	.560	ZBATF	14	H	
63	14	1.52	172	DNT		P1	09H	-.89		TEC	TEH	.560	ZBATF	15	H	
63	14	1.53	173	DNT		P1	09C	-.79		TEC	TEH	.560	ZBATF	15	H	
65	14	2.14	176	DNT		P1	09H	-.90		TEC	TEH	.560	ZBATF	14	H	
65	14	1.98	174	DNT		P1	09C	-.77		TEC	TEH	.560	ZBATF	14	H	
8	15	1.57	183	DNT		P1	03H	7.22		TEC	TEH	.560	ZBATF	10	H	
24	15	1.21	182	DNT		P1	07C	16.15		TEC	TEH	.560	ZBATF	10	H	
24	15	2.03	180	DNT		P1	07C	20.05		TEC	TEH	.560	ZBATF	10	H	
48	15	1.25	173	DNT		P1	09C	-.72		TEC	TEH	.560	ZBATF	14	H	
50	15	1.47	177	DNT		P1	09C	-.73		TEC	TEH	.560	ZBATF	15	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
52	15	1.59	176	DNT		P1	09C	-.72		TEC	TEH	.560	ZBATF	14	H	
54	15	1.16	175	DNT		P1	09H	-.81		TEC	TEH	.560	ZBATF	15	H	
54	15	1.55	175	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	15	H	
56	15	1.48	173	DNT		P1	09C	-.75		TEC	TEH	.560	ZBATF	14	H	
58	15	1.22	174	DNT		P1	09H	-.81		TEC	TEH	.560	ZBATF	15	H	
58	15	1.59	176	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	15	H	
60	15	1.37	175	DNT		P1	09H	-.85		TEC	TEH	.560	ZBATF	14	H	
60	15	2.00	175	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	14	H	
62	15	1.75	175	DNT		P1	09H	-.84		TEC	TEH	.560	ZBATF	15	H	
62	15	1.64	175	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	15	H	
64	15	2.03	177	DNT		P1	09H	-.87		TEC	TEH	.560	ZBATF	14	H	
64	15	2.23	175	DNT		P1	09C	-.75		TEC	TEH	.560	ZBATF	14	H	
66	15	1.85	175	DNT		P1	09H	-.89		TEC	TEH	.560	ZBATF	15	H	
66	15	1.69	174	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	15	H	
68	15	1.51	174	DNT		P1	09H	-.90		TEC	TEH	.560	ZBATF	14	H	
68	15	1.53	175	DNT		P1	09C	-.77		TEC	TEH	.560	ZBATF	14	H	
51	16	1.22	174	DNT		P1	09C	-.71		TEC	TEH	.560	ZBATF	15	H	
55	16	.85	171	DNT		P1	09C	-.73		TEC	TEH	.560	ZBATF	15	H	
57	16	1.29	177	DNT		P1	09H	-.80		TEC	TEH	.560	ZBATF	14	H	
57	16	1.51	175	DNT		P1	09C	-.75		TEC	TEH	.560	ZBATF	14	H	
59	16	1.29	173	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	15	H	
61	16	1.01	175	DNT		P1	09H	-.85		TEC	TEH	.560	ZBATF	14	H	
61	16	2.07	175	DNT		P1	09C	-.75		TEC	TEH	.560	ZBATF	14	H	
63	16	1.54	175	DNT		P1	09H	-.84		TEC	TEH	.560	ZBATF	15	H	
63	16	1.45	173	DNT		P1	09C	-.73		TEC	TEH	.560	ZBATF	15	H	
65	16	2.14	176	DNT		P1	09H	-.85		TEC	TEH	.560	ZBATF	14	H	
65	16	1.06	172	DNT		P1	09C	-.77		TEC	TEH	.560	ZBATF	14	H	
67	16	2.16	175	DNT		P1	09H	-.84		TEC	TEH	.560	ZBATF	15	H	
67	16	2.35	175	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	15	H	
69	16	3.01	178	DNT		P1	09H	-.88		TEC	TEH	.560	ZBATF	14	H	
69	16	2.26	175	DNT		P1	09C	-.77		TEC	TEH	.560	ZBATF	14	H	
54	17	1.02	173	DNT		P1	09C	-.71		TEC	TEH	.560	ZBATF	15	H	
56	17	1.33	174	DNT		P1	09C	-.72		TEC	TEH	.560	ZBATF	14	H	
58	17	1.54	176	DNT		P1	09C	-.71		TEC	TEH	.560	ZBATF	15	H	
60	17	2.02	175	DNT		P1	09C	-.69		TEC	TEH	.560	ZBATF	14	H	
62	17	1.29	174	DNT		P1	09H	-.84		TEC	TEH	.560	ZBATF	15	H	
62	17	1.53	177	DNT		P1	09C	-.71		TEC	TEH	.560	ZBATF	15	H	
64	17	1.29	176	DNT		P1	09H	-.85		TEC	TEH	.560	ZBATF	14	H	
64	17	1.72	174	DNT		P1	09C	-.75		TEC	TEH	.560	ZBATF	14	H	
66	17	1.35	174	DNT		P1	09H	-.84		TEC	TEH	.560	ZBATF	15	H	
66	17	1.77	176	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	15	H	
68	17	1.91	177	DNT		P1	09H	-.85		TEC	TEH	.560	ZBATF	14	H	
68	17	1.96	174	DNT		P1	09C	-.72		TEC	TEH	.560	ZBATF	14	H	
70	17	2.53	175	DNT		P1	09H	-.87		TEC	TEH	.560	ZBATF	15	H	
70	17	3.08	174	DNT		P1	09C	-.76		TEC	TEH	.560	ZBATF	15	H	
72	17	2.30	176	DNT		P1	09H	-.88		TEC	TEH	.560	ZBATF	14	H	
72	17	2.66	175	DNT		P1	09C	-.75		TEC	TEH	.560	ZBATF	14	H	
53	18	2.47	183	DNT		P1	03C	30.51		TEC	TEH	.560	ZBATF	14	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
57	18	.98	174	DNT		P1	09C	-.75		TEC	TEH	.560	ZBATF	14	H	
59	18	.90	171	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	15	H	
61	18	1.54	175	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	14	H	
63	18	.88	170	DNT		P1	09H	-.79		TEC	TEH	.560	ZBATF	15	H	
63	18	1.36	172	DNT		P1	09C	-.71		TEC	TEH	.560	ZBATF	15	H	
65	18	1.19	176	DNT		P1	09H	-.80		TEC	TEH	.560	ZBATF	14	H	
65	18	1.48	175	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	14	H	
67	18	2.29	177	DNT		P1	09H	-.81		TEC	TEH	.560	ZBATF	15	H	
67	18	1.80	176	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	15	H	
69	18	2.63	178	DNT		P1	09H	-.80		TEC	TEH	.560	ZBATF	14	H	
69	18	2.81	176	DNT		P1	09C	-.72		TEC	TEH	.560	ZBATF	14	H	
71	18	2.29	174	DNT		P1	09H	-.84		TEC	TEH	.560	ZBATF	15	H	
71	18	2.74	176	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	15	H	
73	18	1.92	176	DNT		P1	09H	-.85		TEC	TEH	.560	ZBATF	14	H	
73	18	2.19	174	DNT		P1	09C	-.75		TEC	TEH	.560	ZBATF	14	H	
75	18	4.52	178	DNT		P1	09H	-.85		TEC	TEH	.560	ZBATF	14	H	
75	18	1.62	176	DNT		P1	09H	.21		TEC	TEH	.560	ZBATF	14	H	
75	18	2.56	175	DNT		P1	09C	-.78		TEC	TEH	.560	ZBATF	14	H	
75	18	1.12	175	DNT		P1	09C	.30		TEC	TEH	.560	ZBATF	14	H	
18	19	1.17	170	DNT		P1	09C	.79		TEC	TEH	.560	ZBATF	11	H	
50	19	1.91	180	DNT		P1	04H	28.15		TEC	TEH	.560	ZBATF	15	H	
62	19	.98	175	DNT		P1	09H	-.78		TEC	TEH	.560	ZBATF	15	H	
62	19	.86	175	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	15	H	
64	19	1.69	174	DNT		P1	09C	-.73		TEC	TEH	.560	ZBATF	14	H	
66	19	.92	173	DNT		P1	09H	-.76		TEC	TEH	.560	ZBATF	15	H	
66	19	1.51	173	DNT		P1	09C	-.71		TEC	TEH	.560	ZBATF	15	H	
68	19	2.02	174	DNT		P1	09C	-.73		TEC	TEH	.560	ZBATF	14	H	
70	19	1.82	176	DNT		P1	09H	-.81		TEC	TEH	.560	ZBATF	15	H	
70	19	2.06	173	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	15	H	
72	19	2.78	177	DNT		P1	09H	-.80		TEC	TEH	.560	ZBATF	14	H	
72	19	2.63	174	DNT		P1	09C	-.75		TEC	TEH	.560	ZBATF	14	H	
74	19	2.93	175	DNT		P1	09H	-.81		TEC	TEH	.560	ZBATF	15	H	
74	19	1.72	172	DNT		P1	09H	.24		TEC	TEH	.560	ZBATF	15	H	
74	19	3.27	175	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	15	H	
74	19	1.13	174	DNT		P1	09C	.33		TEC	TEH	.560	ZBATF	15	H	
76	19	3.11	176	DNT		P1	09H	-.85		TEC	TEH	.560	ZBATF	14	H	
76	19	2.40	175	DNT		P1	09C	-.75		TEC	TEH	.560	ZBATF	14	H	
65	20	1.26	173	DNT		P1	09C	-.67		TEC	TEH	.560	ZBATF	14	H	
67	20	1.43	173	DNT		P1	09H	-.79		TEC	TEH	.560	ZBATF	15	H	
67	20	1.64	174	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	15	H	
69	20	1.30	174	DNT		P1	09H	-.77		TEC	TEH	.560	ZBATF	14	H	
69	20	1.51	174	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	14	H	
71	20	2.38	177	DNT		P1	09H	-.78		TEC	TEH	.560	ZBATF	15	H	
71	20	1.92	175	DNT		P1	09C	-.71		TEC	TEH	.560	ZBATF	15	H	
73	20	2.80	176	DNT		P1	09H	-.80		TEC	TEH	.560	ZBATF	14	H	
73	20	1.04	176	DNT		P1	09H	.27		TEC	TEH	.560	ZBATF	14	H	
73	20	2.31	175	DNT		P1	09C	-.72		TEC	TEH	.560	ZBATF	14	H	
75	20	1.21	183	DNT		P1	04H	17.51		TEC	TEH	.560	ZBATF	15	H	
75	20	2.80	176	DNT		P1	09H	-.78		TEC	TEH	.560	ZBATF	15	H	
75	20	2.14	176	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	15	H	

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
77	20	3.83	178	DNT		P1	09H	-.82		TEC	TEH	.560	ZBATF	14	H	
77	20	2.29	177	DNT		P1	09H	.24		TEC	TEH	.560	ZBATF	14	H	
77	20	2.79	176	DNT		P1	09C	-.75		TEC	TEH	.560	ZBATF	14	H	
77	20	1.35	175	DNT		P1	09C	.32		TEC	TEH	.560	ZBATF	14	H	
54	21	.99	175	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	15	H	
58	21	1.02	170	DNT		P1	TSH	11.15		TEC	TEH	.560	ZBATF	15	H	
66	21	1.52	176	DNT		P1	09C	-.66		TEC	TEH	.560	ZBATF	15	H	
68	21	1.53	175	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	14	H	
70	21	.95	173	DNT		P1	09H	-.78		TEC	TEH	.560	ZBATF	15	H	
70	21	1.73	173	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	15	H	
72	21	1.27	176	DNT		P1	09H	-.82		TEC	TEH	.560	ZBATF	14	H	
72	21	2.13	175	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	14	H	
74	21	3.77	177	DNT		P1	09H	-.76		TEC	TEH	.560	ZBATF	15	H	
74	21	1.28	170	DNT		P1	09H	.30		TEC	TEH	.560	ZBATF	15	H	
74	21	3.20	174	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	15	H	
76	21	2.52	176	DNT		P1	09H	-.80		TEC	TEH	.560	ZBATF	14	H	
76	21	2.76	176	DNT		P1	09C	-.72		TEC	TEH	.560	ZBATF	14	H	
76	21	1.28	175	DNT		P1	09C	.35		TEC	TEH	.560	ZBATF	14	H	
78	21	2.85	176	DNT		P1	09H	-.78		TEC	TEH	.560	ZBATF	15	H	
78	21	4.80	176	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	15	H	
78	21	2.13	174	DNT		P1	09C	.33		TEC	TEH	.560	ZBATF	15	H	
80	21	5.29	178	DNT		P1	09H	-.80		TEC	TEH	.560	ZBATF	14	H	
80	21	2.26	175	DNT		P1	09H	.27		TEC	TEH	.560	ZBATF	14	H	
80	21	5.81	178	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	14	H	
80	21	2.88	176	DNT		P1	09C	.32		TEC	TEH	.560	ZBATF	14	H	
47	22	1.43	179	DNT		P1	04C	30.21		TEC	TEH	.560	ZBATF	15	H	
55	22	.90	174	DNT		P1	09H	-.73		TEC	TEH	.560	ZBATF	15	H	
67	22	1.23	174	DNT		P1	09C	-.71		TEC	TEH	.560	ZBATF	15	H	
69	22	1.44	176	DNT		P1	09C	-.67		TEC	TEH	.560	ZBATF	14	H	
71	22	1.11	172	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	15	H	
73	22	2.20	176	DNT		P1	09H	-.77		TEC	TEH	.560	ZBATF	14	H	
73	22	2.57	175	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	14	H	
75	22	2.41	177	DNT		P1	09H	-.76		TEC	TEH	.560	ZBATF	15	H	
75	22	1.35	170	DNT		P1	09H	.30		TEC	TEH	.560	ZBATF	15	H	
75	22	3.16	174	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	15	H	
77	22	3.08	178	DNT		P1	09H	-.75		TEC	TEH	.560	ZBATF	14	H	
77	22	1.33	175	DNT		P1	09H	.24		TEC	TEH	.560	ZBATF	14	H	
77	22	3.56	176	DNT		P1	09C	-.72		TEC	TEH	.560	ZBATF	14	H	
77	22	1.42	174	DNT		P1	09C	.38		TEC	TEH	.560	ZBATF	14	H	
79	22	.99	181	DNT		P1	02H	26.32		TEC	TEH	.560	ZBATF	15	H	
79	22	4.44	177	DNT		P1	09H	-.76		TEC	TEH	.560	ZBATF	15	H	
79	22	2.38	174	DNT		P1	09H	.30		TEC	TEH	.560	ZBATF	15	H	
79	22	5.12	177	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	15	H	
79	22	1.66	176	DNT		P1	09C	.39		TEC	TEH	.560	ZBATF	15	H	
81	22	4.91	179	DNT		P1	09H	-.77		TEC	TEH	.560	ZBATF	14	H	
81	22	1.26	172	DNT		P1	09H	.27		TEC	TEH	.560	ZBATF	14	H	
81	22	4.44	176	DNT		P1	09C	-.69		TEC	TEH	.560	ZBATF	14	H	
81	22	2.37	177	DNT		P1	09C	.35		TEC	TEH	.560	ZBATF	14	H	
16	23	4.13	181	DNT		P1	AV8	7.51		TEC	TEH	.560	ZBATF	10	H	
70	23	1.28	174	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	14	H	
72	23	1.07	171	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	15	H	
74	23	1.91	174	DNT		P1	09H	-.80		TEC	TEH	.560	ZBATF	14	H	
74	23	3.15	175	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	14	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
74	23	1.06	173	DNT		P1	09C	.38		TEC	TEH	.560	ZBATF	14	H	
76	23	1.53	175	DNT		P1	09H	-.76		TEC	TEH	.560	ZBATF	15	H	
76	23	2.24	175	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	15	H	
78	23	2.23	176	DNT		P1	09H	-.80		TEC	TEH	.560	ZBATF	14	H	
78	23	1.05	172	DNT		P1	09H	.29		TEC	TEH	.560	ZBATF	14	H	
78	23	3.33	175	DNT		P1	09C	-.65		TEC	TEH	.560	ZBATF	14	H	
78	23	1.71	174	DNT		P1	09C	.38		TEC	TEH	.560	ZBATF	14	H	
80	23	3.76	176	DNT		P1	09H	-.76		TEC	TEH	.560	ZBATF	15	H	
80	23	1.52	169	DNT		P1	09H	.24		TEC	TEH	.560	ZBATF	15	H	
80	23	4.41	175	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	15	H	
82	23	5.88	177	DNT		P1	09H	-.77		TEC	TEH	.560	ZBATF	14	H	
82	23	1.56	174	DNT		P1	09H	.29		TEC	TEH	.560	ZBATF	14	H	
82	23	4.77	177	DNT		P1	09C	-.73		TEC	TEH	.560	ZBATF	14	H	
82	23	1.87	176	DNT		P1	09C	.35		TEC	TEH	.560	ZBATF	14	H	
71	24	2.42	176	DNT		P1	09C	-.63		TEC	TEH	.560	ZBATF	15	H	
73	24	2.04	175	DNT		P1	09C	-.67		TEC	TEH	.560	ZBATF	14	H	
75	24	1.94	176	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	15	H	
77	24	3.39	175	DNT		P1	09H	-.74		TEC	TEH	.560	ZBATF	14	H	
77	24	1.04	174	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	14	H	
77	24	4.35	176	DNT		P1	09C	-.67		TEC	TEH	.560	ZBATF	14	H	
77	24	2.26	176	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	14	H	
79	24	2.67	178	DNT		P1	09H	-.76		TEC	TEH	.560	ZBATF	15	H	
79	24	1.33	170	DNT		P1	09H	.30		TEC	TEH	.560	ZBATF	15	H	
79	24	3.87	175	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	15	H	
81	24	4.67	177	DNT		P1	09H	-.74		TEC	TEH	.560	ZBATF	14	H	
81	24	1.23	174	DNT		P1	09H	.29		TEC	TEH	.560	ZBATF	14	H	
81	24	4.35	177	DNT		P1	09C	-.72		TEC	TEH	.560	ZBATF	14	H	
81	24	1.05	175	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	14	H	
83	24	1.11	173	DNT		P1	08H	-.70		TEC	TEH	.560	ZBATF	15	H	
83	24	4.97	177	DNT		P1	09H	-.78		TEC	TEH	.560	ZBATF	15	H	
83	24	1.96	170	DNT		P1	09H	.27		TEC	TEH	.560	ZBATF	15	H	
83	24	5.39	175	DNT		P1	09C	-.74		TEC	TEH	.560	ZBATF	15	H	
83	24	1.10	174	DNT		P1	09C	.38		TEC	TEH	.560	ZBATF	15	H	
85	24	5.07	179	DNT		P1	09H	-.77		TEC	TEH	.560	ZBATF	14	H	
85	24	1.30	173	DNT		P1	09H	.29		TEC	TEH	.560	ZBATF	14	H	
85	24	4.10	176	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	14	H	
85	24	1.19	174	DNT		P1	09C	.35		TEC	TEH	.560	ZBATF	14	H	
26	25	1.35	171	DNT		P1	09C	.70		TEC	TEH	.560	ZBATF	11	H	
50	25	1.70	184	DNT		P1	04H	28.07		TEC	TEH	.560	ZBATF	14	H	
74	25	2.34	175	DNT		P1	09C	-.64		TEC	TEH	.560	ZBATF	14	H	
76	25	2.93	174	DNT		P1	09C	-.63		TEC	TEH	.560	ZBATF	15	H	
76	25	1.01	173	DNT		P1	09C	.44		TEC	TEH	.560	ZBATF	15	H	
76	25	1.66	180	DNT		P1	TSC	14.22		TEC	TEH	.560	ZBATF	15	H	
78	25	2.46	175	DNT		P1	09H	-.77		TEC	TEH	.560	ZBATF	14	H	
78	25	3.53	176	DNT		P1	09C	-.62		TEC	TEH	.560	ZBATF	14	H	
80	25	3.87	177	DNT		P1	09H	-.73		TEC	TEH	.560	ZBATF	15	H	
80	25	1.88	171	DNT		P1	09H	.33		TEC	TEH	.560	ZBATF	15	H	
80	25	4.45	176	DNT		P1	09C	-.65		TEC	TEH	.560	ZBATF	15	H	
80	25	1.30	173	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	15	H	
82	25	4.67	178	DNT		P1	09H	-.74		TEC	TEH	.560	ZBATF	14	H	
82	25	.94	172	DNT		P1	09H	.27		TEC	TEH	.560	ZBATF	14	H	
82	25	5.70	177	DNT		P1	09C	-.65		TEC	TEH	.560	ZBATF	14	H	
82	25	1.70	174	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	14	H	
84	25	4.76	176	DNT		P1	09H	-.76		TEC	TEH	.560	ZBATF	15	H	
84	25	1.61	172	DNT		P1	09H	.30		TEC	TEH	.560	ZBATF	15	H	
84	25	5.33	175	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	15	H	
84	25	1.46	173	DNT		P1	09C	.39		TEC	TEH	.560	ZBATF	15	H	

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
86	25	6.11	177	DNT		P1	09H	-.77		TEC	TEH	.560	ZBATF	14	H	
86	25	1.21	171	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	14	H	
86	25	5.26	177	DNT		P1	09C	-.72		TEC	TEH	.560	ZBATF	14	H	
86	25	1.63	175	DNT		P1	09C	.38		TEC	TEH	.560	ZBATF	14	H	
1	26	1.03	183	DNT		P1	08C	17.40		09H	TEC	.560	ZBACS	3	C	
3	26	1.62	183	DNT		P1	02H	30.39		09H	TEH	.560	ZBATF	1	H	
39	26	1.01	180	DNT		P1	06C	10.92		TEC	TEH	.560	ZBATF	11	H	
75	26	.86	174	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	15	H	
77	26	1.06	174	DNT		P1	09H	-.72		TEC	TEH	.560	ZBATF	14	H	
77	26	2.01	174	DNT		P1	09C	-.64		TEC	TEH	.560	ZBATF	14	H	
79	26	2.38	176	DNT		P1	09H	-.73		TEC	TEH	.560	ZBATF	15	H	
79	26	1.16	171	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	15	H	
79	26	2.89	175	DNT		P1	09C	-.63		TEC	TEH	.560	ZBATF	15	H	
81	26	4.99	178	DNT		P1	09H	-.72		TEC	TEH	.560	ZBATF	14	H	
81	26	1.80	177	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	14	H	
81	26	3.04	175	DNT		P1	09C	-.65		TEC	TEH	.560	ZBATF	14	H	
83	26	3.99	176	DNT		P1	09H	-.73		TEC	TEH	.560	ZBATF	15	H	
83	26	1.56	170	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	15	H	
83	26	4.17	175	DNT		P1	09C	-.68		TEC	TEH	.560	ZBATF	15	H	
85	26	.92	176	DNT		P1	08H	-.72		TEC	TEH	.560	ZBATF	14	H	
85	26	3.80	179	DNT		P1	09H	-.77		TEC	TEH	.560	ZBATF	14	H	
85	26	.93	173	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	14	H	
85	26	3.79	177	DNT		P1	09C	-.70		TEC	TEH	.560	ZBATF	14	H	
85	26	1.32	172	DNT		P1	09C	.40		TEC	TEH	.560	ZBATF	14	H	
87	26	1.23	173	DNT		P1	08H	-.69		TEC	TEH	.560	ZBATF	14	H	
87	26	6.12	177	DNT		P1	09H	-.75		TEC	TEH	.560	ZBATF	14	H	
87	26	.93	172	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	14	H	
87	26	5.67	177	DNT		P1	09C	-.64		TEC	TEH	.560	ZBATF	14	H	
87	26	1.06	171	DNT		P1	09C	.38		TEC	TEH	.560	ZBATF	14	H	
74	27	1.01	173	DNT		P1	09C	-.63		TEC	TEH	.560	ZBATF	15	H	
78	27	1.70	176	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	15	H	
78	27	2.52	175	DNT		P1	09C	-.60		TEC	TEH	.560	ZBATF	15	H	
80	27	3.14	177	DNT		P1	09H	-.72		TEC	TEH	.560	ZBATF	14	H	
80	27	1.52	175	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	14	H	
80	27	3.39	175	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	14	H	
80	27	.91	171	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	14	H	
82	27	3.19	177	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	15	H	
82	27	1.89	172	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	15	H	
82	27	4.92	174	DNT		P1	09C	-.63		TEC	TEH	.560	ZBATF	15	H	
82	27	2.79	175	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	15	H	
82	27	1.10	173	DNT		P1	08C	-.67		TEC	TEH	.560	ZBATF	15	H	
84	27	3.54	176	DNT		P1	09H	-.74		TEC	TEH	.560	ZBATF	14	H	
84	27	1.09	174	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	14	H	
84	27	4.05	176	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	14	H	
84	27	1.03	173	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	14	H	
86	27	3.94	177	DNT		P1	09H	-.76		TEC	TEH	.560	ZBATF	15	H	
86	27	1.67	170	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	15	H	
86	27	5.39	175	DNT		P1	09C	-.60		TEC	TEH	.560	ZBATF	15	H	
88	27	5.78	178	DNT		P1	09H	-.74		TEC	TEH	.560	ZBATF	14	H	
88	27	2.53	175	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	14	H	
88	27	5.02	177	DNT		P1	09C	-.62		TEC	TEH	.560	ZBATF	14	H	
88	27	1.20	172	DNT		P1	09C	.38		TEC	TEH	.560	ZBATF	14	H	
39	28	2.08	178	DNT		P1	04C	31.13		TEC	TEH	.560	ZBATF	11	H	
55	28	1.11	184	DNT		P1	04H	15.17		TEC	TEH	.560	ZBATF	16	H	
79	28	1.16	175	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	16	H	
79	28	2.71	176	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	16	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
79	28	1.20	175	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	16	H	
81	28	2.49	172	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	17	H	
81	28	2.64	176	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	17	H	
81	28	1.31	175	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	17	H	
83	28	3.06	177	DNT		P1	09H	-.74		TEC	TEH	.560	ZBATF	16	H	
83	28	.72	173	DNT		P1	09H	.34		TEC	TEH	.560	ZBATF	16	H	
83	28	3.72	177	DNT		P1	09C	-.64		TEC	TEH	.560	ZBATF	16	H	
83	28	1.75	177	DNT		P1	09C	.43		TEC	TEH	.560	ZBATF	16	H	
85	28	4.56	176	DNT		P1	09H	-.73		TEC	TEH	.560	ZBATF	17	H	
85	28	1.39	173	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	17	H	
85	28	3.40	173	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	17	H	
85	28	1.18	171	DNT		P1	09C	.36		TEC	TEH	.560	ZBATF	17	H	
87	28	4.55	178	DNT		P1	09H	-.74		TEC	TEH	.560	ZBATF	16	H	
87	28	1.48	176	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	16	H	
87	28	4.45	177	DNT		P1	09C	-.67		TEC	TEH	.560	ZBATF	16	H	
87	28	2.01	176	DNT		P1	09C	.43		TEC	TEH	.560	ZBATF	16	H	
89	28	6.81	175	DNT		P1	09H	-.78		TEC	TEH	.560	ZBATF	17	H	
89	28	1.48	170	DNT		P1	09H	.30		TEC	TEH	.560	ZBATF	17	H	
89	28	4.17	173	DNT		P1	09C	-.63		TEC	TEH	.560	ZBATF	17	H	
91	28	6.11	178	DNT		P1	09H	-.77		TEC	TEH	.560	ZBATF	16	H	
91	28	1.50	174	DNT		P1	09H	.29		TEC	TEH	.560	ZBATF	16	H	
91	28	4.45	178	DNT		P1	09C	-.69		TEC	TEH	.560	ZBATF	16	H	
91	28	1.90	176	DNT		P1	09C	.38		TEC	TEH	.560	ZBATF	16	H	
64	29	2.72	182	DNT		P1	03C	29.54		TEC	TEH	.560	ZBATF	16	H	
80	29	1.55	175	DNT		P1	09C	-.62		TEC	TEH	.560	ZBATF	16	H	
82	29	3.27	173	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	17	H	
82	29	1.31	173	DNT		P1	09H	.38		TEC	TEH	.560	ZBATF	17	H	
82	29	2.40	173	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	17	H	
84	29	2.62	177	DNT		P1	09H	-.75		TEC	TEH	.560	ZBATF	16	H	
84	29	2.68	176	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	16	H	
84	29	1.18	174	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	16	H	
86	29	4.45	173	DNT		P1	09H	-.73		TEC	TEH	.560	ZBATF	17	H	
86	29	1.15	171	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	17	H	
86	29	3.50	174	DNT		P1	09C	-.66		TEC	TEH	.560	ZBATF	17	H	
86	29	1.85	173	DNT		P1	09C	.44		TEC	TEH	.560	ZBATF	17	H	
88	29	1.26	184	DNT		P1	05H	8.65		TEC	TEH	.560	ZBATF	16	H	
88	29	.97	176	DNT		P1	08H	-.72		TEC	TEH	.560	ZBATF	16	H	
88	29	.88	175	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	16	H	
88	29	3.84	178	DNT		P1	09H	-.75		TEC	TEH	.560	ZBATF	16	H	
88	29	1.70	177	DNT		P1	09H	.29		TEC	TEH	.560	ZBATF	16	H	
88	29	4.70	178	DNT		P1	09C	-.62		TEC	TEH	.560	ZBATF	16	H	
88	29	2.39	177	DNT		P1	09C	.43		TEC	TEH	.560	ZBATF	16	H	
90	29	5.82	174	DNT		P1	09H	-.76		TEC	TEH	.560	ZBATF	17	H	
90	29	1.78	173	DNT		P1	09H	.30		TEC	TEH	.560	ZBATF	17	H	
90	29	5.21	174	DNT		P1	09C	-.63		TEC	TEH	.560	ZBATF	17	H	
90	29	2.99	173	DNT		P1	09C	.38		TEC	TEH	.560	ZBATF	17	H	
92	29	4.31	178	DNT		P1	09H	-.80		TEC	TEH	.560	ZBATF	16	H	
92	29	2.68	177	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	16	H	
92	29	4.24	177	DNT		P1	09C	-.67		TEC	TEH	.560	ZBATF	16	H	
92	29	3.23	177	DNT		P1	09C	.38		TEC	TEH	.560	ZBATF	16	H	
79	30	1.70	171	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	17	H	
83	30	1.10	170	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	17	H	
85	30	2.09	176	DNT		P1	09H	-.72		TEC	TEH	.560	ZBATF	16	H	
85	30	2.09	175	DNT		P1	09C	-.62		TEC	TEH	.560	ZBATF	16	H	
87	30	.94	172	DNT		P1	08H	-.73		TEC	TEH	.560	ZBATF	17	H	
87	30	.71	169	DNT		P1	08H	.24		TEC	TEH	.560	ZBATF	17	H	
87	30	4.40	174	DNT		P1	09H	-.73		TEC	TEH	.560	ZBATF	17	H	
87	30	1.47	175	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	17	H	
87	30	2.28	174	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	17	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
87	30	1.31	174	DNT		P1	08C	-.67		TEC	TEH	.560	ZBATF	17	H	
87	30	1.02	173	DNT		P1	08C	.39		TEC	TEH	.560	ZBATF	17	H	
89	30	.78	175	DNT		P1	08H	-.72		TEC	TEH	.560	ZBATF	16	H	
89	30	2.29	176	DNT		P1	09H	-.77		TEC	TEH	.560	ZBATF	16	H	
89	30	1.03	172	DNT		P1	09H	.29		TEC	TEH	.560	ZBATF	16	H	
89	30	2.60	176	DNT		P1	09C	-.64		TEC	TEH	.560	ZBATF	16	H	
89	30	1.41	174	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	16	H	
91	30	3.03	172	DNT		P1	09H	-.78		TEC	TEH	.560	ZBATF	17	H	
91	30	1.71	172	DNT		P1	09H	.30		TEC	TEH	.560	ZBATF	17	H	
91	30	3.84	174	DNT		P1	09C	-.60		TEC	TEH	.560	ZBATF	17	H	
91	30	3.25	175	DNT		P1	09C	.38		TEC	TEH	.560	ZBATF	17	H	
93	30	4.85	178	DNT		P1	09H	-.77		TEC	TEH	.560	ZBATF	16	H	
93	30	3.30	178	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	16	H	
93	30	4.69	178	DNT		P1	09C	-.64		TEC	TEH	.560	ZBATF	16	H	
93	30	4.83	179	DNT		P1	09C	.40		TEC	TEH	.560	ZBATF	16	H	
2	31	1.21	181	DNT		P1	08C	36.38		09H	TEC	.560	ZBACS	4	C	
64	31	1.06	181	DNT		P1	02C	6.70		TEC	TEH	.560	ZBATF	16	H	
84	31	1.69	174	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	16	H	
86	31	2.31	173	DNT		P1	09H	-.73		TEC	TEH	.560	ZBATF	17	H	
86	31	1.53	171	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	17	H	
86	31	1.96	173	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	17	H	
88	31	.88	178	DNT		P1	08H	-.72		TEC	TEH	.560	ZBATF	16	H	
88	31	.97	175	DNT		P1	08H	.29		TEC	TEH	.560	ZBATF	16	H	
88	31	2.54	177	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	16	H	
88	31	1.37	176	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	16	H	
88	31	2.70	177	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	16	H	
88	31	.69	170	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	16	H	
88	31	1.03	175	DNT		P1	08C	-.66		TEC	TEH	.560	ZBATF	16	H	
88	31	.74	174	DNT		P1	08C	.37		TEC	TEH	.560	ZBATF	16	H	
90	31	4.98	174	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	17	H	
90	31	2.66	174	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	17	H	
90	31	2.99	174	DNT		P1	09C	-.57		TEC	TEH	.560	ZBATF	17	H	
90	31	1.87	171	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	17	H	
92	31	2.21	176	DNT		P1	09H	-.77		TEC	TEH	.560	ZBATF	16	H	
92	31	.95	171	DNT		P1	09H	.29		TEC	TEH	.560	ZBATF	16	H	
92	31	4.95	178	DNT		P1	09C	-.62		TEC	TEH	.560	ZBATF	16	H	
92	31	4.43	178	DNT		P1	09C	.40		TEC	TEH	.560	ZBATF	16	H	
94	31	1.45	177	DNT		P1	08H	-.77		TEC	TEH	.560	ZBATF	16	H	
94	31	1.04	174	DNT		P1	08H	.35		TEC	TEH	.560	ZBATF	16	H	
94	31	4.65	179	DNT		P1	09H	-.75		TEC	TEH	.560	ZBATF	16	H	
94	31	2.74	177	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	16	H	
94	31	4.47	177	DNT		P1	09C	-.64		TEC	TEH	.560	ZBATF	16	H	
94	31	5.62	179	DNT		P1	09C	.38		TEC	TEH	.560	ZBATF	16	H	
65	32	2.70	179	DNT		P1	04H	8.70		TEC	TEH	.560	ZBATF	17	H	
65	32	2.19	175	DNT		P1	08H	35.77		TEC	TEH	.560	ZBATF	17	H	
65	32	1.29	173	DNT		P1	08C	28.08		TEC	TEH	.560	ZBATF	17	H	
87	32	1.18	178	DNT		P1	08H	-.74		TEC	TEH	.560	ZBATF	16	H	
87	32	1.27	175	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	16	H	
87	32	2.76	176	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	16	H	
89	32	2.70	171	DNT		P1	09H	-.73		TEC	TEH	.560	ZBATF	17	H	
89	32	1.53	170	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	17	H	
91	32	3.42	178	DNT		P1	09H	-.72		TEC	TEH	.560	ZBATF	16	H	
91	32	1.65	176	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	16	H	
91	32	5.44	178	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	16	H	
91	32	3.83	178	DNT		P1	09C	.43		TEC	TEH	.560	ZBATF	16	H	
93	32	3.07	172	DNT		P1	09H	-.78		TEC	TEH	.560	ZBATF	17	H	
93	32	1.94	175	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	17	H	
93	32	2.89	174	DNT		P1	09C	-.60		TEC	TEH	.560	ZBATF	17	H	
93	32	3.23	174	DNT		P1	09C	.38		TEC	TEH	.560	ZBATF	17	H	
95	32	1.04	174	DNT		P1	08H	-.74		TEC	TEH	.560	ZBATF	16	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
95	32	4.45	177	DNT		P1	09H	-.77		TEC	TEH	.560	ZBATF	16	H	
95	32	3.26	178	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	16	H	
95	32	4.72	178	DNT		P1	09C	-.62		TEC	TEH	.560	ZBATF	16	H	
95	32	4.78	178	DNT		P1	09C	.38		TEC	TEH	.560	ZBATF	16	H	
64	33	1.00	176	DNT		P1	08C	31.34		TEC	TEH	.560	ZBATF	16	H	
86	33	.97	172	DNT		P1	09C	-.52		TEC	TEH	.560	ZBATF	17	H	
88	33	1.15	175	DNT		P1	08H	-.74		TEC	TEH	.560	ZBATF	16	H	
88	33	1.76	172	DNT		P1	09H	-.72		TEC	TEH	.560	ZBATF	16	H	
88	33	2.58	175	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	16	H	
88	33	.93	174	DNT		P1	09C	.43		TEC	TEH	.560	ZBATF	16	H	
90	33	3.20	172	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	17	H	
90	33	1.34	172	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	17	H	
90	33	2.81	173	DNT		P1	09C	-.57		TEC	TEH	.560	ZBATF	17	H	
90	33	1.69	172	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	17	H	
92	33	.76	176	DNT		P1	08H	-.72		TEC	TEH	.560	ZBATF	16	H	
92	33	1.03	174	DNT		P1	08H	.29		TEC	TEH	.560	ZBATF	16	H	
92	33	3.05	178	DNT		P1	09H	-.72		TEC	TEH	.560	ZBATF	16	H	
92	33	2.24	176	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	16	H	
92	33	3.11	176	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	16	H	
92	33	3.04	178	DNT		P1	09C	.43		TEC	TEH	.560	ZBATF	16	H	
92	33	.75	176	DNT		P1	08C	-.66		TEC	TEH	.560	ZBATF	16	H	
92	33	1.01	174	DNT		P1	08C	.37		TEC	TEH	.560	ZBATF	16	H	
94	33	.94	171	DNT		P1	08H	-.75		TEC	TEH	.560	ZBATF	17	H	
94	33	1.19	172	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	17	H	
94	33	3.08	172	DNT		P1	09H	-.73		TEC	TEH	.560	ZBATF	17	H	
94	33	2.30	175	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	17	H	
94	33	4.40	176	DNT		P1	09C	-.57		TEC	TEH	.560	ZBATF	17	H	
94	33	4.86	177	DNT		P1	09C	.44		TEC	TEH	.560	ZBATF	17	H	
96	33	1.15	175	DNT		P1	08H	-.69		TEC	TEH	.560	ZBATF	16	H	
96	33	5.36	178	DNT		P1	09H	-.77		TEC	TEH	.560	ZBATF	16	H	
96	33	1.12	176	DNT		P1	09H	-.32		TEC	TEH	.560	ZBATF	16	H	
96	33	3.70	179	DNT		P1	09H	.29		TEC	TEH	.560	ZBATF	16	H	
96	33	4.69	178	DNT		P1	09C	-.62		TEC	TEH	.560	ZBATF	16	H	
96	33	6.69	179	DNT		P1	09C	.40		TEC	TEH	.560	ZBATF	16	H	
47	34	1.14	178	DNT		P1	08H	27.81		TEC	TEH	.560	ZBATF	17	H	
69	34	2.04	176	DNT		P1	08C	27.35		TEC	TEH	.560	ZBATF	16	H	
87	34	1.01	171	DNT		P1	TSH	16.40		TEC	TEH	.560	ZBATF	17	H	
89	34	1.03	176	DNT		P1	08H	-.72		TEC	TEH	.560	ZBATF	16	H	
89	34	1.08	174	DNT		P1	09H	-.72		TEC	TEH	.560	ZBATF	16	H	
89	34	2.50	176	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	16	H	
89	34	1.19	173	DNT		P1	09C	.43		TEC	TEH	.560	ZBATF	16	H	
91	34	1.20	172	DNT		P1	08H	-.73		TEC	TEH	.560	ZBATF	17	H	
91	34	2.09	170	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	17	H	
91	34	1.25	172	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	17	H	
91	34	2.65	173	DNT		P1	09C	-.55		TEC	TEH	.560	ZBATF	17	H	
91	34	1.92	174	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	17	H	
93	34	1.55	174	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	16	H	
93	34	2.47	177	DNT		P1	09H	-.72		TEC	TEH	.560	ZBATF	16	H	
93	34	1.86	176	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	16	H	
93	34	4.01	177	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	16	H	
93	34	3.68	178	DNT		P1	09C	.43		TEC	TEH	.560	ZBATF	16	H	
93	34	.91	174	DNT		P1	08C	.37		TEC	TEH	.560	ZBATF	16	H	
95	34	4.09	174	DNT		P1	09H	-.73		TEC	TEH	.560	ZBATF	17	H	
95	34	3.09	176	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	17	H	
95	34	3.40	174	DNT		P1	09C	-.62		TEC	TEH	.560	ZBATF	17	H	
95	34	3.58	175	DNT		P1	09C	.38		TEC	TEH	.560	ZBATF	17	H	
97	34	5.67	179	DNT		P1	09H	-.75		TEC	TEH	.560	ZBATF	16	H	
97	34	4.89	178	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	16	H	
97	34	4.67	178	DNT		P1	09C	-.64		TEC	TEH	.560	ZBATF	16	H	
97	34	6.10	179	DNT		P1	09C	.40		TEC	TEH	.560	ZBATF	16	H	
86	35	1.23	183	DNT		P1	07C	1.48		TEC	TEH	.560	ZBATF	17	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
88	35	1.59	175	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	16	H	
88	35	.97	183	DNT		P1	08C	13.48		TEC	TEH	.560	ZBATF	16	H	
90	35	1.14	170	DNT		P1	08H	-.73		TEC	TEH	.560	ZBATF	17	H	
90	35	1.58	171	DNT		P1	09H	-.75		TEC	TEH	.560	ZBATF	17	H	
90	35	2.97	175	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	17	H	
90	35	1.78	173	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	17	H	
92	35	1.15	177	DNT		P1	08H	-.74		TEC	TEH	.560	ZBATF	16	H	
92	35	1.37	175	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	16	H	
92	35	3.87	177	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	16	H	
92	35	2.84	177	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	16	H	
94	35	1.46	173	DNT		P1	08H	-.73		TEC	TEH	.560	ZBATF	17	H	
94	35	.99	173	DNT		P1	08H	.35		TEC	TEH	.560	ZBATF	17	H	
94	35	4.49	174	DNT		P1	09H	-.73		TEC	TEH	.560	ZBATF	17	H	
94	35	2.12	177	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	17	H	
94	35	4.07	174	DNT		P1	09C	-.60		TEC	TEH	.560	ZBATF	17	H	
94	35	3.60	176	DNT		P1	09C	.44		TEC	TEH	.560	ZBATF	17	H	
94	35	1.23	173	DNT		P1	08C	.38		TEC	TEH	.560	ZBATF	17	H	
96	35	.87	174	DNT		P1	08H	.35		TEC	TEH	.560	ZBATF	16	H	
96	35	3.72	177	DNT		P1	09H	-.72		TEC	TEH	.560	ZBATF	16	H	
96	35	3.44	178	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	16	H	
96	35	4.12	177	DNT		P1	09C	-.62		TEC	TEH	.560	ZBATF	16	H	
96	35	4.92	179	DNT		P1	09C	.43		TEC	TEH	.560	ZBATF	16	H	
98	35	1.46	174	DNT		P1	08H	-.72		TEC	TEH	.560	ZBATF	16	H	
98	35	7.10	178	DNT		P1	09H	-.74		TEC	TEH	.560	ZBATF	16	H	
98	35	4.14	179	DNT		P1	09H	.34		TEC	TEH	.560	ZBATF	16	H	
98	35	4.71	179	DNT		P1	09C	-.62		TEC	TEH	.560	ZBATF	16	H	
98	35	4.33	178	DNT		P1	09C	.40		TEC	TEH	.560	ZBATF	16	H	
98	35	.85	174	DNT		P1	08C	.38		TEC	TEH	.560	ZBATF	16	H	
89	36	1.72	174	DNT		P1	09C	-.52		TEC	TEH	.560	ZBATF	17	H	
89	36	1.09	172	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	17	H	
89	36	1.18	172	DNT		P1	08C	19.93		TEC	TEH	.560	ZBATF	17	H	
91	36	1.51	175	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	16	H	
91	36	3.25	176	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	16	H	
91	36	1.45	175	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	16	H	
93	36	1.33	171	DNT		P1	08H	-.75		TEC	TEH	.560	ZBATF	17	H	
93	36	.79	171	DNT		P1	08H	.35		TEC	TEH	.560	ZBATF	17	H	
93	36	2.39	172	DNT		P1	09H	-.75		TEC	TEH	.560	ZBATF	17	H	
93	36	1.17	171	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	17	H	
93	36	3.32	175	DNT		P1	09C	-.60		TEC	TEH	.560	ZBATF	17	H	
93	36	2.04	172	DNT		P1	09C	.47		TEC	TEH	.560	ZBATF	17	H	
95	36	1.05	176	DNT		P1	08H	-.74		TEC	TEH	.560	ZBATF	16	H	
95	36	1.09	172	DNT		P1	08H	.35		TEC	TEH	.560	ZBATF	16	H	
95	36	4.32	178	DNT		P1	09H	-.72		TEC	TEH	.560	ZBATF	16	H	
95	36	3.16	177	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	16	H	
95	36	4.31	177	DNT		P1	09C	-.62		TEC	TEH	.560	ZBATF	16	H	
95	36	3.14	178	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	16	H	
95	36	1.06	175	DNT		P1	08C	.40		TEC	TEH	.560	ZBATF	16	H	
97	36	1.40	170	DNT		P1	08H	-.73		TEC	TEH	.560	ZBATF	17	H	
97	36	1.08	171	DNT		P1	08H	.35		TEC	TEH	.560	ZBATF	17	H	
97	36	4.46	173	DNT		P1	09H	-.75		TEC	TEH	.560	ZBATF	17	H	
97	36	2.70	175	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	17	H	
97	36	4.19	175	DNT		P1	09C	-.60		TEC	TEH	.560	ZBATF	17	H	
97	36	4.82	176	DNT		P1	09C	.44		TEC	TEH	.560	ZBATF	17	H	
99	36	5.43	179	DNT		P1	09H	-.77		TEC	TEH	.560	ZBATF	16	H	
99	36	4.56	178	DNT		P1	09H	.34		TEC	TEH	.560	ZBATF	16	H	
99	36	6.41	178	DNT		P1	09C	-.62		TEC	TEH	.560	ZBATF	16	H	
99	36	4.52	178	DNT		P1	09C	.40		TEC	TEH	.560	ZBATF	16	H	
56	37	.95	177	DNT		P1	04C	27.51		TEC	TEH	.560	ZBATF	18	H	
90	37	1.29	173	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	19	H	
90	37	2.10	175	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	19	H	
92	37	.95	173	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	18	H	
92	37	2.12	174	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	18	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
92	37	1.10	171	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	18	H	
94	37	.96	175	DNT		P1	08H	-.72		TEC	TEH	.560	ZBATF	19	H	
94	37	1.16	171	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	19	H	
94	37	2.36	174	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	19	H	
94	37	1.56	170	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	19	H	
94	37	4.68	176	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	19	H	
94	37	3.67	174	DNT		P1	09C	.43		TEC	TEH	.560	ZBATF	19	H	
94	37	.97	171	DNT		P1	08C	.43		TEC	TEH	.560	ZBATF	19	H	
96	37	1.18	174	DNT		P1	08H	-.71		TEC	TEH	.560	ZBATF	18	H	
96	37	1.41	173	DNT		P1	08H	.34		TEC	TEH	.560	ZBATF	18	H	
96	37	3.80	176	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	18	H	
96	37	2.92	175	DNT		P1	09H	.34		TEC	TEH	.560	ZBATF	18	H	
96	37	4.99	176	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	18	H	
96	37	3.84	175	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	18	H	
96	37	1.09	170	DNT		P1	08C	.40		TEC	TEH	.560	ZBATF	18	H	
98	37	5.19	176	DNT		P1	09H	-.72		TEC	TEH	.560	ZBATF	19	H	
98	37	2.65	173	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	19	H	
98	37	6.00	176	DNT		P1	09C	-.62		TEC	TEH	.560	ZBATF	19	H	
98	37	5.20	174	DNT		P1	09C	.38		TEC	TEH	.560	ZBATF	19	H	
100	37	1.35	174	DNT		P1	08H	-.74		TEC	TEH	.560	ZBATF	18	H	
100	37	5.86	177	DNT		P1	09H	-.74		TEC	TEH	.560	ZBATF	18	H	
100	37	4.30	176	DNT		P1	09H	.29		TEC	TEH	.560	ZBATF	18	H	
100	37	7.89	177	DNT		P1	09C	-.64		TEC	TEH	.560	ZBATF	18	H	
100	37	5.41	175	DNT		P1	09C	.40		TEC	TEH	.560	ZBATF	18	H	
91	38	1.01	172	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	19	H	
93	38	2.11	174	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	18	H	
93	38	1.13	172	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	18	H	
93	38	2.39	174	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	18	H	
93	38	1.12	174	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	18	H	
95	38	.92	174	DNT		P1	08H	-.70		TEC	TEH	.560	ZBATF	19	H	
95	38	1.79	173	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	19	H	
95	38	4.45	175	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	19	H	
95	38	3.56	173	DNT		P1	09C	.43		TEC	TEH	.560	ZBATF	19	H	
97	38	4.38	177	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	18	H	
97	38	2.24	174	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	18	H	
97	38	5.47	175	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	18	H	
97	38	2.83	176	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	18	H	
99	38	1.27	173	DNT		P1	08H	-.75		TEC	TEH	.560	ZBATF	19	H	
99	38	1.13	170	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	19	H	
99	38	4.56	175	DNT		P1	09H	-.72		TEC	TEH	.560	ZBATF	19	H	
99	38	.92	170	DNT		P1	09H	.29		TEC	TEH	.560	ZBATF	19	H	
99	38	5.53	176	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	19	H	
99	38	5.35	174	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	19	H	
101	38	1.25	175	DNT		P1	08H	-.74		TEC	TEH	.560	ZBATF	18	H	
101	38	5.68	176	DNT		P1	09H	-.74		TEC	TEH	.560	ZBATF	18	H	
101	38	2.85	174	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	18	H	
101	38	7.11	176	DNT		P1	09C	-.64		TEC	TEH	.560	ZBATF	18	H	
101	38	4.56	176	DNT		P1	09C	.43		TEC	TEH	.560	ZBATF	18	H	
50	39	1.09	178	DNT		P1	08C	24.29		TEC	TEH	.560	ZBATF	18	H	
70	39	1.11	181	DNT		P1	03C	9.15		TEC	TEH	.560	ZBATF	18	H	
92	39	1.09	172	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	19	H	
94	39	1.48	174	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	18	H	
94	39	2.38	175	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	18	H	
94	39	1.32	172	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	18	H	
96	39	1.18	176	DNT		P1	08H	-.70		TEC	TEH	.560	ZBATF	19	H	
96	39	1.12	170	DNT		P1	08H	.35		TEC	TEH	.560	ZBATF	19	H	
96	39	2.74	174	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	19	H	
96	39	1.52	171	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	19	H	
96	39	4.19	176	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	19	H	
96	39	2.97	173	DNT		P1	09C	.43		TEC	TEH	.560	ZBATF	19	H	
96	39	1.06	170	DNT		P1	08C	.40		TEC	TEH	.560	ZBATF	19	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
98	39	5.23	177	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	18	H	
98	39	3.96	177	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	18	H	
98	39	5.67	175	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	18	H	
98	39	3.89	177	DNT		P1	09C	.45		TEC	TEH	.560	ZBATF	18	H	
98	39	1.01	171	DNT		P1	08C	.40		TEC	TEH	.560	ZBATF	18	H	
100	39	4.46	175	DNT		P1	09H	-.72		TEC	TEH	.560	ZBATF	19	H	
100	39	3.62	175	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	19	H	
100	39	7.09	176	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	19	H	
100	39	5.95	175	DNT		P1	09C	.38		TEC	TEH	.560	ZBATF	19	H	
102	39	1.07	173	DNT		P1	08H	-.74		TEC	TEH	.560	ZBATF	18	H	
102	39	.93	173	DNT		P1	08H	.37		TEC	TEH	.560	ZBATF	18	H	
102	39	6.57	176	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	18	H	
102	39	2.87	175	DNT		P1	09H	.34		TEC	TEH	.560	ZBATF	18	H	
102	39	5.59	176	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	18	H	
102	39	5.47	178	DNT		P1	09C	.40		TEC	TEH	.560	ZBATF	18	H	
102	39	1.11	171	DNT		P1	08C	.42		TEC	TEH	.560	ZBATF	18	H	
3	40	1.20	174	DNT		P1	08C	5.48		09H	TEC	.560	ZBACS	1	C	
17	40	1.22	172	DNT		P1	08H	7.67		TEC	TEH	.560	ZBATF	12	H	
39	40	1.99	173	DNT		P1	09H	.16		TEC	TEH	.560	ZBATF	13	H	
39	40	5.26	176	DNT		P1	08C	35.08		TEC	TEH	.560	ZBATF	13	H	
79	40	1.71	182	DNT		P1	02H	-.67		TEC	TEH	.560	ZBATF	19	H	
93	40	1.07	171	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	18	H	
95	40	1.09	172	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	19	H	
95	40	1.65	174	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	19	H	
95	40	1.07	170	DNT		P1	09C	.43		TEC	TEH	.560	ZBATF	19	H	
97	40	1.89	174	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	18	H	
97	40	1.06	170	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	18	H	
97	40	3.62	176	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	18	H	
97	40	1.83	174	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	18	H	
99	40	1.01	174	DNT		P1	08H	-.75		TEC	TEH	.560	ZBATF	19	H	
99	40	1.35	171	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	19	H	
99	40	3.85	176	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	19	H	
99	40	1.86	172	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	19	H	
99	40	4.12	175	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	19	H	
99	40	2.92	172	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	19	H	
99	40	1.21	170	DNT		P1	08C	.43		TEC	TEH	.560	ZBATF	19	H	
101	40	1.03	174	DNT		P1	08H	-.71		TEC	TEH	.560	ZBATF	18	H	
101	40	1.03	173	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	18	H	
101	40	3.21	176	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	18	H	
101	40	2.71	175	DNT		P1	09H	.32		TEC	TEH	.560	ZBATF	18	H	
101	40	5.97	175	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	18	H	
101	40	6.21	177	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	18	H	
103	40	6.71	177	DNT		P1	09H	-.74		TEC	TEH	.560	ZBATF	18	H	
103	40	2.77	175	DNT		P1	09H	.34		TEC	TEH	.560	ZBATF	18	H	
103	40	5.94	175	DNT		P1	09C	-.63		TEC	TEH	.560	ZBATF	18	H	
103	40	6.03	177	DNT		P1	09C	.45		TEC	TEH	.560	ZBATF	18	H	
94	41	1.36	175	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	19	H	
96	41	1.16	174	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	18	H	
96	41	2.49	175	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	18	H	
96	41	.99	172	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	18	H	
98	41	1.07	171	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	19	H	
98	41	2.38	176	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	19	H	
98	41	1.57	172	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	19	H	
98	41	4.37	176	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	19	H	
98	41	3.58	175	DNT		P1	09C	.43		TEC	TEH	.560	ZBATF	19	H	
100	41	1.26	171	DNT		P1	08H	.34		TEC	TEH	.560	ZBATF	18	H	
100	41	3.32	176	DNT		P1	09H	-.72		TEC	TEH	.560	ZBATF	18	H	
100	41	2.25	175	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	18	H	
100	41	5.18	175	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	18	H	
100	41	4.36	177	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	18	H	
100	41	1.10	170	DNT		P1	08C	.42		TEC	TEH	.560	ZBATF	18	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
102	41	3.82	175	DNT		P1	09H	-.75		TEC	TEH	.560	ZBATF	19	H	
102	41	2.94	174	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	19	H	
102	41	4.37	176	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	19	H	
102	41	3.64	174	DNT		P1	09C	.41		TEC	TEH	.560	ZBATF	19	H	
104	41	1.05	169	DNT		P1	08H	.48		TEC	TEH	.560	ZBATF	18	H	
104	41	6.74	177	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	18	H	
104	41	4.03	177	DNT		P1	09H	.34		TEC	TEH	.560	ZBATF	18	H	
104	41	5.95	175	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	18	H	
104	41	5.50	177	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	18	H	
97	42	1.54	173	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	18	H	
99	42	1.08	176	DNT		P1	08H	-.72		TEC	TEH	.560	ZBATF	19	H	
99	42	.97	172	DNT		P1	08H	.37		TEC	TEH	.560	ZBATF	19	H	
99	42	1.41	172	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	19	H	
99	42	.87	173	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	19	H	
99	42	3.04	176	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	19	H	
99	42	1.77	171	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	19	H	
101	42	.90	173	DNT		P1	08H	-.66		TEC	TEH	.560	ZBATF	18	H	
101	42	1.48	173	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	18	H	
101	42	2.75	175	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	18	H	
101	42	2.14	175	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	18	H	
101	42	3.47	175	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	18	H	
101	42	2.09	173	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	18	H	
101	42	1.49	173	DNT		P1	08C	.42		TEC	TEH	.560	ZBATF	18	H	
103	42	1.29	174	DNT		P1	08H	-.72		TEC	TEH	.560	ZBATF	19	H	
103	42	3.00	175	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	19	H	
103	42	2.36	174	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	19	H	
103	42	3.93	176	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	19	H	
103	42	3.75	175	DNT		P1	09C	.38		TEC	TEH	.560	ZBATF	19	H	
103	42	1.11	171	DNT		P1	08C	.40		TEC	TEH	.560	ZBATF	19	H	
105	42	.99	169	DNT		P1	08H	.45		TEC	TEH	.560	ZBATF	18	H	
105	42	6.24	176	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	18	H	
105	42	3.60	175	DNT		P1	09H	.34		TEC	TEH	.560	ZBATF	18	H	
105	42	3.94	174	DNT		P1	09C	-.63		TEC	TEH	.560	ZBATF	18	H	
105	42	4.12	176	DNT		P1	09C	.45		TEC	TEH	.560	ZBATF	18	H	
105	42	.68	166	DNT		P1	08C	.21		TEC	TEH	.560	ZBATF	18	H	
24	43	1.05	185	DNT		P1	02H	29.14		TEC	TEH	.560	ZBATF	12	H	
98	43	1.57	173	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	18	H	
100	43	1.19	170	DNT		P1	08H	.35		TEC	TEH	.560	ZBATF	19	H	
100	43	1.37	173	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	19	H	
100	43	1.22	171	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	19	H	
100	43	2.95	175	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	19	H	
100	43	1.77	172	DNT		P1	09C	.43		TEC	TEH	.560	ZBATF	19	H	
102	43	1.06	175	DNT		P1	08H	-.71		TEC	TEH	.560	ZBATF	18	H	
102	43	1.94	174	DNT		P1	08H	.29		TEC	TEH	.560	ZBATF	18	H	
102	43	2.41	174	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	18	H	
102	43	1.50	174	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	18	H	
102	43	3.54	174	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	18	H	
102	43	2.72	176	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	18	H	
102	43	1.32	172	DNT		P1	08C	.40		TEC	TEH	.560	ZBATF	18	H	
104	43	1.01	173	DNT		P1	08H	-.75		TEC	TEH	.560	ZBATF	19	H	
104	43	1.69	170	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	19	H	
104	43	2.86	174	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	19	H	
104	43	2.72	174	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	19	H	
104	43	3.81	174	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	19	H	
104	43	3.84	175	DNT		P1	09C	.40		TEC	TEH	.560	ZBATF	19	H	
104	43	1.22	170	DNT		P1	08C	.46		TEC	TEH	.560	ZBATF	19	H	
106	43	1.74	173	DNT		P1	08H	.29		TEC	TEH	.560	ZBATF	18	H	
106	43	3.42	175	DNT		P1	09H	-.77		TEC	TEH	.560	ZBATF	18	H	
106	43	2.93	174	DNT		P1	09H	.34		TEC	TEH	.560	ZBATF	18	H	
106	43	3.87	175	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	18	H	
106	43	4.00	176	DNT		P1	09C	.35		TEC	TEH	.560	ZBATF	18	H	
106	43	.89	170	DNT		P1	08C	.29		TEC	TEH	.560	ZBATF	18	H	
99	44	1.50	175	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	19	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
101	44	1.15	172	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	18	H	
101	44	1.56	175	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	18	H	
101	44	1.73	175	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	18	H	
101	44	2.40	174	DNT		P1	09C	-.55		TEC	TEH	.560	ZBATF	18	H	
101	44	1.53	173	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	18	H	
103	44	1.23	174	DNT		P1	08H	-.74		TEC	TEH	.560	ZBATF	19	H	
103	44	1.84	173	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	19	H	
103	44	2.80	175	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	19	H	
103	44	2.20	174	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	19	H	
103	44	3.29	176	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	19	H	
103	44	3.59	174	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	19	H	
103	44	1.84	171	DNT		P1	08C	.40		TEC	TEH	.560	ZBATF	19	H	
105	44	1.60	170	DNT		P1	08H	.34		TEC	TEH	.560	ZBATF	18	H	
105	44	3.01	176	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	18	H	
105	44	2.76	176	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	18	H	
105	44	3.94	174	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	18	H	
105	44	4.25	175	DNT		P1	09C	.45		TEC	TEH	.560	ZBATF	18	H	
105	44	.95	168	DNT		P1	08C	.37		TEC	TEH	.560	ZBATF	18	H	
107	44	1.38	170	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	18	H	
107	44	3.07	175	DNT		P1	09H	-.76		TEC	TEH	.560	ZBATF	18	H	
107	44	3.81	175	DNT		P1	09H	.34		TEC	TEH	.560	ZBATF	18	H	
107	44	3.05	174	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	18	H	
107	44	5.34	176	DNT		P1	09C	.45		TEC	TEH	.560	ZBATF	18	H	
38	45	1.28	178	DNT		P1	01H	27.88		TEC	TEH	.560	ZBATF	13	H	
100	45	1.00	175	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	20	H	
100	45	1.32	175	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	20	H	
102	45	1.64	174	DNT		P1	08H	.35		TEC	TEH	.560	ZBATF	21	H	
102	45	1.07	175	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	21	H	
102	45	1.67	175	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	21	H	
102	45	1.80	176	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	21	H	
102	45	1.49	175	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	21	H	
102	45	1.32	173	DNT		P1	08C	.40		TEC	TEH	.560	ZBATF	21	H	
104	45	1.04	176	DNT		P1	08H	-.73		TEC	TEH	.560	ZBATF	20	H	
104	45	2.13	176	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	20	H	
104	45	2.49	176	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	20	H	
104	45	2.31	177	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	20	H	
104	45	3.19	176	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	20	H	
104	45	3.40	178	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	20	H	
104	45	1.61	174	DNT		P1	08C	.45		TEC	TEH	.560	ZBATF	20	H	
106	45	1.33	171	DNT		P1	08H	.35		TEC	TEH	.560	ZBATF	21	H	
106	45	4.07	176	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	21	H	
106	45	5.42	178	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	21	H	
106	45	3.30	177	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	21	H	
106	45	3.93	176	DNT		P1	09C	.40		TEC	TEH	.560	ZBATF	21	H	
106	45	1.18	170	DNT		P1	08C	.43		TEC	TEH	.560	ZBATF	21	H	
108	45	1.56	174	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	20	H	
108	45	4.08	177	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	20	H	
108	45	8.20	179	DNT		P1	09H	.39		TEC	TEH	.560	ZBATF	20	H	
108	45	4.39	176	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	20	H	
108	45	8.29	179	DNT		P1	09C	.50		TEC	TEH	.560	ZBATF	20	H	
108	45	1.76	172	DNT		P1	08C	.42		TEC	TEH	.560	ZBATF	20	H	
29	46	1.40	183	DNT		P1	06C	30.66		TEC	TEH	.560	ZBATF	12	H	
49	46	.31	181	DNT		P1	06H	15.67		TEC	TEH	.560	ZBATF	20	H	
101	46	1.11	174	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	20	H	
103	46	1.31	174	DNT		P1	08H	.35		TEC	TEH	.560	ZBATF	21	H	
103	46	1.03	175	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	21	H	
103	46	1.58	174	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	21	H	
103	46	1.60	175	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	21	H	
103	46	1.98	175	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	21	H	
103	46	1.45	172	DNT		P1	08C	.40		TEC	TEH	.560	ZBATF	21	H	
105	46	1.59	174	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	20	H	
105	46	2.03	176	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	20	H	

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
105	46	2.43	177	DNT		P1	09H	.39		TEC	TEH	.560	ZBATF	20	H	
105	46	2.14	176	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	20	H	
105	46	3.31	177	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	20	H	
105	46	1.56	174	DNT		P1	08C	.39		TEC	TEH	.560	ZBATF	20	H	
107	46	1.19	177	DNT		P1	08H	-.74		TEC	TEH	.560	ZBATF	20	H	
107	46	1.74	174	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	20	H	
107	46	2.73	177	DNT		P1	09H	-.74		TEC	TEH	.560	ZBATF	20	H	
107	46	3.29	178	DNT		P1	09H	.34		TEC	TEH	.560	ZBATF	20	H	
107	46	3.30	177	DNT		P1	09C	-.63		TEC	TEH	.560	ZBATF	20	H	
107	46	4.79	179	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	20	H	
107	46	1.14	170	DNT		P1	08C	.42		TEC	TEH	.560	ZBATF	20	H	
40	47	1.01	178	DNT		P1	05H	1.27		TEC	TEH	.560	ZBATF	12	H	
104	47	1.09	176	DNT		P1	08H	-.71		TEC	TEH	.560	ZBATF	20	H	
104	47	2.25	176	DNT		P1	08H	.34		TEC	TEH	.560	ZBATF	20	H	
104	47	1.04	174	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	20	H	
104	47	1.77	174	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	20	H	
104	47	2.20	177	DNT		P1	09C	-.55		TEC	TEH	.560	ZBATF	20	H	
104	47	2.80	178	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	20	H	
104	47	1.32	172	DNT		P1	08C	.42		TEC	TEH	.560	ZBATF	20	H	
106	47	2.47	175	DNT		P1	08H	.35		TEC	TEH	.560	ZBATF	21	H	
106	47	2.11	176	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	21	H	
106	47	2.82	177	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	21	H	
106	47	2.81	177	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	21	H	
106	47	4.67	177	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	21	H	
106	47	1.15	170	DNT		P1	08C	.42		TEC	TEH	.560	ZBATF	21	H	
108	47	1.67	174	DNT		P1	08H	.34		TEC	TEH	.560	ZBATF	20	H	
108	47	3.32	177	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	20	H	
108	47	5.11	179	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	20	H	
108	47	3.14	177	DNT		P1	09C	-.60		TEC	TEH	.560	ZBATF	20	H	
108	47	6.73	179	DNT		P1	09C	.50		TEC	TEH	.560	ZBATF	20	H	
108	47	.94	170	DNT		P1	08C	.42		TEC	TEH	.560	ZBATF	20	H	
103	48	.90	174	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	21	H	
103	48	1.45	174	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	21	H	
105	48	1.73	175	DNT		P1	08H	.37		TEC	TEH	.560	ZBATF	20	H	
105	48	1.32	173	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	20	H	
105	48	3.52	177	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	20	H	
105	48	1.94	175	DNT		P1	09C	-.55		TEC	TEH	.560	ZBATF	20	H	
105	48	2.51	177	DNT		P1	09C	.50		TEC	TEH	.560	ZBATF	20	H	
105	48	1.64	173	DNT		P1	08C	.42		TEC	TEH	.560	ZBATF	20	H	
107	48	2.10	174	DNT		P1	08H	.35		TEC	TEH	.560	ZBATF	21	H	
107	48	2.34	176	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	21	H	
107	48	3.33	177	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	21	H	
107	48	2.60	176	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	21	H	
107	48	5.81	177	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	21	H	
107	48	1.29	172	DNT		P1	08C	.42		TEC	TEH	.560	ZBATF	21	H	
109	48	1.57	173	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	20	H	
109	48	2.63	175	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	20	H	
109	48	5.52	178	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	20	H	
109	48	3.20	175	DNT		P1	09C	-.60		TEC	TEH	.560	ZBATF	20	H	
109	48	8.56	179	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	20	H	
2	49	1.11	182	DNT		P1	08C	29.79		09H	TEC	.560	ZBACS	4	C	
104	49	.92	173	DNT		P1	08H	.35		TEC	TEH	.560	ZBATF	21	H	
104	49	1.05	174	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	21	H	
104	49	2.09	175	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	21	H	
104	49	1.29	174	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	21	H	
104	49	2.15	175	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	21	H	
104	49	1.00	168	DNT		P1	08C	.45		TEC	TEH	.560	ZBATF	21	H	
106	49	.95	174	DNT		P1	08H	.26		TEC	TEH	.560	ZBATF	20	H	
106	49	1.37	174	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	20	H	
106	49	3.92	178	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	20	H	
106	49	2.33	176	DNT		P1	09C	-.55		TEC	TEH	.560	ZBATF	20	H	
106	49	4.21	179	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	20	H	
106	49	1.16	171	DNT		P1	08C	.42		TEC	TEH	.560	ZBATF	20	H	
108	49	2.47	174	DNT		P1	08H	.35		TEC	TEH	.560	ZBATF	21	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
108	49	3.24	176	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	21	H	
108	49	5.30	178	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	21	H	
108	49	2.51	175	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	21	H	
108	49	7.11	177	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	21	H	
108	49	1.33	170	DNT		P1	08C	.42		TEC	TEH	.560	ZBATF	21	H	
110	49	1.66	172	DNT		P1	08H	.34		TEC	TEH	.560	ZBATF	20	H	
110	49	3.68	176	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	20	H	
110	49	7.30	179	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	20	H	
110	49	4.51	177	DNT		P1	09C	-.63		TEC	TEH	.560	ZBATF	20	H	
110	49	11.57	179	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	20	H	
103	50	1.38	171	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	21	H	
105	50	1.42	174	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	20	H	
105	50	1.96	176	DNT		P1	09H	.42		TEC	TEH	.560	ZBATF	20	H	
105	50	1.60	172	DNT		P1	09C	-.50		TEC	TEH	.560	ZBATF	20	H	
105	50	2.63	177	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	20	H	
107	50	1.43	173	DNT		P1	08H	.35		TEC	TEH	.560	ZBATF	21	H	
107	50	1.29	174	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	21	H	
107	50	3.98	177	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	21	H	
107	50	2.19	175	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	21	H	
107	50	5.40	177	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	21	H	
107	50	1.43	171	DNT		P1	08C	.42		TEC	TEH	.560	ZBATF	21	H	
109	50	1.50	173	DNT		P1	08H	.37		TEC	TEH	.560	ZBATF	20	H	
109	50	2.00	173	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	20	H	
109	50	5.60	179	DNT		P1	09H	.39		TEC	TEH	.560	ZBATF	20	H	
109	50	3.46	176	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	20	H	
109	50	7.63	179	DNT		P1	09C	.50		TEC	TEH	.560	ZBATF	20	H	
111	50	1.28	171	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	20	H	
111	50	3.72	176	DNT		P1	09H	-.71		TEC	TEH	.560	ZBATF	20	H	
111	50	7.63	178	DNT		P1	09H	.34		TEC	TEH	.560	ZBATF	20	H	
111	50	4.84	176	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	20	H	
111	50	11.21	179	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	20	H	
16	51	1.06	181	DNT		P1	03H	4.46		TEC	TEH	.560	ZBATF	26	H	
28	51	1.01	173	DNT		P1	06C	26.09		TEC	TEH	.560	ZBATF	26	H	
104	51	1.03	173	DNT		P1	09H	.42		TEC	TEH	.560	ZBATF	21	H	
104	51	.83	173	DNT		P1	09C	-.55		TEC	TEH	.560	ZBATF	21	H	
104	51	1.87	175	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	21	H	
106	51	1.78	174	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	20	H	
106	51	2.25	174	DNT		P1	09C	-.55		TEC	TEH	.560	ZBATF	20	H	
106	51	4.43	179	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	20	H	
108	51	2.10	174	DNT		P1	08H	.34		TEC	TEH	.560	ZBATF	21	H	
108	51	1.41	172	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	21	H	
108	51	4.01	176	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	21	H	
108	51	2.95	176	DNT		P1	09C	-.55		TEC	TEH	.560	ZBATF	21	H	
108	51	6.35	178	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	21	H	
110	51	1.71	174	DNT		P1	08H	.34		TEC	TEH	.560	ZBATF	20	H	
110	51	3.03	176	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	20	H	
110	51	6.25	179	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	20	H	
110	51	4.29	176	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	20	H	
110	51	10.71	179	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	20	H	
59	52	1.17	181	DNT		P1	06H	17.20		TEC	TEH	.560	ZBATF	21	H	
105	52	1.25	173	DNT		P1	09C	-.52		TEC	TEH	.560	ZBATF	22	H	
105	52	2.96	174	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	22	H	
107	52	1.22	171	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	23	H	
107	52	2.38	176	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	23	H	
107	52	1.89	171	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	23	H	
107	52	3.58	177	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	23	H	
109	52	1.94	173	DNT		P1	08H	.37		TEC	TEH	.560	ZBATF	22	H	
109	52	2.02	173	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	22	H	
109	52	4.08	176	DNT		P1	09H	.39		TEC	TEH	.560	ZBATF	22	H	
109	52	3.66	174	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	22	H	
109	52	7.48	177	DNT		P1	09C	.50		TEC	TEH	.560	ZBATF	22	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
109	52	.97	169	DNT		P1	08C	.45		TEC	TEH	.560	ZBATF	22	H	
111	52	1.47	171	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	22	H	
111	52	2.48	174	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	22	H	
111	52	6.47	177	DNT		P1	09H	.34		TEC	TEH	.560	ZBATF	22	H	
111	52	3.42	175	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	22	H	
111	52	10.52	177	DNT		P1	09C	.47		TEC	TEH	.560	ZBATF	22	H	
106	53	.79	174	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	23	H	
106	53	1.38	171	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	23	H	
106	53	2.93	176	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	23	H	
108	53	1.13	172	DNT		P1	08H	.34		TEC	TEH	.560	ZBATF	22	H	
108	53	1.40	172	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	22	H	
108	53	3.04	176	DNT		P1	09H	.39		TEC	TEH	.560	ZBATF	22	H	
108	53	2.69	174	DNT		P1	09C	-.55		TEC	TEH	.560	ZBATF	22	H	
108	53	5.10	177	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	22	H	
110	53	2.32	173	DNT		P1	08H	.35		TEC	TEH	.560	ZBATF	23	H	
110	53	2.77	175	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	23	H	
110	53	4.49	178	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	23	H	
110	53	3.69	174	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	23	H	
110	53	6.94	178	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	23	H	
110	53	1.20	188	DNT		P1	09C	.99		TEC	TEH	.560	ZBATF	23	H	
110	53	.90	171	DNT		P1	08C	.46		TEC	TEH	.560	ZBATF	23	H	
112	53	4.68	175	DNT		P1	09H	-.68		TEC	TEH	.560	ZBATF	22	H	
112	53	7.67	178	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	22	H	
112	53	5.02	175	DNT		P1	09C	-.60		TEC	TEH	.560	ZBATF	22	H	
112	53	10.54	177	DNT		P1	09C	.45		TEC	TEH	.560	ZBATF	22	H	
101	54	1.04	183	DNT		P1	05H	1.93		TEC	TEH	.560	ZBATF	22	H	
105	54	1.06	170	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	22	H	
105	54	.86	171	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	22	H	
105	54	1.43	170	DNT		P1	09C	-.55		TEC	TEH	.560	ZBATF	22	H	
105	54	1.47	174	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	22	H	
107	54	1.03	173	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	23	H	
107	54	1.53	176	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	23	H	
107	54	2.92	176	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	23	H	
109	54	2.56	173	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	22	H	
109	54	4.65	178	DNT		P1	09H	.42		TEC	TEH	.560	ZBATF	22	H	
109	54	4.19	174	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	22	H	
109	54	5.69	178	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	22	H	
111	54	.83	172	DNT		P1	08H	.43		TEC	TEH	.560	ZBATF	23	H	
111	54	3.30	177	DNT		P1	09H	-.61		TEC	TEH	.560	ZBATF	23	H	
111	54	8.13	178	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	23	H	
111	54	3.53	177	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	23	H	
111	54	8.15	179	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	23	H	
113	54	4.14	175	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	22	H	
113	54	9.31	176	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	22	H	
113	54	4.89	175	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	22	H	
113	54	8.91	178	DNT		P1	09C	.45		TEC	TEH	.560	ZBATF	22	H	
70	55	.90	173	DNT		P1	04C	19.25		TEC	TEH	.560	ZBATF	23	H	
106	55	1.00	172	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	23	H	
106	55	1.27	175	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	23	H	
108	55	1.29	171	DNT		P1	08H	.37		TEC	TEH	.560	ZBATF	22	H	
108	55	.95	173	DNT		P1	09H	-.56		TEC	TEH	.560	ZBATF	22	H	
108	55	2.33	174	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	22	H	
108	55	2.76	172	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	22	H	
108	55	3.67	177	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	22	H	
110	55	1.86	175	DNT		P1	08H	.35		TEC	TEH	.560	ZBATF	23	H	
110	55	1.57	173	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	23	H	
110	55	2.87	177	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	23	H	
110	55	2.38	176	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	23	H	
110	55	4.32	178	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	23	H	
110	55	1.02	173	DNT		P1	08C	.51		TEC	TEH	.560	ZBATF	23	H	
112	55	3.42	174	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	22	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
112	55	3.39	178	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	22	H	
112	55	4.44	174	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	22	H	
112	55	7.22	178	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	22	H	
33	56	1.23	181	DNT		P1	01C	13.60		TEC	TEH	.560	ZBATF	25	H	
83	56	.87	181	DNT		P1	02H	13.26		TEC	TEH	.560	ZBATF	23	H	
105	56	1.01	172	DNT		P1	09C	.45		TEC	TEH	.560	ZBATF	22	H	
109	56	1.07	171	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	22	H	
109	56	1.11	172	DNT		P1	09H	.42		TEC	TEH	.560	ZBATF	22	H	
109	56	2.14	172	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	22	H	
109	56	2.17	175	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	22	H	
111	56	2.46	174	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	23	H	
111	56	4.64	179	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	23	H	
111	56	3.00	177	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	23	H	
111	56	5.99	179	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	23	H	
111	56	.86	170	DNT		P1	08C	.48		TEC	TEH	.560	ZBATF	23	H	
113	56	1.58	171	DNT		P1	08H	.37		TEC	TEH	.560	ZBATF	22	H	
113	56	3.29	175	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	22	H	
113	56	5.57	177	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	22	H	
113	56	5.16	174	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	22	H	
113	56	7.72	178	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	22	H	
38	57	1.78	181	DNT		P1	TSH	7.62		TEC	TEH	.560	ZBATF	7	H	
98	57	1.41	179	DNT		P1	08H	9.59		TEC	TEH	.560	ZBATF	22	H	
106	57	.92	173	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	22	H	
108	57	1.05	171	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	23	H	
108	57	.85	173	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	23	H	
108	57	1.12	176	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	23	H	
108	57	1.94	176	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	23	H	
110	57	.65	170	DNT		P1	08H	.42		TEC	TEH	.560	ZBATF	22	H	
110	57	1.41	173	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	22	H	
110	57	2.82	177	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	22	H	
110	57	3.90	174	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	22	H	
110	57	4.55	177	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	22	H	
112	57	1.36	173	DNT		P1	08H	.37		TEC	TEH	.560	ZBATF	23	H	
112	57	2.63	174	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	23	H	
112	57	3.51	178	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	23	H	
112	57	2.58	176	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	23	H	
112	57	6.55	178	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	23	H	
112	57	1.02	171	DNT		P1	08C	.45		TEC	TEH	.560	ZBATF	23	H	
114	57	.82	171	DNT		P1	08H	.32		TEC	TEH	.560	ZBATF	22	H	
114	57	4.33	173	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	22	H	
114	57	5.22	177	DNT		P1	09H	.48		TEC	TEH	.560	ZBATF	22	H	
114	57	3.67	175	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	22	H	
114	57	6.37	178	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	22	H	
114	57	1.10	170	DNT		P1	08C	.45		TEC	TEH	.560	ZBATF	22	H	
45	58	1.29	181	DNT		P1	AV1	11.59		TEC	TEH	.560	ZBATF	25	H	
107	58	1.15	171	DNT		P1	09H	-.62		TEC	TEH	.560	ZBATF	23	H	
107	58	1.07	173	DNT		P1	09C	.57		TEC	TEH	.560	ZBATF	23	H	
109	58	1.02	172	DNT		P1	09C	-.55		TEC	TEH	.560	ZBATF	24	H	
109	58	1.66	174	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	24	H	
111	58	1.84	172	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	23	H	
111	58	2.59	176	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	23	H	
111	58	2.11	176	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	23	H	
111	58	3.75	177	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	23	H	
113	58	.94	171	DNT		P1	08H	.26		TEC	TEH	.560	ZBATF	24	H	
113	58	2.04	175	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	24	H	
113	58	4.52	177	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	24	H	
113	58	3.04	174	DNT		P1	09C	-.60		TEC	TEH	.560	ZBATF	24	H	
113	58	6.29	178	DNT		P1	09C	.50		TEC	TEH	.560	ZBATF	24	H	
113	58	1.08	172	DNT		P1	08C	.42		TEC	TEH	.560	ZBATF	24	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
16	59	1.06	180	DNT		P1	01C	16.68		TEC	TEH	.560	ZBATF	26	H	
108	59	1.60	178	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	27	H	
110	59	1.41	174	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	28	H	
110	59	2.69	176	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	28	H	
112	59	1.30	175	DNT		P1	08H	.34		TEC	TEH	.560	ZBATF	27	H	
112	59	1.93	177	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	27	H	
112	59	4.53	182	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	27	H	
112	59	3.61	180	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	27	H	
112	59	5.98	182	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	27	H	
112	59	1.27	176	DNT		P1	08C	.45		TEC	TEH	.560	ZBATF	27	H	
114	59	1.89	177	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	27	H	
114	59	4.70	180	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	27	H	
114	59	3.93	179	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	27	H	
114	59	9.37	181	DNT		P1	09C	.50		TEC	TEH	.560	ZBATF	27	H	
109	60	.91	174	DNT		P1	09H	.46		TEC	TEH	.560	ZBATF	28	H	
109	60	.86	174	DNT		P1	09C	.43		TEC	TEH	.560	ZBATF	28	H	
111	60	1.01	174	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	27	H	
111	60	2.76	180	DNT		P1	09H	.50		TEC	TEH	.560	ZBATF	27	H	
111	60	2.64	178	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	27	H	
111	60	5.51	182	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	27	H	
113	60	2.29	172	DNT		P1	09H	-.70		TEC	TEH	.560	ZBATF	28	H	
113	60	3.36	178	DNT		P1	09H	.38		TEC	TEH	.560	ZBATF	28	H	
113	60	1.77	173	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	28	H	
113	60	4.97	177	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	28	H	
115	60	1.47	175	DNT		P1	08H	.34		TEC	TEH	.560	ZBATF	27	H	
115	60	2.31	178	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	27	H	
115	60	5.00	180	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	27	H	
115	60	3.23	178	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	27	H	
115	60	7.56	181	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	27	H	
66	61	1.45	179	DNT		P1	05H	21.79		TEC	TEH	.560	ZBATF	28	H	
110	61	1.05	175	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	28	H	
110	61	.84	171	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	28	H	
110	61	1.32	174	DNT		P1	09C	.62		TEC	TEH	.560	ZBATF	28	H	
112	61	1.02	174	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	27	H	
112	61	2.50	179	DNT		P1	09H	.50		TEC	TEH	.560	ZBATF	27	H	
112	61	2.20	177	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	27	H	
112	61	4.60	181	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	27	H	
114	61	2.61	179	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	27	H	
114	61	5.89	182	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	27	H	
114	61	3.21	179	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	27	H	
114	61	8.95	182	DNT		P1	09C	.50		TEC	TEH	.560	ZBATF	27	H	
53	62	1.12	180	DNT		P1	06C	1.99		TEH	TEC	.560	ZBACS	43	C	
109	62	.76	172	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	28	H	
111	62	.86	174	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	27	H	
111	62	2.27	179	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	27	H	
111	62	.97	174	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	27	H	
111	62	2.56	180	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	27	H	
113	62	1.20	171	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	28	H	
113	62	2.73	177	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	28	H	
113	62	2.14	174	DNT		P1	09C	-.75		TEC	TEH	.560	ZBATF	28	H	
113	62	4.53	177	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	28	H	
115	62	2.44	178	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	27	H	
115	62	4.42	181	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	27	H	
115	62	2.61	178	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	27	H	
115	62	7.00	182	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	27	H	
108	63	1.31	178	DNT		P1	09C	.56		TEC	TEH	.560	ZBATF	27	H	
110	63	1.00	176	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	28	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
110	63	1.15	173	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	28	H	
112	63	1.74	178	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	27	H	
112	63	1.73	177	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	27	H	
112	63	4.73	181	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	27	H	
114	63	2.30	176	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	27	H	
114	63	5.36	182	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	27	H	
114	63	3.52	179	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	27	H	
114	63	8.71	181	DNT		P1	09C	.50		TEC	TEH	.560	ZBATF	27	H	
17	64	3.31	182	DNT		P1	AV8	7.30		TEC	TEH	.560	ZBATF	8	H	
43	64	.93	181	DNT		P1	FBH	13.39		TEC	TEH	.560	ZBATF	9	H	
83	64	1.06	180	DNT		P1	AV7	12.16		TEC	TEH	.560	ZBATF	27	H	
111	64	1.29	177	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	27	H	
111	64	2.58	180	DNT		P1	09H	.42		TEC	TEH	.560	ZBATF	27	H	
111	64	1.23	176	DNT		P1	09C	-.53		TEC	TEH	.560	ZBATF	27	H	
111	64	3.13	180	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	27	H	
113	64	1.02	171	DNT		P1	09H	-.65		TEC	TEH	.560	ZBATF	28	H	
113	64	1.92	175	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	28	H	
113	64	1.68	171	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	28	H	
113	64	3.62	176	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	28	H	
115	64	1.56	176	DNT		P1	08H	.34		TEC	TEH	.560	ZBATF	27	H	
115	64	2.51	177	DNT		P1	09H	-.69		TEC	TEH	.560	ZBATF	27	H	
115	64	5.25	182	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	27	H	
115	64	4.97	180	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	27	H	
115	64	12.28	182	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	27	H	
28	65	1.24	180	DNT		P1	01H	.26		TEC	TEH	.560	ZBATF	8	H	
54	65	1.11	174	DNT		P1	TSC	18.32		TEC	TEH	.560	ZBATF	28	H	
110	65	1.05	172	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	28	H	
112	65	1.65	176	DNT		P1	09H	-.63		TEC	TEH	.560	ZBATF	27	H	
112	65	2.41	180	DNT		P1	09H	.42		TEC	TEH	.560	ZBATF	27	H	
112	65	2.40	179	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	27	H	
114	65	1.84	176	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	27	H	
114	65	4.38	181	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	27	H	
114	65	1.92	175	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	27	H	
114	65	4.42	181	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	27	H	
111	66	1.41	177	DNT		P1	09H	.42		TEC	TEH	.560	ZBATF	27	H	
111	66	1.10	173	DNT		P1	09C	-.55		TEC	TEH	.560	ZBATF	27	H	
111	66	2.62	180	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	27	H	
113	66	1.10	172	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	28	H	
113	66	1.61	173	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	28	H	
113	66	.73	170	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	28	H	
113	66	2.41	175	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	28	H	
115	66	2.89	177	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	27	H	
115	66	6.03	182	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	27	H	
115	66	1.72	177	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	27	H	
115	66	4.81	181	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	27	H	
90	67	1.77	183	DNT		P1	03C	30.49		TEC	TEH	.560	ZBATF	30	H	
110	67	.59	173	DNT		P1	09C	.54		TEC	TEH	.560	ZBATF	30	H	
112	67	.79	174	DNT		P1	09H	.56		TEC	TEH	.560	ZBATF	30	H	
112	67	1.33	177	DNT		P1	09C	-.51		TEC	TEH	.560	ZBATF	30	H	
112	67	1.26	174	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	30	H	
114	67	1.36	172	DNT		P1	09H	-.66		TSC	TEH	.560	ZBATF	29	H	
114	67	3.44	177	DNT		P1	09H	.40		TSC	TEH	.560	ZBATF	29	H	
114	67	1.85	173	DNT		P1	09C	-.55		TSC	TEH	.560	ZBATF	29	H	
114	67	5.05	178	DNT		P1	09C	.53		TSC	TEH	.560	ZBATF	29	H	
114	67	1.33	171	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	40	H	
114	67	3.38	178	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	40	H	
114	67	1.74	174	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	40	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
114	67	5.50	177	DNT		P1	09C	.53		TEC	TEH	.560	ZBATF	40	H	
17	68	1.15	182	DNT		P1	08C	12.61		TEC	TEH	.560	ZBATF	8	H	
111	68	.66	174	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	30	H	
111	68	1.03	176	DNT		P1	09C	-.49		TEC	TEH	.560	ZBATF	30	H	
111	68	1.37	175	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	30	H	
113	68	.85	175	DNT		P1	09H	-.59		TEC	TEH	.560	ZBATF	30	H	
113	68	1.96	176	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	30	H	
113	68	1.61	177	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	30	H	
113	68	2.05	177	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	30	H	
115	68	2.43	173	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	31	H	
115	68	5.56	177	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	31	H	
115	68	1.84	171	DNT		P1	09C	-.58		TEC	TEH	.560	ZBATF	31	H	
115	68	3.78	177	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	31	H	
58	69	.92	181	DNT		P1	01H	16.66		TEC	TEH	.560	ZBATF	30	H	
112	69	.84	173	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	30	H	
114	69	2.04	176	DNT		P1	09H	-.59		TEC	TEH	.560	ZBATF	30	H	
114	69	4.54	180	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	30	H	
114	69	1.37	173	DNT		P1	09C	-.57		TEC	TEH	.560	ZBATF	30	H	
114	69	2.14	177	DNT		P1	09C	.43		TEC	TEH	.560	ZBATF	30	H	
35	70	1.41	180	DNT		P1	02C	6.78		TEC	TEH	.560	ZBATF	9	H	
109	70	1.79	184	DNT		P1	06H	28.32		TEC	TEH	.560	ZBATF	30	H	
111	70	1.03	172	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	30	H	
113	70	1.90	177	DNT		P1	09H	.45		TEC	TEH	.560	ZBATF	30	H	
113	70	1.15	174	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	30	H	
113	70	1.55	176	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	30	H	
115	70	1.57	171	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	32	H	
115	70	3.29	176	DNT		P1	09H	.38		TEC	TEH	.560	ZBATF	32	H	
115	70	1.25	172	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	32	H	
115	70	3.49	175	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	32	H	
30	71	2.04	185	DNT		P1	05C	30.16		TEH	TEC	.560	ZBACS	39	C	
34	71	1.10	187	DNT		P1	TSH	5.99		TEH	TEC	.560	ZBACS	39	C	
44	71	1.18	182	DNT		P1	06H	13.91		TEH	TEC	.560	ZBACS	38	C	
86	71	1.51	183	DNT		P1	05H	8.68		TEC	TEH	.560	ZBATF	32	H	
112	71	1.27	174	DNT		P1	09H	.45		TEC	TEH	.560	ZBATF	31	H	
112	71	.94	171	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	31	H	
114	71	1.61	171	DNT		P1	09H	-.67		TEC	TEH	.560	ZBATF	31	H	
114	71	3.51	177	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	31	H	
114	71	1.36	171	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	31	H	
114	71	3.21	176	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	31	H	
113	72	1.69	174	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	32	H	
113	72	1.13	171	DNT		P1	09C	-.54		TEC	TEH	.560	ZBATF	32	H	
113	72	1.95	174	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	32	H	
115	72	1.16	170	DNT		P1	09H	-.61		TEC	TEH	.560	ZBATF	31	H	
115	72	2.43	175	DNT		P1	09H	.35		TEC	TEH	.560	ZBATF	31	H	
115	72	1.08	170	DNT		P1	09C	-.56		TEC	TEH	.560	ZBATF	31	H	
115	72	2.25	175	DNT		P1	09C	.45		TEC	TEH	.560	ZBATF	31	H	
80	73	1.16	178	DNT		P1	02H	29.31		TEC	TEH	.560	ZBATF	31	H	
114	73	1.20	170	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	31	H	
114	73	2.99	175	DNT		P1	09H	.45		TEC	TEH	.560	ZBATF	31	H	
114	73	1.01	173	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	31	H	
113	74	1.28	172	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	32	H	
113	74	.86	168	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	32	H	
115	74	1.02	169	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	31	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
115	74	2.45	176	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	31	H	
115	74	.93	170	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	31	H	
115	74	1.90	174	DNT		P1	09C	.45		TEC	TEH	.560	ZBATF	31	H	
44	75	1.16	182	DNT		P1	07H	28.38		TEH	TEC	.560	ZBACS	38	C	
114	75	1.37	171	DNT		P1	09H	-.61		TEC	TEH	.560	ZBATF	31	H	
114	75	2.50	176	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	31	H	
114	75	1.37	173	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	31	H	
19	76	1.34	185	DNT		P1	TSH	16.99		TEH	TEC	.560	ZBACS	39	C	
115	76	1.55	172	DNT		P1	09H	-.61		TEC	TEH	.560	ZBATF	31	H	
115	76	5.28	177	DNT		P1	09H	.37		TEC	TEH	.560	ZBATF	31	H	
115	76	1.68	173	DNT		P1	09C	.45		TEC	TEH	.560	ZBATF	31	H	
98	77	1.44	181	DNT		P1	05H	37.47		TEC	TEH	.560	ZBATF	32	H	
114	77	1.21	170	DNT		P1	09H	-.66		TEC	TEH	.560	ZBATF	31	H	
114	77	3.70	176	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	31	H	
114	77	1.54	173	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	31	H	
111	78	.92	172	DNT		P1	09C	.51		TEC	TEH	.560	ZBATF	31	H	
113	78	1.17	170	DNT		P1	09H	-.62		TEC	TEH	.560	ZBATF	32	H	
113	78	2.19	174	DNT		P1	09H	.43		TEC	TEH	.560	ZBATF	32	H	
115	78	1.08	171	DNT		P1	09C	-.59		TEC	TEH	.560	ZBATF	31	H	
115	78	2.30	175	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	31	H	
54	79	2.07	173	DNT		P1	08H	35.22		TEC	TEH	.560	ZBATF	32	H	
60	79	2.25	174	DNT		P1	08C	32.16		TEC	TEH	.560	ZBATF	31	H	
112	79	1.73	174	DNT		P1	09H	.42		TEC	TEH	.560	ZBATF	31	H	
114	79	1.14	173	DNT		P1	09H	-.64		TEC	TEH	.560	ZBATF	31	H	
114	79	3.72	176	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	31	H	
114	79	1.43	174	DNT		P1	09C	.45		TEC	TEH	.560	ZBATF	31	H	
113	80	2.09	175	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	32	H	
115	80	1.71	172	DNT		P1	09H	.34		TEC	TEH	.560	ZBATF	31	H	
115	80	1.60	171	DNT		P1	09C	-.61		TEC	TEH	.560	ZBATF	31	H	
115	80	2.30	175	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	31	H	
114	81	2.24	174	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	31	H	
114	81	1.25	172	DNT		P1	09C	.45		TEC	TEH	.560	ZBATF	31	H	
61	82	1.03	175	DNT		P1	08H	34.60		TEH	TEC	.560	ZBACS	43	C	
61	82	.93	172	DNT		P1	08H	35.98		TEH	TEC	.560	ZBACS	43	C	
71	82	1.17	183	DNT		P1	02H	7.10		TEC	TEH	.560	ZBATF	33	H	
113	82	1.75	177	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	33	H	
113	82	.83	169	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	33	H	
115	82	1.69	173	DNT		P1	09C	.48		TEC	TEH	.560	ZBATF	33	H	
36	83	1.15	179	DNT		P1	TSC	3.17		TEH	TEC	.560	ZBACS	38	C	
44	83	1.53	173	DNT		P1	08H	31.65		TEH	TEC	.560	ZBACS	38	C	
44	83	.99	171	DNT		P1	08H	35.19		TEH	TEC	.560	ZBACS	38	C	
104	83	1.14	173	DNT		P1	TSH	15.18		TEC	TEH	.560	ZBATF	33	H	
112	83	1.13	173	DNT		P1	09H	.40		TEC	TEH	.560	ZBATF	33	H	
112	83	.99	172	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	33	H	
114	83	1.28	173	DNT		P1	09H	.38		TEC	TEH	.560	ZBATF	33	H	
114	83	1.50	172	DNT		P1	09C	.46		TEC	TEH	.560	ZBATF	33	H	
109	84	.86	173	DNT		P1	09C	-.64		TEH	TEC	.560	ZBATF	26	C	
109	84	1.31	176	DNT		P1	09C	.45		TEH	TEC	.560	ZBATF	26	C	
113	84	1.27	171	DNT		P1	09H	.43		TEH	TEC	.560	ZBATF	26	C	
113	84	1.11	173	DNT		P1	09C	.37		TEH	TEC	.560	ZBATF	26	C	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
44	85	1.16	183	DNT		P1	07H	35.09		TEH	TEC	.560	ZBACS	38	C	
13	86	.88	182	DNT		P1	07C	36.44		TEH	TEC	.560	ZBACS	38	C	
33	86	1.34	179	DNT		P1	05C	9.26		TEH	TEC	.560	ZBACS	38	C	
6	87	.73	162	DNT		P1	09H	.39		TEH	TEC	.560	ZBACS	41	C	
5	92	1.13	182	DNT		P1	08C	35.54		TEH	TEC	.560	ZBACS	43	C	
37	92	1.32	181	DNT		P1	08C	11.89		TEH	TEC	.560	ZBACS	40	C	
80	93	.99	186	DNT		P1	TSH	11.61		TEH	TEC	.560	ZBATF	29	C	
41	94	1.06	183	DNT		P1	04C	26.18		TEH	TEC	.560	ZBATF	6	C	
58	95	1.05	183	DNT		P1	03H	11.26		TEH	TEC	.560	ZBATF	31	C	
76	95	1.48	182	DNT		P1	05C	1.21		TEH	TEC	.560	ZBATF	28	C	
76	95	1.05	179	DNT		P1	04C	21.18		TEH	TEC	.560	ZBATF	28	C	
102	95	1.81	182	DNT		P1	04C	37.14		TEH	TEC	.560	ZBATF	19	C	
53	96	1.01	182	DNT		P1	TSC	2.63		TEH	TEC	.560	ZBATF	30	C	
105	96	1.34	183	DNT		P1	01H	36.84		TEH	TEC	.560	ZBATF	19	C	
1	98	1.67	178	DNT		P1	04H	26.87		09H	TEH	.560	ZBATF	3	H	
3	98	1.40	180	DNT		P1	03C	29.63		09H	TEC	.560	ZBACS	3	C	
103	98	.98	183	DNT		P1	06H	1.53		TEH	TEC	.560	ZBATF	30	C	
42	99	.95	180	DNT		P1	08C	9.41		TEH	TEC	.560	ZBATF	7	C	
52	99	1.08	179	DNT		P1	03C	27.49		TEH	TEC	.560	ZBATF	30	C	
23	100	1.13	184	DNT		P1	08C	18.65		TEH	TEC	.560	ZBATF	6	C	
82	101	1.45	180	DNT		P1	FBH	1.84		TEH	TEC	.560	ZBATF	19	C	
5	102	.98	181	DNT		P1	04C	27.30		TEH	TEC	.560	ZBATF	6	C	
10	103	1.18	181	DNT		P1	08C	37.50		TEH	TEC	.560	ZBATF	7	C	
32	103	1.25	184	DNT		P1	07H	28.88		TEH	TEC	.560	ZBATF	7	C	
32	105	1.28	181	DNT		P1	FBC	5.26		TEH	TEC	.560	ZBATF	7	C	
92	105	1.78	183	DNT		P1	05H	35.25		TEH	TEC	.560	ZBATF	30	C	
92	105	1.03	182	DNT		P1	06C	9.92		TEH	TEC	.560	ZBATF	30	C	
56	107	1.48	175	DNT		P1	09H	.59		TEH	TEC	.560	ZBATF	32	C	
60	109	1.28	185	DNT		P1	FBH	2.82		TEH	TEC	.560	ZBATF	34	C	
76	109	1.07	180	DNT		P1	07C	16.54		TEH	TEC	.560	ZBATF	34	C	
25	110	1.26	186	DNT		P1	01C	23.17		TEH	TEC	.560	ZBATF	9	C	
39	110	.87	180	DNT		P1	TSC	2.12		TEH	TEC	.560	ZBATF	9	C	
77	110	1.02	171	DNT		P1	07H	28.10		TEH	TEC	.560	ZBATF	21	C	
82	111	1.30	171	DNT		P1	08H	-.08		TEH	TEC	.560	ZBATF	21	C	
82	111	3.54	176	DNT		P1	08H	4.92		TEH	TEC	.560	ZBATF	21	C	
90	111	1.29	173	DNT		P1	03C	36.31		TEH	TEC	.560	ZBATF	21	C	
90	111	1.30	180	DNT		P1	TSC	8.18		TEH	TEC	.560	ZBATF	21	C	
14	113	1.37	182	DNT		P1	06C	34.59		TEH	TEC	.560	ZBATF	8	C	
72	115	2.83	177	DNT		P1	08H	11.64		TEH	TEC	.560	ZBATF	34	C	
15	118	1.40	179	DNT		P1	08H	35.54		TEH	TEC	.560	ZBATF	9	C	

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
17	118	1.05	181	DNT		P1	08C	35.57		TEH	TEC	.560	ZBATF	9	C	
25	118	1.22	183	DNT		P1	07C	22.08		TEH	TEC	.560	ZBATF	9	C	
53	118	1.19	184	DNT		P1	08H	9.36		TEH	TEC	.560	ZBACS	35	C	
83	118	.97	181	DNT		P1	03C	4.66		TEH	TEC	.560	ZBATF	23	C	
64	121	4.08	178	DNT		P1	08C	26.77		TEH	TEC	.560	ZBACS	35	C	
70	121	1.89	175	DNT		P1	09H	.52		TEH	TEC	.560	ZBATF	23	C	
57	122	1.21	175	DNT		P1	09H	.19		TEH	TEC	.560	ZBATF	34	C	
57	122	1.14	171	DNT		P1	09C	-.67		TEH	TEC	.560	ZBATF	34	C	
57	122	3.48	175	DNT		P1	09C	.45		TEH	TEC	.560	ZBATF	34	C	
16	123	1.78	183	DNT		P1	03C	8.70		TEH	TEC	.560	ZBATF	10	C	
38	123	.87	181	DNT		P1	TSH	9.69		TEH	TEC	.560	ZBATF	10	C	
37	124	.86	184	DNT		P1	FBC	12.88		TEC	TEH	.560	ZBATF	40	H	
51	124	1.15	179	DNT		P1	FBC	1.29		TEH	TEC	.560	ZBATF	23	C	
14	125	.99	183	DNT		P1	FBC	11.54		TEH	TEC	.560	ZBATF	10	C	
70	125	2.28	182	DNT		P1	04C	32.87		TEH	TEC	.560	ZBATF	23	C	
4	127	1.19	182	DNT		P1	06C	32.45		09H	TEC	.560	ZBACS	3	C	
36	127	.93	181	DNT		P1	04C	15.51		TEH	TEC	.560	ZBATF	10	C	
1	128	.99	184	DNT		P1	06H	27.48		09H	TEH	.560	ZBATF	1	H	
31	128	1.35	185	DNT		P1	FBH	5.98		TEH	TEC	.560	ZBATF	11	C	
43	130	1.15	179	DNT		P1	06C	35.47		TEC	TEH	.560	ZBATF	5	H	
4	131	.99	183	DNT		P1	04C	2.17		09H	TEC	.560	ZBACS	3	C	
15	132	1.74	182	DNT		P1	05H	16.43		TEC	TEH	.560	ZBATF	5	H	
23	134	1.59	178	DNT		P1	05H	.38		TEC	TEH	.560	ZBATF	5	H	
22	137	1.15	181	DNT		P1	01C	22.20		TEC	TEH	.560	ZBATF	4	H	
12	139	1.87	184	DNT		P1	TSH	1.24		TEC	TEH	.560	ZBATF	4	H	
12	139	1.69	174	DNT		P1	TSH	8.44		TEC	TEH	.560	ZBATF	4	H	
12	139	7.48	178	DNT		P1	TSH	9.53		TEC	TEH	.560	ZBATF	4	H	
26	139	1.50	181	DNT		P1	02C	35.79		TEC	TEH	.560	ZBATF	5	H	
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

Tubes: 528 Records: 1372

SG - C NON-QUANTIFIABLE SIGNALS

Shearon Harris RFO11 CQL D75

X 81 TUBE WITH NON-QUANTIFIABLE SIGNAL

* 4 STAY

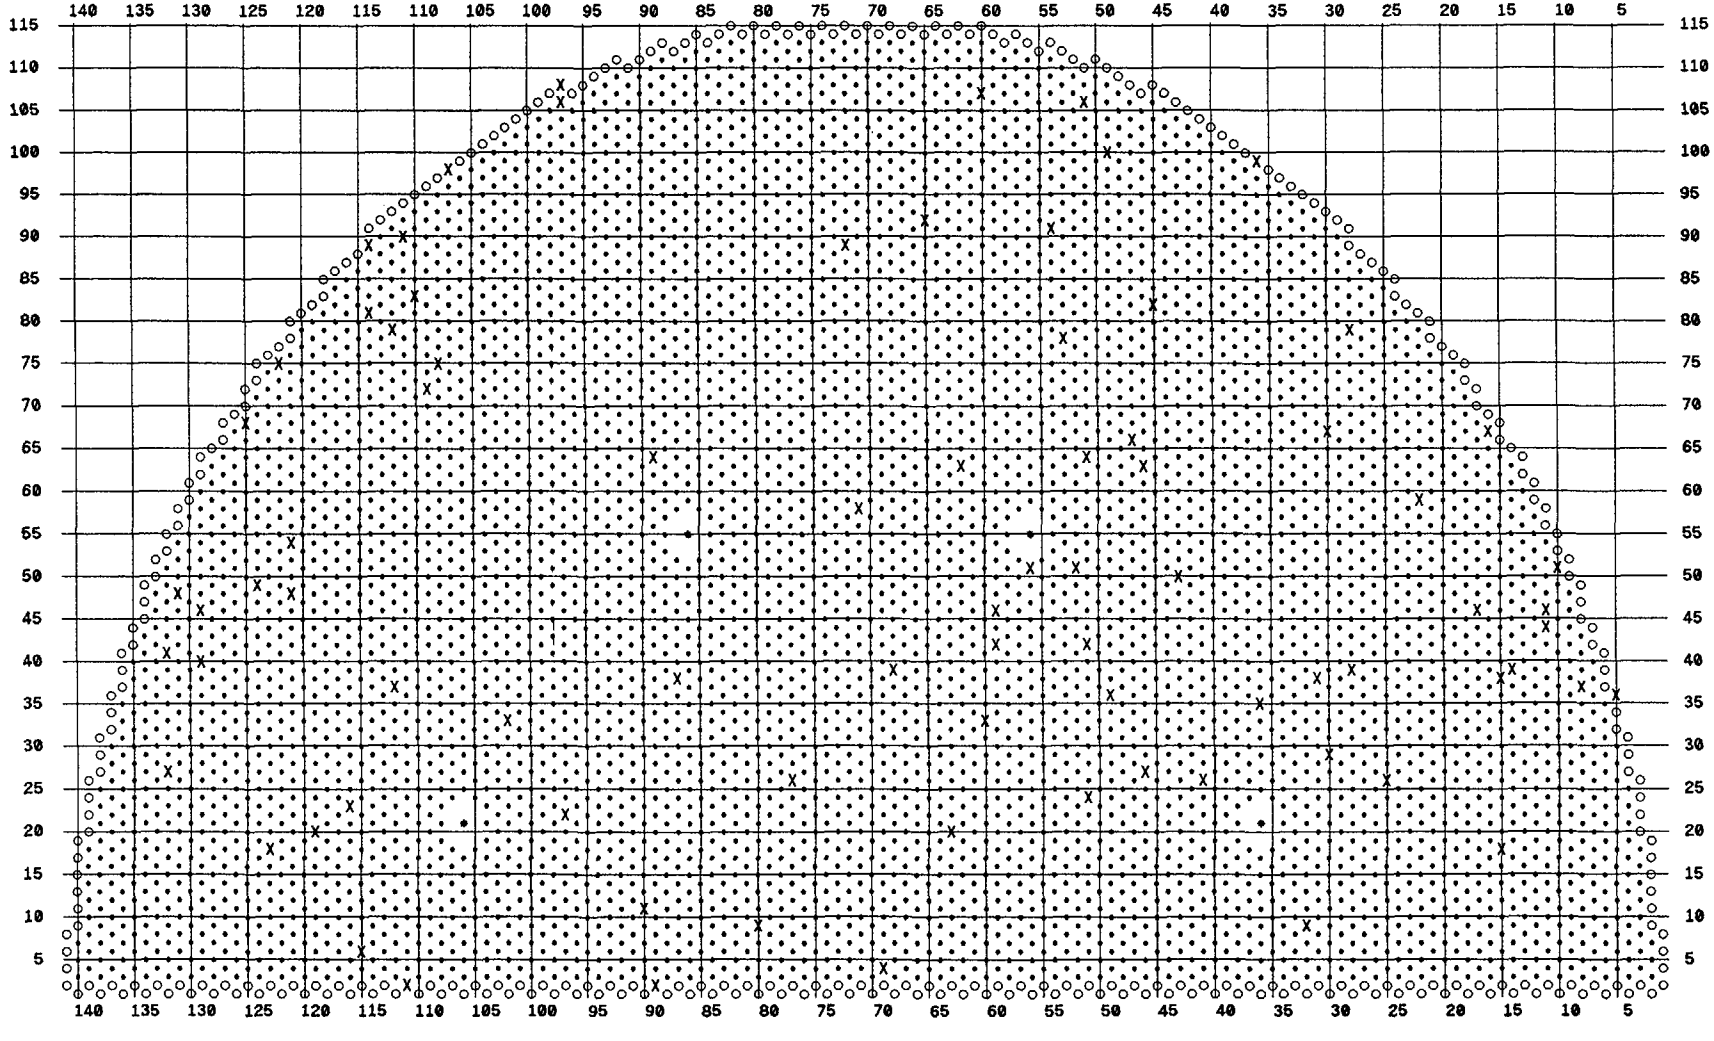

Westinghouse Electric Company LLC - NSBU ST2000 05/08/2003 02:26:49

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	I	CRLEN	CEG	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
36	5	.12	158	NQS		P1	05H	33.82					TEC	TEH	.560	ZBATF	36	H	Result of Senior/History Analyst Review
37	8	.04	69	NQS		P1	05H	30.06					TEC	TEH	.560	ZBATF	36	H	Result of Senior/History Analyst Review
51	10	.07	35	NQS		P1	02C	36.38					TEC	TEH	.560	ZBATF	35	H	Result of Senior/History Analyst Review
44	11	.07	43	NQS		P1	02C	8.40					TEC	TEH	.560	ZBATF	35	H	Result of Senior/History Analyst Review
46	11	.19	13	NQS		P1	08H	28.18					TEC	TEH	.560	ZBATF	35	H	Result of Senior/History Analyst Review
39	14	.10	67	NQS		P1	07C	37.36					TEC	TEH	.560	ZBATF	10	H	Result of Senior/History Analyst Review
18	15	.05	98	NQS		P1	06C	31.97					TEC	TEH	.560	ZBATF	11	H	Result of Senior/History Analyst Review
38	15	.49	20	NQS		P1	06H	20.22					TEC	TEH	.560	ZBATF	11	H	Result of Senior/History Analyst Review
67	16	.39	156	NQS		P1	03C	18.57					TEC	TEH	.560	ZBATF	15	H	Result of Senior/History Analyst Review
46	17	.13	86	NQS		P1	07C	12.45					TEC	TEH	.560	ZBATF	15	H	Result of Senior/History Analyst Review
59	22	.14	45	NQS		P1	07H	24.85					TEC	TEH	.560	ZBATF	15	H	Result of Senior/History Analyst Review
26	25	.12	10	NQS		P1	05H	31.45					TEC	TEH	.560	ZBATF	11	H	Result of Senior/History Analyst Review
39	28	.24	144	NQS		P1	04C	30.86					TEC	TEH	.560	ZBATF	11	H	Result of Senior/History Analyst Review
79	28	1.05	16	NQS		P1	08H	33.59					TEC	TEH	.560	ZBATF	16	H	Result of Senior/History Analyst Review
29	30	.91	12	NQS		P1	03H	2.39					TEC	TEH	.560	ZBATF	10	H	Result of Senior/History Analyst Review
67	30	.07	84	NQS		P1	02H	15.57					TEC	TEH	.560	ZBATF	17	H	Result of Senior/History Analyst Review
38	31	.18	130	NQS		P1	02C	17.17					TEC	TEH	.560	ZBATF	11	H	Result of Senior/History Analyst Review
9	32	.05	95	NQS		P1	03C	29.77					TEC	TEH	.560	ZBATF	10	H	Result of Senior/History Analyst Review
35	36	.82	3	NQS		P1	03C	23.47					TEC	TEH	.560	ZBATF	12	H	Result of Senior/History Analyst Review
35	36	1.03	4	NQS		P1	03C	25.78					TEC	TEH	.560	ZBATF	12	H	Result of Senior/History Analyst Review
99	36	.10	139	NQS		P1	09H	9.26					TEC	TEH	.560	ZBATF	16	H	Result of Senior/History Analyst Review
26	41	.15	44	NQS		P1	08H	27.98					TEC	TEH	.560	ZBATF	13	H	Result of Senior/History Analyst Review
50	43	1.11	4	NQS		P1	05H	8.77					TEC	TEH	.560	ZBATF	18	H	Result of Senior/History Analyst Review
50	43	.09	15	NQS		4	05H	8.70					05H	06H	.560	ZRS3C	42	H	
50	43	.10	55	NQS		4	05H	18.99					05H	06H	.560	ZRS3C	42	H	
82	45	.08	119	NQS		P1	TSH	8.33					TEC	TEH	.560	ZBATF	21	H	Result of Senior/History Analyst Review
27	46	.17	142	NQS		P1	08H	19.42					TEC	TEH	.560	ZBATF	13	H	Result of Senior/History Analyst Review
63	46	.12	39	NQS		P1	07C	36.44					TEC	TEH	.560	ZBATF	21	H	Result of Senior/History Analyst Review
66	47	.31	178	NQS		P1	05H	28.56					TEC	TEH	.560	ZBATF	21	H	Result of Senior/History Analyst Review
66	47	.09	88	NQS		4	05H	28.28					05H	06H	.560	ZRS3C	42	H	
36	49	.72	9	NQS		P1	02H	30.59					TEC	TEH	.560	ZBATF	6	H	Result of Senior/History Analyst Review
36	49	.50	188	NQS		4	02H	30.57					02H	03H	.560	ZRS3C	42	H	
100	49	.08	31	NQS		P1	02C	11.95					TEC	TEH	.560	ZBATF	21	H	Result of Senior/History Analyst Review
24	51	.09	45	NQS		P1	08H	7.79					TEC	TEH	.560	ZBATF	6	H	Result of Senior/History Analyst Review
42	51	.15	16	NQS		P1	01H	16.54					TEC	TEH	.560	ZBATF	7	H	Result of Senior/History Analyst Review
42	51	.07	161	NQS		4	01H	16.58					01H	02H	.560	ZRS3C	43	H	
64	51	.12	36	NQS		P1	AV2	2.63					TEC	TEH	.560	ZBATF	21	H	Result of Senior/History Analyst Review
106	51	.12	149	NQS		P1	05H	24.56					TEC	TEH	.560	ZBATF	20	H	Result of Senior/History Analyst Review
51	52	.42	4	NQS		P1	06C	18.94					TEC	TEH	.560	ZBATF	21	H	Result of Senior/History Analyst Review
78	53	.19	153	NQS		P1	04C	2.72					TEC	TEH	.560	ZBATF	23	H	Result of Senior/History Analyst Review
91	54	.24	162	NQS		P1	08H	12.88					TEC	TEH	.560	ZBATF	23	H	Result of Senior/History Analyst Review
51	56	.09	53	NQS		P1	03H	2.61					TEC	TEH	.560	ZBATF	22	H	Result of Senior/History Analyst Review
51	56	.08	300	NQS		4	03H	2.85					03H	04H	.560	ZRS3C	42	H	
42	59	.12	117	NQS		P1	08C	22.41					TSC	TEH	.560	ZBATF	9	H	Result of Senior/History Analyst Review
46	59	.12	83	NQS		P1	07H	29.04					TEC	TEH	.560	ZBATF	28	H	Result of Senior/History Analyst Review
46	59	.10	133	NQS		4	07H	28.66					07H	08H	.560	ZRS3C	42	H	
33	60	.07	107	NQS		P1	06C	21.56					TEC	TEH	.560	ZBATF	8	H	Result of Senior/History Analyst Review
107	60	.07	72	NQS		P1	03H	15.54					TEC	TEH	.560	ZBATF	27	H	Result of Senior/History Analyst Review
63	62	.13	41	NQS		P1	07C	28.39					TEC	TEH	.560	ZBATF	27	H	Result of Senior/History Analyst Review
20	63	.10	99	NQS		P1	06H	14.62					TEC	TEH	.560	ZBATF	8	H	Result of Senior/History Analyst Review
92	65	.21	127	NQS		P1	04C	18.75					TEC	TEH	.560	ZBATF	27	H	Result of Senior/History Analyst Review
39	68	.12	80	NQS		P1	07H	9.47					TEC	TEH	.560	ZBATF	9	H	Result of Senior/History Analyst Review
39	68	.15	109	NQS		P1	08C	36.30					TEC	TEH	.560	ZBATF	9	H	Result of History Review
39	68	.12	231	NQS		4	07H	9.59					07H	08H	.560	ZRS3C	42	H	
4	69	.14	135	NQS		P1	06C	34.18					09H	TEC	.560	ZBACS	2	C	Result of Senior/History Analyst Review
58	71	.06	27	NQS		P1	05C	32.50					TEC	TEH	.560	ZBATF	32	H	Result of Senior/History Analyst Review
89	72	.16	28	NQS		P1	FBH	16.66					TEC	TEH	.560	ZBATF	32	H	Result of Senior/History Analyst Review
26	77	.07	62	NQS		P1	07C	34.49					TEH	TEC	.560	ZBACS	39	C	Result of Senior/History Analyst Review
9	80	.12	30	NQS		P1	08H	14.41					TEH	TEC	.560	ZBACS	40	C	Result of Senior/History Analyst Review
38	87	.48	7	NQS		P1	FBC	12.64					TEH	TEC	.560	ZBACS	41	C	Result of Senior/History Analyst Review
2	89	.13	41	NQS		P1	03C	13.64					09H	TEC	.560	ZBACS	4	C	Result of Senior/History Analyst Review
64	89	.07	137	NQS		P1	03H	33.31					TEH	TEC	.560	ZBATF	28	C	Result of Senior/History Analyst Review

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	I	CRLEN	CEG	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
11	90	.08	94	NQS		P1	02H	37.70					TEH	TEC	.560	ZBACS	41	C	Result of Senior/History Analyst Review
22	97	.11	34	NQS		4	08H	36.04					08H	09H	.560	ZRS3C	42	H	
106	97	1.26	3	NQS		P1	06H	26.45	34.05				TEH	TEC	.560	ZBATF	19	C	Result of Senior/History Analyst Review
108	97	.13	46	NQS		P1	AV4	8.97					TEH	TEC	.560	ZBATF	30	C	Result of Senior/History Analyst Review
33	102	.02	53	NQS		P1	TSC	17.19					TEH	TEC	.560	ZBATF	6	C	Result of Senior/History Analyst Review
98	107	.06	120	NQS		P1	08H	3.15					TEH	TEC	.560	ZBATF	30	C	Result of Senior/History Analyst Review
75	108	.15	101	NQS		P1	08H	8.84					TEH	TEC	.560	ZBATF	21	C	Result of Senior/History Analyst Review
72	109	.06	75	NQS		P1	05C	17.56					TEH	TEC	.560	ZBATF	34	C	Result of Senior/History Analyst Review
83	110	.09	148	NQS		4	02H	21.28					02H	03H	.560	ZRS3C	42	H	
2	111	.07	58	NQS		P1	08C	6.37					09C	TEC	.560	ZBATF	5	C	Result of Senior/History Analyst Review
2	111	.04	40	NQS		P1	08C	6.68					09H	TEC	.560	ZBACS	42	C	Result of Senior/History Analyst Review
90	111	.48	8	NQS		P1	TSC	8.37					TEH	TEC	.560	ZBATF	21	C	Result of Senior/History Analyst Review
37	112	1.07	3	NQS		P1	03C	30.49					TEH	TEC	.560	ZBATF	9	C	Result of Senior/History Analyst Review
79	112	.10	34	NQS		P1	02C	20.93					TEH	TEC	.560	ZBATF	21	C	Result of Senior/History Analyst Review
81	114	.07	63	NQS		P1	TSH	8.68					TEH	TEC	.560	ZBATF	21	C	Result of Senior/History Analyst Review
89	114	.13	23	NQS		P1	08H	19.32					TEH	TEC	.560	ZBATF	21	C	Result of Senior/History Analyst Review
6	115	.16	137	NQS		P1	06C	19.80					TEH	TEC	.560	ZBATF	8	C	Result of Senior/History Analyst Review
23	116	.09	131	NQS		P1	07H	21.98					TEH	TEC	.560	ZBATF	9	C	Result of Senior/History Analyst Review
20	119	.04	99	NQS		P1	03H	18.02					TEH	TEC	.560	ZBATF	8	C	Result of Senior/History Analyst Review
48	121	.18	112	NQS		P1	06H	10.96					TEH	TEC	.560	ZBACS	35	C	Result of Senior/History Analyst Review
54	121	.29	159	NQS		P1	05H	14.81					TEH	TEC	.560	ZBATF	23	C	Result of Senior/History Analyst Review
75	122	.08	19	NQS		P1	07C	16.83					TEH	TEC	.560	ZBATF	23	C	Result of Senior/History Analyst Review
18	123	.06	51	NQS		P1	07C	12.24					TEH	TEC	.560	ZBATF	10	C	Result of Senior/History Analyst Review
49	124	.11	119	NQS		4	TSH	13.62					TSH	01H	.560	ZRS3C	42	H	
49	124	.07	79	NQS		4	TSH	14.67					TSH	01H	.560	ZRS3C	42	H	
68	125	.34	27	NQS		P1	AV6	7.47					TEH	TEC	.560	ZBACS	35	C	Result of Senior/History Analyst Review
40	129	.10	47	NQS		P1	08H	2.54					TEC	TEH	.560	ZBATF	5	H	Result of Senior/History Analyst Review
46	129	.11	23	NQS		P1	01C	2.57					TEC	TEH	.560	ZBATF	4	H	Result of Senior/History Analyst Review
48	131	.10	84	NQS		P1	06C	32.49					TEC	TEH	.560	ZBATF	34	H	Result of Senior/History Analyst Review
27	132	.08	18	NQS		P1	04C	19.58					TEC	TEH	.560	ZBATF	5	H	Result of Senior/History Analyst Review
41	132	.12	48	NQS		P1	02C	13.03					TEC	TEH	.560	ZBATF	4	H	Result of Senior/History Analyst Review
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	I	CRLEN	CEG	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

Tubes: 81 Records: 93

SG - C PERMEABILITY VARIATIONS

Shearon Harris RFO11 CQL D75

X 1 TUBE WITH PEMEABILITY VARIATION

* 4 STAY

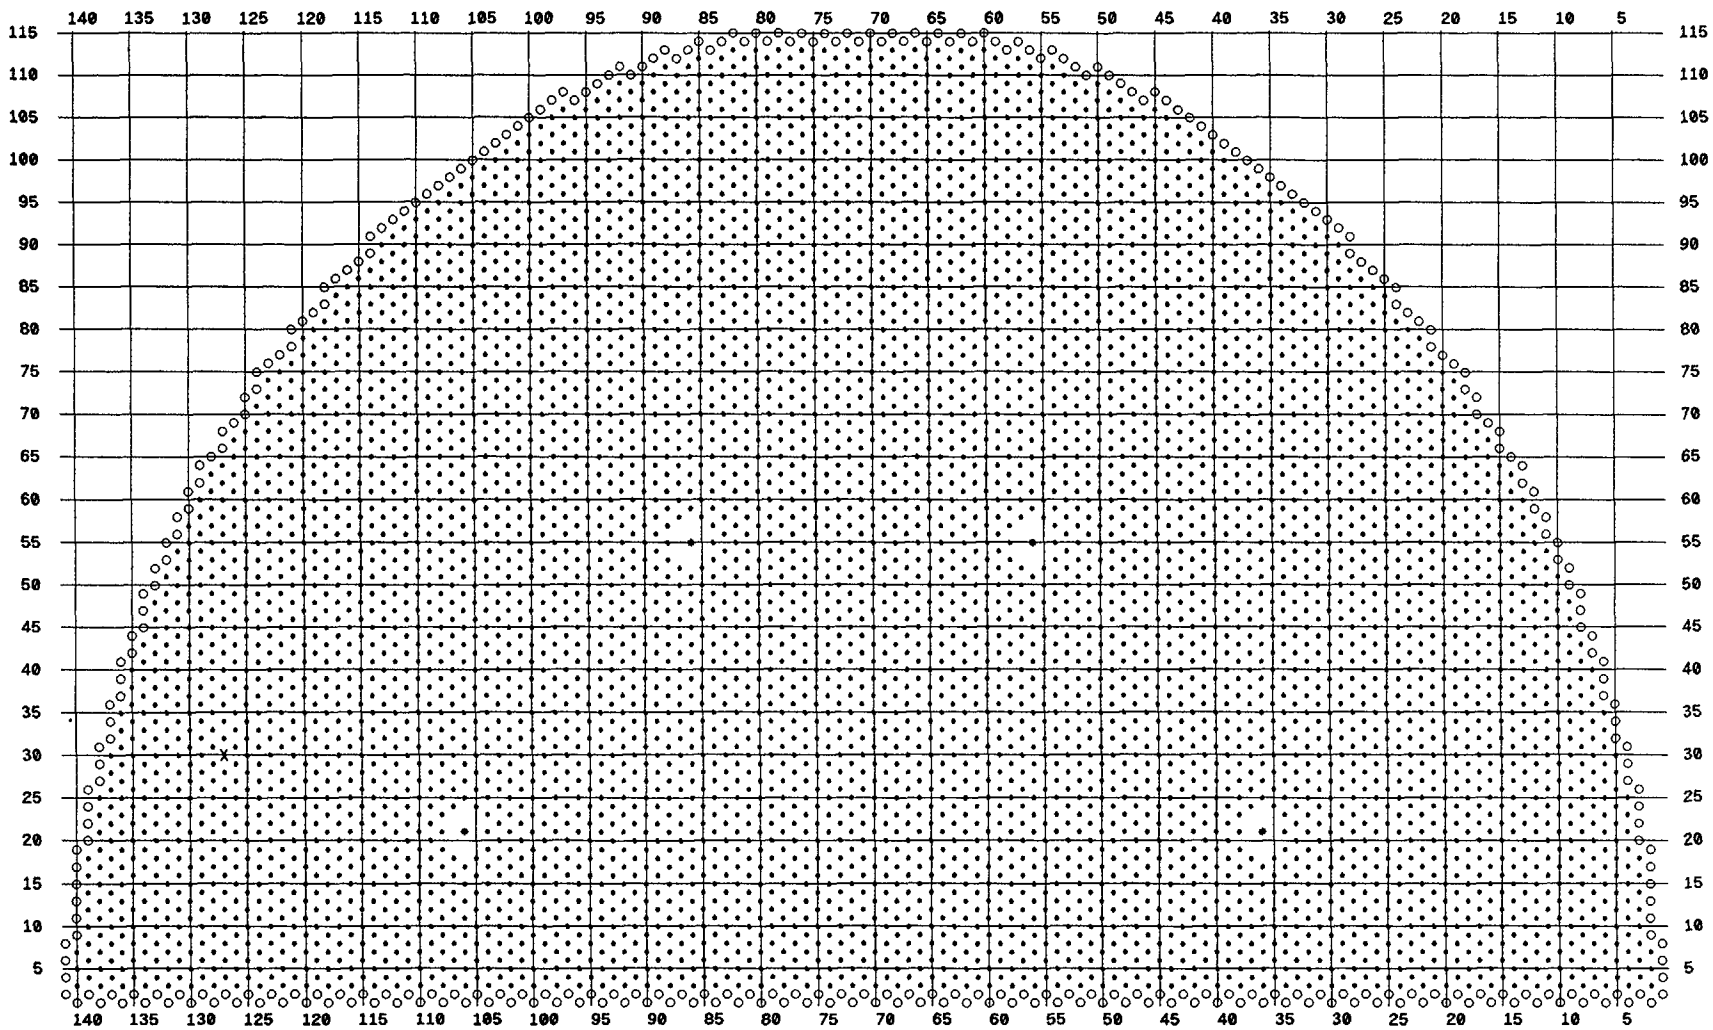

Westinghouse Electric Company LLC - NSBU ST2000 05/08/2003 02:09:12

SG - C Permeability Variations

Shearon Harris 1 RF011 CQL 20030501 05/08/2003 01:43:50

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
30	127	4.55	13	PVN		1	AV8	2.86		TEH	TEC	.560	ZBATF	11	C	Result of Senior Analyst Review
ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM

Tubes: 1 Records: 1

SG - C HOT LEG SPECIAL INTEREST ROTATING COIL INSPECTION

Shearon Harris RFO11 CQL D75

T 2 TEST TSH +/- 2"
S 1 TEST TSH -2" THROUGH 01H
F 1 TEST FBH THROUGH 01H
1 2 TEST 01H THROUGH 02H
2 2 TEST 02H THROUGH 03H
3 1 TEST 03H THROUGH 04H
V 1 TEST 05H +/- 2"
5 3 TEST 05H THROUGH 06H
7 2 TEST 07H THROUGH 08H
8 2 TEST 08H THROUGH 09H
* 4 STAY

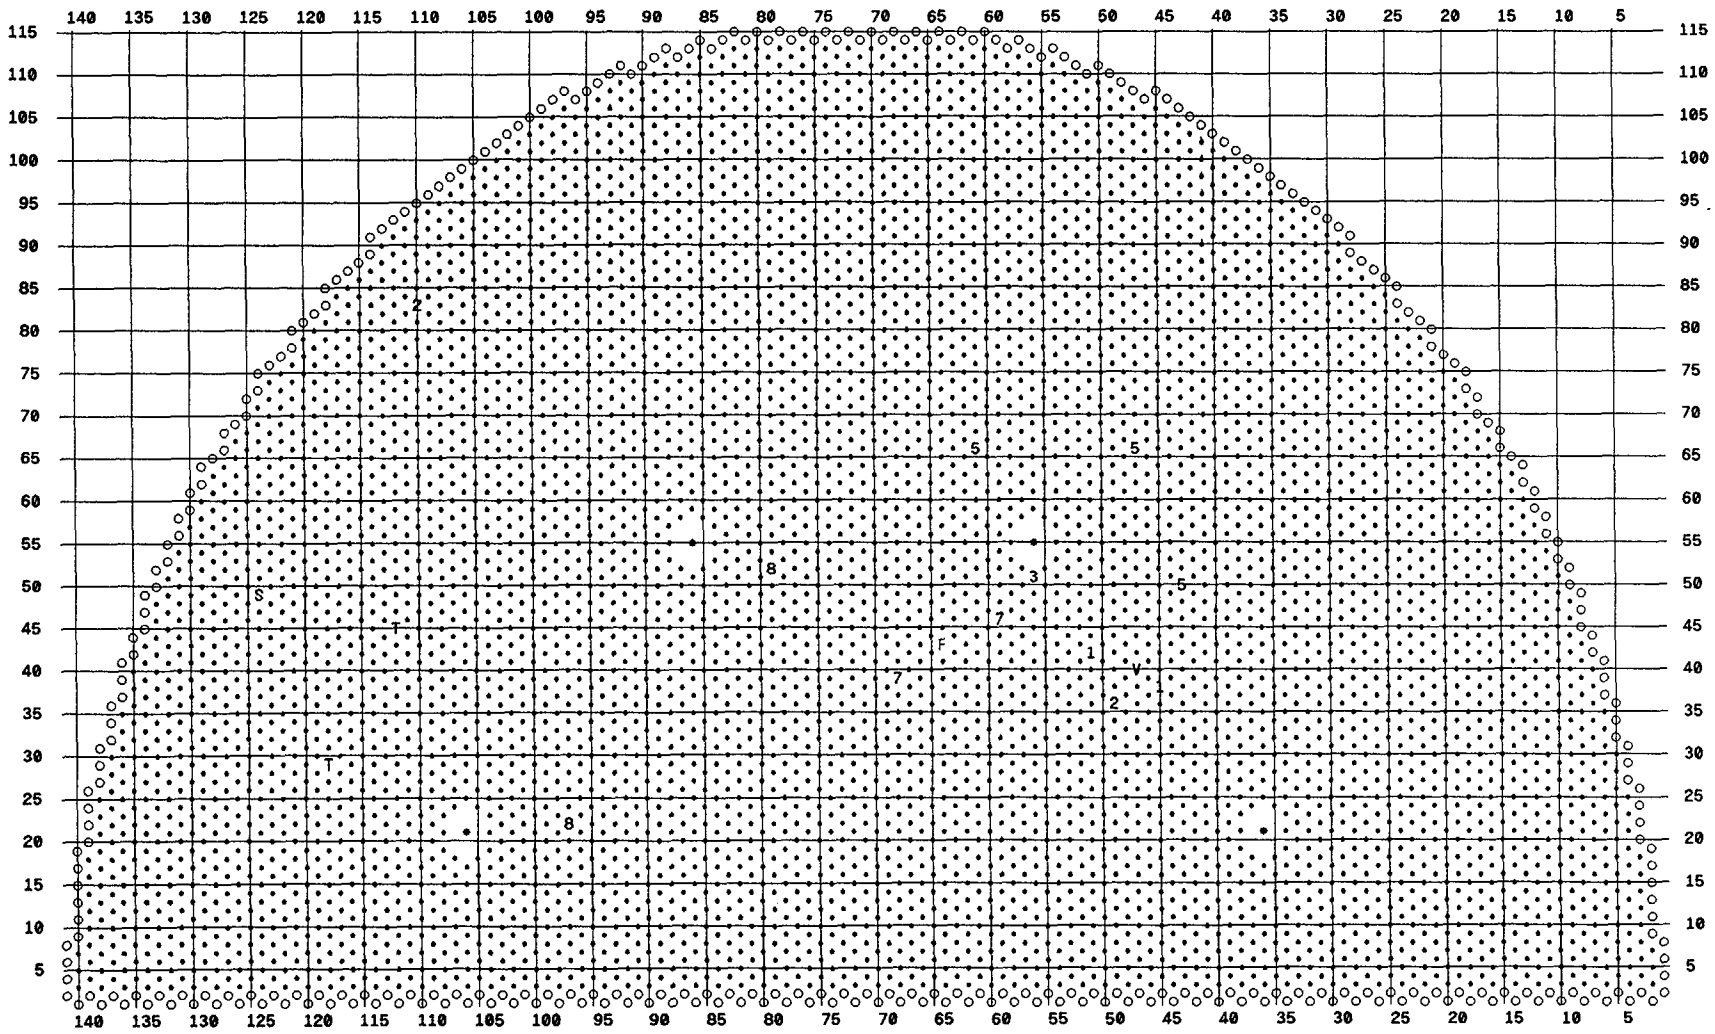

Westinghouse Electric Company LLC - NSBU ST2000 05/08/2003 01:51:11

ROW	COL	VOLTS	DEG	IND	PER	CHN	LOCN	INCH1	INCH2	BEGT	ENDT	PDIA	PTYPE	CAL	L	COM
50	43	1.11	4	NQS		P1	05H	8.77		TEC	TEH	.560	ZBATF	18	H	Result of Senior/History Analyst Review
50	43	.09	15	NQS		4	05H	8.70		05H	06H	.560	ZRS3C	42	H	
50	43	.10	55	NQS		4	05H	18.99		05H	06H	.560	ZRS3C	42	H	
38	45	1.28	178	DNT		P1	01H	27.88		TEC	TEH	.560	ZBATF	13	H	
38	45	.38	33	INR		P1	01H	28.17		TEC	TEH	.560	ZBATF	13	H	Result of Senior/History Analyst Review
38	45															Non-Relevant Response - Non-flaw like in nature
38	45			NDF		4	01H	27.99		01H	02H	.560	ZRS3C	42	H	
40	47	1.01	178	DNT		P1	05H	1.27		TEC	TEH	.560	ZBATF	12	H	
40	47			NDF		4	05H	1.33		05H	05H	.560	ZRS3C	42	H	
66	47	.31	178	NQS		P1	05H	28.56		TEC	TEH	.560	ZBATF	21	H	Result of Senior/History Analyst Review
66	47	.09	88	NQS		4	05H	28.28		05H	06H	.560	ZRS3C	42	H	
36	49	.72	9	NQS		P1	02H	30.59		TEC	TEH	.560	ZBATF	6	H	Result of Senior/History Analyst Review
36	49	.50	188	NQS		4	02H	30.57		02H	03H	.560	ZRS3C	42	H	
42	51	.15	16	NQS		P1	01H	16.54		TEC	TEH	.560	ZBATF	7	H	Result of Senior/History Analyst Review
42	51	.07	161	NQS		4	01H	16.58		01H	02H	.560	ZRS3C	43	H	
51	56	.09	53	NQS		P1	03H	2.61		TEC	TEH	.560	ZBATF	22	H	Result of Senior/History Analyst Review
51	56	.08	300	NQS		4	03H	2.85		03H	04H	.560	ZRS3C	42	H	
46	59	.12	83	NQS		P1	07H	29.04		TEC	TEH	.560	ZBATF	28	H	Result of Senior/History Analyst Review
46	59	.10	133	NQS		4	07H	28.66		07H	08H	.560	ZRS3C	42	H	
66	61	1.45	179	DNT		P1	05H	21.79		TEC	TEH	.560	ZBATF	28	H	
66	61			NDF		4	05H	21.90		05H	06H	.560	ZRS3C	42	H	
43	64	.93	181	DNT		P1	F8H	13.39		TEC	TEH	.560	ZBATF	9	H	
43	64			NDF		4	F8H	13.57		F8H	01H	.560	ZRS3C	42	H	
39	68	.12	80	NQS		P1	07H	9.47		TEC	TEH	.560	ZBATF	9	H	Result of Senior/History Analyst Review
39	68	.15	109	NQS		P1	08C	36.30		TEC	TEH	.560	ZBATF	9	H	Result of History Review
39	68	.12	231	NQS		4	07H	9.59		07H	08H	.560	ZRS3C	42	H	
52	79	.26	145	DDI		P3	08H	31.70		TEC	TEH	.560	ZBATF	31	H	Result of Senior/History Analyst Review
52	79			NDF		4	08H	31.70		08H	09H	.560	ZRS3C	42	H	
22	97	.36	24	INR		P1	08H	36.04		TEH	TEC	.560	ZBATF	7	C	Result of Senior/History Analyst Review
22	97															Shows change in ABS signal but is not flaw like
22	97	.11	34	NQS		4	08H	36.04		08H	09H	.560	ZRS3C	42	H	
83	110	.61	12	INR		P1	02H	21.20		TEH	TEC	.560	ZBACS	35	C	Result of Senior/History Analyst Review
83	110															Shows change in ABS signal but is not flaw like
83	110	.09	108	INR		P1	TSC	4.85		TEH	TEC	.560	ZBACS	35	C	Result of Senior Analyst Review
83	110															Non-Relevant Response - Non-flaw like in nature
83	110	.09	148	NQS		4	02H	21.28		02H	03H	.560	ZRS3C	42	H	
45	112	.26	149	INR		P1	TSH	.59		TEH	TEC	.560	ZBATF	9	C	Result of Senior/History Analyst Review
45	112															Shows change in ABS signal but is not flaw like
45	112			NDF		4	TSH	.59		TSH	TSH	.560	ZRS3C	42	H	
29	118	.20	149	INR		P1	TSH	.57		TEH	TEC	.560	ZBATF	9	C	Result of Senior Analyst Review
29	118															Shows change in ABS signal but is not flaw like
29	118			NDF		4	TSH	.57		TSH	TSH	.560	ZRS3C	42	H	
49	124	.07	98	NQI		P1	TSH	14.44		TEH	TEC	.560	ZBATF	34	C	Result of Senior/History Analyst Review
49	124	.11	119	NQS		4	TSH	13.62		TSH	01H	.560	ZRS3C	42	H	
49	124	.07	79	NQS		4	TSH	14.67		TSH	01H	.560	ZRS3C	42	H	

| ROW | COL | VOLTS | DEG | IND | PER | CHN | LOCN | INCH1 | INCH2 | BEGT | ENDT | PDIA | PTYPE | CAL | L | COM |

Indication codes used:
Distorted Dent Indication (DDI)
Dents (DNT)
Indication Not Reportable (INR)
No Defect Found (NDF)
Non-Quantifiable Indication (NQI)
Non-Quantifiable Signal (NQS)