

# NITRONIC 50

**Nitrogen-Strengthened Austenitic Stainless Steel**

## Bar and Wire

- Superior corrosion resistance
- Almost double the yield strength
- Exceptionally low magnetic permeability
- Outstanding cryogenic properties

## Applications Potential

Outstanding corrosion resistance gives NITRONIC 50 Stainless Steel the leading edge for applications where Types 316, 316L, 317 and 317L are only marginal. It's an effective alloy for the petroleum, petrochemical, chemical, fertilizer, nuclear fuel recycling, pulp and paper, textile, food processing and marine industries.

Components using the combination of excellent corrosion resistance and high strength currently include pumps, valves and fittings, fasteners, cables, chains, screens and wire cloth, marine hardware, boat and pump shafting, heat exchanger parts, springs and photographic equipment.

## Page Contents

3	Annealing
3-8	Mechanical properties
9	Galling and wear resistance
9-10	Physical properties
10-15	Corrosion resistance
16	Fabrication
16-17	Welding
18	Machinability

The information and data in this product data bulletin are accurate to the best of our knowledge and belief, but are intended for general information only. Applications suggested for the materials are described only to help readers make their own evaluations and decisions, and are neither guarantees nor to be construed as express or implied warranties of suitability for these or other applications.

Data referring to mechanical properties and chemical analyses are the result of tests performed on specimens obtained from specific locations of the products in accordance with prescribed sampling procedures; any warranty thereof is limited to the values obtained at such locations and by such procedures. There is no warranty with respect to values of the materials at other locations.

Armco, the Armco Triangle, NITRONIC, 17-4PH<sup>®</sup> trademarks of Armco Inc. 22-13-5 is a trademark of Armco Inc.

Nitronic alloys are produced by BSSC under license from Armco Inc.

## Armco NITRONIC 50 Stainless Steel Product Description

Armco NITRONIC 50 Stainless Steel provides a combination of corrosion resistance and strength not found in any other commercial material available in its price range. This austenitic stainless steel has corrosion resistance greater than that provided by Types 316, 316L, 317, and 317L, plus approximately twice the yield strength at room temperature. In addition, Armco NITRONIC 50 Stainless Steel has very good mechanical properties at both elevated and sub-zero temperatures. And, unlike many austenitic stainless steels, NITRONIC 50 does not become magnetic when cold worked or cooled to sub-zero temperatures. High Strength (HS) NITRONIC 50 Stainless Steel has a yield strength about three to four times that of Type 316 stainless steel.

## Composition

	%
Carbon	0.06 max
Manganese	4.00/6.00
Phosphorus	0.040 max
Sulfur	0.030 max
Silicon	1.00 max
Chromium	20.50/23.50
Nickel	11.50/13.50
Molybdenum	1.50/3.00
Nitrogen	0.20/0.40
Columbium	0.10/0.30
Vanadium	0.10/0.30

## Specifications

NITRONIC 50 bar, wire, sheet, plate, forgings and forging billets are covered by the following specifications. It is suggested the issuing agency be contacted for the latest revision of the specification.

Armco NITRONIC 50 Stainless Steel is listed as Grade XM-19 (UNS S20910) in:

- ASTM A314—Bar and Billet
- ASTM A240 — Plate, Sheet and Strip for Fusion Welded Unfired Pressure Vessels
- ASTM A412 — Plate, Sheet and Strip
- ASTM A479 — Bars and Shapes for Use in Boilers and Other Pressure Vessels
- ASTM A276 — Bars and Shapes
- ASTM A580 — Wire
- ASTM A182 — Forged or Rolled Pipe Flanges, Forged Fittings and Valves
- ASTM A193 — Bolting (Grade B8R)
- ASTM A194 — Nuts (Grade 8R)
- ASTM A249 — Welded Superheater, Heat-Exchanger and Condenser Tubes
- ASTM A269 — Seamless and Welded Tubing for General Service
- ASTM A312 — Seamless and Welded Pipe
- ASTM A351 and A743—Castings (Grade CG6MMN)
- ASTM A403 — Wrought Piping, Fittings
- ASTM A358 — Electric Fusion Welded Pipe
- AMS 5764 — Bars, Forgings and Extrusions
- ASME Design Allowables Listed in Table UHA-23 of Section VIII Division 1
- ASME Design Values Listed in Section III Division 1 Appendices
- NACE MR-01-75
- Annealed and High Strength (HS) Conditions Acceptable to a Hardness of Rockwell C35 Max.

In valves and chokes, NITRONIC 50 Stainless Steel may be used for valve shafts, stems and pins in the cold-worked condition provided this cold working is preceded by an anneal.

Other specification coverage is pending. It is suggested that Armco be contacted for information concerning additional coverage.

## Annealing Temperature

Armco NITRONIC 50 Stainless Steel can be supplied annealed at 1950 F to 2050 F (1066 C to 1121 C). For most applications, the 1950 F (1066 C) condition should be selected, as it provides a higher level of mechanical properties along with excellent corrosion resistance. When as-welded material is to be used in strongly corrosive media, the 2050 F (1121 C) condition should be specified in order to minimize the possibility of intergranular attack.

## Metric Practice

The values shown in this bulletin were established in U.S. customary units. The metric equivalents of U.S. customary units shown may be approximate. Conversion to the metric system, known as the International System of Units (SI), has been accomplished in accordance with the American Iron and Steel Institute Metric Practice Guide, 1978.

The newton (N) has been adopted by the SI as the metric standard unit of force as discussed in the AISI Metric Practice Guide. The term for force per unit of area (stress) is the newton per square metre (N/m<sup>2</sup>). Since this can be a large number, the prefix mega is used to indicate 1,000,000 units and the term meganewton per square metre (MN/m<sup>2</sup>) is used. The unit (N/m<sup>2</sup>) has been designated a pascal (Pa). The relationship between the U.S. and the SI units for stress is: 1000 pounds/in<sup>2</sup> (psi) = 1 kip/in<sup>2</sup> (ksi) = 6.8948 mega-newtons/m<sup>2</sup> (MN/m<sup>2</sup>) = 6.8948 megapascals (MPa). Other units are discussed in the Metric Practice Guide.

## Mechanical Properties

Table 1  
Minimum Properties Acceptable for Material Specification  
Annealed Bars

Condition	UTS psi (MPa)	0.2% YS psi (MPa)	Elongation % in 2" (50.8 mm)	Reduction of Area %
Annealed 1950 F (1066 C) to 2050 F (1121 C) and water quenched (up to 144 in <sup>2</sup> {929.0 cm <sup>2</sup> })	100.000 (690)	55.000 (379)	35	55
Over 144 in <sup>2</sup> (929.0 cm <sup>2</sup> ) to 324 in <sup>2</sup> (2091 cm <sup>2</sup> )	95.000 (655)	50.000 (345)	30	45

Table 2  
**Typical Room Temperature Properties\***  
**1" (25.4 mm) Diameter Bar**

Condition	Tensile Properties						Torsional Properties	
	UTS ksi (MPa)	0.2% YS ksi (MPa)	Elong. % in 2" (50.8 mm)	Red. of Area %	Hardness Rockwell	Impact Charpy V-Notch ft-lbs (J)	0.2% Torsional YS ksi (MPa)	Modulus of Rupture ksi (MPa)
Annealed 2050 F (1121 C) plus water quench	120 (827)	60 (414)	50	70	B98	170 (230)	44.5 (307)	114.5 (789)
Annealed 1950 F (1066 C) plus water quench	125 (862)	65 (448)	45	65	C23	130 (176)	55 (379)	120 (827)

\* Average of duplicate tests.

Table 3  
**Typical Short-Time Elevated Temperature Tensile Properties\***

Condition	Test Temperature F (C)	UTS ksi (MPa)	0.2% YS ksi (MPa)	Elongation % in 2" (50.8 mm)	Reduction of Area %
Annealed 1950 F (1066 C) Bars 3/4" to 1-1/4" (19.1 to 31.8 mm) Diameter	75 (24)	124 (855)	78 (538)	40.5	67.5
	200 (93)	112 (772)	66 (455)	40.5	67.5
	400 (204)	102 (703)	58 (400)	37.5	67
	600 (316)	98 (676)	54 (372)	37.5	64
	800 (427)	94 (648)	50 (345)	39.5	63
	1000 (538)	89 (614)	48 (331)	36.5	62.5
	1200 (649)	80 (552)	44 (303)	36.5	63
	1350 (732)	68 (469)	42 (290)	42.5	71.5
Annealed 2050 F (1121 C) Bars 1" to 1-1/2" (25.4 to 38.1 mm) Diameter	1500 (816)	50 (345)	32 (221)	59.5	85
	75 (24)	117 (807)	60 (414)	45	71
	200 (93)	107 (738)	50 (338)	43.5	70.5
	400 (204)	96 (662)	38 (262)	43.5	69.5
	600 (316)	92 (634)	35 (241)	42.5	67.5
	800 (427)	89 (614)	34 (234)	43.5	66
	1000 (538)	84 (579)	32 (221)	41	66.5
	1200 (649)	74 (510)	31 (214)	38	64
1350 (732)	66 (455)	31 (214)	37	61.5	
1500 (816)	52 (359)	30 (207)	41	61	

\* Average of triplicate tests from each of three heats.

Table 4  
**Typical Stress-Rupture Strength\***

Condition	Test Temp. F (C)	Stress for Failure, ksi (MPa)		
		100 Hours	1,000 Hours	10,000 Hours (estimated)
Annealed 1950 F (1066 C) Bars 3/4" to 1-1/4" (19.1 - 31.8 mm) Diameter	1000 (538)	91 (627)	88 (607)	72 (496)
	1100 (593)	72 (496)	62 (427)	47 (324)
	1200 (649)	55 (379)	38 (262)	22 (152)
	1350 (732)	21 (145)	12 (82.7)	6 (41.4)
	1500 (816)	10 (69.0)	3.7 (25.5)	1.3 (9.0)
Annealed 2050 F (1121 C) Bars 1" to 1-1/2" (25.4 - 38.1 mm) Diameter	1000 (538)	—	—	—
	1100 (593)	65 (448)	54 (372)	43 (296)
	1200 (649)	50 (345)	41 (283)	32.5 (224)
	1350 (732)	29 (200)	15 (103)	8.5 (58.6)
	1500 (816)	13 (89.6)	6.5 (44.8)	3.5 (24.1)

\* Average of tests from three heats.

Table 5  
**Typical Creep Strength\***  
**1" (25.4 mm) Diameter Bar**

Condition	Test Temp F (C)	Stress for min Creep Rate, ksi (MPa)	
		.0001% per Hour	.00001% per Hour
Annealed 2050 F (1121 C)	1100 (593)	41 (283)	34.5 (238)
	1200 (649)	22 (152)	16 (110)

\* Tests from one heat.

Table 6  
**Typical Mechanical Properties\***  
**Cold Drawn Wire**

Cold Reduction %	UTS ksi (MPa)	0.2% YS ksi (MPa)	Elongation % in 4 x D	Reduction of Area %
15	165 (1138)	143 (986)	23	56
30	194 (1338)	174 (1200)	15	49
45	216 (1489)	196 (1351)	11	45
60	234 (1613)	216 (1489)	9	42
75	246 (1696)	234 (1613)	8	39

\* Average of duplicate tests.

Starting size: 1/4" (6.35 mm) dia rod annealed at 2050 F (1121 C).

In common with other NITRONIC alloys, NITRONIC 50 Stainless Steel, when cold reduced 60% or more without in-process anneals, will embrittle very rapidly when exposed at temperatures in the range of 800 to 1000 F (426 to 538 C). Therefore, springs made of NITRONIC 50 Stainless Steel should not be given the low-temperature, stress-relief treatment commonly used for austenitic stainless steels.

Table 7  
**Typical Sub-Zero Mechanical Properties\***  
**1" (25.4 mm) Diameter Bar — Annealed 2050 F (1121 C)**

Test Temp. F (C)	UTS ksi (MPa)	0.2% YS ksi (MPa)	Elongation % in 2" (50.8 mm)	Reduction of Area %
-100 (-73)	146 (1007)	85 (586)	49.5	65
-320 (-196)	226 (1558)	128 (883)	41	51

\* Average of duplicate tests

Table 8  
**Typical Impact Strength**  
**1" (25.4 mm) Diameter Bar — Annealed 2050 F (1121 C)**

Test Temp. F (C)	Impact — Charpy V-Notch, ft-lbs (J)	
	Annealed	Simulated HAZ*
75 (24)	170 (230)	170 (230)
-100 (-73)	115 (156)	115 (156)
-320 (-196)	50 (68)	50 (68)

\* Heat treated at 1250 F (677 C) for 1 hour to simulate the heat-affected zone of heavy weldments.

Average of duplicate tests.

Table 9

**Effect of Cold Reduction on Mechanical Properties of Bars**

Diameter Bar in. (mm)	Cold Reduction %	UTS ksi (MPa)	0.2% YS ksi (MPa)	Elongation % 2" (50.8 mm) or 4 x D	Red. of Area %	Hardness Rockwell	Charpy Impact, ft-lbs (J)		
							Test Temperature, F (C)		
							80 (27)	-40 (-40)	-110 (-79)
.750 (19.05)	0	116.6 (804)	57.6 (397)	47.0	70.6	B91	232 (314)	—	—
.750 (19.05)	13	142.5 (982)	126.0 (869)	31.0	67.0	C30	116 (157)	—	—
		141.1 (973)	122.5 (844)	31.0	65.7		115 (156)	—	—
.650 (16.51)	28	157.6 (1086)	153.4 (1058)	21.0	63.8	C34	98 (133)	74 (100)	—
		156.0 (1076)	150.6 (1036)	24.0	63.6		91 (123)	54 (73)	—
.750 (19.05)	46	185.9 (1282)	183.8 (1268)	18.0	57.9	C36	54 (73)	48 (65)	38 (51)
		183.1 (1263)	180.6 (1245)	16.0	57.8		53 (71)	43 (58)	39 (53)

**High Strength (HS)  
Bar Properties**

Armco NITRONIC 50 Stainless Steel bars also are available in a high-strength condition attained by special processing techniques. The superior strength of NITRONIC 50 HS Stainless Steel produced by hot rolling is size-dependent, approaching that of annealed bars with sizes over 3" (76.2 mm) diameter. Because its high strength is produced by mill processing, hot forging, welding or brazing operations cannot be performed on this material without loss of strength. High-strength bars produced by rotary forging—special practice may have somewhat reduced resistance to corrosion and sulfide stress cracking.

Table 10

**Minimum Room Temperature Tensile Properties  
of High-Strength (HS) Bars (Hot Rolled Unannealed)**

Size in (mm)	UTS ksi (MPa)	0.2% YS ksi (MPa)	Elongation or 4 X D	Reduction of Area %	Hardness Brinell	Charpy V-Notch ft-lbs (J)
3/4 to 1-1/4 (17.5 to 31.8)	145 (1000)	130 (896)	18	45	283	80 (108)
Over 1-1/4 to 2 incl. (31.8 to 50.8)	135 (931)	105 (724)	20	50	260	100 (135)
*Over 2 to 2-1/2 (50.8 to 63.5)	120 (827)	95 (655)	20	50	220	100 (135)
Over 2-1/2 to 3 incl.	115 (793)	75 (517)	25	50	210	100 (135)

Table 11

**Torsional Properties of High-Strength (HS) Bars (Hot Rolled Unannealed)  
1-1/4" to 2" (31.7 to 50.8 mm) Diameter, Inclusive\***

	Prop. Limit ksi (MPa)	0.2% YS ksi (MPa)	Modulus of Rupture ksi (MPa)
Typical	65 (448)	100 (690)	140 (965)
Minimum	50 (345)	70 (483)	120 (827)

\* Average of duplicate tests. Properties of material over 2" (50.8 mm) are somewhat lower. Please inquire.

Table 12

**Minimum Properties Acceptable for Material Specification  
High-Strength Bars (Produced by Rotary Forging Special Practice)**

	2½" (63.5 mm) to 6" incl. (152.4 mm)	Over 6" (152.4 mm) to 8½" incl. (215.9 mm)	Over 8½" (215.9 mm) to 9½" incl. (241.3 mm)
UTS, psi (MPa) min.	130,000 (896)	125,000 (862)	120,000 (827)
0.2% YS, psi (MPa) min	110,000 (758)	90,000 (621)	90,000 (621)
Elong. % in 2" (50.8 mm) min	15	20	20
Red. of Area % min	45	50	50
Charpy V-Notch, ft-lbs (J)	100 (135)	100 (135)	100 (135)

Table 13

**Typical Short-Time Elevated Temperature Tensile Properties of High-Strength (HS) Bars\* (Hot Rolled Unannealed)**

Test Temperature F (C)	UTS ksi (MPa)	0.2% YS ksi (MPa)	Elongation % in 2" (50.8 mm)	Reduction of Area, %
75 (24)	150 (1034)	126 (869)	29	64
200 (93)	135 (931)	112 (772)	28	65
400 (204)	124 (855)	101 (696)	27	63.5
600 (316)	117 (807)	93 (641)	27.5	61
800 (427)	111 (765)	86 (593)	28.5	61
1000 (538)	103 (710)	80 (552)	27	60.5
1100 (593)	99 (683)	77 (531)	26	59.5

\* Bars 1" to 2" (25.4 to 50.8 mm) diameter.

Average of triplicate tests from each of three heats.

Table 14

**Typical Stress-Rupture Strength of 1" (25.4 mm) Diameter High-Strength (HS) Bars\* (Hot Rolled Unannealed)**

Test Temp. F (C)	Stress for Failure, ksi (MPa)		
	100 Hours	1,000 Hours	10,000 Hours (est.)
1000 (538)	98 (676)	95 (655)	78 (538)
1100 (593)	85 (586)	66 (455)	51 (352)

\* Average of tests from two heats.

NITRONIC 50 high-strength (HS) bars are not recommended for prolonged use at temperatures above 1100 F (593 C).

Table 15

**Typical Sub-Zero Impact Strength of High-Strength (HS) Bars\* (Hot Rolled Unannealed)**

Test Temp., F (C)	Charpy V-Notch Impact, ft-lbs (J)		
	1" (25.4 mm) dia.	1-1/2" (38.1 mm) dia.	2" (50.8 mm) dia.
80 (27)	126 (171)	150 (203)	148 (201)
-75 (-60)	114 (155)	131 (178)	131 (178)
-200 (-129)	48 (65)	62 (84)	61 (83)
-320 (-196)	31 (42)	41 (56)	36 (49)

\* Average of duplicate tests from two heats of each bar size.

Table 16

**Typical Cryogenic Mechanical Properties of High-Strength (HS) 2" (50.8mm) Bar**

Temperature F (C)	0.2% YS ksi (MPa)	UTS ksi (MPa)	Elongation % in 2" (50.8 mm)	Reduction in Area %
Room	115.5 (796)	142.5 (983)	40.0	65.0
-100 (-73)	136.6 (942)	169.9 (1171)	35.5	66.5
-200 (-129)	152.4 (1051)	189.7 (1308)	28.0	61.0
-250 (-157)	166.9 (1151)	200.4 (1382)	25.5	63.5
-320 (-196)	192.9 (1330)	241.3 (1664)	28.5	*

\* Piece broke from specimen, making accurate determination of final diameter impossible.

## Fatigue Strength

Table 17  
Rotating Beam Fatigue Tests

Condition	Bar Size	Fatigue Strength at 10 <sup>8</sup> Reversals of Stress ksi(MPa)	
		Tested in Air*	Tested in Seawater**
Annealed 2050 F (1121 C)	1" dia (25.4 mm)	42 (290)	22 (152)
Annealed 1950 F (1066 C)	1" dia (25.4 mm)	47 (324)	—
High-Strength (HS) Bars (Hot Rolled Unannealed)	1" dia (25.4 mm)	68 (469)	18 (124)
	2-1/2" dia (63.5 mm)	58 (400)	15 (103)
	4" dia (102 mm)	44 (303)	15 (103)

\* R. R. Moore specimens tested at room temperature.

\*\* McAdam specimens tested in ambient temperature seawater (11-31 C) at LaQue Corrosion Laboratory, Wrightsville Beach, N.C.

Tests from one heat for each size and condition.

## Shear Strength

The shear strength of NITRONIC 50 Stainless Steel in double shear has been determined following Boeing Aircraft Co. D2-2860, Procedures for Mechanical Testing of Aircraft Structural Fasteners. The results, determined from a typical heat, are as shown.

Table 18  
Shear Strength

Condition	UTS ksi (MPa)	Double Shear ksi (MPa)	Shear/Tensile Ratio, %
Annealed 1950 F (1066 C)	126 (869)	86.8 (598)	69
Annealed 2050 F (1121 C)	113 (779)	78.5 (541)	69.5

Average of duplicate tests.

## Elastic Properties

The elastic properties of annealed NITRONIC 50 at room temperature are as shown.

Table 19  
Elastic Properties

Modulus of Elasticity in Tension (E) psi (MPa)	Modulus of Elasticity in Torsion (G) psi (MPa)	Poisson's Ratio
28.9 x 10 <sup>6</sup> (199 x 10 <sup>3</sup> )	10.8 x 10 <sup>6</sup> (74,500)	0.312

Average of duplicate tests.

## Notch Sensitivity

Tensile tests were performed at room temperature using notched specimens with a stress-concentration factor of K<sub>t</sub> = 1.3. The following data at right show Armco NITRONIC 50 Stainless Steel is not notch sensitive.

Table 20  
Elastic Properties at Elevated Temperatures\*

Temperature F (C)	Young's Modulus in Tension		Poisson's Ratio
	psi	(MPa)	
72 (22)	28.9 x 10 <sup>6</sup>	(199 x 10 <sup>3</sup> )	0.312
200 (93)	27.8 x 10 <sup>6</sup>	(192 x 10 <sup>3</sup> )	0.307
300 (149)	27.0 x 10 <sup>6</sup>	(186 x 10 <sup>3</sup> )	0.303
400 (204)	26.1 x 10 <sup>6</sup>	(180 x 10 <sup>3</sup> )	0.299
500 (260)	25.3 x 10 <sup>6</sup>	(174 x 10 <sup>3</sup> )	0.295
600 (315)	24.6 x 10 <sup>6</sup>	(170 x 10 <sup>3</sup> )	0.291
700 (371)	24.0 x 10 <sup>6</sup>	(165 x 10 <sup>3</sup> )	0.288

\*Tests performed on sheet samples in the longitudinal direction using strain gages.

Table 21  
Notch Sensitivity

Condition	UTS — Smooth, ksi (MPa)	UTS — Notched, ksi (MPa)
Annealed 2050 F (1121 C)	114.5 (790)	155 (1069)
Annealed 1950 F (1066 C)	120.5 (830)	—
High-Strength (HS) Bars	151 (1041)	196.5 (1354)

Average of duplicate tests.

## Galling and Wear Resistance

The galling resistance of Armco NITRONIC 50 Stainless Steel is similar to Type 316 or just slightly better.

Metal-to-metal wear tests demonstrate the superiority of NITRONIC 50 over alloy K-500 despite the higher hardness of the latter. Comparative wear data are shown.

For applications requiring superior galling, wear and cavitation resistance coupled with good corrosion resistance, Armco NITRONIC 60 Stainless Steel should be considered.

## Physical Properties

Density at 75 F (24 C)  
7.88 gm/cm<sup>3</sup>  
.285 lbs/in<sup>3</sup>

Electrical Resistivity at 70 F (21 C) — 82 microhm-cm

### Magnetic Permeability

Armco NITRONIC 50 Stainless Steel does not become magnetic when severely cold worked. This characteristic makes the alloy useful for applications requiring a combination of excellent corrosion resistance and low magnetic permeability.

The magnetic permeability of Armco NITRONIC 50 Stainless Steel remains very low at cryogenic temperatures, but not as low as Armco NITRONIC 33 and NITRONIC 40 Stainless Steels. The magnetic susceptibility data in Table 25 were obtained on mill-annealed sheet samples using the Curie Force Method.

Note that the magnetic susceptibility of Armco NITRONIC 50 Stainless Steel exhibits a cusp at approximately -400 F (-240 C). This phenomenon, which

Table 22  
Weight Loss of Couple\*  
mg/1000 cycles

Alloy (Rockwell Hardness)	versus	Alloy K-500 (C34)	NITRONIC 50 (C28)	Type 316	NITRONIC 60 (B95)
Type 316 (B91)		33.78	10.37	12.51 (B91)	4.29
17.4 PH (C43)		34.08	12.55	18.50 (B91)	5.46
Cobalt Alloy 6B (C48)		18.78	3.26	5.77 (B72)	1.85
Type 431 (C42)		26.40	6.73	5.03 (B72)	3.01
Ti-6Al-4V (C36)		17.19	6.27	6.31 (B72)	4.32
Alloy K-500 (C34)		30.65	34.98	33.78 (B91)	22.87
NITRONIC 50 (C28)		34.98	9.37	10.37 (B72)	4.00
NITRONIC 60 (B95)		22.87	4.00	4.29 (B91)	2.79

\* Test Conditions: Taber Met-Abrader machine, .500"  $\emptyset$  crossed (90°) cylinders, dry, 16-lb load, 105 RPM, room temperature, 120 grit surface finish, 10,000 cycles, degreased, duplicates, weight loss corrected for density differences

Table 23  
Cavitation Resistance of Annealed NITRONIC 50 Stainless Steel

Alloy	Weight Loss mg*
NITRONIC 50	30
Type 316	100

\* Data provided by outside laboratory per ASTM G32 Test Method.

Table 24  
Wire\*

Condition	Typical Magnetic Permeability at Field Strength of		
	50 Oer. (3978 A/m)	100 Oer. (7957 A/m)	200 Oer. (15,914 A/m)
Annealed	1.004	1.004	1.004
Cold Drawn 27%	1.004	1.004	1.003
Cold Drawn 56%	1.004	1.004	1.004
Cold Drawn 75%	1.004	1.004	1.004

\* Average of duplicate tests.

Table 25

Temperature F (C)	Magnetic Mass Susceptibility, $\chi$ , $10^{-6} \text{ cm}^3 \text{ g}^{-1}$	Typical Magnetic Permeability, $\mu$
72 (22)	21.5	1.0021
-9 (-23)	22.5	1.0022
-99 (-73)	25	1.0025
-189 (-123)	28.5	1.0028
-279 (-173)	35.5	1.0035
-369 (-223)	54	1.0053
-400 (-240)	74	1.0073
-432 (-258)	61	1.0060

Reference: *Advances in cryogenic Engineering Materials*, Vol. 26 (1980), pp. 37-47.

also occurs with Armco NITRONIC 33 and NITRONIC 40 Stainless Steels, is dependent on temperature but not on field strength. Unlike the AISI 300 series stainless steels, most Armco NITRONIC Alloys show no supermagnetism.

## Coefficient of Thermal Expansion

Table 26

### Coefficient of Thermal Expansion Annealed Material\*

Temperature Range F (C)	Coefficient of Thermal Expansion microinches/in/°F, (μm/m•K)	
70-200 (21-93)	9.0	(16.2)
70-400 (21-204)	9.2	(16.6)
70-600 (21-316)	9.6	(17.3)
70-800 (21-427)	9.9	(17.8)
70-1000 (21-538)	10.2	(18.4)
70-1200 (21-649)	10.5	(18.9)
70-1400 (21-760)	10.8	(19.4)
70-1600 (21-871)	11.1	(20.0)

\* Average of duplicate tests.

Table 27

### Thermal Contraction

Temperature F (C)	Contraction Parts Per Million (ppm)	Mean Expansion Coefficient Between T and 75 F (24 C)	
		ppm/°F	ppm/°C
-41 (-41)	948	8.17	14.61
-51 (-46)	1016	8.06	14.53
-60 (-51)	1074	7.95	14.34
-80 (-62)	1237	7.98	14.40
-100 (-73)	1398	7.99	14.43
-125 (-87)	1560	7.80	14.07
-150 (-101)	1723	7.66	13.80
-178 (-117)	1951	7.71	13.84
-200 (-129)	2079	7.56	13.60
-225 (-143)	2231	7.44	13.37
-260 (-162)	2333	6.96	12.55
-320 (-196)	2542	6.44	11.56

## Thermal Conductivity

Table 28

Temperature F (C)	Thermal Conductivity*	
	BTU/hr/ft <sup>2</sup> /in/°F	(W/m•K)
70 (21)	—	—
300 (149)	108	(15.6)
600 (316)	124	(17.9)
900 (482)	141	(20.3)
1200 (649)	160	(23.0)
1500 (816)	175	(25.2)

\* Average of duplicate tests.

## Corrosion Resistance

Armco NITRONIC 50 Stainless Steel provides outstanding corrosion resistance — superior to Types 316, 316L, 317 and 317L in many media. For many applications the 1950 F (1066 C) annealed condition provides adequate corrosion resistance and a higher strength level. In very corrosive media or where material is to be used in the as-welded condition, the 2050 F (1121 C) annealed condition should be specified. High-Strength (HS) NITRONIC 50 bars are useful for applications such as shafting and bolting, but do not quite exhibit the corrosion resistance of the annealed conditions in all environments.

Typical corrosion rates obtained from laboratory tests on NITRONIC 50 Stainless Steel in its several conditions are shown in Table 29 along with comparable data for Types 316, 316L, 317 and 317L stainless steels.

Table 29

**Laboratory Corrosion Test Data**

Test Medium	Corrosion Rates in Inches per Year (IPY) Unless Otherwise Indicated <sup>(1)</sup>				
	NITRONIC 50 Bar Annealed 1950 F (1066 C)	NITRONIC 50 Bar Annealed 2050 F (1121 C)	NITRONIC 50 High-Strength (HS) Bar <sup>(3)</sup>	Types 316 & 316L Annealed Bar	Types 317 & 317L Annealed Bar
10% FeCl <sub>3</sub> , 25 C — plain <sup>(2)</sup>	<.001 g/in <sup>2</sup>	<.001 g/in <sup>2</sup>	<.001 g/in <sup>2</sup>	.011 g/in <sup>2</sup>	—
10% FeCl <sub>3</sub> , 25 C — creviced <sup>(2)</sup>	<.001 g/in <sup>2</sup>	<.001 g/in <sup>2</sup>	<.001 g/in <sup>2</sup>	.186 g/in <sup>2</sup>	—
1% H <sub>2</sub> SO <sub>4</sub> , 80 C	<.001	<.001	<.001	0.002	<.001
2% H <sub>2</sub> SO <sub>4</sub> , 80 C	<.001	<.001	<.001	0.011	<.001
5% H <sub>2</sub> SO <sub>4</sub> , 80 C	<.001	<.001	<.001	0.060	0.036
10% H <sub>2</sub> SO <sub>4</sub> , 80 C	—	0.028	—	0.10	0.049
20% H <sub>2</sub> SO <sub>4</sub> , 80 C	—	0.133	—	0.48	0.155
1% H <sub>2</sub> SO <sub>4</sub> , Boiling	—	0.027	—	—	0.013
2% H <sub>2</sub> SO <sub>4</sub> , Boiling	—	0.064	—	0.12	0.027
5% H <sub>2</sub> SO <sub>4</sub> , Boiling	.194	0.131	0.296	0.26	0.093
10% H <sub>2</sub> SO <sub>4</sub> , Boiling	—	0.356	—	0.73	0.465
20% H <sub>2</sub> SO <sub>4</sub> , Boiling	—	1.64	—	2.20	1.30
1% HCl, 35 C	<.001	<.001	<.001	0.012	0.002
2% HCl, 35 C	0.024	<.001	0.027	0.021	0.023
1% HCl, 80 C	—	<.001	0.239	—	0.148
2% HCl, 80 C	—	0.439	0.452	—	0.263
65% HNO <sub>3</sub> , Boiling	0.010	0.007	—	0.012	0.012
70% H <sub>3</sub> PO <sub>4</sub> , Boiling	0.203	0.154	—	0.202	0.201
33% Acetic Acid, Boiling	<.001	<.001	<.001	<.001	<.001
20% Formic Acid, Boiling	—	<.001	—	0.027	—
40% Formic Acid, Boiling	—	0.032	—	0.034	—
10% HNO <sub>3</sub> + 1% HF, 35 C	—	0.007	—	0.064	—
10% HNO <sub>3</sub> + 1% HF, 80 C	—	0.069	—	0.442	—

<sup>(1)</sup>Immersion tests performed on 5/8" dia. x 5/8" (15.9 x 15.9 mm) long machined cylinders. Results are average of five 48-hour periods. Specimens tested at 35 C and 80 C were intentionally activated for third, fourth, and fifth periods. Where both active and passive conditions occurred, only active rates are shown.

<sup>(2)</sup>Exposure for 50 hours with rubber bands on some specimens to produce crevices.

<sup>(3)</sup>Corrosion rates for hot rolled bars. For other mill products, contact Armco.

Table 30

**Laboratory Corrosion Test Data\***  
**Cast NITRONIC 50**

Test Medium	NITRONIC 50 As-Cast	NITRONIC 50 Cast + Annealed 2050 F (1121 C)
10% FeCl <sub>3</sub> — Uncreviced 50 hrs., Room Temperature	—	<.001 g/in <sup>2</sup>
10% FeCl <sub>3</sub> — Crevices 50 hrs., Room Temperature	—	.029 g/in <sup>2</sup>
5% H <sub>2</sub> SO <sub>4</sub> , 80 C	95 MPY	81 MPY
5% H <sub>2</sub> SO <sub>4</sub> , Boiling	—	418 MPY
1% HCl, 35 C	<1 MPY	<1 MPY
70% H <sub>3</sub> PO <sub>4</sub> , Boiling	—	83 MPY

\* All tests performed on 5/8" (15.9 mm) diameter x 5/8" (15.9 mm) long machined cylinders. Except for the ferric chloride tests, all results are the average of five 48-hour periods. Specimens tested at 35 C and at 80 C were intentionally activated for the third, fourth, and fifth periods. Where both active and passive periods occurred, only active rates are shown.

## Intergranular Attack

The resistance of Armco NITRONIC 50 Stainless Steel to intergranular attack is excellent even when sensitized at 1250 F (675 C) for one hour to simulate the heat-affected zone of heavy weldments. Material annealed at 1950 F (1066 C) has very good resistance to intergranular attack for most applications. However, when thick sections of Armco NITRONIC 50 Stainless Steel are used in the as-welded condition in certain strongly corrosive media, the 2050 F (1121 C) condition gives optimum corrosion resistance. This is illustrated by Table 32.

## Stress-Corrosion Cracking Resistance

In common with most stainless steels, under certain conditions, Armco NITRONIC 50 Stainless Steel may stress-corrosion crack in hot chloride environments. When tested in boiling 42% MgCl<sub>2</sub> solution, a very accelerated test, NITRONIC 50 Stainless Steel is between types 304 and 316 stainless steels in resistance to cracking. There is little difference in susceptibility to cracking whether in the annealed, high-strength (HS), or cold-drawn conditions. This is illustrated by the comparative data in Table 33 using the direct-loaded tensile-type test method (described in detail in ASTM STP 425, September 1967). Note that this is a severe test, especially at these temperatures. For marine applications, the following better reflects the resistance of NITRONIC 50 Stainless Steel:

Table 31

### Intergranular Corrosion Resistance of Cast NITRONIC 50

Huey Test, IPM		% Ferrite
Annealed*	Sensitized**	
0.0005	0.0006	Nil
0.0004	0.0015	4

\*2050 F (1121 C) - 1/2-Hour - Water Quenched

\*\*2050 F (1121 C) - 1/2-Hour - Water Quenched + 1250 F (677 C) - 1/2-Hour - Air Cooled.

Even sensitized cast NITRONIC 50 Stainless Steel has an acceptable intergranular corrosion rate less than 0.0020 IPM with up to 4% ferrite present.

Table 32

### Intergranular Attack Resistance of NITRONIC 50 Bar per ASTM A262

Condition	Practice B Ferric Sulfate	Practice E Copper-Copper Sulfate
Annealed 1950 F (1066 C)	0.0010 IPM	Passed
Annealed 1950 F (1066 C) + 1250 F (677 C) - 1 hr. - A.C.	0.0038 IPM	Passed
Annealed 2050 F (1121 C)	0.0009 IPM	Passed
Annealed 2050 F (1121 C) + 1250 F (677 C) - 1 hr. - A.C.	0.0022 IPM	Passed
High-Strength (Bar Mill)	0.0031 IPM	Passed
High-Strength (PRF) Edge	0.0013 IPM	Passed
Intermediate Center	0.0012 IPM 0.0011 IPM	Passed Passed

Table 33

### Boiling MgCl<sub>2</sub>

Alloy	Condition	Time to Failure, Hours Under Stress of		
		75 ksi (517 MPa)	50 ksi (345 MPa)	25 ksi (172 MPa)
Type 304	Annealed	0.2	0.3	0.8
Type 316	Annealed	0.8	2.5	7.0
NITRONIC 50	Annealed	0.4	1.2	5.0
NITRONIC 50	High-Strength	1.2	1.5	6.0
NITRONIC 50	Cold Drawn	1.2	2.6	3.3

U-bend-type stress corrosion test specimens of NITRONIC 50 in the following metallurgical conditions have been exposed to marine atmosphere on the 80' lot at Kure Beach, N.C.

(1) Mill Annealed 1950 F (1063 C)

(2) Mill Annealed & Sensitized 1250 F (675 C)

(3) Cold Rolled 44% (160 ksi yield strength)

Tests were begun on June 3, 1970. No failure occurred after 15 years exposure.

## Sulfide Stress Cracking

Both laboratory tests and field service experience show that Armco NITRONIC 50 Stainless Steel has excellent resistance to sulfide stress cracking in all conditions. NITRONIC 50 Stainless Steel in both the annealed and high-strength (hot-rolled) conditions has been included in the 1988 revision of NACE Standard MR-01-75, "Sulfide Stress Cracking Resistant Material for Oil Field Equipment," at hardness levels up to RC35 maximum. The cold-worked condition to RC35 maximum also is acceptable in valves

and chokes for valve shafts, stems and pins, provided this cold working is preceded by an anneal.

Table 34 illustrates the resistance of Armco NITRONIC 50 Stainless Steel to cracking in laboratory tests in synthetic sour-well solution (5% NaCl + 1/2% acetic acid, saturated with H<sub>2</sub>S). Comparable data are included for Armco 17-4 PH Stainless Steel, which is considered acceptable by NACE for use in sour-well service in the two heat-treated conditions shown.

Table 34  
Resistance to Sulfide Stress Cracking<sup>(1)</sup>

Alloy	Condition	Hardness Rockwell	0.2% YS ksi (MPa)	Time to Failure, hr., Under Stress, ksi (MPa)						
				150 (1034)	140 (965)	125 (862)	100 (690)	75 (517)	50 (345)	25 (172)
NITRONIC 50	Annealed 1950 F (1066 C)	C22	67 (448)	—	—	—	>1000	>1000	>1000	—
NITRONIC 50	High-Strength (HS) <sup>(3)</sup> 1" (25.4 mm) dia.	C33	135 (931)	—	204	320	>1000	>1000	—	—
NITRONIC 50	High-Strength (HS) <sup>(3)</sup> 1" (25.4 mm) dia.	C35	146 (1007)	—	358	—	—	—	—	—
NITRONIC 50	High-Strength (HS) <sup>(3)</sup> 1" (25.4 mm) dia.	C36	144 (993)	170 <sup>(2)</sup>	>1000	>1000	>1000	—	—	—
NITRONIC 50	Cold Drawn 3/8" (9.5 mm) dia.	C41	160 (1103)	>1000	—	—	>1000	—	—	—
17-4 PH	H 1150+ 1150	C32.5	110 (758) est.	—	—	—	—	9.5	16	225
17-4 PH	H 1150-M	C29	85 (586)	—	—	—	—	13.5	29	850

<sup>(1)</sup> Longitudinal tensile specimens tested according to NACE TM 01-77

<sup>(2)</sup> Ductile creep failure.

<sup>(3)</sup> For hot rolled bars only.

NITRONIC 50 Stainless Steel spring temper wire coiled into a spring was exposed to the NACE solution at room temperature under the following conditions:

Table 35

Condition	Wire UTS ksi (MPa)	Applied Stress ksi (MPa)	Hrs to Failure
Cold Drawn Wire Wound into a Helical Spring	282 (1944)	100 (689)	> 1584(discontinued)


## Seawater Resistance

Here is how NITRONIC 50 High-Strength (HS) shafting and Alloy 400 (Ni-Cu) looked after 18 months' exposure in quiet seawater off the coast of North Carolina. The test was conducted without zinc anodes to establish the relative corrosion resistance of NITRONIC 50 High-Strength (HS) shafting. Had zinc anodes been used or a bronze propeller fitted to these bars, no crevice corrosion should have occurred. The photograph was taken after barnacles and other forms of marine life were cleared from the test bars.

Before exposure, all specimens were polished to 120 grit finish, degreased and passivated. They were then clamped into pepperwood racks and exposed fully immersed in seawater. NITRONIC 50 high-strength (HS) shafting showed no crevice attack under the wooden blocks after the 18 months. One bar of NITRONIC 50 high-strength (HS) shafting remained perfect, while the other showed a few areas of very light crevice attack,  $<.001"$  (0.025 mm) deep under marine attachments. Both samples of Alloy 400 suffered shallow crevice attack  $.001"$ -. $.003"$  (0.025-0.076 mm) deep under the area in contact with the wooden rack, and also under numerous attached barnacles.

Type 316 stainless steel tested similarly for nine months suffered random pitting and crevice corrosion under the area in contact with the wooden rack and also under marine attachments, while NITRONIC 50 again remained in perfect condition. These specimens are shown in the photograph.

## NITRONIC 50

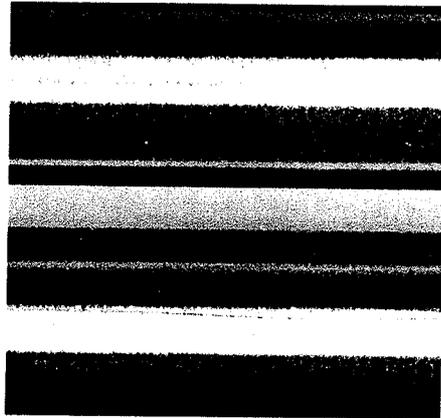


Wood Block

## Alloy 400 (Ni-Cu)



Wood Block

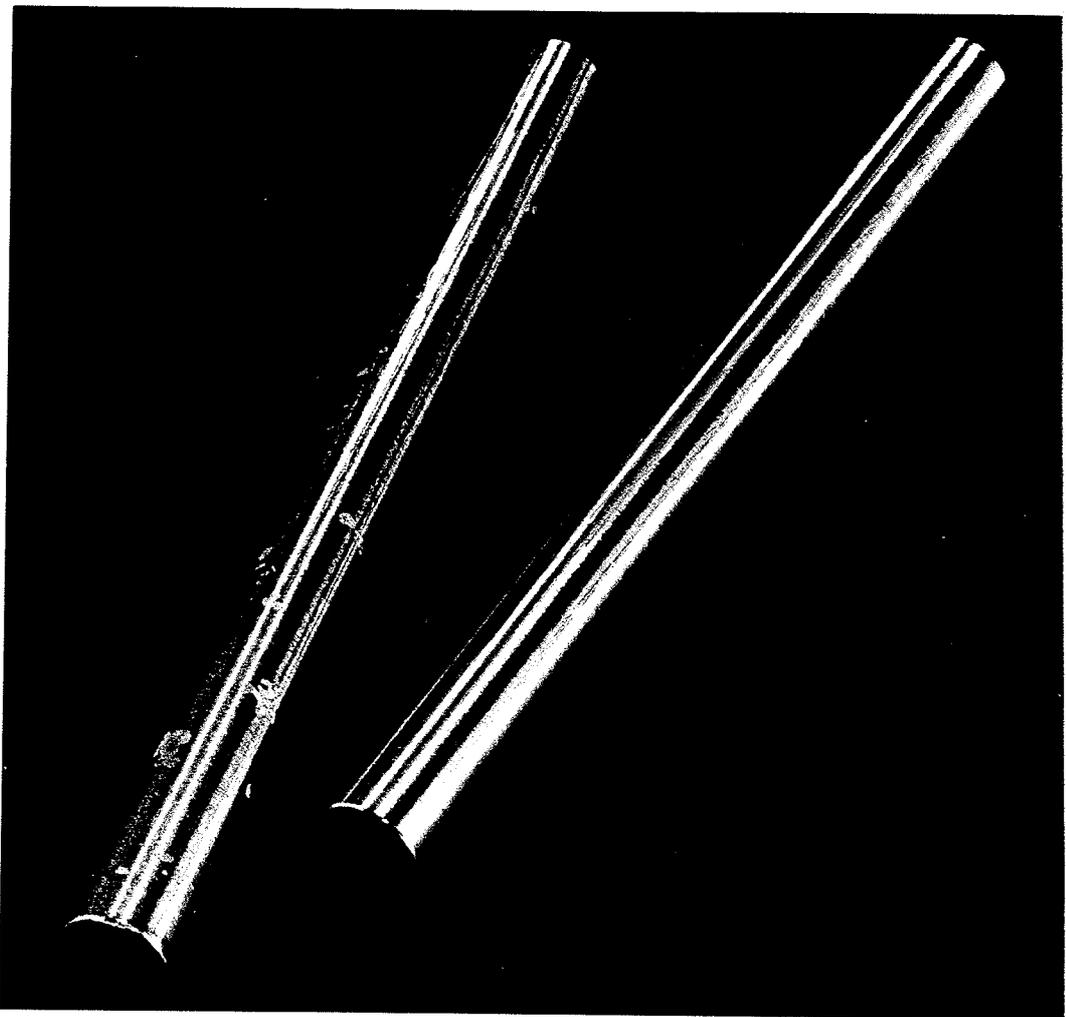

These two bars are immersed in quiet seawater for nine months. Bright shiny bar at right is Armco NITRONIC 50 stainless steel, and at left is Type 316 stainless steel showing considerable pitting and crevice corrosion.

## Salt Fog — Marine Environment

No change was apparent in NITRONIC 50 Stainless Steel in any condition after exposure to 5% NaCl fog at 35 C for 500 hours, or after exposure to marine atmospheres on the 800-foot (24.4m) lot at Kure Beach, North Carolina, for 7½ years. Similar exposure to marine atmospheres produces light staining on Type 316 stainless steel.

## Food Handling

Armco NITRONIC 50 Stainless Steel is considered suitable for food contact use. The National Sanitation Foundation includes Armco NITRONIC 50 Stainless Steel in their "List of Acceptable Materials for Food Contact Surfaces."

## Polythionic Acid Resistance


Polythionic acids are of the general formula  $H_2S_xO_6$ , where x is usually 3, 4 or 5. These acids can form readily in petroleum refinery units, particularly desulfurizers, during shutdown.

Stressed U-bend specimens of NITRONIC 50 stainless, in both the annealed condition and after sensitizing at 1250 F (677 C) for 1 hour, showed no trace of cracking after exposure to polythionic acids for 500 hours at room temperature.

## Pitting Resistance



These pieces of bar were all exposed to 10% ferric chloride solution for 50 hours at room temperature. A rubber band was placed around each to promote crevice corrosion which sometimes occurs in areas where the surface is shielded from oxygen. From left to right, they are Armco NITRONIC 50 Stainless Steel, Type 316 stainless steel and Type 304 stainless steel. Only Armco NITRONIC 50 stainless is still bright and shiny. The Type 316 and Type 304 stainless steels are badly pitted and show severe crevice corrosion in the area where the rubber bands were placed.

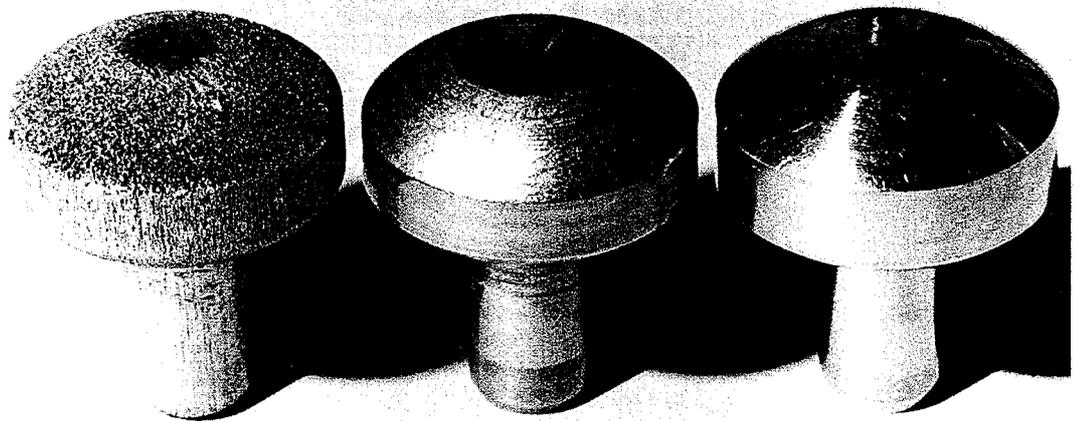

Type 304

Type 316

NITRONIC 50

## Urea Production

Ammonium carbamate — an intermediate produced during the manufacture of urea — is extremely corrosive to process equipment. Pump parts in the process are subjected to a combination of severe corrosive attack, high temperatures and cyclical operating pressures ranging up to 3000 psi. Some parts made of Type 316L stainless steel have shown surface attack in just a few months.

A manufacturer of special valves tested three stainless steels in ammonium carbamate. As shown in the

photograph, Type 304 stainless steel became severely etched in two weeks and Type 316 stainless steel showed some corrosive attack in all exposed areas after six weeks. Armco NITRONIC 50 Stainless Steel remained unaffected after six weeks' exposure to this aggressive medium.

Armco NITRONIC 50 Stainless Steel is presently being specified for the blocks, plungers and related parts of reciprocating pumps when service requires handling ammonium carbamate or other corrosive materials.

## Fabrication

Although Armco NITRONIC 50 Stainless Steel is considerably stronger than the conventional 300 series stainless steels, the same fabricating equipment and techniques can be used.

## Forging

NITRONIC 50 Stainless Steel is readily forged like Type 316 stainless steel, except that it requires more power and the temperature is 2150 F to 2250 F (1177 C to 1232 C).

## Annealing

Like other austenitic stainless steels, NITRONIC 50 must be rapidly cooled. In-process anneals to facilitate cold forming should be done at 2050 F (1066 C). Please note Page 3.

Table 36

**Nominal Composition and Typical Mechanical Properties of Several Austenitic All-Weld-Metal Deposits**

Alloy Type	Nominal Composition, Weight %						Typical Mechanical Properties		
	C	Mn	Cr	Ni	Others		UTS ksi (MPa)	0.2% YS ksi (MPa)	Elong. %
					Mo	N			
AWS 308L	0.04 max	1.0 2.5	19.5 22.0	9.0 11.0	—		85 (586)	55 (379)	45
AWS 309	0.15 max	1.0 2.5	22.0 25.0	12.0 14.0	—		90 (621)	55 (379)	40
AWS 312	0.15 max	1.0 2.5	28.0 32.0	8.0 10.5	—		110 (758)	80 (552)	30
Armco NITRONIC 50W (AWS E 209)	0.05	4.0	20.5	9.5	1.5	.10	110 (758)	85 (586)	20
	max	7.0	24.0	12.0	3.0	.30			
INCONEL 182	0.10	5.0	13.0	Bal.	6.0	1.0	85 (586)	55 (379)	40
	max	9.5	17.0		10.0	2.5			

## Welding

In addition to the improved mechanical properties and corrosion resistance, Armco NITRONIC 50 Stainless Steel can be welded successfully by using any of the conventional welding processes that are normally employed with the austenitic stainless steels.

Armco NITRONIC 50 Stainless is readily arc welded in all forms. As with most austenitic stainless steels, good weld joint properties can be obtained without the necessity of preheat or post-weld annealing. Good shielding of the molten weld puddle is important to prevent any absorption of nitrogen from the atmosphere that could result in porosity.

Autogenous, high-power density joining processes such as electron beam (EB) and laser welding should be used with caution due to the low FN potential of the base metal (FN approximately 2). Field reports also indicate the possibility of severe outgassing during EB welding in a vacuum atmosphere. Under vacuum conditions, this outgassing is to be expected for liquid weld metal containing a high nitrogen level.

## Filler Metals

Filler metal, when added to the joint, should be Armco NITRONIC 50W (AWS E/ER 209), a matching filler metal composition that provides comparable strength and corrosion resistance to the base metal. However, sound weld joints may also be obtained using the conventional austenitic stainless steel fillers such as Types 308L and 309. When using these more common filler metal compositions, allowances should be made for the strength and corrosion differences.

Nominal compositions and representative mechanical properties are shown for the more common electrode filler rods in Table 36. The weld metal alloys are listed generally in the order of (a) increasing alloy content, (b) increasing strength level, (c) increasing corrosion resistance and (d) increasing cost.

These data show that the highest strength levels with good tensile ductility and alloy elements that impart good corrosion resistance are provided by the Armco NITRONIC 50W Electrode. In some specific applications where the high strength

levels or superior corrosion resistance in the weld deposits are not required, other filler metals can be used to advantage because of reduced costs and/or ready availability.

The matching weld filler (NITRONIC 50W, AWS E/ER 209) for Armco NITRONIC 50 Stainless Steel is similar to many of the regular austenitic stainless steel filler metals in that a small percentage of the magnetic ferrite phase has been introduced to assure sound weld deposits. The small quantity of the second phase usually produces a magnetic permeability value of approximately 1.2 in shielded metal-arc weld deposits. This corresponds to a ferrite number (FN) of approximately 6.

Highly overalloyed Ni base fillers are suggested for applications requiring high resistance to pitting media or very low as-deposited magnetic permeability.

### GTA Weld Joints

Gas tungsten arc weld joints have been fused successfully in several flat-rolled thicknesses of Armco NITRONIC 50 Stainless Steel. Mechanical property values similar to those of the base metal have been obtained in the as-welded condition.

The corrosion resistance of GTA welded joints has been evaluated using the standard Huey test (ASTM A 262, Practice C) for detecting intergranular attack in stainless steels. Laboratory test experience shows that welds made using the NITRONIC 50W Stainless Steel filler metal exhibit the same resistance to intergranular attack as the base metal.

Table 37

### Typical Mechanical Properties Armco NITRONIC 50 Stainless Plate Weld Joints

Weld Process	Weld Filler	UTS ksi (MPa)	0.2% YS ksi (MPa)	Elong. % in 2"	Red. in Area, %	Failure Location
Shielded Metal Arc (SMA)	NITRONIC 50W	113 (779)	76 (524)	20	36	Weld Metal
Gas Metal Arc (GMA) Spray	NITRONIC 50W	112 (772)	77 (531)	21	30	Weld Metal

### Heavy Section Weld Joint Properties

The mechanical properties of welds in 1-1/4" (32.1 mm) thick plate have been determined using two weld processes that are normally employed in heavy section welding, namely, (a) shielded metal arc (SMA) or stick electrode welding and (b) gas metal arc (GMA) or MIG welding with the spray mode. Typical test values that can be expected from tensile samples cut transverse to the weld centerline are shown in Table 37.

Heat input is important in obtaining the most satisfactory weld joint. Narrow stringer beads rather than a wide "weave" technique should be used for highest weld ductility. Good shielding of the molten puddle is important to eliminate additional nitrogen from the atmosphere that could cause porosity. Both stringer beads and adequate shielding are normal factors in good stainless steel welding practice.

### Resistance Welding

Although no direct resistance welding experience has been obtained with Armco NITRONIC 50 Stainless Steel, the similarity of the alloy to Armco NITRONIC 40 Stainless Steel suggests a good response to resistance spot welding and cross-wire welding techniques. The welding schedules outlined in the fabricating bulletin, "Welding Armco Stainless Steels," can be used as a guide to produce sound, high-strength joints in both annealed and cold-reduced sheet. Average shear strength data for spot welded joints in Armco NITRONIC 40 Stainless Steel appear in the Product Data Bulletin, "Armco NITRONIC 40 Stainless Steel Sheet and Strip." Armco NITRONIC 50 Stainless Steel is expected to perform in a similar manner.

For more specific suggestions and for NITRONIC 50W filler metal sources, contact Baltimore Specialty Steels Corporation.

# Machinability

Armco NITRONIC 50 Stainless Steel has machining characteristics similar to other austenitic stainless steels. It is suggested that *coated carbides* be considered when machining all NITRONIC alloys, since higher cutting rates may be realized. NITRONIC 50 Stainless Steel is more susceptible to cold work hardening than types 304 and 316 stainless steels. Also, the alloy has higher strength. Machining tests show the alloy to machine at approximately 21% of the cutting rate for B1112. This means NITRONIC 50 Stainless Steel can be machined at approximately 1/2 the cutting rate (SFM) used for Type 304 or 316 stainless steels, based on using high-speed tool steels. For that reason, as stated above, *coated carbides* are recommended for best results.

Because of the high strength of NITRONIC 50 Stainless Steel, more rigid tool and work holders than used for Types 304 and 316 stainless steels should be used. Care should be taken not to allow tools to slide over the alloy. Positive cutting action should be initiated as soon as possible. The alloy provides a good surface finish.

Table 38

## Machinability\*

AISI B 1112	Type 304	Armco NITRONIC 50
100%	45%	21%

\*1"  $\phi$  (25.4 mm)—annealed—R<sub>B</sub> 95  
 Five-hour form tool life using high-speed tools  
 Data based on duplicate tests

Table 39

## Recommended Machining Rates for NITRONIC 50

Machining Operation	Cutting Rates, SFM
Automatic Screw Machine	40-65
Heavy duty Single or Multiple Spindle and Turret Lathe	40-65
High Speed Tools. Rates may be increased 15-30% with High-Cobalt or Cast Alloys	
Automatic Screw Machine (Swiss Type)	40-65
Cast Alloy or Carbide Tools	
Single Point Turning	
Carbide Tools	
Roughing	90-140
Finishing	120-190
High Cobalt or Cast Alloy Tools	
Roughing	50-65
Finishing	50-75
High-Speed Steel Tools	
Roughing	30-45
Finishing	50-60
Milling (When using end mills, use two-fluted type and shorten it 25%)	20-40
Reaming	
Smooth Finish	15-40
Work Sizing	40-60
High-speed steel reamers. Greatly increased rates obtainable with carbide tooling.	
Threading and Tapping	10-25
Drilling	30-50
High-Speed Drills	

## Castings

Armco NITRONIC 50 Stainless Steel may be readily cast by all conventional techniques. Castings should be annealed at 2050F (1121 C) for 1/2-hour and water quenched in order to attain a high level of corrosion resistance. Cast NITRONIC 50 Stainless Steel is listed as Grade CG6MMN in ASTM A 351/351M and A 743.

Table 40

### Typical Room Temperature and Short-Time Elevated Temperature Properties of Cast NITRONIC 50 Stainless Steel (CG6MMN) Annealed\*

Text Temperature F (C)	UTS ksi (MPa)	0.2% YS ksi (MPa)	Elongation % in 2" (50.8 mm)	Reduction %
75 (24)	93 (641)	50 (345)	48	46
200 (93)	84 (579)	39 (269)	47	57
400 (204)	74 (510)	30 (207)	50	54
600 (316)	67 (462)	27 (186)	49	48
800 (427)	65 (448)	27 (186)	47	55
1000 (538)	60 (414)	25 (172)	46	51
1200 (649)	54 (372)	24 (166)	43	55

\*Average of three heats, two tests per heat. Data supplied by Wisconsin Centrifugal, Inc.

For further information please do not hesitate to contact your AK Steel sales-office:



**AK Steel GmbH**  
**Sedanstr. 37**  
**D-50668 Koeln**

Contact: Thomas Wolter

Phone: +49-221-97352-19

Fax: +49-221-97352-10

E-mail: [wolter@aksteel.de](mailto:wolter@aksteel.de)