




Review of Key Aspects of the FAVOR Model Relevant to Small Surface Breaking Flaws

Mark Kirk, Josh Kusnick, and Mike Benson
*United States Nuclear Regulatory Commission
Office of Nuclear Regulatory Research
Division of Engineering, Component Integrity Branch
mark.kirk@nrc.gov*

Appendix G Periodic Meeting
NRC Headquarters
June 24th 2013

- Prediction of crack initiation / propagation from shallow surface flaws in the cladding may be influenced by aspects of the FAVOR model
 - CTE mismatch
 - *Addressed previously*
 - HAZ toughness not modeled
 - If the crack initiates it is modeled to instantly run long and then run deep
- This presentation reviews the adequacy and appropriateness of these latter two aspects of the FAVOR model

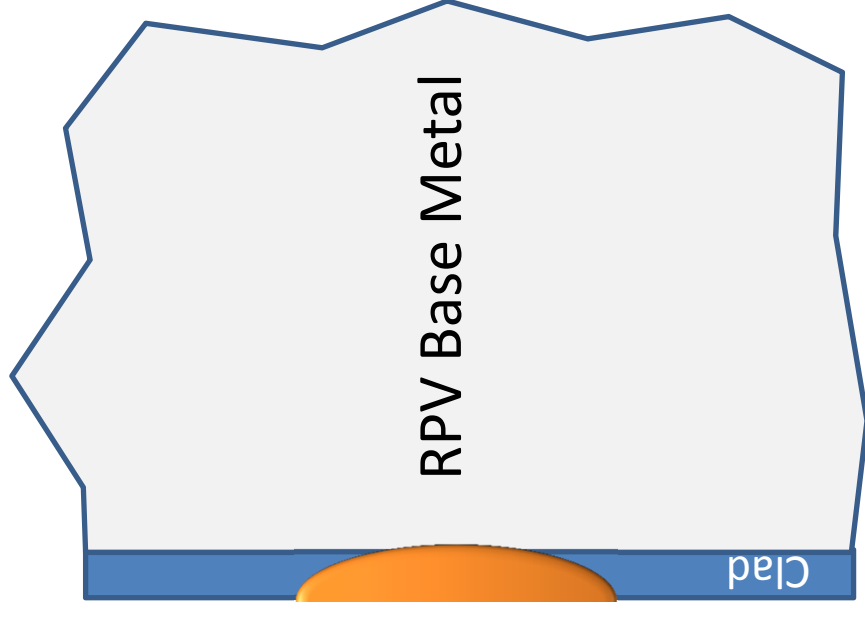

Key References

- HAZ Toughness, or closely related measures
 - Of structural welds
 - Troyer & Erickson, 2013
 - Of clad welds
 - McCabe, 1985-88
 - Iskander, 1992
 - Todeschini, 2013
- Crack / cladding / HAZ interaction behavior
 - Iskander, 1992
 - Clad beams
 - Cheverton, 1990
 - Thermal shock experiments
 - Dickson, 1999
 - Analysis

Many more citations reviewed, these were the most pertinent.


HAZ of Structural Welds

Troyer & Erickson, 2013



United States Nuclear Regulatory Commission
Protecting People and the Environment


- Comprehensive summary based on USA surveillance testing
 - Data from PR-EDB
- HAZ T_{30} values compared with T_{30} values for companion plate or forging
- Key findings
 - T_{30} of HAZ < T_{30} of plate or forging in virtually all cases
 - Embrittlement behavior (ΔT_{30}) of HAZ, plates, and forgings very similar

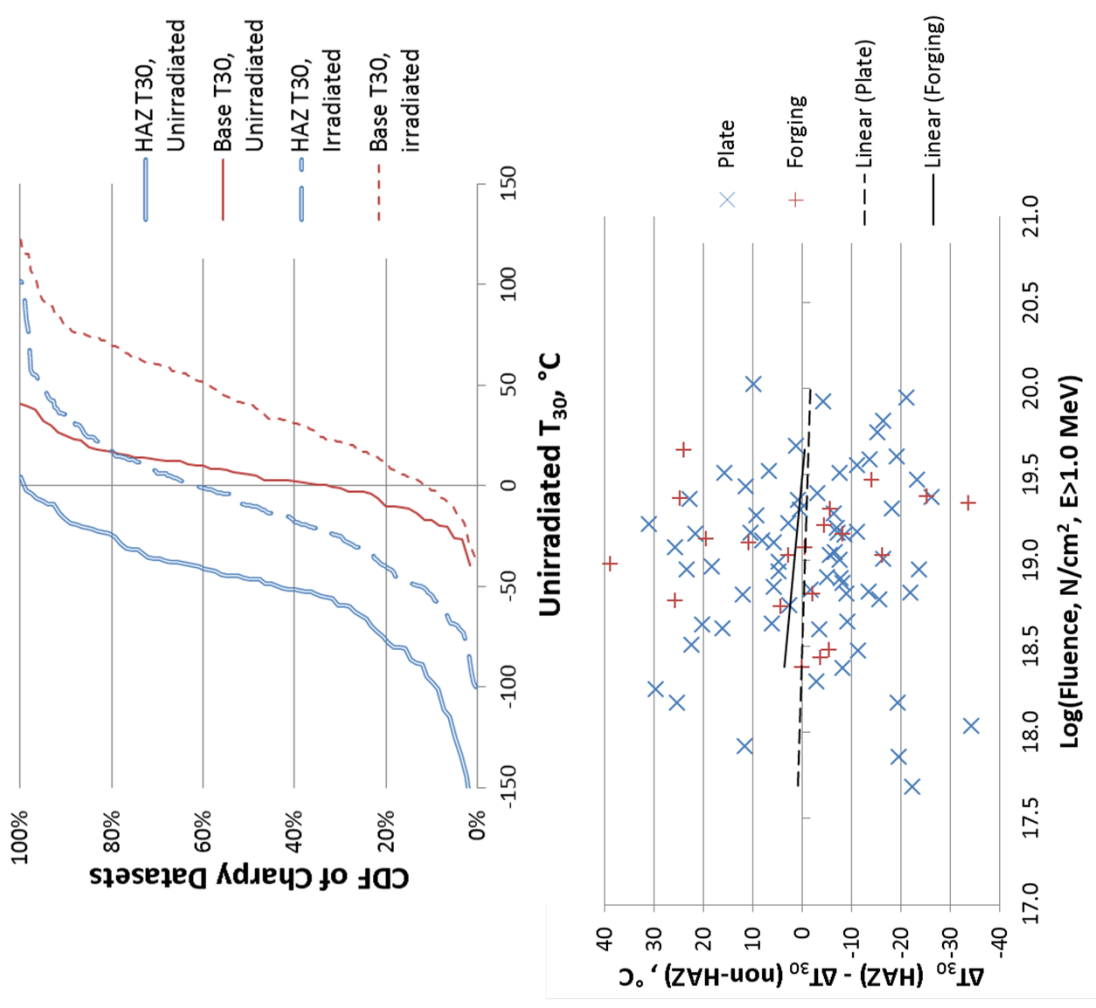

Troyer, G., and Erickson, M., "Empirical Analyses of Effects of the Heat Affected Zone and Post Weld Heat Treatment on Irradiation Embrittlement of Reactor Pressure Vessel Steel," 26th ASTM Symposium on Radiation Effects, Indianapolis, IN, 2013

HAZ of Cladding

- Iskander 1992, NUREG/CR-5785 &/etc.
 - Test block for mechanical specimens: 3 layer cladding
 - $T_{30(HAZ)} < T_{30(BASE)}$

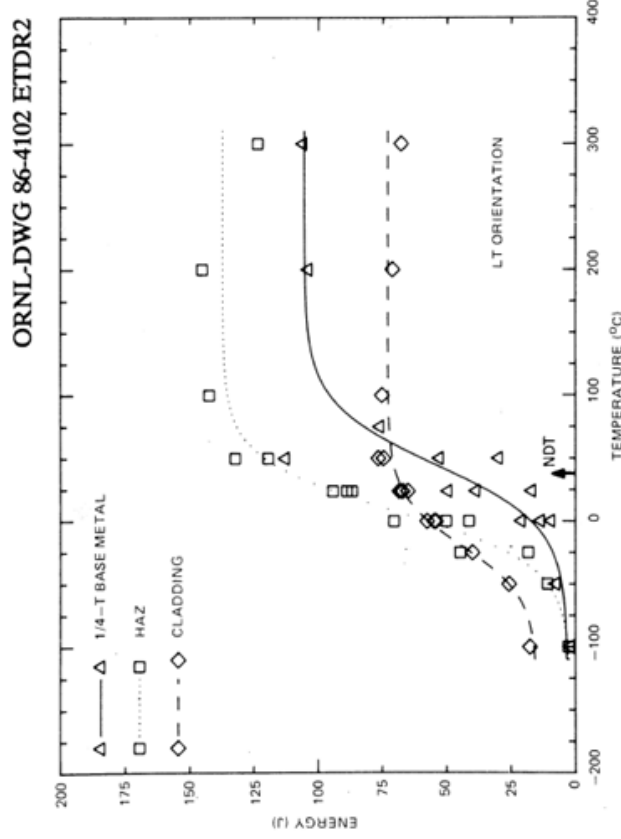

- McCabe 1985-89, various NUREG/CRs
 - Results qualitatively similar to those reported by Iskander, i.e.:
 - $T_{30(HAZ)} < T_{30(BASE)}$
 - However, HAZ specimens smaller than base metal specimens, so loss of constraint may have also reduced the HAZ transition temperature

HAZ of Cladding

Todeschini et al., 2013

INFORMALLY THIS
ORIGINS REDACTED
PAGE WAS

HAZ of Cladding

Todeschini et al., 2013



United States Nuclear Regulatory Commission

Protecting People and the Environment

INFORMALLY THIS
ORIGINS REDACTED
PAGE WAS

HAZ of Cladding

Summary

- Structural welds have many passes, which improves HAZ toughness properties relative to the base metal
 - More passes →
 - More opportunities for grain refinement
 - Smaller regions of coarse grains
 - Tempering of martensite
 - all of which tend to increase toughness
- HAZ under cladding does not experience as many thermal cycles (especially single layer cladding)
 - Less tempering
 - Less grain refinement
- Recent toughness measurements by Todeschini indicates potential for HAZ toughness to be (sometimes) lower and (sometimes) higher than the base metal
 - Modeling of the HAZ is therefore not expected to alter the “late peaking” behavior that leads to the risk-dominance of shallow surface breaking flaws in FAVOR

Crack/Clad/HAZ Interaction




United States Nuclear Regulatory Commission

Protecting People and the Environment

Iskander

- Experimental details
 - 4-point bending
 - Thermally embrittled plate material
 - H₂ charged cracks
- Results
 - Once initiated, cracks run long but do not rupture cladding
 - However
 - Propagating flaws tunnel, even without the cladding & HAZ, probably due to the max value of K_I/K_{Ic} occurring below the surface.
 - Load-bearing capacity of the clad plates enhanced by compressive stresses due to bending

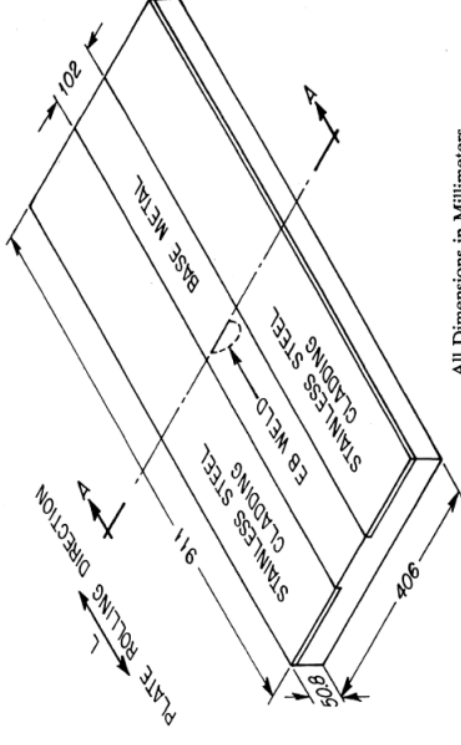


All Dimensions in Millimeters

ORNL-DWG 90-16519

CP-16

- ① EVENT 1, H₂ POP-IN OF EB WELD AND ARREST, STATIC FLAW INITIATION
- ② EVENT 2, FIRST ARREST PROFILE
- ③ EVENT 3, STATIC FLAW INITIATION
- ④ EVENT 4, SECOND ARREST PROFILE

ALL DIMENSIONS IN cm

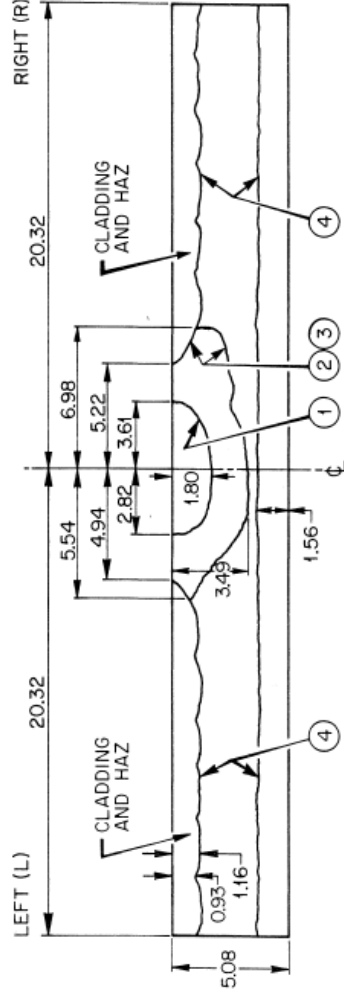


Crack/Clad/HAZ Interaction



United States Nuclear Regulatory Commission
Protecting People and the Environment

- Experimental details
 - Thermally embrittled cylinders
 - Insulated on OD
 - Dunked in LN₂ → thermal shock only (no pressure)
 - Tests performed both with and without cladding

ORNL-DWG 78-21013

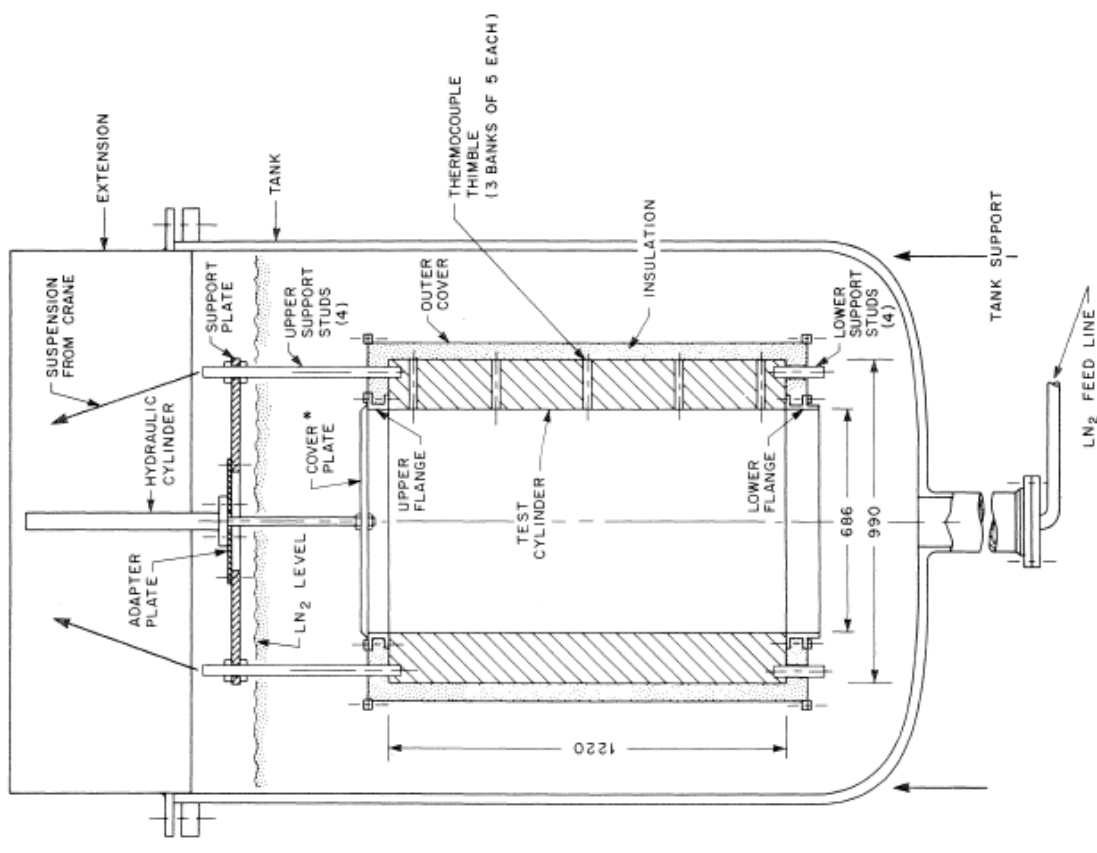

* POSITION DURING SUBMERGENCE,
RAISED TO INITIATE FLOODING

DIMENSIONS IN mm

Crack/Clad/HAZ Interaction

Cheverton – TSE-7 (no cladding)



United States Nuclear Regulatory Commission
Protecting People and the Environment

- Experimental results
 - Significant bifurcation on ID
 - Cracks run long
 - Cracks run deep
 - Series of 3 initiation / run / arrest events predicted reasonably well by FAVOR precursor software

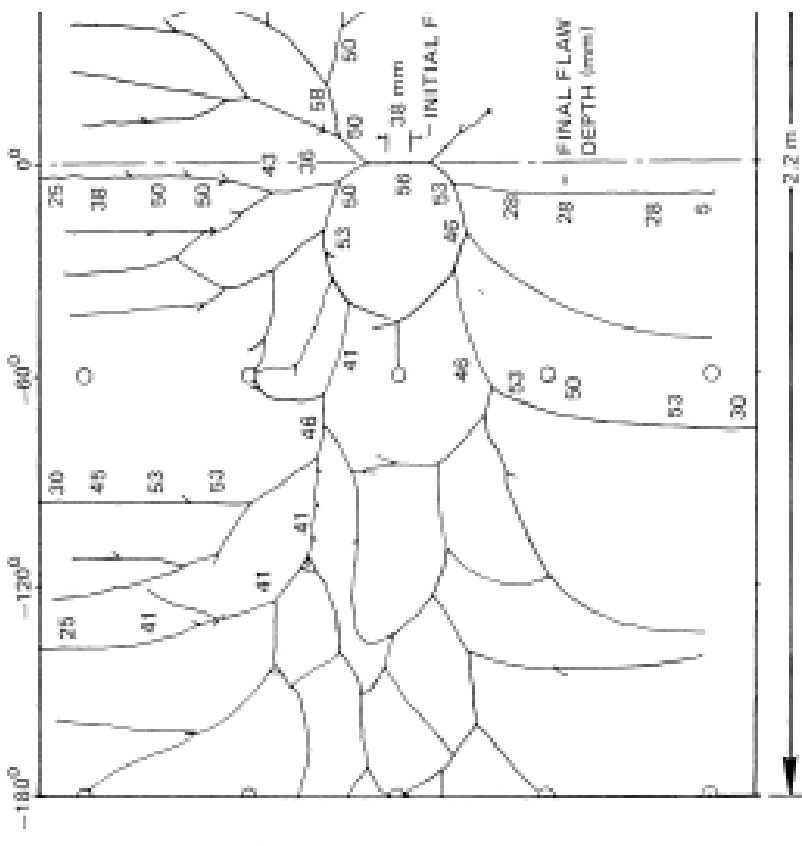


Fig. 8.12. Developed view of inner surf. showing final crack pattern and IT estimates selected locations.

Crack/Clad/HAZ Interaction

Cheverton – TSE-8&11 (with cladding)



United States Nuclear Regulatory Commission
Protecting People and the Environment

- Experimental results
 - Significant bifurcation on ID
 - Cracks run long
 - Cracks run deep
 - Significant through-thickness propagation even in the absence of pressure
 - Cladding not severed by underlying crack
- Analytical results
 - Dickson, 1999
 - Accounts for effect of pressure
 - Cladding rupture predicted by action of pressure

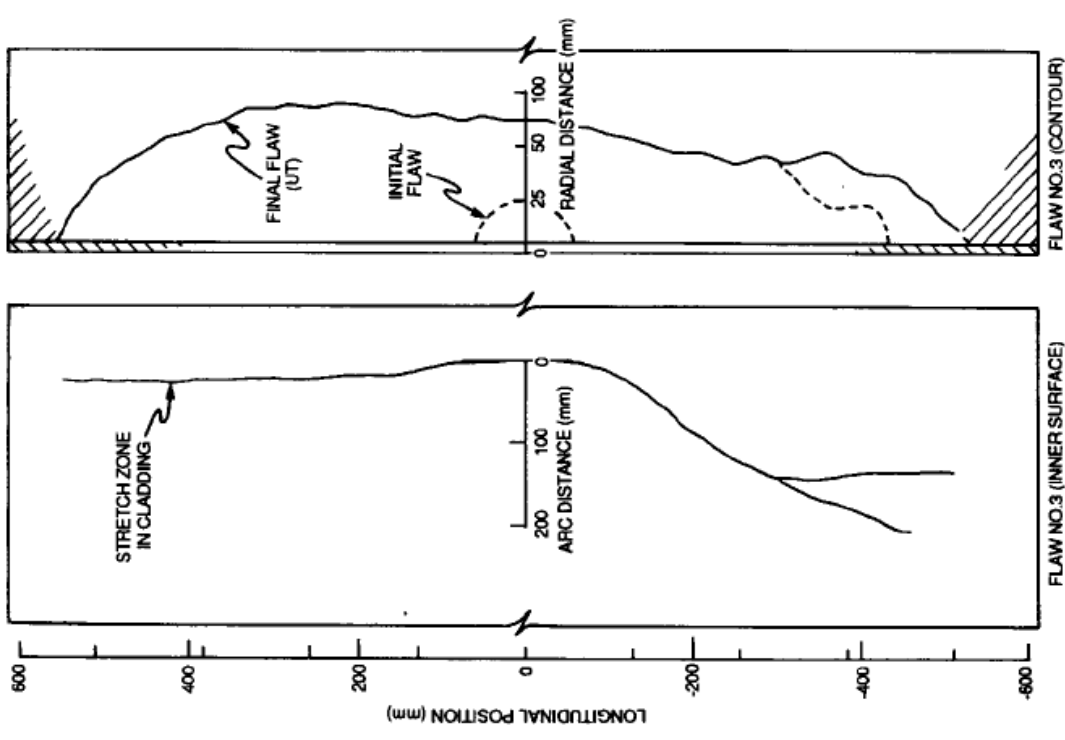


Fig. 8. Stretch-zone and UT indication of flaw 3 TSE-8 extension.

Crack/Clad/HAZ Interaction

Summary



- Both clad beams (bending) and clad cylinders (thermal shock only) show
 - Cracks run long
 - Cracks run deep
 - Cladding (& perhaps HAZ) not severed by underlying crack

Note: $Max K_{APPLIED}$ being sub-surface could also rationalize this tunneling behavior

- Effect of pressure in addition to thermal loading in cylinders
 - Could cause rupture of cladding