# Assessment of BTP 5-3 Protocols to Estimate $RT_{NDT(u)}$ and USE

**Mark Kirk**
*Senior Materials Engineer*
*RES/DE/CIB*
mark.kirk@nrc.gov

**Simon Sheng**
*Senior Materials Engineer*
*NRR/DE/EVIB*
simon.sheng@nrc.gov

NRC/EPRI Annual Materials Issue Program Information Exchange Meeting
4th June 2014
Rockville, Maryland, USA

# Outline of Presentation

- Un-Irradiated $RT_{NDT}$ ($RT_{NDT(u)}$) & Un-Irradiated Upper Shelf Energy (USE) definitions & estimates

- Background of questions concerning BTP 5-3

- Staff Assessment Part I - Technical evaluation of BTP 5-3 estimation of $RT_{NDT(u)}$ & USE

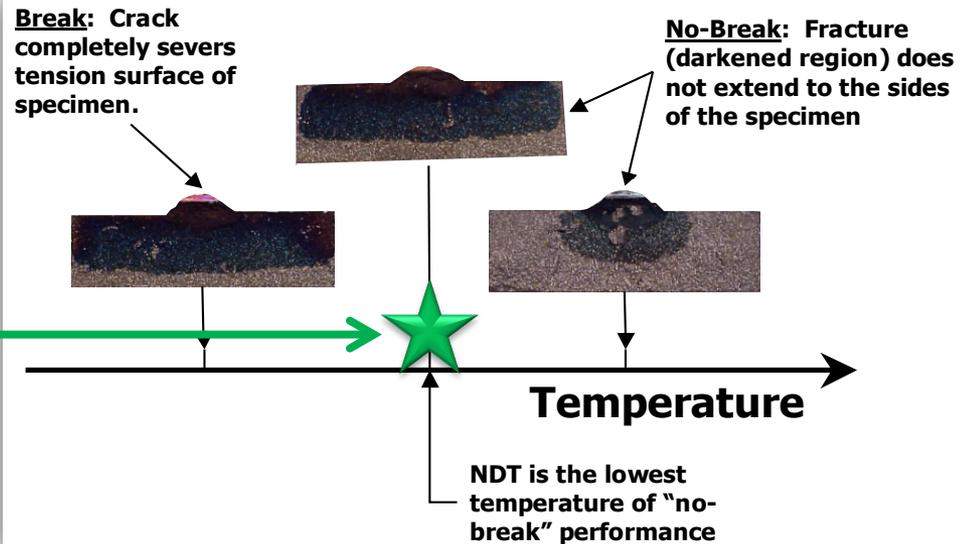- Staff Assessment Part I – Potentially Affected Plants
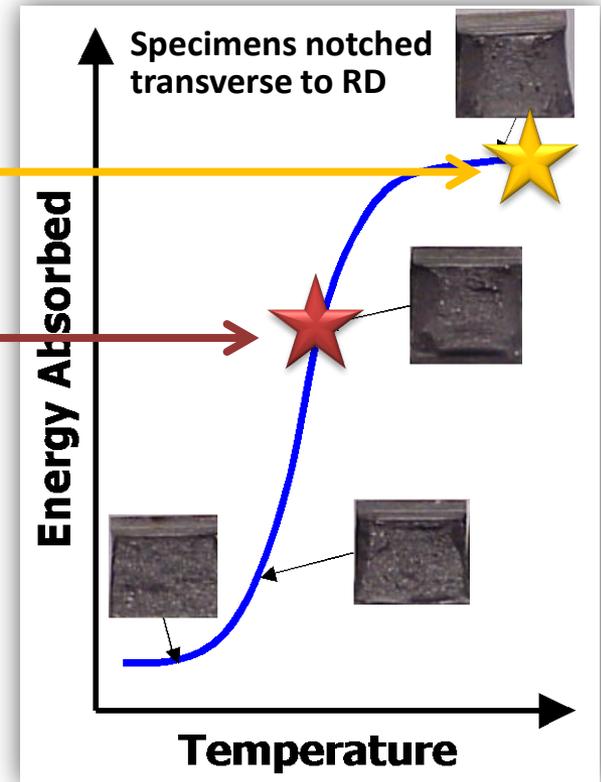
- Next steps

# Definitions: RT$_{NDT(u)}$ & USE

USE $\equiv$ average of all energies > 95% shear

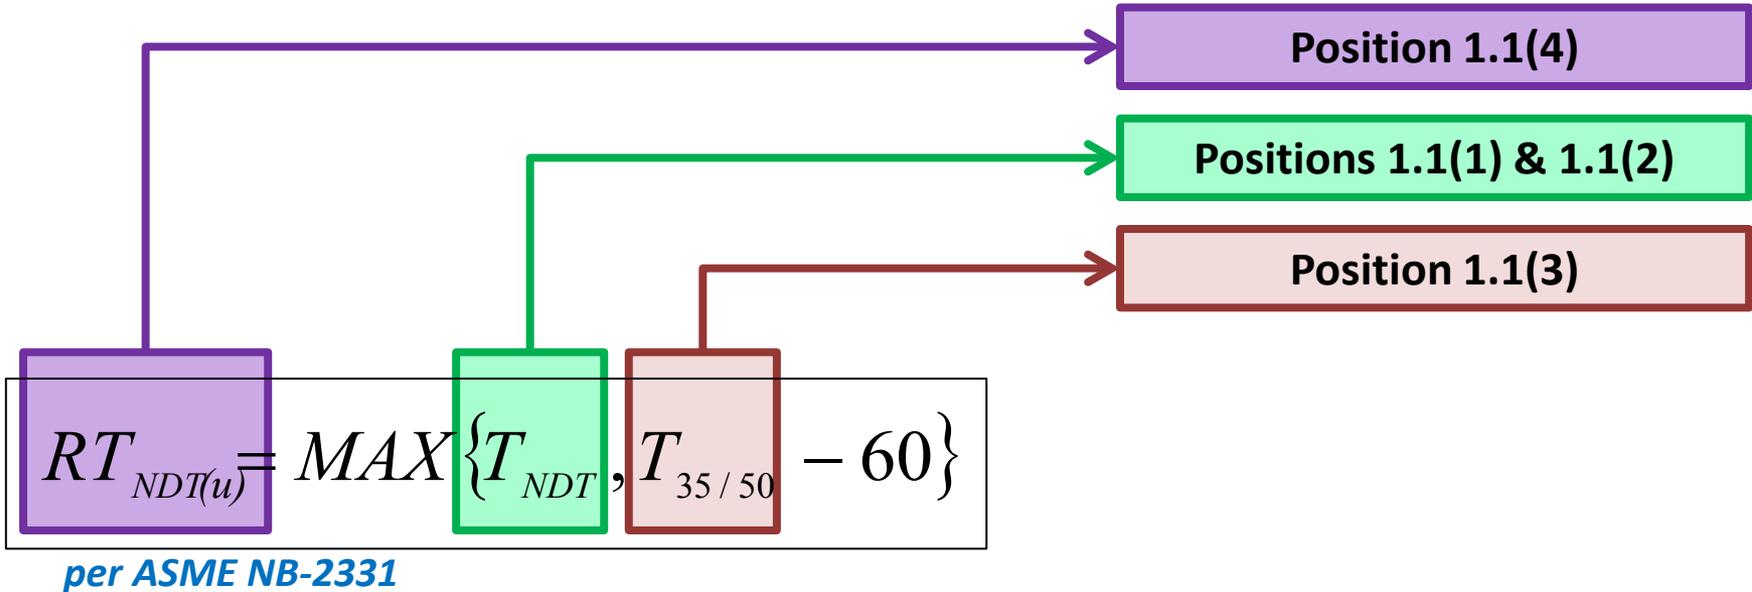*per ASTM E185-82*

$$RT_{NDT(u)} = MAX\{T_{NDT}, T_{35/50} - 60\}$$

*per ASME NB-2331*

Specimens notched transverse to RD

Energy Absorbed

Temperature

**Break:** Crack completely severs tension surface of specimen.

**No-Break:** Fracture (darkened region) does not extend to the sides of the specimen

Temperature

NDT is the lowest temperature of "no-break" performance

# RT$_{NDT(u)}$ & USE
## Estimated by NUREG-0800 BTP 5-3



**Approximations**

Position 1.1(4)

Positions 1.1(1) & 1.1(2)

Position 1.1(3)

$$RT_{NDT(u)} = MAX\{T_{NDT}, T_{35/50} - 60\}$$

*per ASME NB-2331*

Position 1.2

$$USE \equiv \text{average of all energies} > 95\% \text{ shear}$$

*per ASTM E185-82*

# Background of Questions Concerning BTP 5-3



- AREVA Letter (30 Jan 2014, AREVA Ref. NRC:14:004) & PVP Paper (PVP2014-28897) claim Position 1.1(4) of BTP 5.3 is sometimes non-conservative for A508-2 forgings

- Literature search reveals 1983 EG&G report & 1985 IJPVP paper
  - Evaluation of BTP 5-3 (then MTEB 5-2) for NRC
  - Conclusions
    - Always conservative
      - Position 1.1(1): estimates $T_{NDT}$
      - Position 1.1(2): estimates $T_{NDT}$
    - Sometime non-conservative
      - Position 1.1(3): estimates $T_{CVE(50/35)}$
      - Position 1.1(4): estimates $RT_{NDT}$
      - Position 1.2: estimates USE



January 30, 2014
NRC:14:004

U.S. Nuclear Regulatory Commission
Document Control Desk
11555 Rockville Pike
Rockville, MD 20852

**Potential Non-Conservatism in NRC Branch Technical Position 5-3**



**DRAFT**

Proceedings of the ASME 2014 Pressure Vessels & Piping Conference
PVP2014
July 20-24, 2014, Anaheim, California, USA

**PVP2014-28897**

**AN ASSESSMENT OF BRANCH TECHNICAL POSITION 5-3 TO DETERMINE UNIRRADIATED RT$_{NDT}$ FOR SA-508 CL. 2 FORGINGS**

Greg Troyer
AREVA Inc.
Lynchburg, Virginia, USA

Matthew DeVan
AREVA Inc.
Lynchburg, Virginia, USA

# Background of Questions Concerning BTP 5-3

- AREVA Letter (30 Jan 2014, AREVA Ref. NRC:14:004) & PVP Paper (PVP2014-28897) claim Position 1.1(4) of BTP 5.3 is sometimes non-conservative for A508-2 forgings

- Literature search reveals 1983 EG&G report & 1985 IJPVP paper
  - Evaluation of BTP 5-3 (then MTEB 5-2) for NRC
  - Conclusions
    - Always conservative
      - Position 1.1(1): estimates $T_{NDT}$
      - Position 1.1(2): estimates $T_{NDT}$
    - Sometime non-conservative
      - Position 1.1(3): estimates $T_{CVE(50/35)}$
      - Position 1.1(4): estimates $RT_{NDT}$
      - Position 1.2: estimates USE

EGG-MS-6310

CORRELATION OF CHARPY V-NOTCH DATA WITH FRACTURE TOUGHNESS
PARAMETERS FOR SA-533B-1 AND SA-508-2 STEELS

P. K. Nagata
W. G. Reuter
A. K. Richardson
W. L. Server

Published December 1983

*Int. J. Pres. Ves. & Piping* 19 (1985) 299–315

**Adequacy of Estimates and Variability of Fracture-related Properties for Reactor Pressure Vessel Materials\***

A. K. Richardson, W. L. Server & W. G. Reuter

E.G. & G. Idaho, Inc., PO Box 1625, Idaho Falls, Idaho 83415, USA

(Received: 3 October, 1984)

# NRC Staff Assessment Process

**Part I: Technical evaluation of BTP 5-3 estimation of $RT_{NDT(u)}$ and USE**

- Data sources
  - Processed data ($T_{50}$, USE, …) from 1983 EG&G report
  - Raw data (CVE, MLE, temp) in both specimen orientations from surveillance reports (stored in REAP)
  - Raw data (NDTT) from RVID refs.

- Focus on
  - Plates & forgings only
    - No plants have used BTP 5-3 for welds
  - Positions identified as sometimes non-conservative in 1983 by EG&G report
    - Position 1.1(3): estimates $T_{CVE(50/35)}$
    - Position 1.1(4): estimates $RT_{NDT}$
    - Position 1.2: estimates USE

**Part II: Assessment of applicability to plants**

- Query RVID
  - $RT_{NDT(u)}$: establishes BTP 5-3 use, but not which position was used
  - USE: establishes BTP 5-3 use

- Search for documents referenced by RVID in ADAMS legacy
  - Focus on plants closest to PTS (50.61) limit, these being most prone to influence by potential non-conservatisms
  - References establish which position of BTP 5-3 was used for $RT_{NDT(u)}$
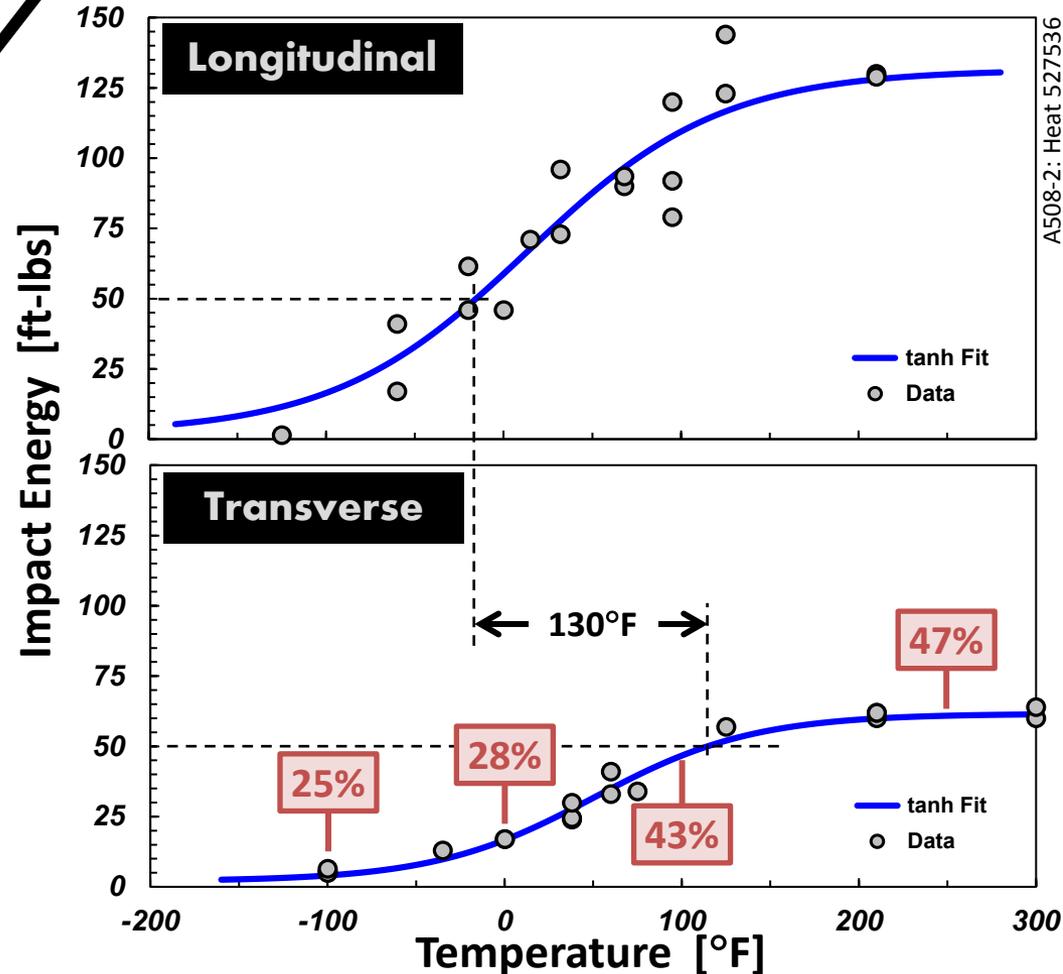
# Part I: Technical Evaluation

## Overview

- Data sources
  - Processed data ($T_{50}$, USE, …) from 1983 EG&G report
  - Raw data (CVE, MLE, temp) from surveillance reports (stored in REAP)
  - Raw data (NDTT) from RVID refs.

- While similar answers are expected from both sources …
- Given the potential impact of this evaluation, going back to the raw data was seen to be important.

- Focus on
  - Plates & forgings only
    - No plants have used BTP 5-3 for welds
  - Positions identified as sometimes non-conservative by 1983 EG&G report
    - Position 1.1(3): estimates $T_{CVE(50/35)}$
    - Position 1.1(4): estimates $RT_{NDT}$
    - Position 1.2: estimates USE



A508-2: Heat 527536

Longitudinal

Transverse

130°F

25%   28%   43%   47%

Impact Energy [ft-lbs]

Temperature [°F]

tanh Fit
Data

# Position 1.1(3)

## Quotation

If transversely-oriented Charpy V-notch specimens were not tested, the temperature at which 68 J (50 ft-lbs) and 0.89 mm (35 mils) LE would have been obtained on transverse specimens may be estimated by one of the following criteria:

- Test results from longitudinally-oriented specimens reduced to 65% of their value to provide conservative estimates of values expected from transversely oriented specimens.

- Temperatures at which 68 J (50 ft-lbs) and 0.89 mm (35 mils) LE were obtained on longitudinally-oriented specimens increased 11 °C (20 °F) to provide a conservative estimate of the temperature that would have been necessary to obtain the same values on transversely-oriented specimens.

**Tests Required**

Longitudinally oriented CVN specimens

**Clear Interpretation**

Note that this position applies only to conversion between longitudinal and transverse Charpy values.

There are two approximations. They may not produce the same results. They are as follows

(a)  $E_{TRANS} = 0.65 \times E_{LONG}$, then calc $T_{C(TRANS)}$
$MLE_{TRANS} = 0.65 \times MLE_{LONG}$, then calc $T_{C(TRANS\text{-}MLE)}$

(b)  $T_{C(TRANS)} = T_{C(LONG)} + 20\ °F$
$T_{C(TRANS\text{-}MLE)} = T_{C(LONG\text{-}MLE)} + 20\ °F$

where

| | |
|---|---|
| $E_{LONG}$ | is CVN energy measured by a longitudinally oriented specimen |
| $E_{TRANS}$ | is the estimated CVN for a transversely oriented specimen |
| $T_{C(LONG)}$ | is the temperature at which the minimum of three longitudinal CVN tests exhibits >35 mils AND >50 ft-lbs |
| $T_{C(TRANS)}$ | is the estimated temperature at which the minimum of three transverse CVN tests exhibits >35 mils AND >50 ft-lbs |

# Position 1.1(3)

1. Per the BTP, reduce longitudinal measurements to 65% of the measured values

2. Fit Charpy curves
   - Energy vs. temperature
   - Lateral expansion vs. temperature

3. Determine MAX($T_{50ft-lb}$, $T_{35mills}$)

4. Value from Step 3 estimates the transition temperature of transverse data
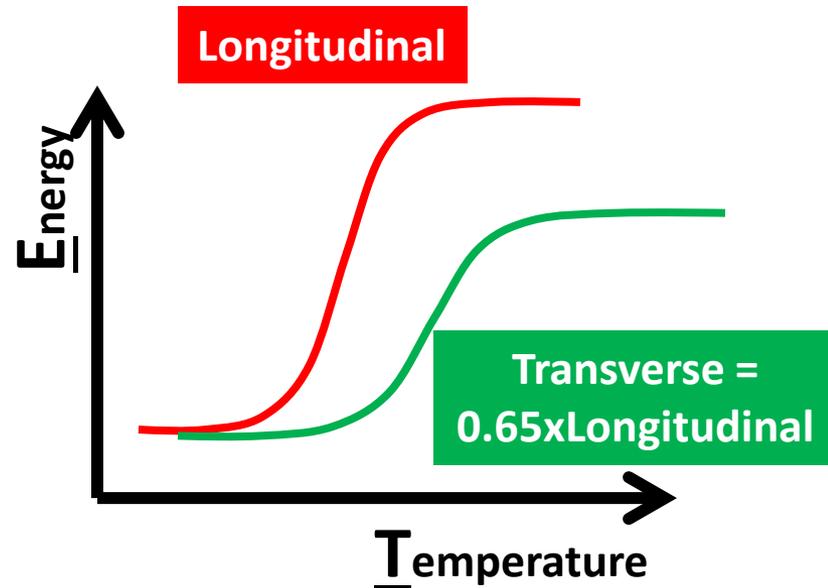
**Longitudinal**

**Energy**

**Transverse = 0.65xLongitudinal**

**Temperature**

# Position 1.1(3)

## Assessing(a): Trans = 0.65×Long
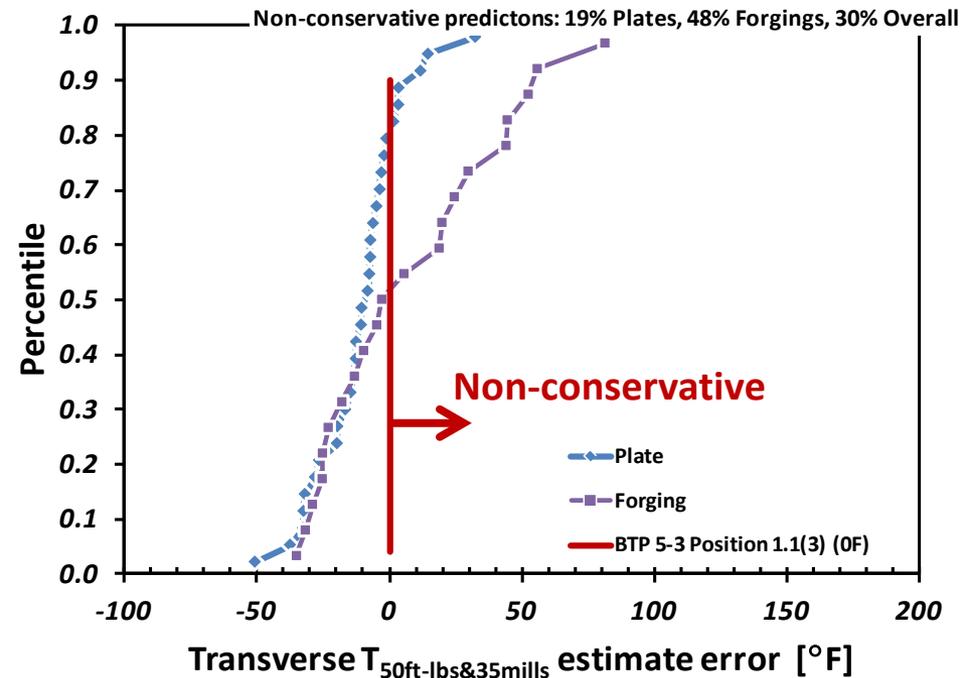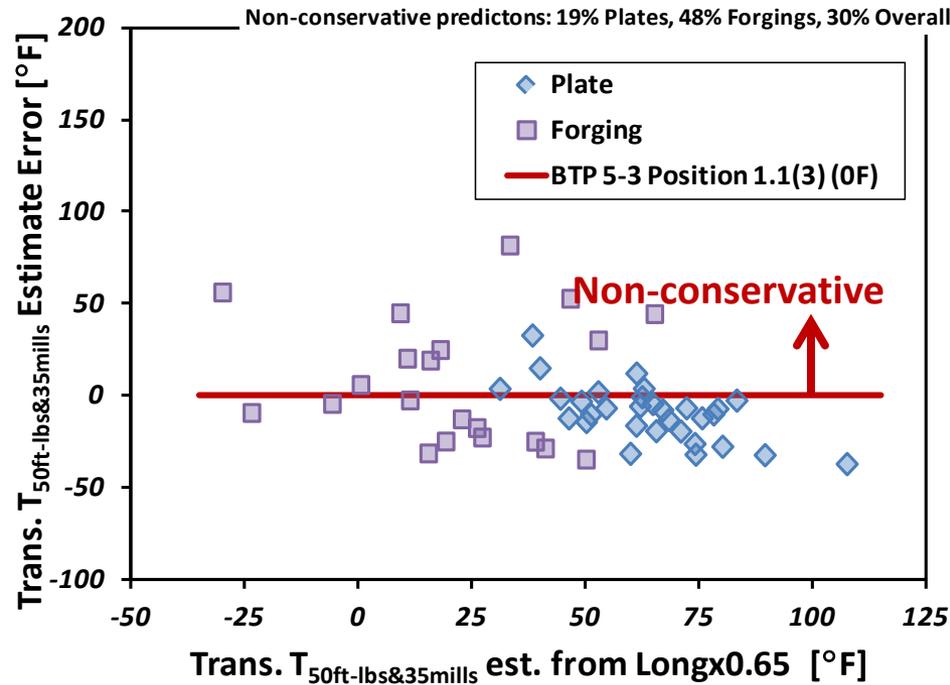
Same data plotted two different ways
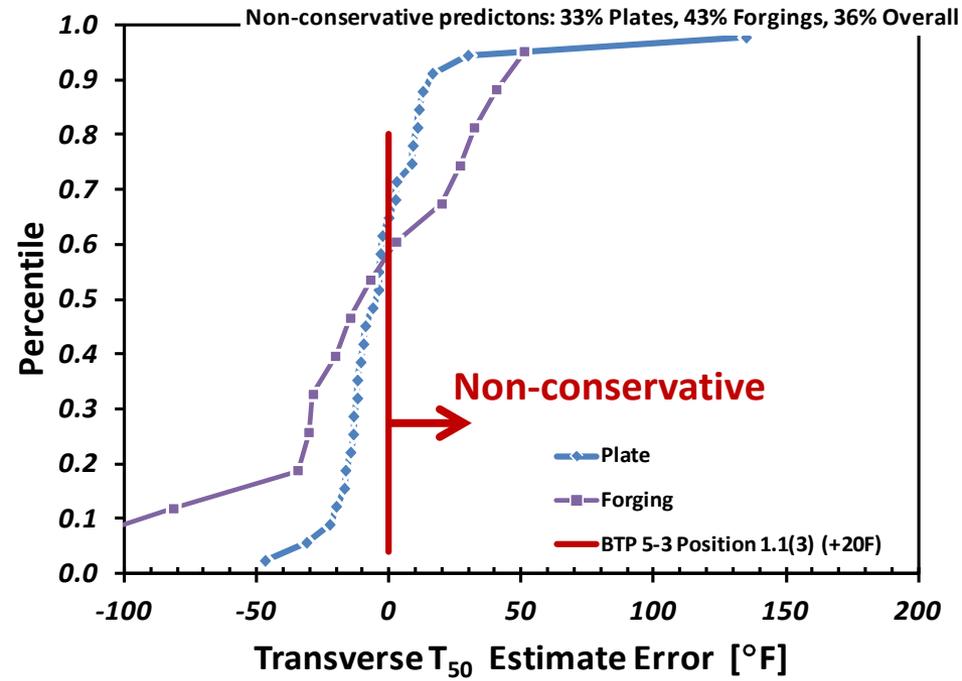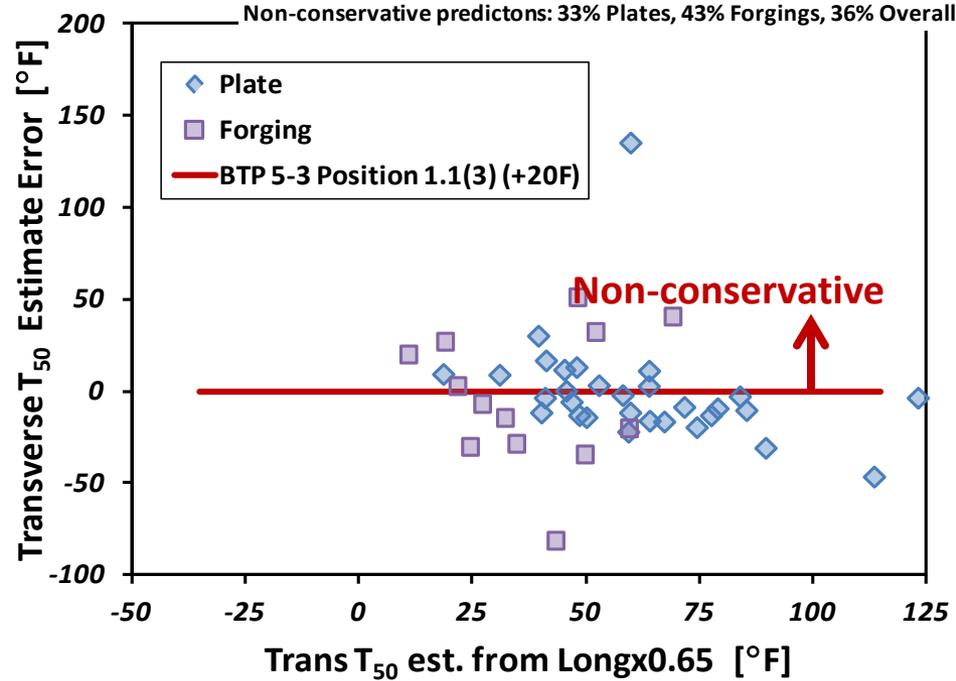


**Position is non-conservative about 36% of the time**

EG&G Data

# Position 1.1(3)

## Assessing(a): Trans = 0.65×Long
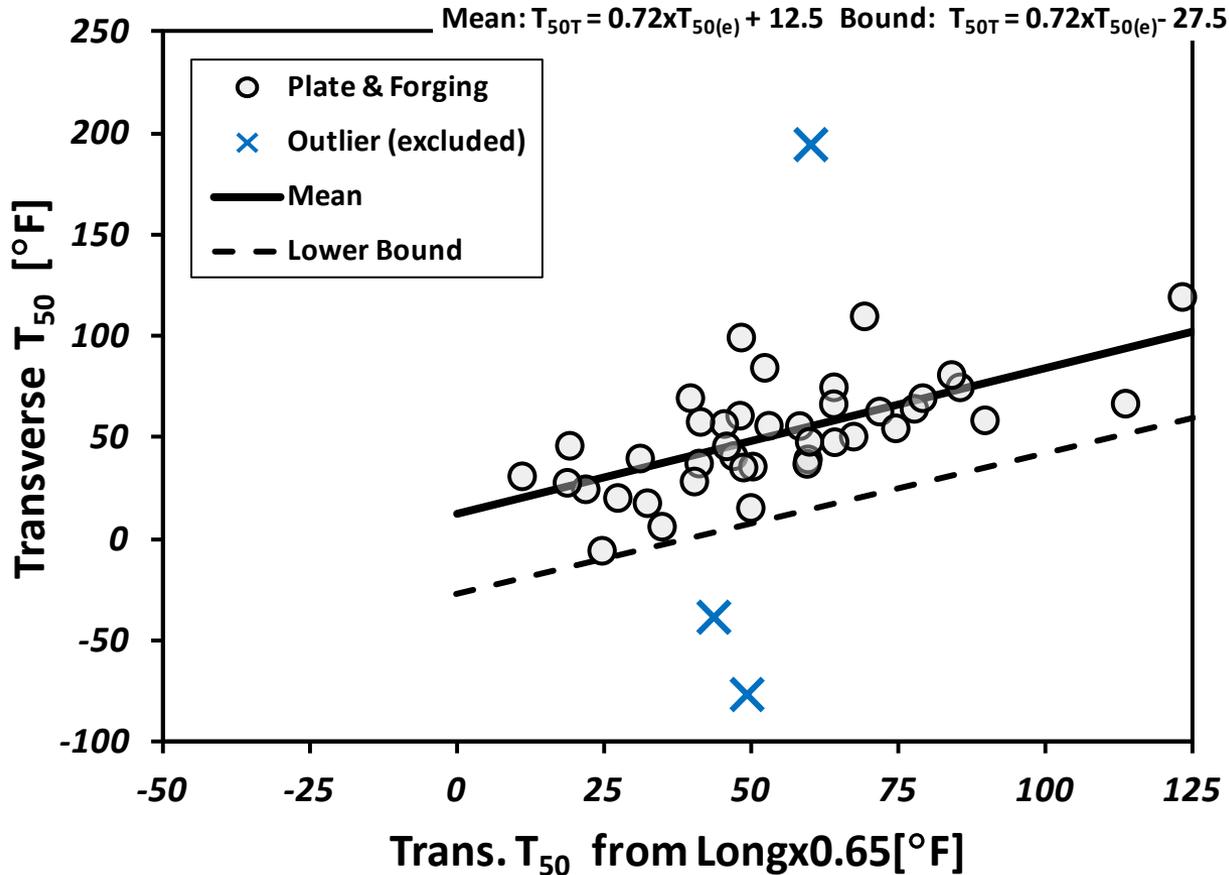
Same data plotted two different ways



$T_{50ft-lbs}$ determines the value of $T_{50ft-lbs\&35mills}$
- **81% of the time for longitudinal specimens**
- **92% of the time for transverse specimens**

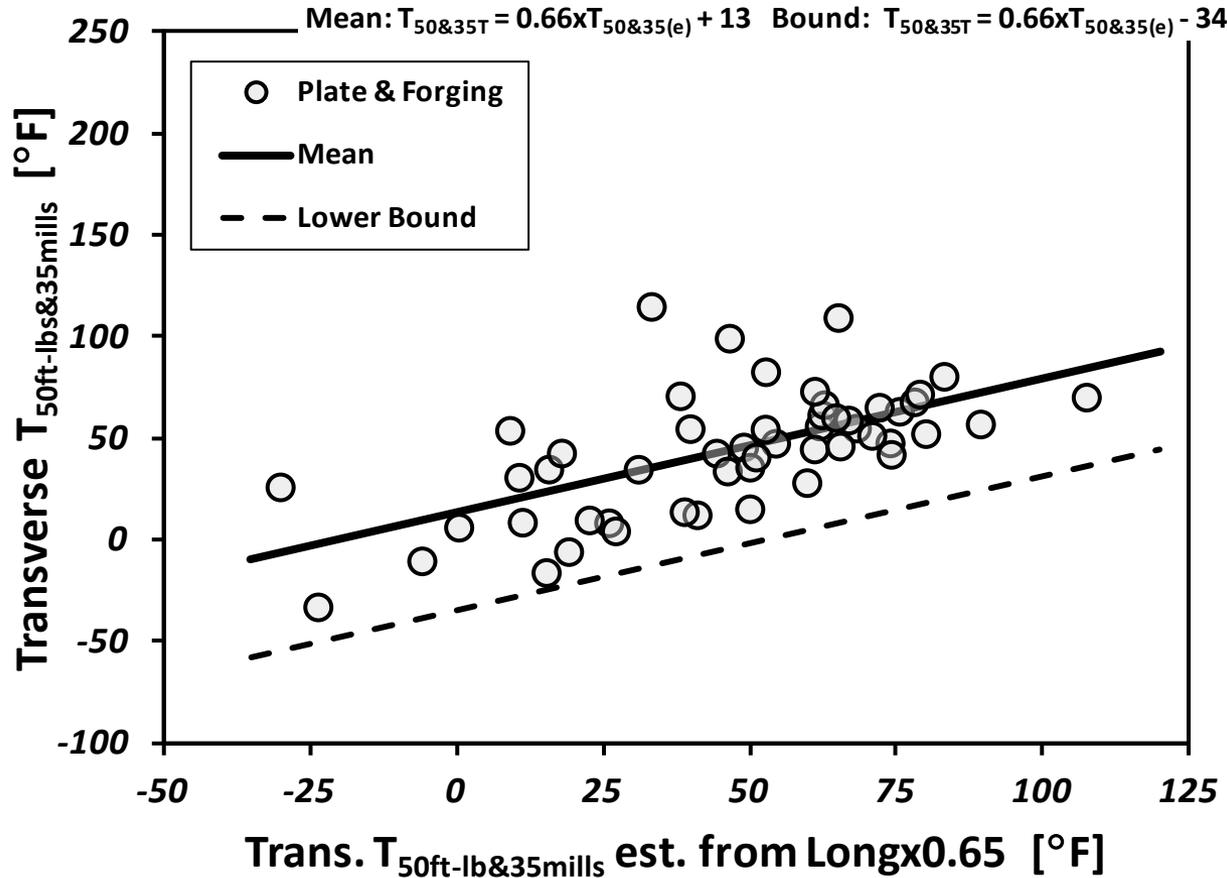**Position is non-conservative about 30% of the time**

**Raw Data**

# Position 1.1(3)
## Assessing(b): Alternative $T_{C(TRANS)}$ Estimates



Mean: $T_{50T} = 0.72 \times T_{50(e)} + 12.5$   Bound: $T_{50T} = 0.72 \times T_{50(e)} - 27.5$

Legend:
- ○ Plate & Forging
- ✕ Outlier (excluded)
- —— Mean
- – – Lower Bound

Y-axis: Transverse $T_{50}$ [°F]
X-axis: Trans. $T_{50}$ from Longx0.65[°F]

**Preliminary analysis suggests that alternative formulae could be developed to convert longitudinal to transverse $T_{50}$ values in a manner that is always conservative.**

EG&G Data

# Position 1.1(3)
## Assessing(a): Alternative $T_{C(TRANS)}$ Estimates



Mean: $T_{50\&35T} = 0.66 \times T_{50\&35(e)} + 13$   Bound: $T_{50\&35T} = 0.66 \times T_{50\&35(e)} - 34$
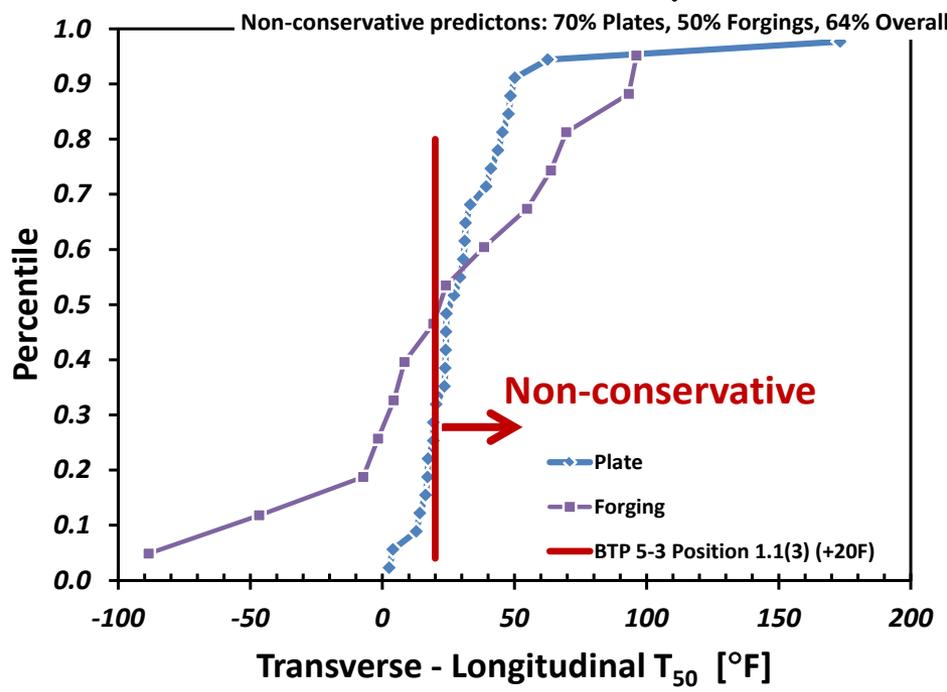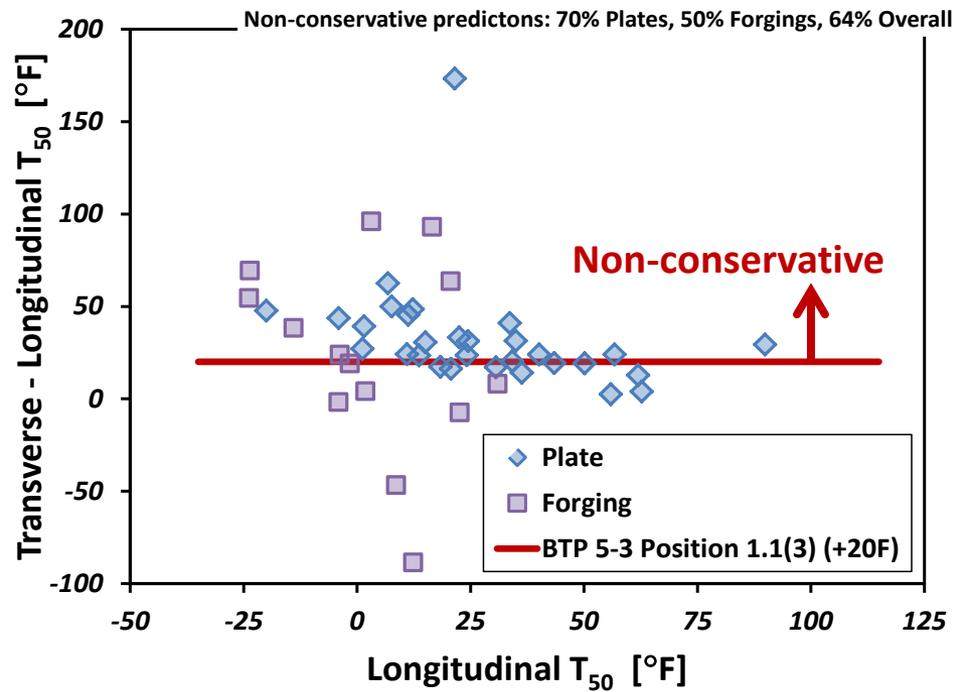
**Preliminary analysis suggests that alternative formulae could be developed to convert longitudinal to transverse $T_{50}$ values in a manner that is always conservative.**

**Raw Data**

# Position 1.1(3)

**Assessing(b): $T_{C(TRANS)} = T_{C(LONG)} + 20\ °F$**
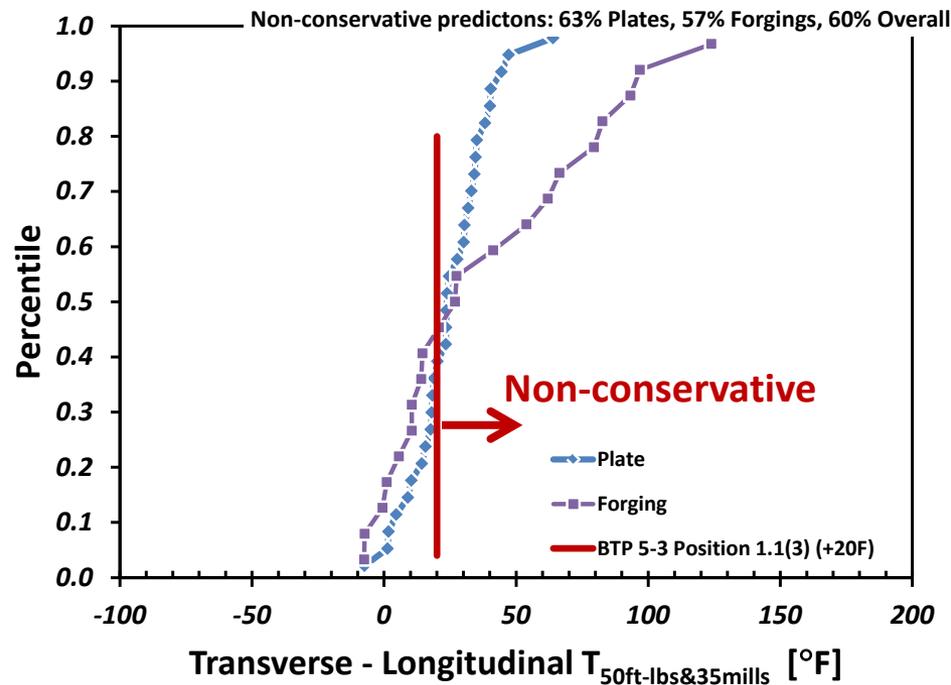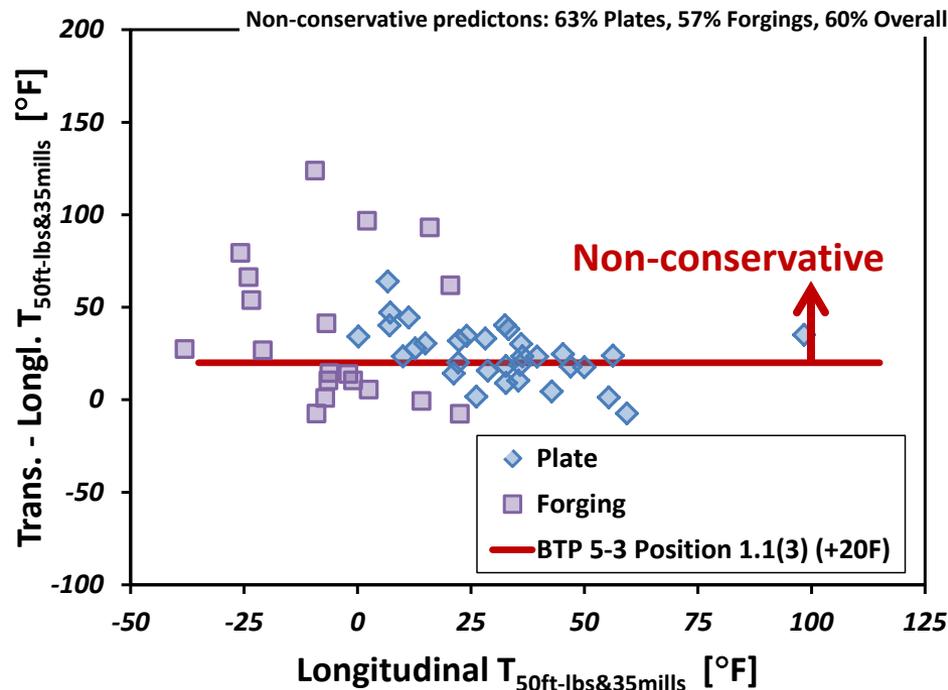
Same data plotted two different ways



**Position is non-conservative about two-thirds of the time**

EG&G Data

# Position 1.1(3)

**Assessing(b): $T_{C(TRANS)} = T_{C(LONG)} + 20\,°F$**

Same data plotted two different ways



Non-conservative predictons: 63% Plates, 57% Forgings, 60% Overall

Non-conservative

- Plate
- Forging
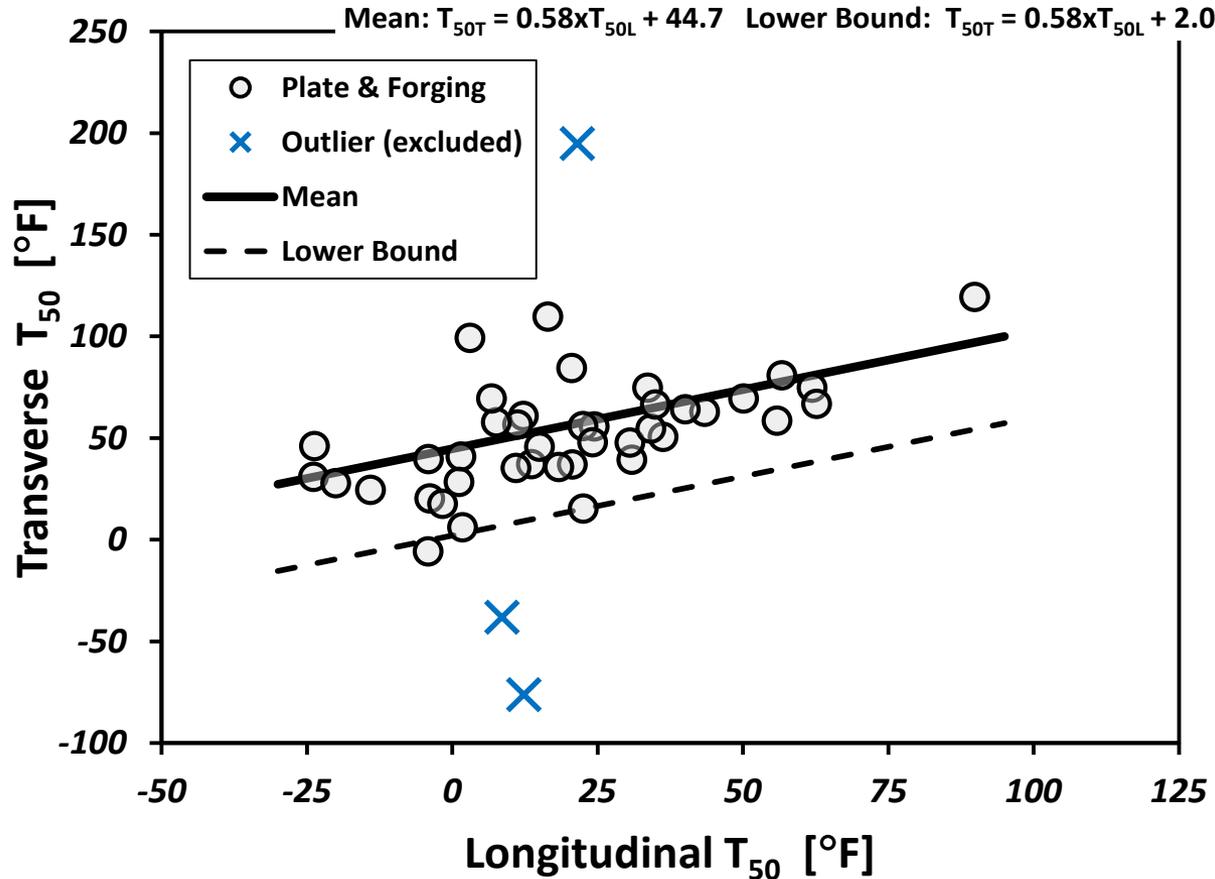- BTP 5-3 Position 1.1(3) (+20F)

$T_{50ft\text{-}lbs}$ **determines the value of** $T_{50ft\text{-}lbs\&35mills}$
- **81% of the time for longitudinal specimens**
- **92% of the time for transverse specimens**

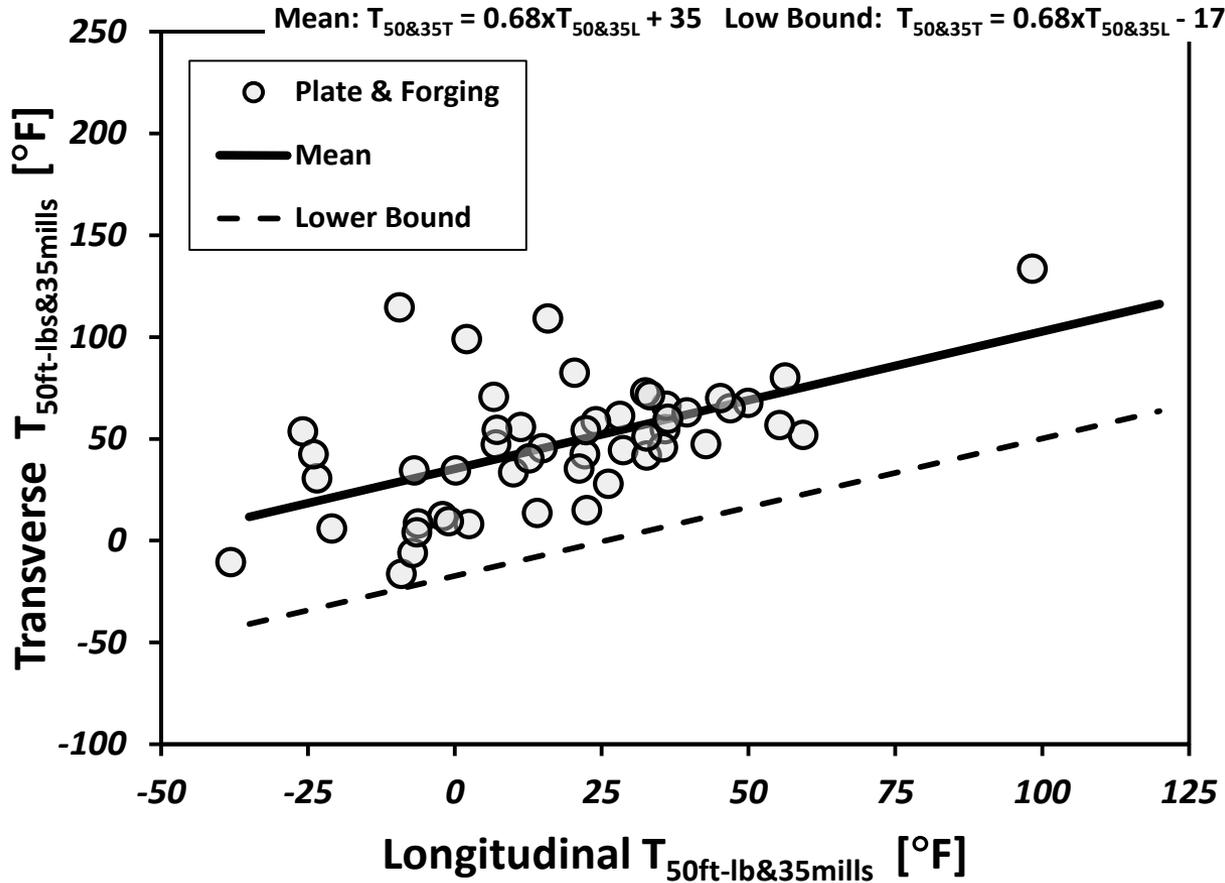**Position is non-conservative about two-thirds of the time**

**Raw Data**

## Assessing(b): Alternative $T_{C(TRANS)}$ Estimates



Mean: $T_{50T} = 0.58 \times T_{50L} + 44.7$   Lower Bound: $T_{50T} = 0.58 \times T_{50L} + 2.0$

Legend:
- ○ Plate & Forging
- ✕ Outlier (excluded)
- ── Mean
- – – Lower Bound

Y-axis: Transverse $T_{50}$ [°F]
X-axis: Longitudinal $T_{50}$ [°F]

**Preliminary analysis suggests that alternative formulae could be developed to convert longitudinal to transverse $T_{50}$ values in a manner that is always conservative.**

EG&G Data

# Position 1.1(3)

**Assessing(b): Alternative $T_{C(TRANS)}$ Estimates**

Mean: $T_{50\&35T} = 0.68 \times T_{50\&35L} + 35$   Low Bound: $T_{50\&35T} = 0.68 \times T_{50\&35L} - 17$



**Preliminary analysis suggests that alternative formulae could be developed to convert longitudinal to transverse $T_{50}$ values in a manner that is always conservative.**

**Raw Data**

# Position 1.1(4)

## Quotation

If limited Charpy V-notch tests were performed at a single temperature to confirm that at least 41 J (30 ft-lbs) was obtained, that temperature may be used as an estimate of the $RT_{NDT}$ provided that at least 61J (45 ft-lbs) was obtained if the specimens were longitudinally oriented. If the minimum value obtained was less than 61 J (45 ft-lbs), the $RT_{NDT}$ may be estimated as 11 °C (20 °F) above the test temperature.

| Tests Required |
| --- |
| Limited longitudinally oriented CVN tests at a single temperature |

| Interpretation |
| --- |

Define:     $T_{TEST}$ = the temperature at which limited longitudinally oriented CVN tests were conducted

           $C_V$ = absorbed energy observed at $T_{TEST}$

IF           $C_V \geq$    45 ft-lbs then $RT_{NDT} = T_{TEST}$
ELSE       $RT_{NDT} = T_{TEST} + 20$ °F

When assessed using data sets for which full Charpy energy curves are available, EG&G interpreted Position 1.1(4) as having 2 possible meanings:
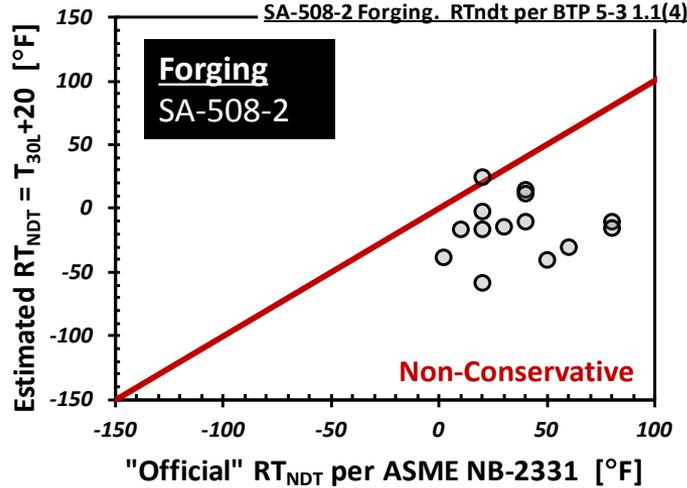
–   $RT_{NDT} = T_{45(LONG)}$, and

–   $RT_{NDT} = T_{30(LONG)} + 20$ °F

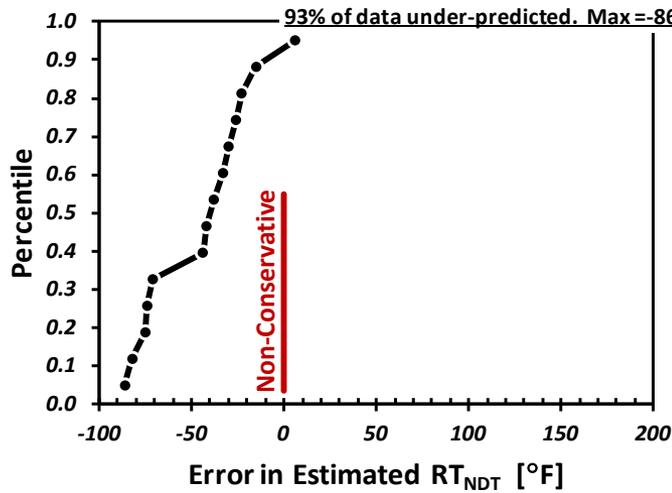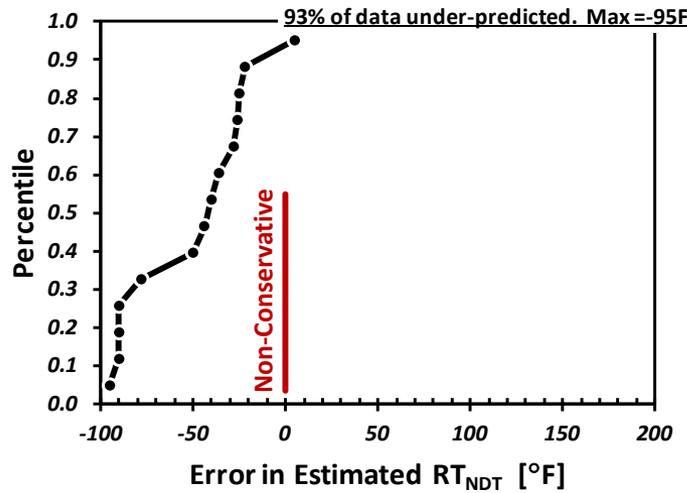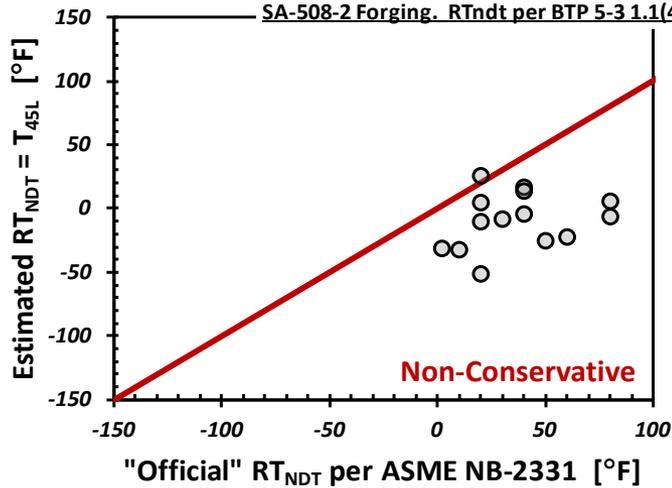These might not produce the same result.  Therefore, both were assessed.

# Position 1.1(4)
## Assessed for Forgings

**U.S.NRC**
United States Nuclear Regulatory Commission
*Protecting People and the Environment*

### $RT_{NDT} = T_{30(LONG)} + 20 \ °F$



SA-508-2 Forging. RTndt per BTP 5-3 1.1(4)

**Forging**
SA-508-2

Estimated $RT_{NDT} = T_{30L}+20$ [°F]

**Non-Conservative**

"Official" $RT_{NDT}$ per ASME NB-2331 [°F]

### $RT_{NDT} = T_{45(LONG)}$



SA-508-2 Forging. RTndt per BTP 5-3 1.1(4)

Estimated $RT_{NDT} = T_{45L}$ [°F]

**Non-Conservative**

"Official" $RT_{NDT}$ per ASME NB-2331 [°F]

93% of data under-predicted. Max =-95F

Percentile

Non-Conservative

Error in Estimated $RT_{NDT}$ [°F]

93% of data under-predicted. Max =-86F

Percentile

Non-Conservative

Error in Estimated $RT_{NDT}$ [°F]

**Top & bottom panel of each pair are the same data plotted two different ways**
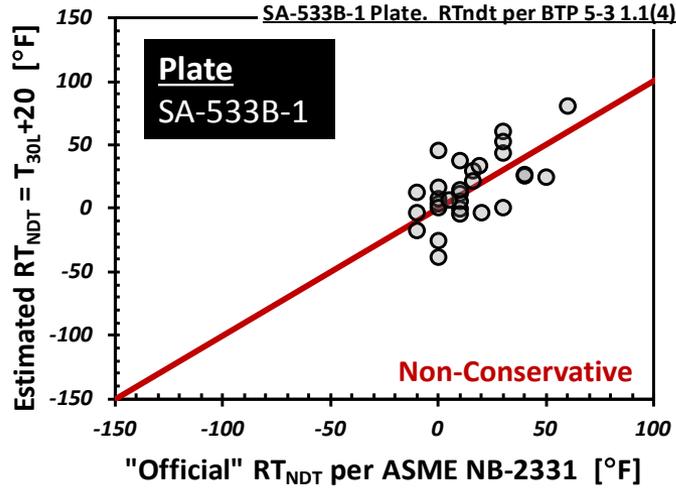
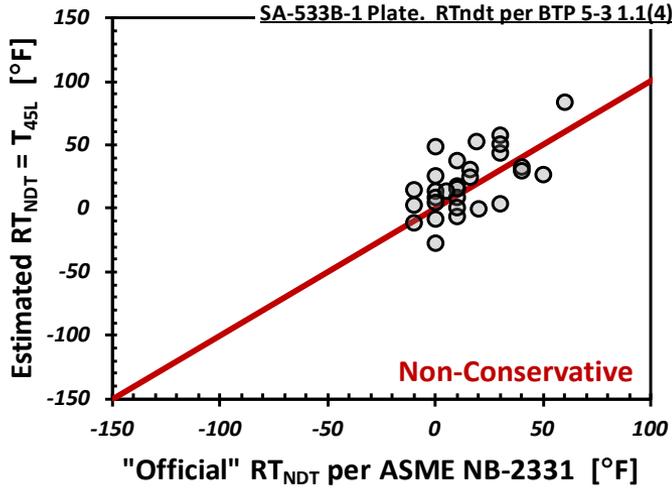**Position is non-conservative about 90% of the time**

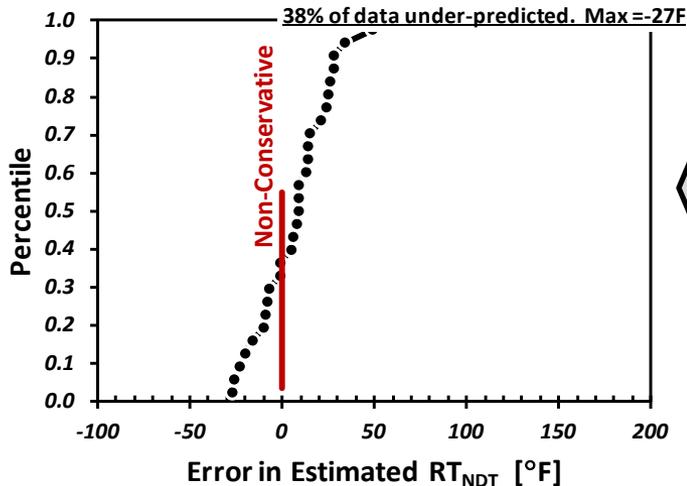**EG&G Data**

# Position 1.1(4)
## Assessed for Plates

$$RT_{NDT} = T_{30(LONG)} + 20 \text{ °F}$$

$$RT_{NDT} = T_{45(LONG)}$$



SA-533B-1 Plate.  RTndt per BTP 5-3 1.1(4)

Plate
SA-533B-1

Estimated $RT_{NDT} = T_{30L}+20$ [°F]

"Official" $RT_{NDT}$ per ASME NB-2331 [°F]

Non-Conservative



SA-533B-1 Plate.  RTndt per BTP 5-3 1.1(4)

Estimated $RT_{NDT} = T_{45L}$ [°F]

"Official" $RT_{NDT}$ per ASME NB-2331 [°F]

Non-Conservative

Top & bottom panel of each pair are the same data plotted 2 different ways



38% of data under-predicted.  Max =-38F

Percentile

Non-Conservative

Error in Estimated $RT_{NDT}$ [°F]



38% of data under-predicted.  Max =-27F

Percentile

Non-Conservative

Error in Estimated $RT_{NDT}$ [°F]
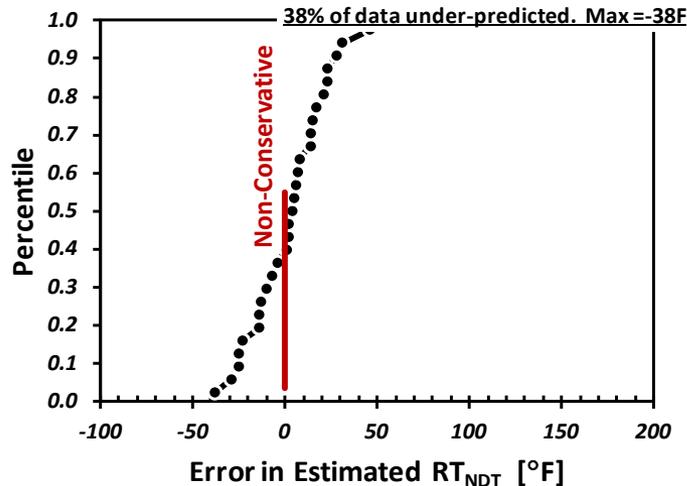
**Position is non-conservative about 40% of the time**

EG&G Data

# Position 1.2

## Quotation

For the beltline region of reactor vessels, the upper shelf toughness must account for the effects of neutron radiation. Reactor vessel beltline materials must have Charpy upper shelf energy, in the transverse direction for base material and along the weld for weld material according to the ASME Code, of no less than 102 J (75 ft-lbs) initially and must maintain Charpy upper shelf energy throughout the life of the vessel of no less than 68 J (50 ft-lbs).

If Charpy upper shelf energy values were not obtained, conservative estimates should be made using results of tests on specimens from the first surveillance capsule removed.

**If tests were only made on longitudinal specimens, the values should be reduced to 65% of the longitudinal values to estimate the transverse properties.**

| Tests Required |
|---|
| Longitudinally oriented CVN specimens tested on the upper shelf. |

| Clear Interpretation |
|---|

$$USE_{TRANS} = 0.65 \times USE_{LONG}$$
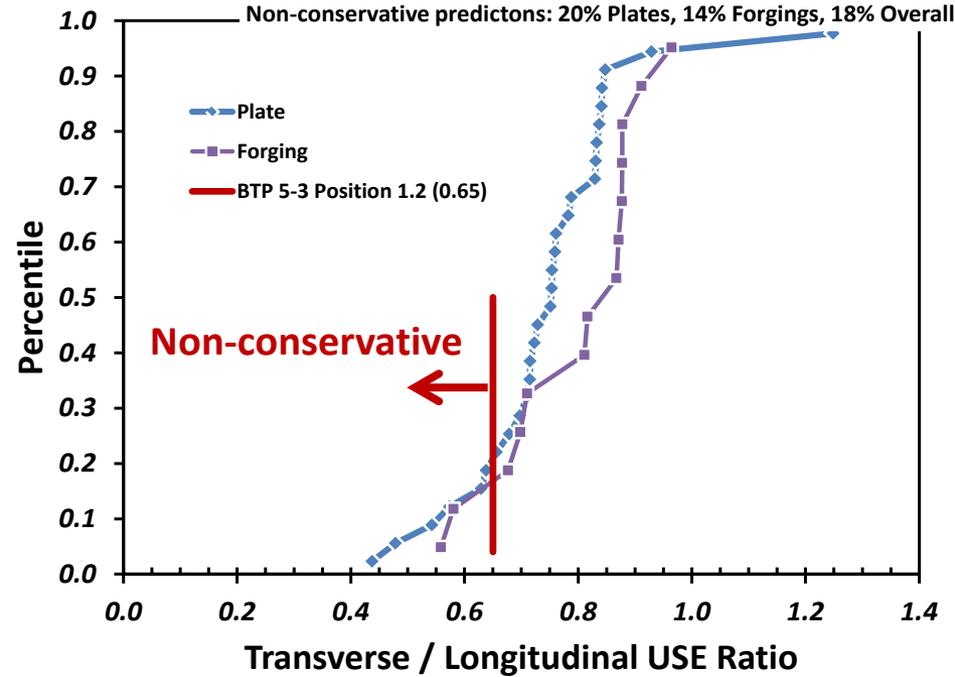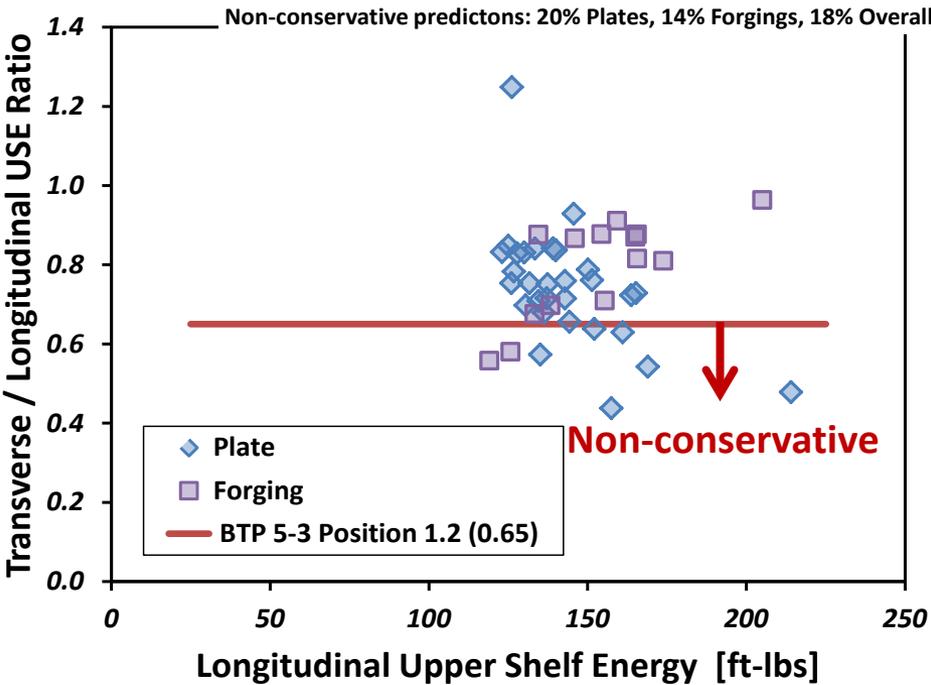
where

| | |
|---|---|
| $USE_{LONG}$ | is CVN energy measured by longitudinally oriented specimens on the upper shelf |
| $USE_{TRANS}$ | is the estimated CVN energy for transversely oriented specimens on the upper shelf |

# Position 1.2

**Assessing: $USE_{TRANS} = 0.65 \times USE_{LONG}$**

Same data plotted two different ways



Non-conservative predictons: 20% Plates, 14% Forgings, 18% Overall

Non-conservative

Plate
Forging
BTP 5-3 Position 1.2 (0.65)

Transverse / Longitudinal USE Ratio
Longitudinal Upper Shelf Energy [ft-lbs]

Non-conservative predictons: 20% Plates, 14% Forgings, 18% Overall

Plate
Forging
BTP 5-3 Position 1.2 (0.65)

Non-conservative

Percentile
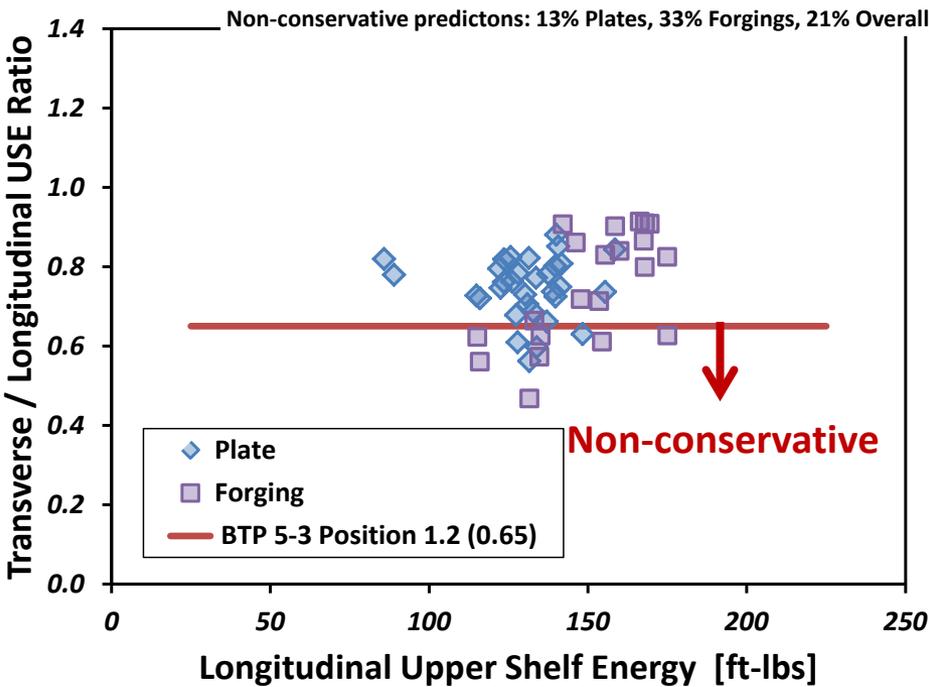Transverse / Longitudinal USE Ratio

**Position is non-conservative about 18% of the time**

**EG&G Data**

# Position 1.2
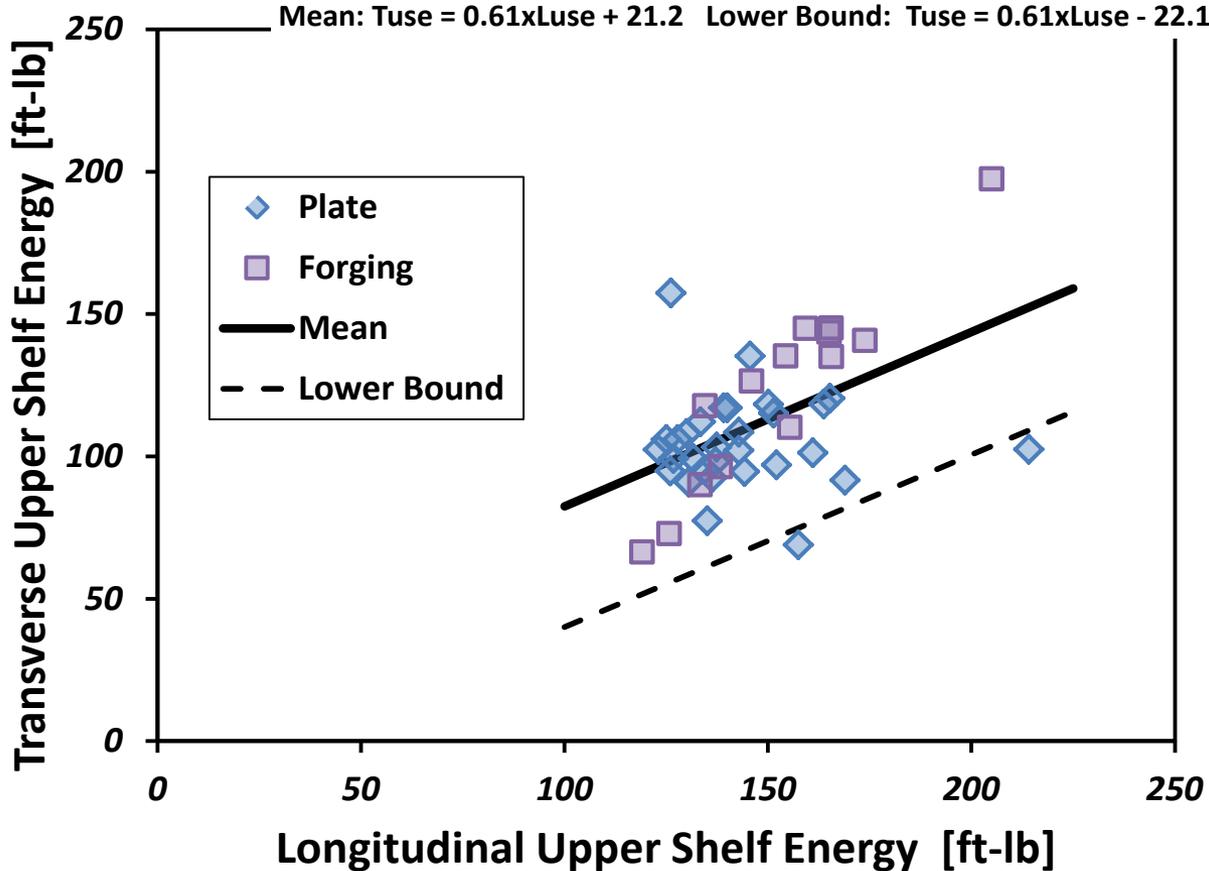## Assessing: $USE_{TRANS} = 0.65 \times USE_{LONG}$



Same data plotted two different ways

Non-conservative predictons: 13% Plates, 33% Forgings, 21% Overall
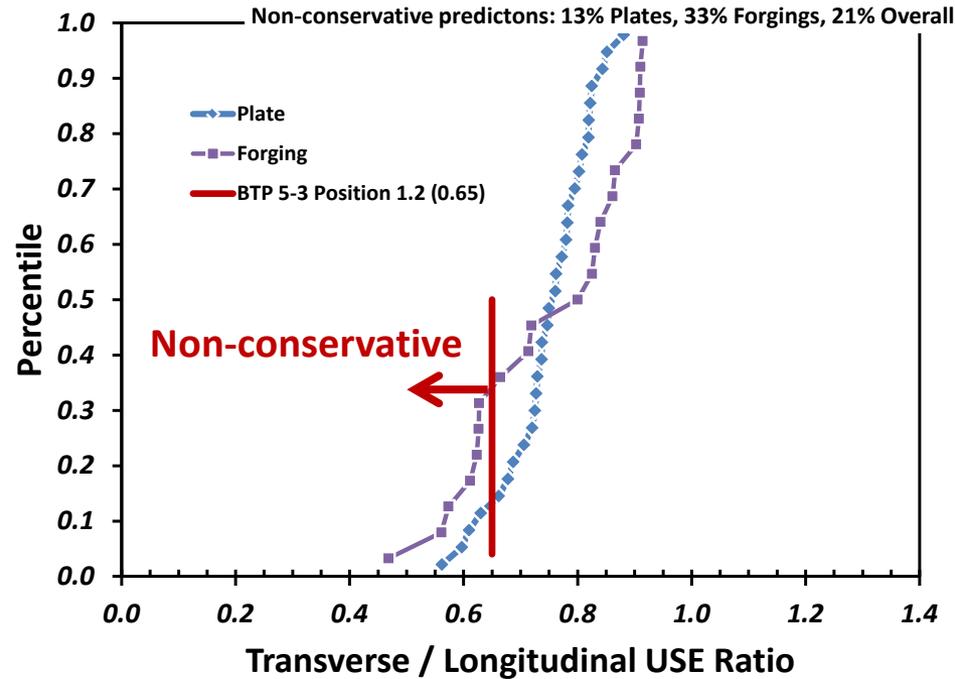
**Position is non-conservative about 21% of the time**

**Raw Data**

# Position 1.2

## Assessing: Alternative USE$_{TRANS}$ Estimates



Mean: Tuse = 0.61xLuse + 21.2   Lower Bound:  Tuse = 0.61xLuse - 22.1

Preliminary analysis suggests that alternative formulae could be developed to convert longitudinal to transverse USE values in a manner that is always conservative.

EG&G Data

# Position 1.2
## Assessing: Alternative USE$_{TRANS}$ Estimates



Mean: Tuse = Luse - 36   Lower Bound:  Tuse = Luse - 65
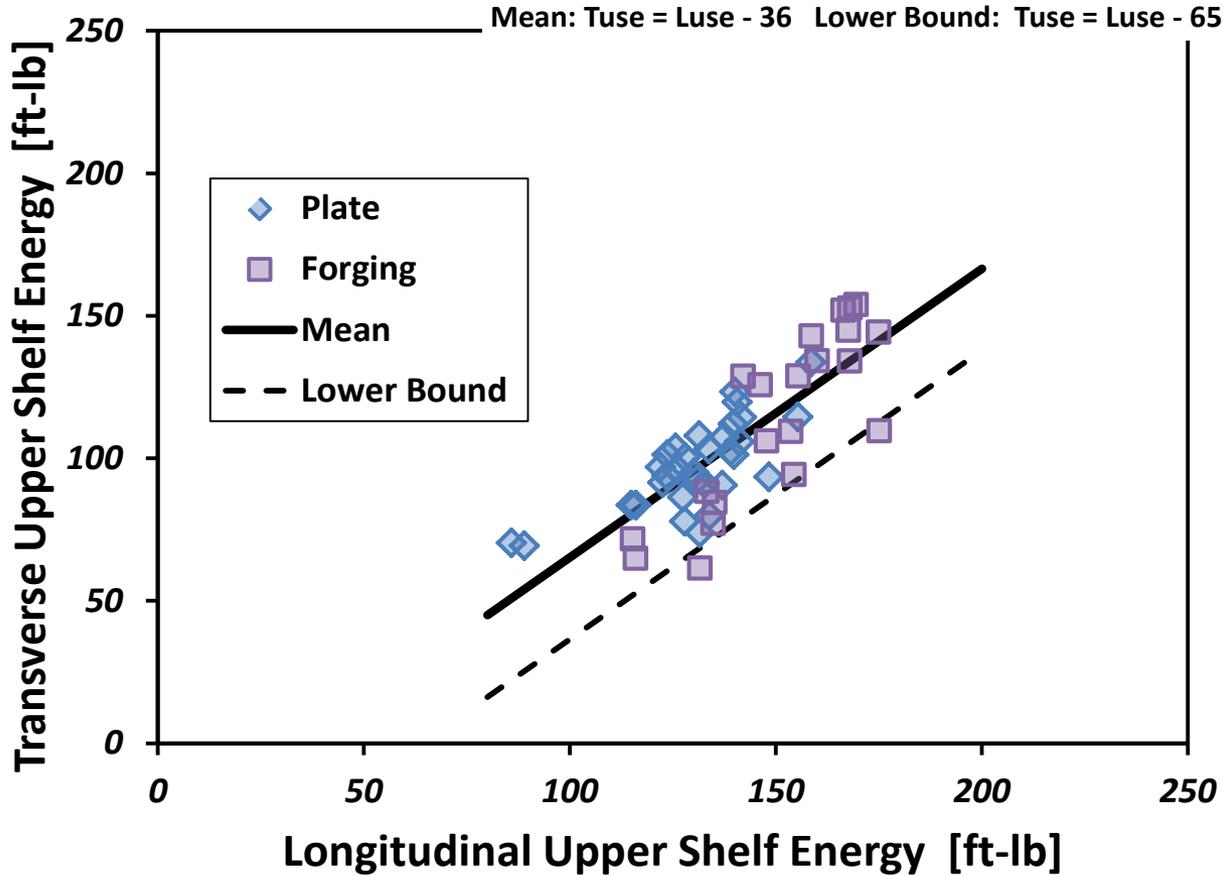
**Preliminary analysis suggests that alternative formulae could be developed to convert longitudinal to transverse USE values in a manner that is always conservative.**

Raw Data

# Summary on Part I – Technical Evaluation

- Positions 1.1(3) and 1.2
  - Results of the two studies are similar
  - Staff analysis confirms non-conservatism
- Position 1.1(4)
  - EG&G report demonstrates position is non-conservative
  - Awaiting NDTT data from Archives to complete staff assessment

| Position of BPT 5-3 | | Forging Non-Conservative Prediction Rate | | Plate Non-Conservative Prediction Rate | |
|---|---|---|---|---|---|
| | | EG&G Data | Raw Data | EG&G Data | Raw Data |
| 1.1(3) | (a) TRANS = 0.65×LONG | 43% | 48% | 33% | 19% |
| | (b) $T_{C(TRANS)} = T_{C(LONG)} + 20\ °F$ | 50% | 57% | 70% | 63% |
| 1.1(4) | $RT_{NDT} = T_{45(LONG)}$ | 93% | TBD | 38% | TBD |
| | $RT_{NDT} = T_{30(LONG)} + 20\ °F$ | 93% | TBD | 38% | TBD |
| 1.2 | $USE_{TRANS} = 0.65 \times USE_{LONG}$ | 14% | 33% | 20% | 13% |

# Part II: Assess Potentially Affected Plants - Position 1.1(3)

Plant Identification

- Search RVID for plants using BTP 5-3 to determine plate (forging) $RT_{NDT(u)}$:

  20 operating plants

- Rank plates (forging) according to the difference between $RT_{PTS}$ at 32 EFPY and 270 °F:

  Eight plants have their limiting plates or forgings using BTP5-3 with difference less than 100 °F.
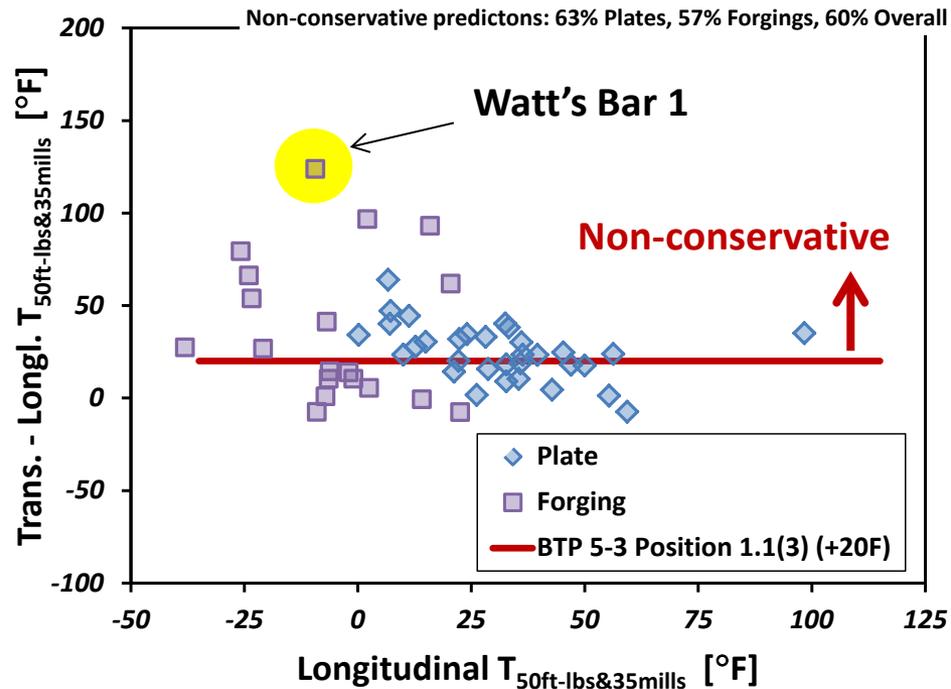
# Plant-specific evaluation results

- The majority of the plants did not specify which BTP 5-3 B1.1 position was used in determining their $RT_{NDT(u)}$ values

- Details of calculation of $RT_{NDT(u)}$ values are not available.

- One plant has full transverse Charpy data and the staff confirmed that BTP 5-3 was not used , so it will be dropped from the list

- A few plants have full longitudinal Charpy data
    - The staff's $RT_{NDT(u)}$ values using lower bound Charpy data
      and linear interpolation between two temperatures are
      lower than the licensee's value by 10 °F

- A few plants may have PTS concern because the $RT_{PTS}$ values are below 270 °F <u>by less than 75 °F</u>
    - In one case, the longitudinal Charpy data for one plate are
      significantly higher than other plates, indicating potential mislabeling
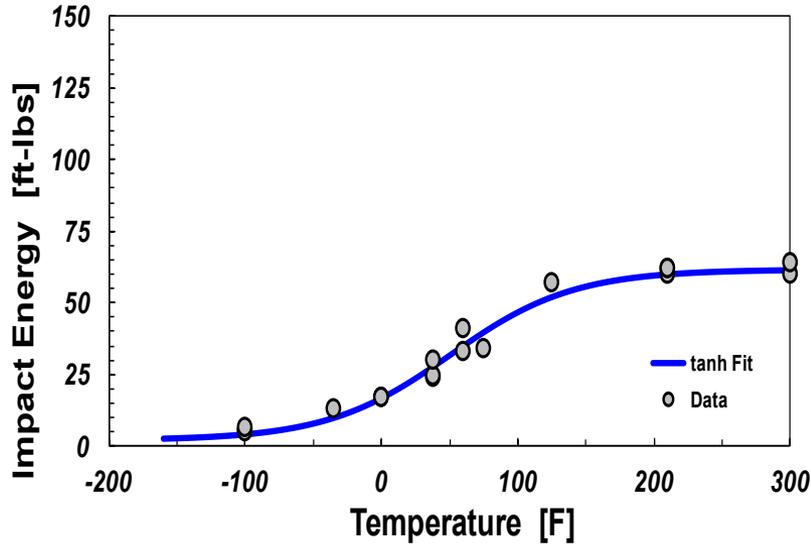
# Why do we use the Selecting criterion of 75 °F?

**- Identify raw data with the greatest conservatism and non-conservatism**

Watts's Bar 1 – greatest non-conservatism
Millstone 2 – greatest conservatism

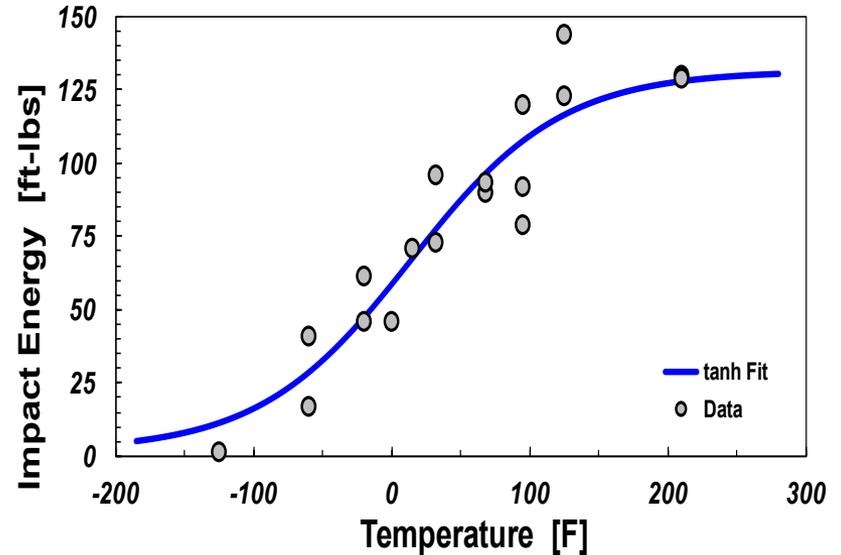Non-conservative predictons: 63% Plates, 57% Forgings, 60% Overall

Watt's Bar 1

Non-conservative

Trans. - Longl. $T_{50ft\text{-}lbs\&35mills}$ [°F]

Longitudinal $T_{50ft\text{-}lbs\&35mills}$ [°F]

Plate
Forging
BTP 5-3 Position 1.1(3) (+20F)

# Closer Look at the Charpy Data with the Greatest Non-Conservatism



| $T_{50flb}$ [°F] | $T_{35mill}$ [°F] |
|---|---|
| 114.5 | 83.0 |

**Transverse Data**

| $T_{50flb}$ [°F] | $T_{35mill}$ [°F] |
|---|---|
| 31 | - |

**Longitudinal Data X .65**

| $T_{50flb}$ [°F] | $T_{35mill}$ [°F] |
|---|---|
| -15.5 | -9.4 |

**Longitudinal Data**

# Determine the $RT_{NDT}$ for the Raw Data with the Greatest Non-Conservatism

- Nil-ductility transition temperature (NDTT): -22 °F
- Official $RT_{NDT(u)}$ value: = <u>54.5 °F</u>

  (114.5 °F - 60 °F)
- $RT_{NDT(u)}$ based on BTP 5-3B1.1(3)a: -22 °F

  (At 31 °F, the equivalent Charpy energy (.65 x

  longitudinal data) is 50 ft-lb; $RT_{NDT}$ = NDTT)
- $RT_{NDT(u)}$ based on BTP 5-3B1.1(3)b: <u>-22 °F</u>

  (At -15.5 °F, the Charpy energy is 50 ft-lb; since the

  adjusted temp is (-15.5 °F + 20 °F ), less than (-22°F +

  60 °F), $RT_{NDT}$ = NDTT)

# Summary on the Study Focusing on the Raw Data with the Highest Non-Conservatism

- The highest non-conservative raw data is about 75 °F

- $RT_{NDT}$ determination is not sensitive to whether B1.1(3)a or B1.1(3)b is used for this case

- $RT_{NDT}$ determination is affected by whether curve fitting of the entire Charpy data or hand calculations based on Charpy data at two temperatures are used

# Part II: Assess Potentially Affected Plants - Position 1.2

- **Plant Identification**
  - 45 operating plants identified in RVID as using Position 1.2
  - RVID clearly identifies Position 1.2 as *UNIRR_USE_METHOD*=65%
  - Spot-checking of RVID references to confirm accuracy still TBD

- **Non-conservatism**
  - Data analysis shows the Position 1.2 estimate to be non-conservative between 13% and 33% of the time

# Next Steps

**NRC**

- **Complete technical analysis**
  - Need NDTT data from Archives to complete assessment of Position 1.1(4)
  - Investigate GE $RT_{NDT(u)}$ procedure
  - Document findings
- **Complete plant assessment**
  - Need to assess the impact to Pressure-temperature limits
  - Recommend to NRC management regarding use of interim conservatism in defining $RT_{NDT(u)}$ for the plants which may need to update their PTS evaluations
- **Communicate findings to affected plants**
  - Precise means TBD
- **May need to revise BTP 5-3 in Standard Review Plan**

**Industry**

- **Assess the impact of reported potential non-conservatism including the need to redefine the $RT_{NDT(u)}$ on pressure-temperature limits and PTS evaluations**

# BACKUP SLIDES

# Comparison of Charpy Fit Methods

| Method | NDTT [°F] | Meas. $T_{50}$ [°F] | Trans. $T_{50}$ [°F] | $RT_{NDT}$ [°F] | Non Conservatism [°F] |
|---|---|---|---|---|---|
| Charpy Fit Method: *tanh* (mean) | | | | | |
| NB-2331 | -22 | 114.5 | 114.5 | 54.5 | --- |
| 1.1(3)a: Energy*0.65 | -22 | 31 | 31 | -22 | 76.5 |
| 1.1(3)b: $T_{50(LONG)}$+20 °F | -22 | -15.5 | 4.5 | -22 | 76.5 |
| Charpy Fit Method: Interpolate lower bound data | | | | | |
| NB-2331 | -22 | 109.5 | 109.5 | 49.5 | --- |
| 1.1(3)a: Energy*0.65 | -22 | 41 | 41 | -19 | 68.5 |
| 1.1(3)b: $T_{50(LONG)}$+20 °F | -22 | 0 | 20 | -22 | 71.5 |

## Main Points

- There is some effect of *tanh* fitting versus lower-bound interpolation
  - Interpolation can produce higher or lower transition temperature values than *tanh* fitting

- Using either Charpy fitting method, BTP 5-3 Position 1.1(3) is non-conservative