
Evaluation and Compilation of DOE Waste Package Test Data

Biannual Report: February 1987 - July 1987

Prepared by C. Interrante, E. Escalante, A. Fraker, D. Hall, S. Harrison,
W. Liggett, M. Linzer, R. Ricker, J. Ruspi, R. Shull

U.S. Department of Commerce
National Bureau of Standards

Prepared for
U.S. Nuclear Regulatory
Commission

8806070059 880531
PDR NUREG
CR-4735 R PDR

NOTICE

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, or any of their employees, makes any warranty, expressed or implied, or assumes any legal liability of responsibility for any third party's use, or the results of such use, of any information, apparatus, product or process disclosed in this report, or represents that its use by such third party would not infringe privately owned rights.

NOTICE

Availability of Reference Materials Cited in NRC Publications

Most documents cited in NRC publications will be available from one of the following sources:

1. The NRC Public Document Room, 1717 H Street, N.W.
Washington, DC 20555
2. The Superintendent of Documents, U.S. Government Printing Office, Post Office Box 37082,
Washington, DC 20013-7082
3. The National Technical Information Service, Springfield, VA 22161

Although the listing that follows represents the majority of documents cited in NRC publications, it is not intended to be exhaustive.

Referenced documents available for inspection and copying for a fee from the NRC Public Document Room include NRC correspondence and internal NRC memoranda; NRC Office of Inspection and Enforcement bulletins, circulars, information notices, inspection and investigation notices; Licensee Event Reports; vendor reports and correspondence; Commission papers; and applicant and licensee documents and correspondence.

The following documents in the NUREG series are available for purchase from the GPO Sales Program: formal NRC staff and contractor reports, NRC-sponsored conference proceedings, and NRC booklets and brochures. Also available are Regulatory Guides, NRC regulations in the *Code of Federal Regulations*, and *Nuclear Regulatory Commission Issuances*.

Documents available from the National Technical Information Service include NUREG series reports and technical reports prepared by other federal agencies and reports prepared by the Atomic Energy Commission, forerunner agency to the Nuclear Regulatory Commission.

Documents available from public and special technical libraries include all open literature items, such as books, journal and periodical articles, and transactions. *Federal Register* notices, federal and state legislation, and congressional reports can usually be obtained from these libraries.

Documents such as theses, dissertations, foreign reports and translations, and non-NRC conference proceedings are available for purchase from the organization sponsoring the publication cited.

Single copies of NRC draft reports are available free, to the extent of supply, upon written request to the Division of Information Support Services, Distribution Section, U.S. Nuclear Regulatory Commission, Washington, DC 20555.

Copies of industry codes and standards used in a substantive manner in the NRC regulatory process are maintained at the NRC Library, 7920 Norfolk Avenue, Bethesda, Maryland, and are available there for reference use by the public. Codes and standards are usually copyrighted and may be purchased from the originating organization or, if they are American National Standards, from the American National Standards Institute, 1430 Broadway, New York, NY 10018.

Evaluation and Compilation of DOE Waste Package Test Data

Biannual Report: February 1987 - July 1987

Manuscript Completed: November 1987
Date Published: May 1988

Prepared by
C. Interrante, E. Escalante, A. Fraker, D. Hall, S. Harrison,
W. Liggett, M. Linzer, R. Ricker, J. Ruspi, R. Shull

U.S. Department of Commerce
National Bureau of Standards
Center for Materials Science and Engineering
Metallurgy Division - Corrosion Section
Gaithersburg, MD 20899

Prepared for
Division of High-Level Waste Management
Office of Nuclear Material Safety and Safeguards
U.S. Nuclear Regulatory Commission
Washington, DC 20555
NRC FIN A4171

ABSTRACT

The report summarizes results of the National Bureau of Standards (NBS) evaluations of Department of Energy (DOE) activities on waste packages designed for containment of radioactive high-level nuclear waste (HLW). The waste package is a proposed engineered barrier that is part of a permanent repository for HLW. Metal alloys are the principal barriers within the engineered system. Technical discussions are given for the corrosion of metals proposed for the canister, particularly carbon steels, stainless steels, and copper. The current level of understanding of several canister materials is questioned for the candidate repository in tuff. Three issues are addressed, the possibility of the stress-induced failure of Zircaloy, the possible corrosion of copper and copper alloys, and the lack of site-specific characterization data. Within the Basalt Waste Isolation Project (BWIP) section of this report, discussions are given on problems concerning localized corrosion and environmentally assisted cracking of AISI 1020 steel at elevated temperatures (150°C). For the proposed salt site, the importance of the duration of corrosion tests and some of the conditions that may preclude prompt initiation of needed long-term testing are two issues that are discussed. NBS work related to the vitrification of HLW borosilicate glass at the West Valley Demonstration Project (WVDP) and the Defense Waste Processing Facility (DWPF) is discussed. Activities of the Materials Characterization Center (MCC) are presented. To stress the benefit and necessity of independent data interpretations, an illustration is given.

TABLE OF CONTENTS.

	<u>Page</u>
ABSTRACT	iii
TABLES OF CONTENTS	v
LIST OF FIGURES _	vii
EXECUTIVE SUMMARY	xi
1.0 INTRODUCTION	1
2.0 NNWFI -- NEVADA NUCLEAR WASTE STORAGE INVESTIGATIONS	
2.1 Zircaloy	1
2.2 Copper	4
2.3 Spent Fuel	3
2.4 Glass	5
2.5 Additional Discussion	6
3.0 BWIP -- BASALT WASTE ISOLATION PROJECT	7
3.1 Reviews	7
3.2 Conclusions	9
4.0 SRP -- SALT REPOSITORY PROJECT	9
4.1 Potential Problem Areas	10
4.2 Reviews	11
5.0 VITRIFICATION OF HIGH-LEVEL WASTE	12
5.1 Technical Issues	12
5.2 Reviews	13
5.3 Technical Exchange Meetings	15
6.0 MCC -- MATERIALS CHARACTERIZATION CENTER	16
6.1 Program Administration	17
6.2 Quality Assurance	17
6.3 Support to the Office of Geologic Repositories (RW-23)	18
6.4 Salt Repository Project	19
6.5 Basalt Waste Isolation Project	19
6.6 Defense High-Level Waste Technology Project	19
6.7 Transportation Technology Center	20
6.8 West Valley Demonstration Project	21
6.9 Comments	22

TABLE OF CONTENTS (cont.)

	<u>Page</u>
7.0 AN ILLUSTRATION OF UNCERTAINTIES IN THE CHOICE OF GLASS COMPOSITION	23
7.1 Introduction	23
7.2 Response Surface Experiments	24
7.3 Reinterpretation of a Leaching Experiment	25
7.4 Recommendations	28
8.0 REFERENCES	35
Appendix A. Draft NBS Reviews of DOE Reports Concerning the Durability of Proposed Packages for High-Level Radioactive Wastes	A-1
Appendix B. Database Activities for the NBS/NRC Database for Reviews and Evaluations of High-Level Waste Data.	B-1

LIST OF FIGURES

	<u>Page</u>
1. Experimental Apparatus Used in Laboratory Leaching Tests	14
2. Normalized Si Release Predicted by Cubic Model from 101 Data Points and Quadratic Model from 76 Data Points	30
3. Normalized Si Release Predicted by Cubic Model from 101 Data Points and Quadratic Model from 76 Data Points	31
4. Normalized Waste Release Predicted by Cubic Model from 76 Data Points	32
5. Composite Leach Response Predicted by Quadratic Model from 76 Data Points	33

EXECUTIVE SUMMARY

This is the third biannual progress report on the National Bureau of Standards (NBS) assessments of the Department of Energy (DOE) activities related to the waste package for disposal of radioactive high-level waste (HLW). It contains NBS reviews conducted over the period February 1, 1987, to July 31, 1987, on DOE reports related to activities of the three DOE project offices for candidate repositories in host media of basalt, salt, and tuff. Status reports given here highlight the NBS assessments of DOE activities of these three offices. In addition, a summary is given for the activities of the Materials Characterization Center.

For the candidate repository in tuff, ten reviews of publications resulting from DOE sponsored work in the Nevada Nuclear Waste Storage Investigations (NNWSI) during this six-month period are given. Discussion of this work is divided into four categories: Zircaloy, copper, spent fuel, and glass. Three issues are emphasized: (1) the possibility of stress-induced failure of Zircaloy, (2) the possible high corrosion rates for copper and copper alloys, and (3) the lack of site-specific characterization data.

In the two previous biannual NBS reports, the major deficiencies in the available data pertaining to a waste repository in basalt were noted, with specific emphasis placed on the corrosion resistance of the candidate waste-package container materials. Four of the evaluations completed during the present reporting period indicate that AISI 1020 steel, a candidate waste-canister material, exhibits both localized corrosion and environmentally assisted cracking at elevated temperatures (150°C) when immersed in basalt repository-like groundwater. If this material is to receive further consideration, much more work at the Basalt Waste Isolation Project (BWIP) is required in the areas of establishing conservative "time-to-failure" values. Further research on different thickness of rolled plate and on weldments is also necessary. Improvements to the simulation of repository environments for laboratory studies have been made; however, more data are needed to verify the exact chemical reactions to be expected under repository conditions.

For the Salt Repository Project (SRP), an overview of the Deaf Smith site and its potential problem areas points up the importance of the duration of corrosion tests and of some of the conditions that may preclude prompt initiation of needed long-term testing. Five reviews of SRP reports are presented. Three are concerned with colloidal sodium. A fourth which discussed the corrosion of type A-216 steel

demonstrates the considerably higher corrosion rates associated with high-magnesium brines. A fifth review concerns buckling of a container, and it highlights the importance of mechanically induced stress on local corrosion processes.

Technical exchange meetings were held at two sites expected soon to produce vitrified HLW, the West Valley Demonstration Project (WVDP) and the Defense Waste Processing Facility (DWPF). These meetings concluded with the understanding that technical discussions in greater depth and sharper focus are needed to keep abreast of current developments. The principal concerns are (1) verification of the composition of production runs, and (2) leaching characteristics (in actual repository environments) of the specified glass composition.

Reviews of several reports on glass leaching are included, and many more have been initiated but not yet completed. The leaching characteristics of vitrified HLW can be affected by various factors, principal among which are the composition of the glass used to vitrify the HLW and the environment in which the leaching may take place. Repository environments are simulated in laboratory tests. Refinements in these simulated repository conditions have been implemented to improve prediction of leach rates in a repository, using the laboratory tests. In leaching of glass, a preliminary assessment of the role of redox potential (Eh) leads to the conclusion that solutions of a more reducing nature are less aggressive. This suggests that repositories in which reducing conditions persist in the vicinity of the waste package would be desirable and would favor low leaching rates of vitrified waste.

Pertinent activities of the Materials Characterization Center are summarized and included here in eight categories, which correspond to categories of the MCC's monthly reports. These are Program Administration, Quality Assurance (QA), and support to various offices: the Office of Geologic Repositories, the Salt Repository Project (SRP), the Basalt Waste Isolation Project (BWIP), the Defense HLW Technology Program (DP-12), the Transportation Technology Center (TTC), and the West Valley Demonstration Project (WVDP). It appears that increased support and cooperation on the part of all repository offices and other pertinent DOE offices is needed. Such support will enable MCC to meet their objectives of ensuring materials data are available on waste materials, by developing standard test methods, testing waste (and other) materials, and publishing the Nuclear Waste Materials Handbook.

An example of an NBS alternate interpretation of published data on glass is given in this report to stress the benefit and necessity of independent interpretation of data used in predicting the performance of materials proposed for use in a nuclear waste package. This illustration contrasts published results with results obtained from an alternate NBS interpretation of the same data. A conclusion reached from the alternate analysis is that leach rates of glass recommended in the original report would be improved by changing the recommended composition, in particular, by substitution of Al_2O_3 for Na_2O .

An appendix on the NBS/NRC Data Center activities describes various software enhancements developed recently to aid in data handling and retrieval. For data retrieval, it highlights a menu system developed for use by both novice and experienced users.

1.0 INTRODUCTION

Current NBS activities related to reviews and evaluations of the Department of Energy (DOE) waste-package activities are detailed in this biannual report. Reviews related to research performed for the three DOE project offices, the Nevada Nuclear Waste Storage Investigations (NNWSI), the Basalt Waste Isolation Project (BWIP), and the Salt Repository Project (SRP) are discussed in sections 2 through 4, respectively.

DOE is actively engaged in programs for the vitrification of high-level radioactive waste in borosilicate glass. Both the West Valley Demonstration Project (WVDP) at West Valley, New York and the Defense Waste Processing Facility (DWPF) located at the Savannah River Plant near Aiken, South Carolina are expected to vitrify HLW in the near future. NBS activities in this area have continued to increase; six reports were reviewed during this reporting period. The work on glass is presented in section 5. In section 7, an illustration of the uncertainties in the choice of glass composition is given to illustrate the importance of independent interpretation of data.

Activities of the DOE-sponsored Materials Characterization Center for the period January 1, 1987, through June 30, 1987, are discussed in section 6.

Draft NBS reviews and evaluations conducted over the period February 1, 1987, through July 31, 1987, are included as Appendix A; contributing reviewers for these works are acknowledged as a group on the cover page of this report. As reviews are completed and approved for publication, they are included in the NBS/NRC Database for Reviews and Evaluations on High-Level Waste Data. One of the NBS goals is to make this database "user friendly". The system is designed so that it is easy for the novice searcher to find relevant information quickly and with a minimum of effort and training. Appendix B contains information on database activities for the period covered in this report.

Studies involving laboratory testing at the NBS are continuing in four areas, but no reports on this work are given here. These tests were initiated in June, 1987, and present plans indicate that completions can be expected during 1988 on some aspects of these studies. Reports are likely to be issued separately for each study. The objective of these laboratory tests is to confirm the accuracy of DOE data and the validity of the conclusions deduced from it. Topics of these four studies are as follows: (1) Evaluation of Methods for Detection of Stress Corrosion Crack

Propagation in Fracture Mechanics Samples, (2) Effect of Resistivity and Transport on Corrosion of Waste Package Materials, (3) Pitting Corrosion of Steel Used for Nuclear Waste Storage, and (4) Corrosion Behavior of Zircaloy Nuclear Fuel Cladding.

2.0 NNWSI - NEVADA NUCLEAR WASTE STORAGE INVESTIGATIONS

One of the three proposed nuclear-waste repository sites is the Yucca Mountain site. It is located in the Yucca Mountains of Nevada about 100 miles northwest of Las Vegas. The Environmental Assessment published by the Department of Energy (DOE) describes a repository located 400 m below the surface and 100 m above the water table. Tuff, the geologic formation found here, is composed of a dry, compacted volcanic ash.

Ten reviews were concluded during this reporting period, and three issues of concern were emphasized. Briefly, these concerns deal with the possibility of stress-induced failure of Zircaloy, the possible high corrosion rate of copper and copper alloys, and the lack of site-specific characterization data.

The reviews of publications resulting from DOE-sponsored work in NNWSI during this six-month period are divided into four categories as follows: (1) Zircaloy, (2) copper, (3) spent fuel, and (4) glass. Each will be discussed within its own category, followed by a general discussion of other important issues not necessarily identified in these reviews.

2.1 Zircaloy

Radioactive fuel, in the form of small cylinders, is clad (encased) in a thin-walled Zircaloy sleeve. Failure of the Zircaloy sleeve allows the escape of radioactive material. Thus, two potentially important areas of research are the causes of failure of the sleeve and the rate of dissolution of the radioactive waste after this cladding has been breached.

Two publications describe plans for future experiments designed to provide information on the corrosion reactions of Zircaloy [Smith 1986a; Smith 1986b]. Both publications consider two simulated repository conditions. The first condition simulates that period in the life of a repository after 90 to 100 years of closure, and it assumes an unbreached canister holding breached Zircaloy-clad fuel rods. The second condition simulates the period 1000 years after closure, and it assumes a breached canister and breached fuel rods. Information on the progress of the corrosion reactions will be obtained from chemical analysis of water samples in which the materials are immersed. Samples are taken periodically throughout the experimental periods (2, 6, and 12 months). Examination of the corroded surfaces after the experiments may include metallographic examination using light microscopes, scanning electron microscopy, and Auger

techniques. Whereas these surface measurements will provide valuable information, they could be augmented by including other measurements during the test, such as electrochemical polarization, a.c. impedance, and other appropriate electrochemical measurements that can provide information on corrosion rate [Smith 1986b].

In the second report, Smith describes an experimental plan in which the stress corrosion failure of Zircaloy is studied. C-rings machined from "defueled" Zircaloy cladding are loaded to an unspecified stress level and exposed to the same environments described in the previous experiment. This test procedure does not conclusively reveal the susceptibility of Zircaloy to stress corrosion cracking (SCC) because failure may occur through other means (Hydride formation, for example, may embrittle the alloy and lead to failure). In the absence of failure in the proposed tests, slow-strain-rate measurements would provide a more severe test of susceptibility to SCC [Smith 1986a]. Other workers have shown embrittlement of Zircaloy in gaseous iodine at 350°C with increased tendency to failure at low oxygen concentrations [Gangloff 1979].

The third report relating to Zircaloy is an early listing of a variety of proposed experiments and experiments in progress [Ballou 1985a].

2.2 Copper

Prior to emplacement in a repository, fuel rods will be placed in metal canisters that will facilitate handling and prevent the movement of radioactive waste into the environment after the repository is closed. Because copper is one of the metals being considered as a container material, information on the rate of corrosion of copper in a tuff environment is important.

Ballou, L. B. and McCright, R. D. provided an early description of plans for testing copper as a possible canister material [Ballou 1985b]. Implementation of these plans resulted in a two-year study which concludes that copper and two of its alloys appear to be good candidates for use as canister materials, but this report cautions that the effects of gamma radiation on the corrosion behavior of these metals has not been addressed. The authors point out that nitric acid is severely corrosive to copper and copper alloys, even in fairly dilute solutions of nitric acid. This consideration becomes extremely important because other workers, Van Konynenburg in 1986 and Abrajano in 1986, have indicated that nitrogen fixation by gamma radiation will lead to the formation of nitric acid [Abrajano 1986; Van Konynenburg 1986].

2.3 Spent Fuel

Once the Zircaloy sleeve (or cladding) of a fuel rod is breached, the release of radionuclides can occur. If the metal canister holding the fuel rods is also breached, moisture can contact the spent fuel. In the presence of moisture, dissolution of the spent fuel is one mechanism for the release of radionuclides. The oxidation state of the spent fuel affects the rate at which this dissolution will take place. Oxidation is one of many important factors in this process.

Oxidation of spent fuel contained in breached Zircaloy cladding can increase the solubility and concentration of specific radionuclides. Einzinger describes a series of tests to measure the degree of oxidation of spent fuel under various conditions of exposure (temperature, moisture, time). However, it is not clear whether the authors have taken into consideration the increased vapor pressure of water at elevated temperatures. An increase in vapor pressure could result in oxidation rates considerably different from those in dry air [Einzinger 1986].

The rules and regulations for licensing a high-level nuclear waste repository, as set by NRC and EPA, are discussed by Oversby in UCRL-94659 [Oversby 1986]. Site-specific performance-assessment calculations are necessary in order to compare the behavior of the waste form under the conditions of exposure for all proposed sites. Oversby reviews the factors that affect radionuclide release rates and identifies the following six areas where new data are needed: (1) the effect of reactor type on the dissolution properties of spent fuel, (2) dissolution of stainless steel clad fuel, (3) dissolution of oxidized spent fuel, (4) dissolution of assembly components, (5) inventory and release characteristics of carbon-14, and (6) thermodynamic properties of solids that may limit radionuclide solubility.

2.4 Glass

Materials other than spent fuel rods will be vitrified into borosilicate glass. The vitrified waste materials will be placed in metallic canisters. The effects of radiation on this vitrified waste and its subsequent solubility are important.

Theoretical modeling calculations on the effects of radiation on waste glass tested in water, as described by Van Konynenburg result in reasonable agreement with experimental observations. On the basis of these modeling calculations, it is shown that the principal reactions result in the

formation of H_2 , O_2 , NO_2^- , NO_3^- , and H^+ [Van Konynenburg 1986]. Abrajano, et al., describe a more recent compilation of experimental data on which the modeling calculations of the Van Konynenburg reference are based in part. These experimental data emphasize that the production of nitric acid is an important reaction during the irradiation of moist air. However, dissolution of the glass waste and buffering action of the bicarbonate in tuff tend to counter the effect of the nitric acid so that the pH drops no lower than 6.4. The effect on glass dissolution is less than originally expected [Abrajano 1986].

UCRL-15723 and ANL-85-41 describe a test for measuring dissolution of radionuclides in unsaturated repository conditions. J-13 water is dripped onto a radionuclide-doped glass form in a tuff cup. Analysis of leachate provides information on the rate of radionuclide dissolution. Local dissolution of the stainless-steel waste holder increased the rate at which the matrix breaks down and this resulted in an increased rate of radionuclide release [Bates 1985; Bates 1986].

2.5 Additional Discussion

Of the three sites proposed for the first repository, Yucca Mountain is unique in its low moisture content and oxic conditions. In addition, availability of soluble salts is low; this results in a relatively noncorrosive environment. However, information on this site is based on data obtained from the surrounding land. At this time, the lack of site-specific characterization data may be the most crucial shortcoming in the program. It is on these data that critical decisions affecting the future of the NNWSI program are based.

The quality of some of the most important site characterization information, such as the composition of soluble salts in the water, is questionable. Present information on water composition for this site has been assumed to be essentially that of J-13 well water taken from a point several miles from the proposed repository site [DOE 1986]. Composition of the electrolyte bears directly on the leaching or corrosion processes by which the glass or the metallic components of a waste package will be degraded.

Well water in the compacted tuff travels through fractures and other large, interconnected imperfections in the geological formation. Pore water, held in the interstices and pores of the rock, is relatively immobile. The lack of fractures and freely flowing water in the tuff at this site make the composition of pore water all the more important.

While the composition of the pore water is unknown, it is very likely that the pore water is the most abundant water at the tuff site.

3.0 BWIP -- BASALT WASTE ISOLATION PROJECT

3.1 Reviews

In two previous biannual NBS reports, the major deficiencies in the available data pertaining to a waste repository in basalt were noted with specific emphasis placed on the corrosion resistance of the candidate waste-package container materials [Interrante 1987a; Interrante 1987b]. In the past six months, several reports on corrosion studies have been received at NBS and formal evaluations of these reports have been initiated. Four of these evaluations have now been completed and their results follow.

Anantatmula studied the corrosion behavior of AISI 1020 hot-rolled steel packed in a mixture of 75 percent basalt and 25 percent bentonite (the packing material mixture proposed for the future repository in basalt) while immersed in various liquids [Anantatmula 1984]. Twelve different tests were performed (six at 100°C and six at 200°C) using liquids comprised of deionized water and various combinations of Cl^{-1} , F^{-1} , SO_4^{-2} , and CO_3^{-2} ions. The extent of corrosion was determined by weight losses measured after 4 weeks immersion. A Plackett-Burman statistical analysis method was used to determine the significant variables. In addition, the exposed metal surfaces were studied by optical metallography, scanning electron microscopy, and X-ray diffraction. Only temperature, not the liquid chemistry, was found to be a significant variable here. However, since only twelve tests were run, and without replicate samples, the statistical relevance of this test is extremely limited. Higher corrosion rates were measured at 100°C than at 200°C, consistent with previous findings. It was concluded that the formation at higher temperatures of a partially protective iron-rich clay (iron saponite) on the surface of the metal caused this anomalous behavior [Anantatmula 1984]. Only the magnetite form of iron was found in the corrosion product on samples tested at the highest temperature. This result (which has not received much attention in the past, but certainly warrants further investigation) undoubtedly indicates different corrosion mechanisms at the two temperatures.

In 1984, a study was completed by Brehm, Lutton, Rivera, Maffei, Bohringer, Paine, and Pingel concerning the metallic corrosion likely to occur in a basalt repository. A series of 48 test specimens of Fe-9Cr-1Mo steel (normalized and

tempered) were tested at 100°C and 200°C while immersed for 1 month in liquids containing various concentrations of sulphate, carbonate, fluoride, and chloride ions. Weight-loss measurements were performed to determine the extent of corrosion [Brehm 1984]. Unfortunately, the data measured in this study, which was well planned initially, were not sensitive enough to indicate any general trends in the effects of either temperature or electrolyte on the corrosive attack of this steel. As a result, a further study using more sensitive equipment was initiated. In the present study, the electrochemical passivation characteristics of various proposed waste-container materials immersed in synthetic Grande Ronde groundwater were studied. Similar types of passive regions (although at different potentials) were found for AISI 1020 steel, Fe-9Cr-1Mo steel, and cupronickel (90Cu-10Ni). However, only the passive region for the AISI 1020 steel was specified; and it was measured to exist at potentials between -0.5 and -0.25 volts. For higher potentials than these, the AISI 1020 steel developed pits. The pitting behavior of the other steels will be the subject of a future report by these authors.

Pitman conducted a series of 20 slow-strain-rate tests at two different extension rates and at two different temperatures on AISI 1020 wrought steel plate (one of the candidate waste-package container metals) either in air or immersed in synthetic Grande Ronde groundwaters. Environmentally assisted cracking (EAC) processes were found to be occurring in this material at 150°C when tested at the lowest strain rate (2×10^{-7} /s). Compared to material tested in air, a significant reduction in cross-section area (RA) was measured for this material when it was immersed in simulated groundwater. Highly stressed regions (e.g. machined edges, sample grip areas, necked regions) of those specimens exhibiting the reduced RA values were also found to exhibit pitting attack. Further evidence of EAC in these low-ductility samples also was indicated by the presence of intergranular fracture, transgranular cleavage, and secondary cracking [Pitman 1983] on the fracture surfaces [Pitman 1983].

Jantzen conducted a simulation study of the redox potentials likely to exist in a waste repository in basalt. Since redox potentials are important to the determination of what chemical reactions will occur in a system, such information is needed for both corrosion and leaching studies. Simulation of the basalt repository Eh-pH conditions was found in this investigation to be easily achievable when crushed basalt was used as an additive to deionized water. This is preferable to previous methods of adding to the liquid environment substances foreign to the repository, such as hydrazine. However, even though the above method is good

for achieving the proper Eh values, care must still be exercised in the measurement methods used to obtain these data. Care must also be exercised in using these data to determine the extent of reactions likely to occur. This study points out the large difference in redox potentials between oxic and anoxic solutions and the consequential differences in waste-form leaching behavior. Under oxic conditions the presence of iron was also found to significantly enhance the leaching of a waste glass, SRL 165 [Jantzen 1984].

3.2 Conclusions

In conclusion, it appears that the candidate waste canister material, AISI 1020 (hot-rolled) wrought steel, exhibits both localized corrosion and environmentally assisted cracking behavior at elevated temperatures (150°C) when immersed in basalt repository-like groundwater. At this elevated temperature, this material also exhibits an overall reduction in its general corrosion rate. If this material is to receive further consideration, much more work is required, especially in the areas of establishing conservative "time-to-failure" values. Further work on different thicknesses of roll plate (each possibly possessing a different microstructure) and on weldments is also needed. Improvements in the simulation of repository environments for laboratory studies have been made. However, more experimental data is needed to verify the exact chemical reactions to be expected to occur under repository conditions.

4.0 SRP - - SALT REPOSITORY PROJECT

The Deaf Smith site is in the southern high plains of the Texas panhandle, 35 miles southwest of Amarillo in the north-central part of Deaf Smith County. Deaf Smith County is composed primarily of crop land with some rangeland and has a population density of about four people per square mile. The proposed repository site will consist of nine square miles and acquisition of the initial 61 acres required for site characterization is projected to be completed in 1987. The formal process of site characterization has begun and is projected to be completed in 1988.

The host rock of the repository is 2400 to 2500 feet below the surface and approximately 1000 feet below the aquifer that supplies much of this region with irrigation water. The host rock is bedded rock salt approximately 160 feet thick. The rock salt bed is the result of the drying of a salt lake during the Permian Age. As a result, the salt bed may contain varying amounts of impurities and included water. The presence of impurities and included water makes it difficult

to predict the chemical composition of the water which will come into contact with the waste disposal container. That is, migration of included brine to the container would result in brine with significant concentrations of ionic species (e.g. Mg) which were rejected by the salt as it crystallized (included brine), while dissolution of the salt by flooding of the repository would result in brines of low ionic content (dissolution brine). However, bedded rock salt has numerous advantages that lead to the selection of a salt-bed site, including the following:

- deep, thick and laterally extensive deposits
- low seismic activity
- stable (undisturbed for 10^7 to 10^8 years)
- high thermal conductivity
- low permeability
- easily deformed
- good radiation and shielding properties

After evaluation of salt domes and salt beds over the United States, the Deaf Smith site in May 1986 was selected for further study and characterization.

4.1 Potential Problem Areas

Land Acquisition -- In May 1986, when this site was selected for further study and characterization, all of the land at the site was privately owned. Acquisition of the land is under way and needs to be completed so that actual characterization of the site can proceed. Condemnation proceedings, if required, could delay site characterization. This would delay corrosion testing and decrease the available time for testing [GAO 1987].

On-Site Characterization -- It is important to characterize the salt environment thoroughly and begin long-term corrosion testing on the entire range of expected environments as soon as possible. The accuracies of corrosion rate estimates and their extrapolations, which are used in making lifetime predictions of the container, may be greatly affected by the duration of the tests.

Container Alloys -- At present, the primary candidate alloy for the waste container is A-216 Steel. The reasons for DOE's selection of this alloy and the reservations of NBS reviewers with this selection were discussed in previous reports [Interrante 1987a and b]. Alloy selection was based on the assumption that, if uniform corrosion of the alloy proceeds uninhibited then other corrosion-related failure mechanisms could be ignored. However, after making this assumption, DOE's test program has focused on identifying alloys with slow corrosion rates due to the formation of surface layers or scales. We believe that these scales will not be homogeneous,

that access (of the environment) to the container will not be uniform and that local electrochemical cell action cannot be avoided. As a result, pitting, crevice corrosion, stress corrosion cracking and hydrogen embrittlement are potential failure modes that must be evaluated by mechanistic modeling and experimental observations, and not by assumption.

The alternate alloy for container fabrication is Ti-code 12. Ti-code 12 was selected because of its corrosion resistance; the corrosion to be resistance of this alloy is the result of the formation of a passive film. Since local breakdown of this passive film would result in very high localized corrosion rates, the uniform corrosion assumption cannot be applied to this alloy. Also, Ti-code 12 is susceptible to hydrogen embrittlement, so that radiation-induced hydrogen evolution must be considered.

DOE is considering corrosion models that assume the rate of corrosion limited by the quantity of brine available to react with the container. This "limited-brine assumption" is a critical issue in container alloy selection. If DOE can guarantee that only limited quantities of brine will reach the containers, then alloys with very low resistance to corrosion can be used. However, if DOE is forced to assume unlimited brine then more corrosion-resistant alloys are likely to be considered.

4.2 Reviews

During the period covered by this report, five pertinent papers for the Deaf Smith site were reviewed.

Three reports are concerned with the formation of sodium colloids, which result from irradiation of the rock salt surrounding the waste-storage container [Clark 1986; Levy 1983; Levy 1984]. Interest in the formation of colloidal sodium is due to concern over the influence of colloidal sodium on the chemistry of the environment around the container. However, most of the work has concentrated on the scientific basis of radiation-induced colloid formation and not the resulting changes in chemistry, transport and corrosion behavior.

The fourth report is concerned with the corrosion of cast A-216 steel (with two different heat treatments) for waste-package containers [Westerman et al. 1986]. The tests were conducted under continuous exposure conditions (unlimited brine), which the authors consider severe. The results show that considerably higher corrosion rates result from high-Mg brines (containing 130 mg/l). The magnesium concentrations of included brine present in the salt bed are expected to be in

this range which is the water composition expected in the salt beds [Westerman 1986].

The fifth report concerns mechanical failure of the waste container by buckling [Mallett 1986]. As the authors point out, buckling is not really a "failure" mode because container integrity is preserved. Only the shape of the container will have changed. However, buckling of the container will result in high tensile stresses in the external surfaces of the container, and this condition could lead to stress corrosion cracking or hydrogen embrittlement of the container.

5.0 VITRIFICATION OF HIGH-LEVEL WASTE

The processing and properties of the glass waste form will be critically important issues as the Nuclear Regulatory Commission (NRC) makes licensing decisions on facilities for disposing of high-level waste. NBS activities in high-level-waste (HLW) vitrification provide the NRC with technical information needed in their consultations with DOE on the acceptability of vitrified waste for disposal in a repository. The NBS objective is accomplished primarily by technical assessments of work performed by DOE, its contractors, and other laboratories.

5.1 Technical Issues

The primary technical issues in HLW vitrification are reflected in three questions: (1) Will the facilities proposed by the Defense Waste Processing Facility (DWPF) and the West Valley Demonstration Project (WVDP) produce a glass of the composition to be specified, (2) how will the composition of glass poured during actual production runs be verified, and (3) will the leaching behavior of the specified glass meet NRC criteria for radionuclide release.

During the current reporting period, NBS activity in the HLW vitrification area has been directed towards the question of glass leaching. Several literature reports on glass-leaching studies have been reviewed, and a number of technical issues have been identified. Some of these issues are addressed below.

Glass leaching studies reviewed thus far indicate that the repository environment is an important factor in determining the rate of glass leaching. As discussed in section 5.2, the experimental evidence indicates that the leach rate may be lower in a repository than in laboratory tests. Because leaching studies at the candidate repositories are not now possible, improved laboratory and field simulations are an important means of predicting leaching behavior in the

repositories. Papers reviewed during this reporting period, and the work presented at the DWPF Technical Exchange Meeting, which is discussed below, show an increased emphasis on simulated repository conditions in laboratory leaching studies. Simulations include, for example, rock cups used to hold the leachant and the glass sample. Pieces of the canister metal may also be added to this simulated environment. These refinements are shown in Figure 1, which shows the apparatus used in leaching tests reported by Wicks, et al. [Wicks 1984] -- a review of this report may be found on page A-102 of this report. In principle, repository simulation tests can incorporate flow, but this variable has not been used in the simulation studies reviewed to date. These refinements make the tests potentially more reliable as indicators of behavior in real repositories. However, more detailed data on the hydrology and geology of the repository site will be needed to determine how well the simulation corresponds to the actual repository conditions. Thus, the issue of site characterization remains critical.

5.2 Reviews

Draft reviews of several papers on glass leaching were completed. These papers addressed both the leaching characteristics of various glasses under specific conditions and the methodology of glass durability testing. A review paper by Bibler, et al. considered the specific effects of simulated tuff, salt, basalt and granite environments on waste glass durability [Bibler 1986]. The reviewed work supported the hypothesis that Defense Waste Processing Facility waste glass will be more durable in the repository than in laboratory tests. However, it remains to be established that the laboratory tests adequately simulate the repositories.

Wicks, et al. described a repository simulation test in which the test vessel was made of the host rock (tuff was used in their experimental study) and pieces of canister material were included [Wicks 1984]. Such tests have been developed with the aim of closer correspondence to actual repository conditions. The paper contains good discussions of both the factors that went into the development of the test and the limitations of repository simulation methods. Experimental data indicated that tuff will act as a buffer to stabilize groundwater pH at lower values than would otherwise be obtained, thereby retarding leaching. This finding is being investigated in further studies by Wicks and co-workers.

A draft review of a key paper on the role of the redox potential (Eh) in glass leaching was completed, and it is reported under the BWIP section of this report [Jantzen 1984]. Further papers on this subject are now being reviewed to provide a more complete evaluation of work in this area of the

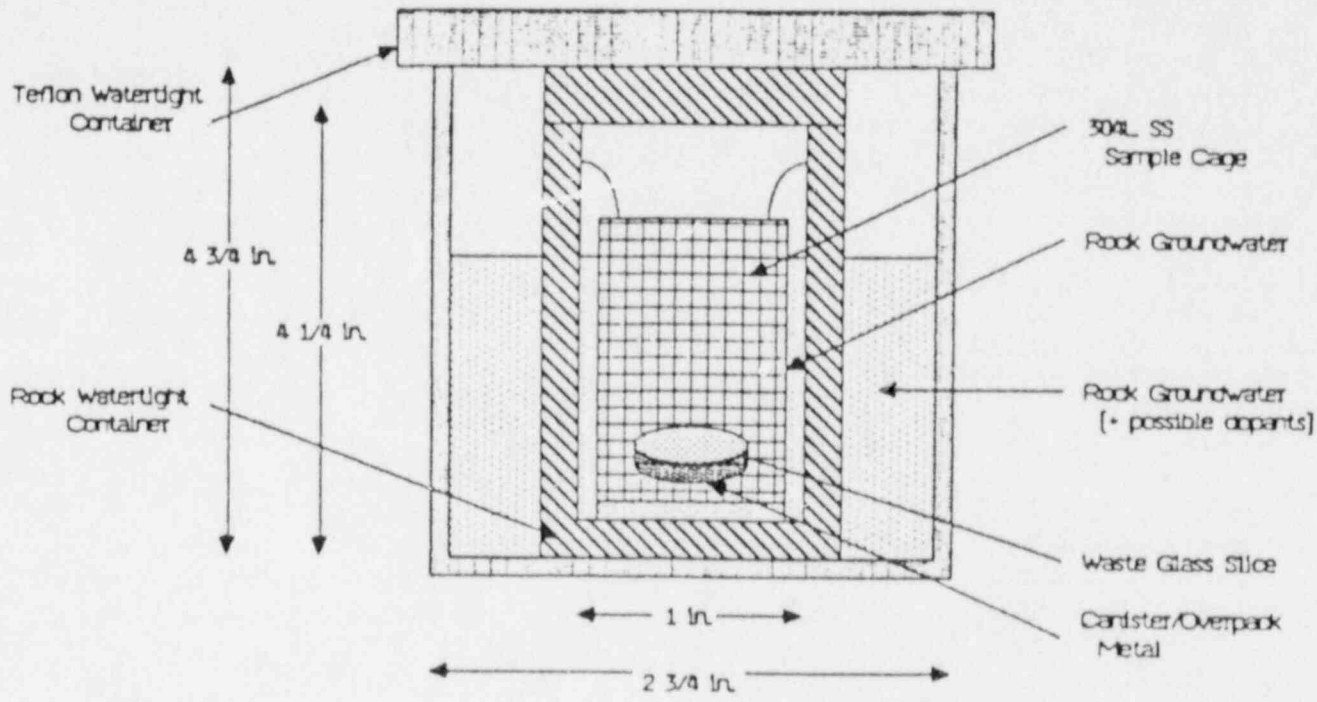


Figure 1. Experimental Apparatus Used in Laboratory Leaching Tests.

Wicks, G. G., Bibler, N. E., Jantzen, C. M., and Plodinec, M. J., "Repository Simulation Tests," Savannah River Laboratory, [DP-MS-83-138], 1984, p. 11.

nuclear waste program. As part of the review process, background documents from Swedish studies on the role of redox potential were also studied, and experts on Eh-pH (Pourbaix) diagrams were consulted. The basic conclusion in Jantzen's paper, that solutions of a more reducing nature are less aggressive in leaching glass, appears to be valid. The experimental methodology and interpretation of Eh in describing the redox behavior of leachant solutions must be considered carefully in future reviews.

Preliminary reviews of Chapters 1 and 7 of Pacific Northwest Laboratory Report PNL-5157, "Final Report of the Defense High-level Waste Leaching Mechanisms Program," have been completed. Because of the importance of Chapter 1 as a summary of progress in glass leaching studies through 1984, a multiple review was conducted. Three independent reviewers completed reviews which were edited into a single composite review. This composite review was then returned to the reviewers for comments before being submitted for the formal NBS approval process. The preliminary review of Chapter 7 is being expanded. A second reviewer has been added at the request of the first, to provide expertise in evaluating the results of modeling studies. A preliminary review of Chapter 4 of PNL-5157 has been started and is expected to be completed during August 1987. Chapters 2 and 3 have been reviewed. The reviews were returned to the reviewer for more detailed comments, with completion scheduled for December 1987. Chapters 5 and 6 have not been assigned for review.

5.3 Technical Exchange Meetings

Plants at West Valley, New York and Savannah River, South Carolina are currently developing technology and facilities for vitrifying HLW. The West Valley Demonstration Project (WVDP) deals with commercial HLW, while the Defense Waste Processing Facility (DWPF) at the DOE Savannah River Plant is working on defense HLW. Technical Exchange Meetings attended by NBS contractors and personnel, were held at both West Valley and Savannah River during this semiannual reporting period. A brief summary of these meetings follows.

The WVDP Technical Exchange Meeting took place in West Valley on February 18-19, 1987. NBS attendees included Charles Interrante, Melvin Linzer, Ernest Plante and NBS consultants Bruce Adams and John Wasylyk. Talks were presented on the processing, physical properties, and leaching behavior of the waste-glass form. A tour of the facilities was conducted as part of the meeting.

A DWPF Technical Exchange Meeting was held at Savannah River on April 22-23, 1987. This meeting was attended by Charles

Interrante and Dale Hall of NBS, and NBS consultants Bruce Adams and John Wasylyk. The meeting included tours of (1) Savannah River's HLW Waste Cave Laboratory, where laboratory-scale processing studies are carried out, (2) the Equipment Test Facility, where canister decontamination, welding and melting procedures are developed, and (3) the DWPF construction site and scale model. Several technical presentations were also made. In the area of glass HLW forms, an overview of leaching studies was given. The overview was a useful update on the SRP's views on test methods and current understanding of glass leaching behavior.

The West Valley and Savannah River Technical Exchanges gave NBS participants an opportunity to broaden their knowledge of WVDP and DWPF activities and to discuss critical issues with DOE personnel and their contractors. The meetings also provided information in a more timely manner than is possible from published documents, which usually appear some time after the reported work is carried out. At each of the Technical Exchanges, some suggestions were outlined for future NRC/NBS interactions with WVDP/DWPF personnel on HLW vitrification. Technical sessions, with discussions in greater depth and sharper focus than was possible during the formal Technical Exchanges, were recommended as an effective means of keeping abreast of current developments. To date, no such meetings have been scheduled.

6.0 MCC -- MATERIALS CHARACTERIZATION CENTER

The Materials Characterization Center (MCC) was established by the Department of Energy (DOE) in 1980 to ensure that qualified materials data are available on nuclear waste materials. This purpose is being met by (1) developing standard test methods and having them approved, (2) testing nuclear waste materials using approved test methods, and (3) publishing test procedures and data in the Nuclear Waste Materials Handbook. Test methods and data packages are submitted to the Materials Review Board (MRB) for approval.

Organizationally, the MCC and the MRB are under the Materials Integration Office (MIO), which is based in Chicago, Illinois. The MRB is made up of individual scientists from government and academia. The MCC is located in Richland, Washington and is operated for the DOE by the Pacific Northwest Laboratories (PNL) of the Battelle Memorial Research Institute. The MCC is supported at approximately a sixty percent level by the DOE, and the remainder of MCC's funding comes from the projects discussed in this report.

The MCC prepares monthly reports in addition to project reports and other various reports submitted to its supporting agencies. The MCC monthly reports are divided into the following categories.

- A. Program Administration
- B. Quality Assurance (QA)
- C. Support to the Office of Geologic Repositories (OGR)(RW-23)
- D. Support to the Salt Repository Project (SRP)
- E. Support to the Basalt Waste Isolation Project (BWIP)
- F. Support to the Defense HLW Technology Program (DP-12)
- G. Support to the Transportation Technology Center (TTC)
- H. Support to the West Valley Demonstration Project (WVDP)(NE-20)

This report is a brief summary of MCC activities from January 1, 1987, through June 30, 1987. The reader is referred to the monthly reports for further details or for information not discussed here.

6.1 Program Administration

The organization of the MCC stayed essentially the same as that reported earlier, in Figure 1 of NUREG/CR-4735, Vol. 2, 1987, page 18 [Interrante 1987b]. Work was initiated for the Sandia National Laboratory, and this is reported in the Transportation Technology Section. The MCC manager attended a program review at West Valley, New York and also met with the Materials Integration Office (MIO) manager in Chicago, Illinois to discuss the status of the MCC. There were other reviews, planning meetings and submissions of statements of work (SOW), and plans carried out under program administration. A midyear review of the MCC status in terms of budget, schedule, milestones and open issues was held in May 1987. Also the manager of MIO and technical support staff from Argonne National Laboratory (ANL) visited PNL in May to discuss an MCC five-year plan and the 1988 program. No information pertaining to the findings of the review or the meeting was given.

6.2 Quality Assurance

Records were collected for all tasks and transferred to the PNL Record Center. SRP and also BWIP records were reviewed and turned over to the respective projects. Records for reference glasses, ATM-5, ATM-6, ATM-3, ATM-4, ATM-1 and MCC-76-68 were transferred to the PNL Record Center for life-time storage. Plans were started for archival storage of ATM-5 and ATM-6 reference glasses. Storage of these records must meet requirements of PAP-802, "Test Material and Sample

Archiving," and also the more stringent requirements of the Nuclear Materials Inventory.

The MCC Quality Assurance Plan, WTC-002, reflects the formation of the Waste Technology Center (WTC). The MCC operates under this QA plan which covers work for SRP, BWIP and WVDP as well as all other work.

An internal PNL Quality Assurance (QA) audit was conducted in April 1987 and corrections were made regarding findings and observations. Various other audits were held during the 6 months covered in this report, and corrections were made. There is increased emphasis on QA, including areas of procedures, reviews, staff credentials and training.

6.3 Support to the Office of Geologic Repositories (RW-23)

Test development work, American Society for Testing and Materials (ASTM) activities, spent-fuel analysis and operations, interactions with the Commission of European Communities (CEC), and some database work are included in this activity. The CEC round-robin leach test for a granite host rock is described.

The ASTM interactions are with Committee C26 on Nuclear Waste Materials. The ASTM activity on drafting a practice for accelerated testing was completed; no further activity is planned and no further OGR support has been allocated. The MCC-1 Static Leach Test was balloted through the ASTM, and a combined subcommittee/committee ballot was sent out in June and was scheduled for completion by July 1987.

The Spent Fuel Working Group (SFWG) met in January 1987 to review a draft list of spent-fuel characteristics. Radiochemical testing is being conducted to determine fission gases including ^{129}I on the cladding and ^{135}Cs in the fuel.

Metallography/Ceramography and transmission electron microscopy (TEM) are being used for solid state analysis. Gamma scans of ATM-106 fuel rods showed high fission-gas release for some rods, but not for all, and this is being studied. Gamma scans of ATM-105 (BWR) showed higher activity in the bottom half of the fuel rod, and duplicate runs were made to verify this finding.

MCC is participating in CEC round-robin testing. The test involves repository simulation with measurements taken every 28 days and at other times up to one year. The test uses granite host rock with smectite and sand packing materials, and a SON-68-glass-waste form (a French reference waste glass) in a volvic water (commercially available bottled

granite spring water (from France) leachant under test conditions which are expected during the lifetime of a repository.

6.4 Salt Repository Project

This activity deals with a number of topics including test method development, workshops such as one held on stress corrosion cracking, sensing electrodes, and stability of brines. A draft was prepared on "Validation of Corrosion Tests." This involves test procedures for container materials under anticipated salt repository conditions. Additional material was incorporated in the SRP-BNL 1 Standard Test Method for Salt Irradiation Testing, and this method was submitted to the Lawrence Berkeley Laboratory for external peer review. The SRP-WPP 18 corrosion test method entitled "New Standard Test Method for Determination of General Corrosion Rate of Candidate Structural Materials in Brines and Brine/Salt Mixtures" was balloted through the ASTM C26.07 task group. Three negative votes were received. Plans are to eventually submit SRP-WPP 18 for ballot at the subcommittee level.

Development of a pH sensing electrode and of pH and Eh reference electrodes for use in high temperature brines continued, and tests for this development and for calibration were conducted. Efforts are being made to correct for sources of uncertainty in measuring hydrogen-ion activity, and the MCC investigators are interacting with the PNL waste-package program investigators in activities relevant to other salt repository studies. Laboratory tests are being conducted to determine the compositional stability of brines.

6.5 Basalt Waste Isolation Project

All experimental work in this activity was stopped in November 1986, and records were transmitted to the Record Center. Work on the Development of the MCC/BWIP 14.4 Waste Form Compliance Test Method has continued. This test deals with leach rates of glass waste forms such as ATM-10 and ATM-11. Hot testing of ATM-11 has been delayed awaiting BWIP concurrence and the setting up of appropriate test facilities.

6.6 Defense High-Level Waste Technology Project

This activity involves test method standardization, reference and testing materials, a database, waste form durability, canister materials performance, models, and thermal and processing properties. The MCC-3 Agitated Powder Leach Test Method was submitted to the MRB, with changes essentially the same as those made in MCC-1.

Leach testing was completed on saw-cut round-robin specimens, cut by five different laboratories using a standard procedure, to determine if there were significant differences in leaching. Data were incorporated into MCC-1 Static Leach Test Procedure, and the procedure was resubmitted to the MRB.

There are 597 papers in the glass thermal property database, and 370 of these are on borosilicate glass. There are approximately 400 papers either received or on order on glass durability. A comparison of this database activity with the National Bureau of Standards (NBS)/Nuclear Regulatory Commission (NRC) indicated that the NBS/NRC database allows a highly refined literature search that tells where the data is, but does not contain any tabulations of data. This is true, the NBS database is actually a data index which directs the user to available data on various topics related to the high-level waste package. This database contains the NBS reviews of DOE reports concerning the durability of proposed waste packages and their components. Users of this database must obtain the data from the referenced papers. The NBS/NRC database does give lists of all data available in the original document. In addition, it gives a technical evaluation of the data, its relevance to issues dealing with nuclear-waste storage, and the author's abstract. This abstract usually contains significant numerical results. The most pertinent original documents for a given topic can be discovered using this NBS/NRC data index, and users can obtain those originals when details such as numerical data, tables, etc. are needed.

No funding was provided for the fabrication of ATM-18 glass.

6.7 Transportation Technology Center

At the beginning of this reporting period in January 1987, insufficient funding was available for the TTC work. Funds were approved in April. A Transportation Flaw Leak Test was developed. This test uses nucleopore filters for collecting fine glass which exits flaws during a 2000 mile transport. Related work was conducted on the development of a Pressurized Flaw Leak Procedure. Part of the reason for developing and conducting these tests is to determine if any amount of respirable fines and glass material are released. Flaw leak testing was conducted on glass-filled canisters which were transported from the Hanford Site to Cheyenne, Wyoming, and back to the Hanford Site, a distance of approximately 2000 miles. After the trip, filters and collected glass were removed and amounts released were correlated with the reference design flaw and its position on the canister. Size distribution of the fines was shown for each filter number (reference design flaw). Data from these

tests do not take into account effects on the glass of aging, decay heating, or irradiation. Results showed that primary release of glass from a flaw is in the canister plenum. Release in this area is an order of magnitude greater than the amount released in the impact area. However, the amount of respirable glass fines (less than 20 μm in diameter) released from design flaws in the impact area is an order of magnitude greater than the amount released from the canister plenum. Total amounts of glass and respirable fines released from each design flaw tested were below the level established for cask transport, although the established level was not given.

6.8 West Valley Demonstration Project

This activity deals with reference glass durability testing, characterization and documentation of some Approved Test Materials (ATMs), fabrication of some ATMs, and a database. All reference glass tests are in progress or have been completed. ATM-10 glass is a radioactive, reference West Valley glass which was made with extreme care. The original composition of the glass had very little aluminum but it has been modified based on work from Catholic University, and the glass now contains approximately six percent aluminum. This glass will be used in West Valley tests and probably in some BWIP tests. The Chemical Test Standard (CTS) glass is a non-doped glass and is made in a large melter at West Valley. MCC-1 and MCC-3 leach tests of ATM-10, CTS glass, and ARM-1 in deionized water, and MCC-1 tests of CTS glass in PBB-1 brines were completed and summarized in a report and forwarded to the WVDP. This report also contains a statistical analysis of the results. The conclusion given in the report was that the leaching behavior of the West Valley glass was comparable to that of the other waste glasses tested and that the West Valley glass met the NNWSI criterion of leaching losses (less than 1 g/m² per day averaged over the first 28 days) for specified elements. Earlier reports stated that the ATM-10 was more durable than the CTS glass. Pulsed flow tests of CTS glass, ATM-10, and ARM-1 were completed. Initially the leach-release-rate from the CTS glass was approximately four times greater than that of ATM-10 glass. Later, the leach rate of CTS glass decreased due to the slow transport of silicic acid in the growing surface layer on the glass particles. This decrease in leach rate is not observed in the more durable glasses.

Characterization of ATM-10 and a statistical analysis of the ATM-10 composition data were completed. The ATM-10 materials were packaged and sent for use by the West Valley test program at PNL, the Nevada Nuclear Waste Storage Investigations (NNWSI) program at the Lawrence Livermore National Laboratory (LLNL), and the Salt Repository

Laboratory (SRL). Fabrication of the nonradioactive ATM-WV/205 reference glass containing dopants was completed, and characterization of ATM-WV/205 is nearing completion.

An Analytical Methods Workshop was held in April 21-22, 1987, at the Battelle Seattle Research Center. This workshop was supported by WVDP, OGR, and DHLWTP. There were about fifteen participants from six DOE and contractor laboratories in addition to two NBS scientists specializing in sample preparation methods and analyses by inductively coupled plasma (ICP) and x-ray fluorescence (XRF).

Work is continuing on setting up a computerized system for the database. This is a multifunded task supported at present by the WVDP and the DHLWTP. The purpose of this database is to compile the material properties data that is needed by nuclear-waste-glass producers, the repositories, and other participants in the waste licensing process. This database is for data as described, and it should not be confused with the Nuclear Waste Materials Handbook which will contain MCC test methods which have been approved by the MRB. The outline for the database handbook is as follows.

COMPREHENSIVE DATABASE HANDBOOK

- I. INTRODUCTION
- II. SCOPE
- III. CONVERSION CONSTANTS, SYMBOLS, etc.
- IV. GLASS WASTE FORM PROPERTIES
 - A. LEACHING, DISSOLUTION PERFORMANCE
 - B. THERMAL STABILITY UNDER PROJECTED TEMPERATURES
 - C. THERMAL and PROCESSING PROPERTIES
 - D. REACTIVITY/CHEMICAL COMPATIBILITY with CANISTER FILLER
 - E. BULK PHYSICAL PROPERTIES

6.9 Comments

The monthly reports of the MCC indicate that the center is responsive to the offices that support it. There is considerable effort spent on quality assurance as indicated by various audits and reviews and corrections made. During this reporting period, there was progress made in developing, testing, and characterizing some of the ATM waste glasses. Most of the work done at the MCC is supported by the OGR, SRP, DHLWTP, TTC, WVDP and, to a lesser extent, BWIP. There is essentially very little work done for the NNWSI.

It is not clear why there is not more support for the development of standard approved-test methods. Other standards groups, such as the various ASTM committees and the NBS, have demonstrated that the time invested in developing

test procedures, material specifications, etc. produces useful results. The approval process through the MRB is not unreasonable, as evidenced by the development of some of the more difficult and complex leach tests that have or are nearing final approval. The additional step of getting input from various ASTM committee memberships is helpful, but the MCC has the final responsibility to determine the test methods and materials specifications that will be submitted to the MRB for approval and use.

The activity of working with ASTM Committee C26 to develop a document for accelerated testing was in progress for about one year. Support for this effort has been discontinued by the DOE Office of Geologic Repositories (OGR). The accelerated testing activity needed input and cooperation of the repositories, and this input had been requested in the previous 6-month reporting period [Interrante 1987b]. No information regarding the contents of the final accelerated testing document or reasons for not continuing this work were given in the MCC reports.

7.0 AN ILLUSTRATION OF UNCERTAINTIES IN THE CHOICE OF GLASS COMPOSITION

7.1 Introduction

An illustration of the importance of data interpretation is given to stress the need for independent interpretation of the data to be used to predict the performance of materials proposed for use in a nuclear waste package. This illustration contrasts published conclusions [Chick 1984] with substantially different conclusions obtained from an alternate NBS interpretation of the same data.

The example used in this illustration involves a response surface model of the type that will be used for waste-package decisions. Glass compositions for the vitrification of high-level nuclear waste are being chosen, in part, on the basis of empirical models of performance characteristics such as leaching. These models are response surface models. They describe a relation between glass performance and controlled variables that affect performance. The performance characteristics in question are the leaching characteristics of the glass. Pertinent controlled variables are the glass composition and the processing (melting/cooling) conditions used in the production of the glass.

The NBS analysis assumed that glasses containing greater than 25 percent Na_2O have leach rates that are so high that these glasses are undesirable. Further, the higher compositions would complicate the analysis and the model needed to portray

the data. Thus, the NBS analysis is not applicable to glass above the 25 percent level for Na_2O . A conclusion reached from this alternate analysis is that leach rates of the glass recommended in the original report would be improved by changing the recommended composition, in particular, by substitution of Al_2O_3 for Na_2O -- it is noted that there must be a tradeoff between leachability and producibility of borosilicate glass, and that the suggested addition of the alumina may be unwarranted when all factors are considered. Nevertheless, the alternate NBS interpretations of these data have led to alternative recommendations for the composition of glass for this application. Hence, the example serves its intended purpose of illustrating the benefit and necessity of independent interpretation of data taken to represent materials performance.

Empirical models entail a variety of uncertainties that must be assessed before conclusions are finalized. The uncertainties that are most difficult to assess are those connected with the choice of a parametric form for the model. Resolution of questions of the proper choice of the form of the model is the subject of this section.

7.2 Response Surface Experiments

The response-surface models that relate glass performance to the various controllable variables typically involve polynomials in the controllable variables. Generally, a separate model is developed for each performance characteristic, which in the case of glass leaching means a separate model for each component measured in the leachate. Let y denote a performance characteristic, and let x, z, \dots , denote the controllable variables. The variable y might be the normalized concentration of SiO_2 in the leachate or the logarithm of this normalized concentration, and x and z might be the proportion of SiO_2 and B_2O_3 in the glass, for example. Response surface models typically have the form

$$y = \beta_0 + \beta_1 x + \beta_2 z + \beta_3 xz + \beta_4 x^2 + \beta_5 z^2 + \dots,$$

where, of course, the number of controllable variables might be larger than two and the polynomial on the right side might be of higher order than quadratic. One important characteristic of a model of this form is that it can represent a performance characteristic that attains an optimum level for some setting of the controllable variables.

Consider the experiment needed to obtain a response surface model for a particular performance characteristic. Such an experiment is composed of trials. In each trial, the performance characteristic is measured for a particular setting of each of the controllable variables. Such an

experiment entails more than the estimation of the parameters β_0, β_1, \dots . The experiment must also provide a basis for choosing the form of the polynomial to be used for the response surface, any transformation that is to be applied to the response variable y , and the region in the space of the controllable variables over which the response surface is valid. These latter choices involve uncertainties that are much more difficult to quantify than the uncertainty in the estimation of the parameters β_0, β_1, \dots .

After a response surface is determined for each of the performance characteristics of interest, the best glass composition and processing procedure are chosen. Moreover, tolerance limits that assure that the glass created is reasonably close to the best obtainable must also be chosen. Since the various performance characteristics will not all reach optimum levels for the same setting of the controllable variables, this choice involves tradeoffs. This section will not discuss these tradeoffs. The purpose of this section is to discuss the response surfaces that must be estimated in preparation for making the tradeoffs.

7.3 Reinterpretation of a Leaching Experiment

As an example of the uncertainty associated with the choice of the form of the model, we consider the study by Chick, et al. and, in particular, their leaching results. This study involves seven leaching tests of different types (MCC-1, MCC-2, MCC-3, and MCC-5) run at different temperatures (40 to 150°C) for different periods (3 to 28 days) with different leachants (deionized water and water buffered to pH 3). When this study was conceived, the designers thought that quadratic response surface models would be adequate for the region containing the glass compositions of interest. Thus, the response surface experiment was designed to provide precise estimates of the coefficients of quadratic models [Chick 1984]. Unfortunately, a quadratic model was not adequate for any of the performance characteristics considered. Thus, as part of the data analysis, a decision had to be made about how to obtain adequate models. This decision introduces an uncertainty into the modeling that is not reflected in the usual standard errors of the parameters β_0, β_1, \dots . These authors decided to fit a cubic response surface model as a solution to their modeling problem. This solution is not the only alternative.

In the fitting of empirical models, the investigator can choose between fitting a simpler model to a smaller region or fitting a more complicated model to a larger region. The authors of this study chose the latter alternative. Inspection of the data suggests that the reason that a quadratic model does not fit is that the region over which

the experimental points are spread includes concentrations of Na_2O that are too high, as indicated by very high rates of leaching at high concentrations of Na_2O . Thus, an alternative to a cubic model is a quadratic model over a smaller region. A smaller region that seems to allow an adequate fit to a quadratic model has an upper bound on Na_2O of 0.25 instead of the original upper bound of 0.30. This restriction eliminates 25 of the 101 original data points. It also simplifies the model by eliminating 35 terms. The fits of the two models can be compared on the basis of the residuals for the data points with Na_2O less than 0.25. On this basis, the alternative quadratic model seems to fit nearly as well as the original cubic model.

Our comparison of the two models is based on the contour plots shown in Figures 2-5. Before discussing the comparison, we consider the interpretation of these plots. Consider the top plot in Figure 2. This plot shows the logarithm of the normalized Si release for the 28-day MCC-1 test run at 90°C with deionized water as the leachant. The normalized Si release is shown as a function of the seven components that make up the glass [Chick 1984]. Of the seven components, three are allowed to vary in each of these contour plots and the other four are held constant at the proportions for the glass recommended as optimum in the study, SiO_2 0.454, B_2O_3 0.024, Na_2O 0.155, CaO 0.102, Al_2O_3 0.009, Fe_2O_3 0.135, and Waste 0.121. The level of the response is shown by the letters, periods, and commas, and a scale for these symbols is shown on the right of the plot. Each symbol represents an interval in the response. This interval begins at the value shown next to the symbol and ends at the higher value one step along on the scale. Note that the B's in the middle of the plot indicate a minimum in the Si release. In the plot on top of Figure 2, the response is shown as a function of Al_2O_3 , Na_2O , and Waste. The sum of these three components must be 0.285, as the other four components are fixed. The component Al_2O_3 is constant along horizontal lines, lines parallel to the base of the triangle. The component Na_2O is constant along lines parallel to the left side of the triangle. The component Waste is constant along lines parallel to the right side of the triangle. The minimum shown by the B's is near the proportions Al_2O_3 0.09, Na_2O 0.155, and Waste 0.04. Thus, this Figure suggests that better leach performance can be obtained by substituting Al_2O_3 for Waste.

The two contour plots in Figure 2 contrast the original cubic model shown on the top with the alternative quadratic model shown on the bottom. The two plots are generally similar. However, the quadratic model does not show a distinct minimum in the middle as the cubic model does. Rather, the quadratic model suggests that better leach performance can be obtained

by substituting Al_2O_3 for Na_2O while holding the waste proportion constant.

Figure 3 also contrasts the cubic and quadratic models but in terms of a different perspective on the response surface. The study by Chick, et al. discusses the fact that better leach performance can be obtained with more CaO and less B_2O_3 than has been recommended in previous studies [Chick 1984]. While this conclusion seems generally to hold for both models, the change in leach behavior is more gradual under the quadratic model. Moreover, the quadratic model shows a minimum at the lowest level of Na_2O for B_2O_3 near 0.06.

Figure 4 shows the quadratic model obtained for another leach component, the logarithm of the normalized Waste from the 28-day MCC-1 test. The top plot shows the components that are shown in Figure 2, and the bottom plot shows the components that are shown Figure 3. The top plot shows distinctly that better leach performance can be obtained by substituting Al_2O_3 for Na_2O while holding the Waste constant. The bottom plot supports the assertion in the original study that better performance is obtained with higher CaO and correspondingly lower B_2O_3 .

Figure 5 shows the quadratic model obtained from the composite leach response used in the original study to judge leach performance. This composite response is calculated from responses from five of the seven leaching tests performed. Again the top plot corresponds to Figure 2, and the bottom to Figure 3. The top plot shows better leach performance is obtained with more Al_2O_3 and less Na_2O . The bottom plot suggests that for low levels of Na_2O , the substitution of CaO for B_2O_3 can be carried too far.

Can one of the two alternative models be selected on the basis of the data available? In this study, the selection of one of these models is hampered by the fact that too few replicate data points were obtained. Only ten replicates were run, and of these one pair of results was eliminated because of mistakes in the laboratory work. Without an adequate assessment of the pure error in an experiment, the choice between alternative models is difficult.

The above example discusses the choice between two alternative models with attendant alternative regions of validity. Besides the choice of model complexity and region of interest, there is the choice of transformation of the response variable. In the above example a log transform was chosen. Although this is a reasonable choice, alternatives might be proposed that cannot be eliminated on the basis of the available data.

7.4 Recommendations

Consider the uncertainties associated with the choice of model complexity, region of validity, and response-variable transformation. In the choice of the composition of the nuclear waste glasses, these uncertainties must be treated in an objective manner. But how is this to be done? There is no standard method for describing the uncertainties associated with these choices as there is for describing the uncertainties in the parameters β_0, β_1, \dots . The statistics literature contains some methods for making these choices, which are applicable if the proper set of trials have been run. The literature suggests methods for characterizing the associated uncertainties, but these methods are neither simple nor standard.

In the study discussed above, the authors defend their choice of a cubic model in two ways. First, they eliminated terms from the full cubic model by stepwise regression. Then they argue that since the number of independent terms in the model is much smaller than the number of different trials, the available data provides adequate estimates for the coefficients in their model. Second, they argue that their model is adequate because its R^2 , the proportion of the variability explained, is high. Although too many parameters for the number of data points or a small value of R^2 indicate a modeling problem, the converse is not true. In particular, neither of their arguments rules out the quadratic alternative suggested above.

A solution to the problem of the uncertainties associated with the choice of model form is reanalysis of the data by an independent investigator. This solution, which is widely recognized in science, requires that the investigators responsible for the initial recommendations on glass composition make all their data available to others, as the authors of the study discussed above did. An independent investigator should be provided a machine-readable file containing the valid measurements, the results of the measurement assurance program from the laboratory that performed the work, and a discussion of any measurement problems suspected by the original investigators. A reanalysis requires time and money, which must be provided at the planning stage.

A reanalysis of the data will raise questions about the initial analysis but is unlikely to resolve these questions. Resolution of the questions will undoubtedly require additional experimental work. The additional experimental work might include trials for glass compositions closer to the recommended composition or trials that would allow a more


complicated model to be fit and compared to the initial model.

The confirmatory experiment should, of course, be built on the initial experiment. This does not mean that the confirmatory experiment will be smaller than the initial experiment. Further experimentation associated with the example discussed above might require the measurement of as many different glass compositions as considered originally.

The questions to be answered in the confirmatory experiment might be difficult to answer because of the experimental error, and thus might require a large number of trials for resolution.

In the response surface literature, confirmatory experiments are almost universally recommended although one might suspect that they are less than universally performed. The choice of composition for the nuclear waste glasses is certainly critical enough to warrant a confirmatory experiment by an independent organization.


Confirmatory experiments are not inexpensive. However, the effort spent struggling with inadequate data is also very expensive, given that all costs are properly considered. For example, an explanation to a lay audience of why a decision was made despite inadequate data can take an enormous amount of preparation. A confirmatory experiment that reaches essentially the same conclusion as the initial experiment will usually be accepted as conclusive by the scientific community.

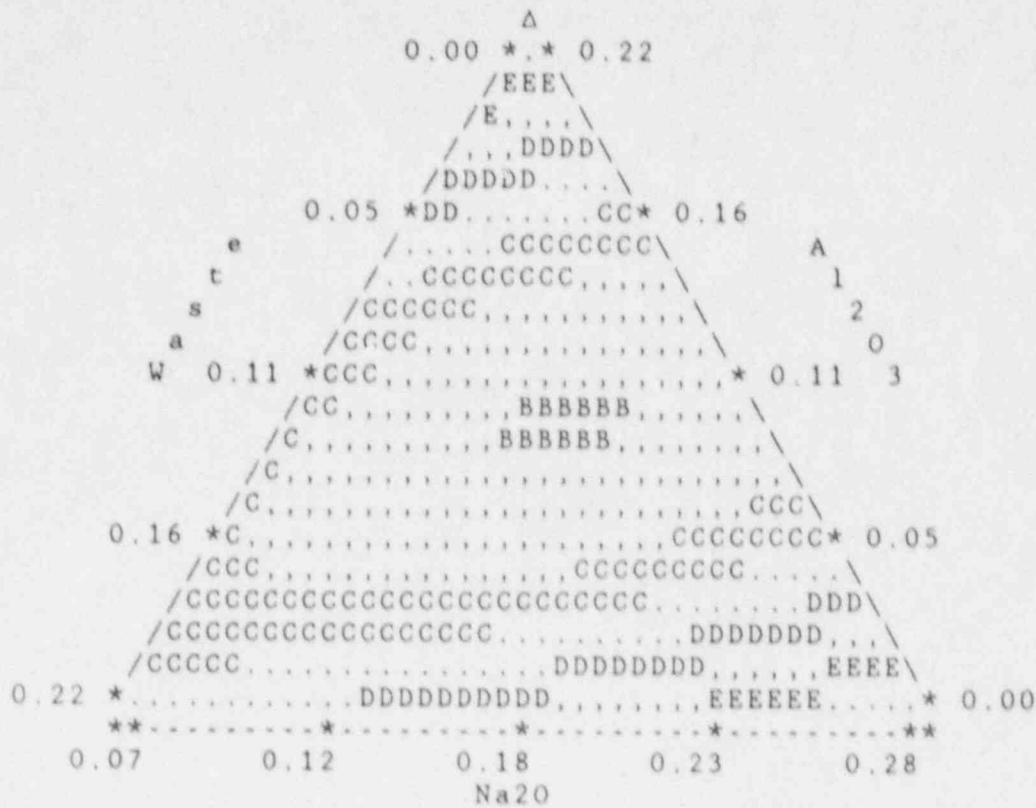

Si_28DAY

A	=	0.0000
.	=	0.2308
B	=	0.4615
,	=	0.6923
C	=	0.9231
.	=	1.1538
D	=	1.3846
,	=	1.6154
E	=	1.8462
.	=	2.0769
F	=	2.3077
,	=	2.5385
G	=	2.7692
.	=	3.0000

SiO2 = 0.454
B2O3 = 0.024
CaO = 0.102
Fe2O3 = 0.135

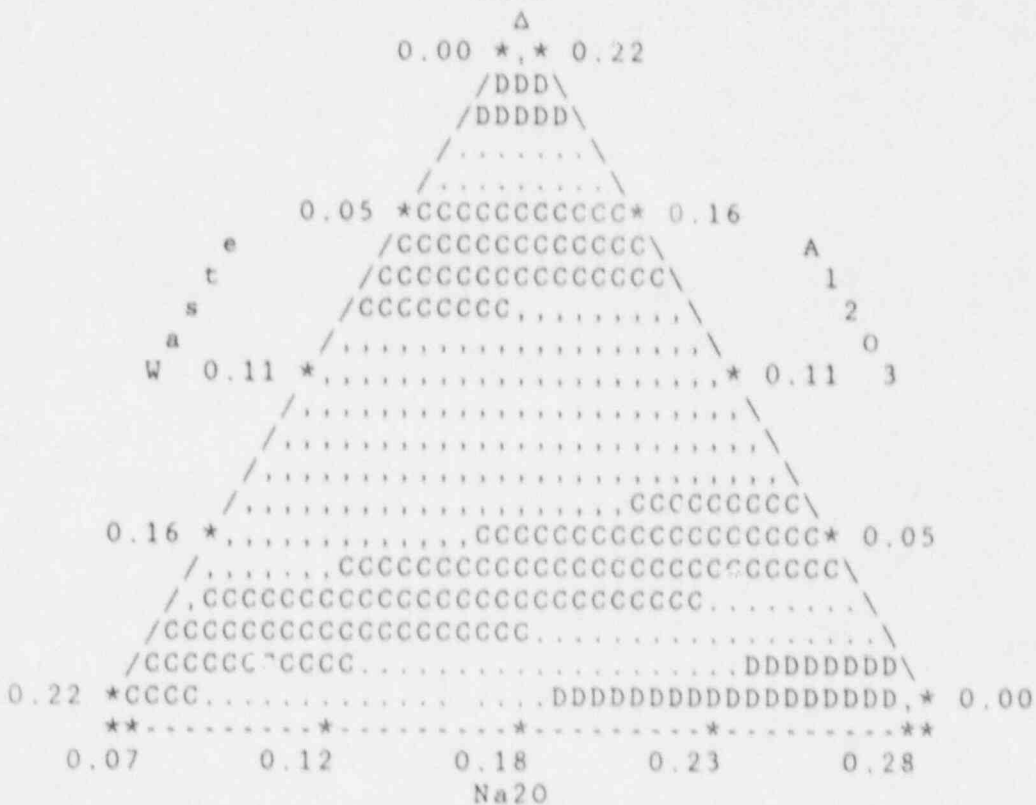


Si_28DAY

A	=	0.0000
.	=	0.2308
B	=	0.4615
,	=	0.6923
C	=	0.9231
.	=	1.1538
D	=	1.3846
,	=	1.6154
E	=	1.8462
.	=	2.0769
F	=	2.3077
,	=	2.5385
G	=	2.7692
.	=	3.0000

SiO2 = 0.454
B2O3 = 0.024
CaO = 0.102
Fe2O3 = 0.135


Figure 2. Normalized Si Release [Chick 1984] predicted by cubic model from 101 data points (TOP) and quadratic model from 76 data points (BOTTOM).

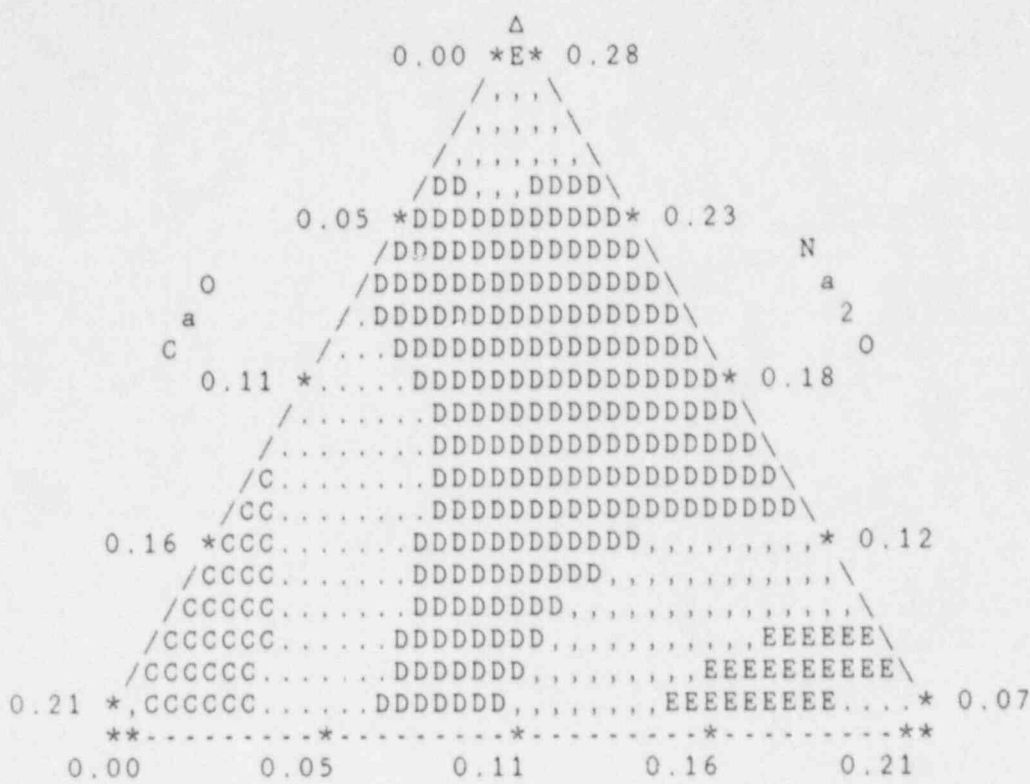

Si_28DAY

A = 0.0000
 . = 0.2308
 B = 0.4615
 , = 0.6923
 C = 0.9231
 . = 1.1538
 D = 1.3846
 , = 1.6154
 E = 1.8462
 . = 2.0769
 F = 2.3077
 , = 2.5385
 G = 2.7692
 . = 3.0000

SiO2 = 0.454
 Al2O3 = 0.009
 Fe2O3 = 0.135
 Waste = 0.121

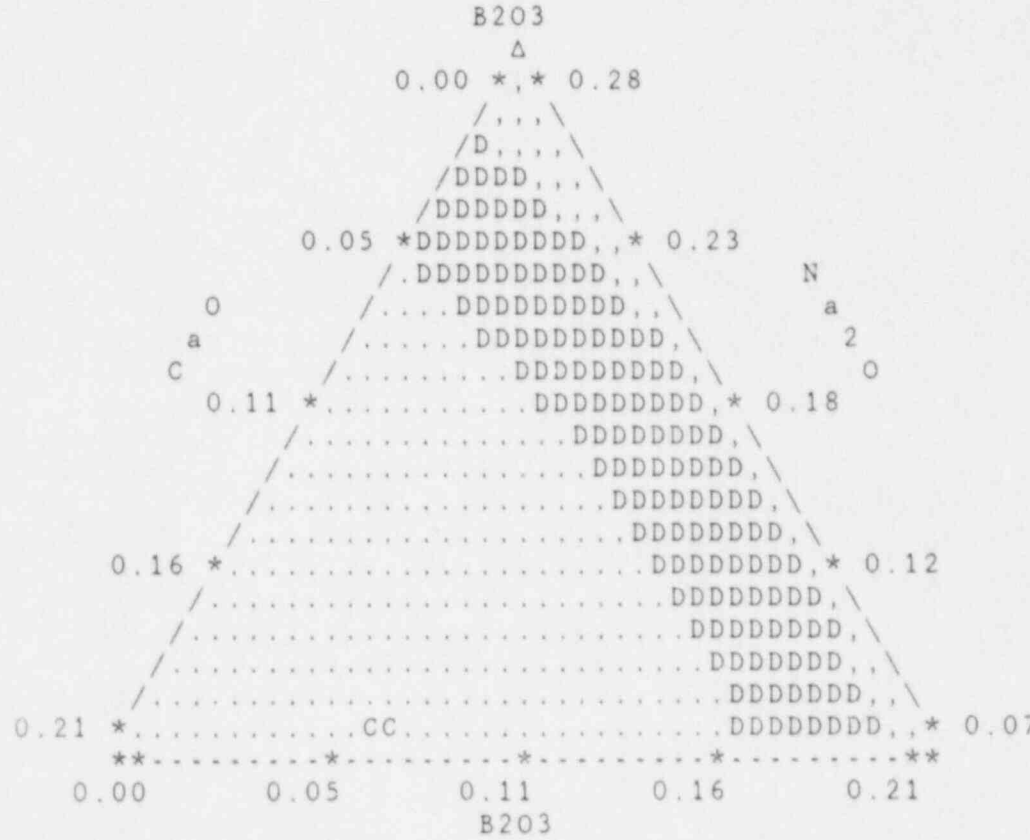


Si_28DAY

A = 0.0000
 . = 0.2308
 B = 0.4615
 , = 0.6923
 C = 0.9231
 . = 1.1538
 D = 1.3846
 , = 1.6154
 E = 1.8462
 . = 2.0769
 F = 2.3077
 , = 2.5385
 G = 2.7692
 . = 3.0000

SiO2 = 0.454
 Al2O3 = 0.00
 Fe2O3 = 0.135
 Waste = 0.121


Figure 3. Normalized Si Release [Chick 1984] predicted by cubic model from 101 data points (TOP) and quadratic model from 76 data points (BOTTOM).

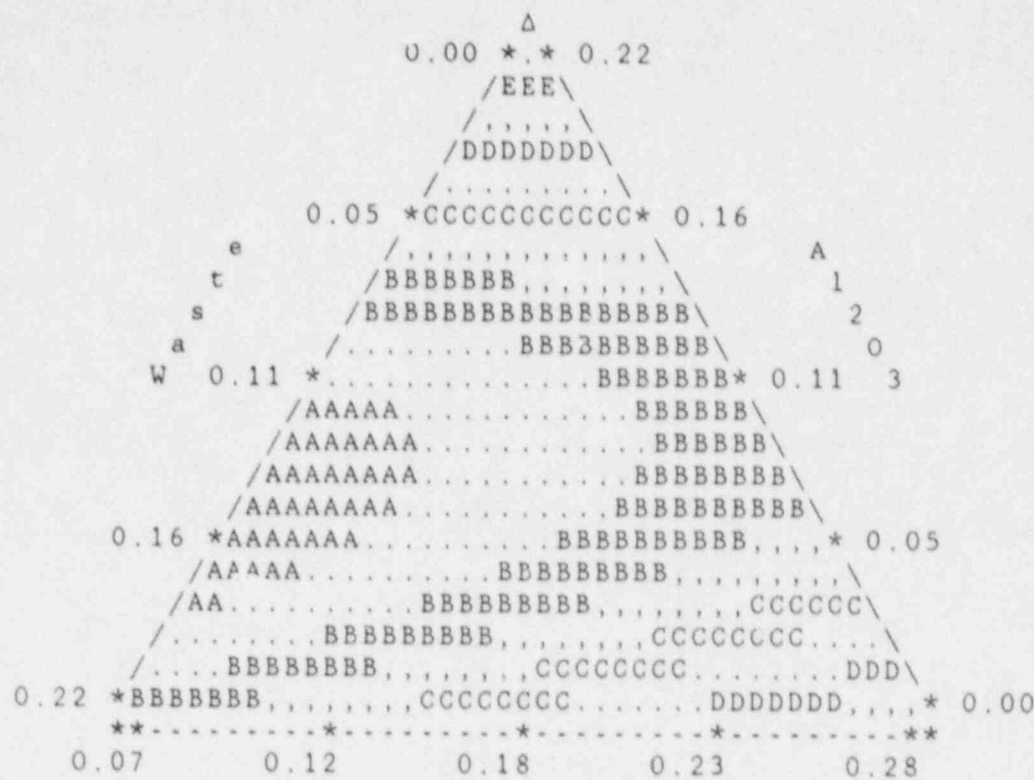

Waste_28

A = -1.0000
 . = -0.7155
 B = -0.4309
 , = -0.1464
 C = 0.1381
 . = 0.4227
 D = 0.7072
 , = 0.9918
 E = 1.2763
 . = 1.5608
 F = 1.8454
 , = 2.1299
 G = 2.4144
 . = 2.6990

SiO2 = 0.454
 B2O3 = 0.024
 CaO = 0.102
 Fe2O3 = 0.135

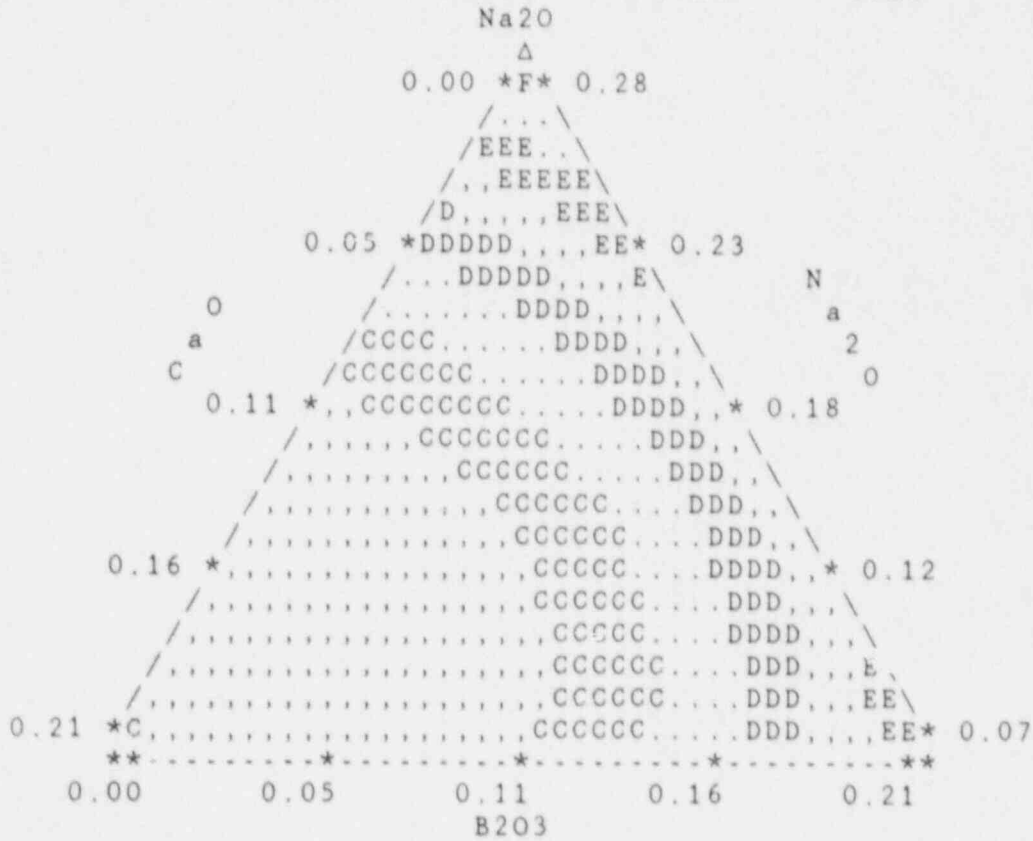


Waste_28

A = -1.0000
 . = -0.7155
 B = -0.4309
 , = -0.1464
 C = 0.1381
 . = 0.4227
 D = 0.7072
 , = 0.9918
 E = 1.2763
 . = 1.5608
 F = 1.8454
 , = 2.1299
 G = 2.4144
 . = 2.6990

SiO2 = 0.454
 Al2O3 = 0.009
 Fe2O3 = 0.135
 Waste = 0.121


Figure 4. Normalized Waste Release [Chick 1984] predicted by quadratic model from 76 data points.

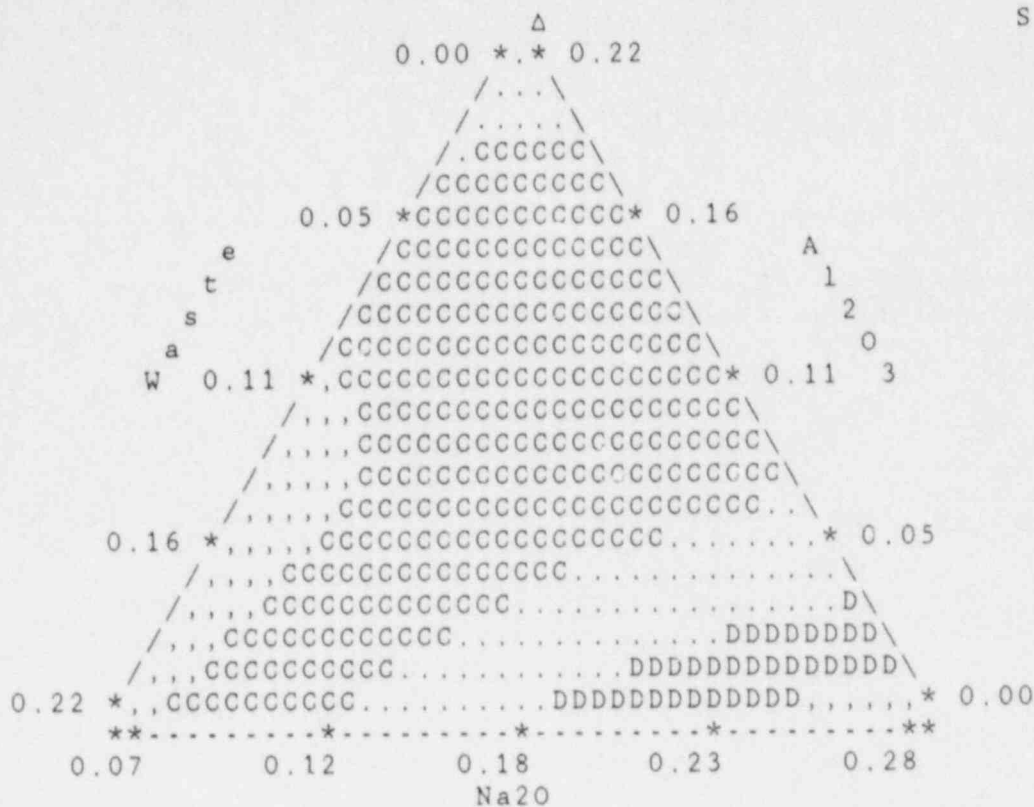

SI4PH_Composite

- A = 1.000
- . = 1.692
- B = 2.385
- , = 3.077
- C = 3.769
- . = 4.462
- D = 5.154
- , = 5.846
- E = 6.538
- . = 7.231
- F = 7.923
- , = 8.615
- G = 9.308
- . = 10.000

- SiO2 = 0.454
- B2O3 = 0.024
- CaO = 0.102
- Fe2O3 = 0.135

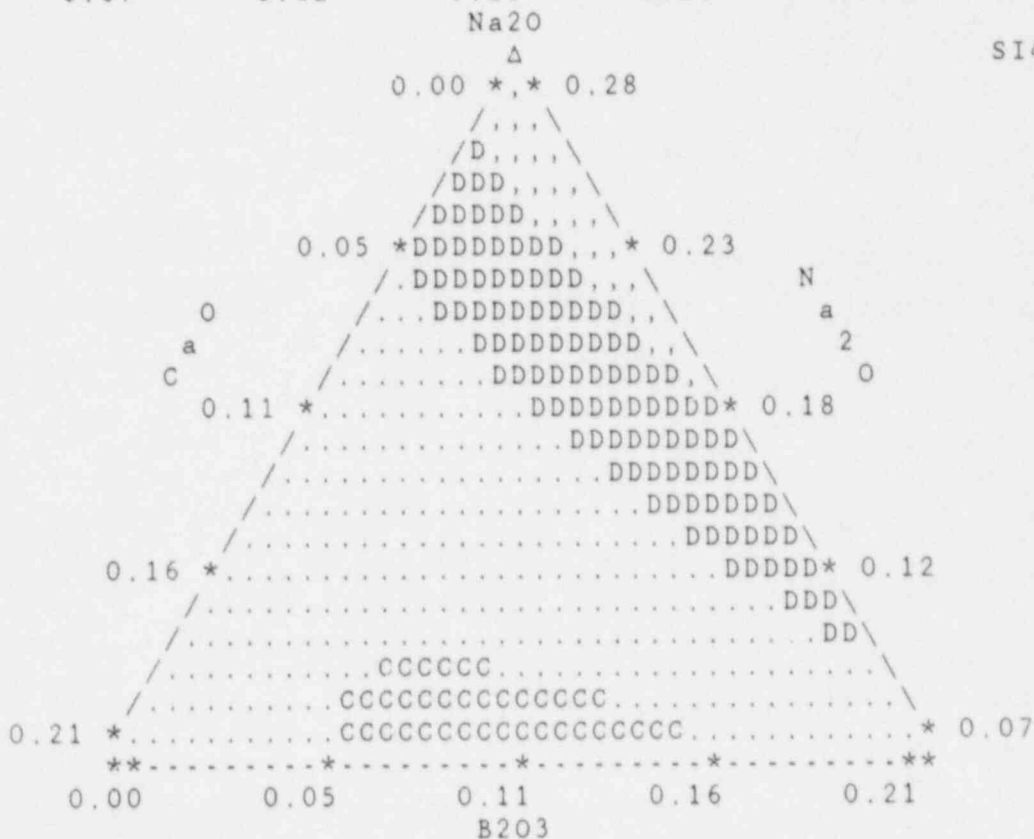

SI4PH_Composite

- A = 1.000
- . = 1.692
- B = 2.385
- , = 3.077
- C = 3.769
- . = 4.462
- D = 5.154
- , = 5.846
- E = 6.538
- . = 7.231
- F = 7.923
- , = 8.615
- G = 9.308
- . = 10.000

- SiO2 = 0.454
- Al2O3 = 0.009
- Fe2O3 = 0.135
- Waste = 0.121

Figure 5. Composite Leach Response [Chick 1984] predicted by quadratic model from 76 data points.

ACKNOWLEDGEMENTS

The editor wishes to thank Ms. Joyce F. Harris who typed, proofread, and coordinated the reviews included in this report and Ms. Carla Messina for her continued assistance in developing applications software for the NBS/NRC Database for Reviews and Evaluations on High-Level Waste (HLW) Data.

9.0 REFERENCES

Abrajano, T., Bates, J., Ebert, W., and Gerding, T., "The Effect of Gamma Radiation on Groundwater Chemistry and Glass Leaching as Related to the NNWSI Repository Site," Lawrence Livermore National Laboratory, UCRL-15825, May 1986.

Anantatmula, R. P., "The Effects of Grande Ronde Basalt Groundwater Composition and Temperature on the Corrosion of Low-Carbon Steel in the Presence of Basalt-Bentonite Packing," Rockwell Hanford Operations, RHO-BW-SA-391P, August 1985.

Anantatmula, R. P., Delegard, C. H., and Fish, R. L., "Corrosion Behavior of Low-Carbon Steels in Grande Ronde Basalt Groundwater in the Presence of Basalt-Bentonite Packing," proceedings the Materials Research Society Symposium Proceedings, 26, 1984, p. 1-10, also RHO-BW-SA-314P.

Ballou, L. B. and McCright, R. D., "LLNL, Attachment 1 to Letter Dated March 8, 1985," to M. Steindler, Argonne National Laboratory, background information for Materials Review Board ad hoc panel review of NNWSI (and other) repository project corrosion testing programs, Lawrence Livermore National Laboratory, MRB-0418, 1985a.

Ballou, L. B., and McCright, R. D., "LLNL, Attachment 2 to Letter Dated March 8, 1985," to M. Steindler, Argonne National Laboratory, background information for Materials Review Board ad hoc panel review of NNWSI (and other) repository project corrosion testing programs, Lawrence Livermore National Laboratory, MRB-0418, 1985b.

Bates, J. K., and Gerding, T. J., "NNWSI Waste Form Test Method for Unsaturated Disposal Conditions," Lawrence Livermore National Laboratory, UCRL-15723, March 1985.

Bates, J. K., and Gerding, T. J., "One-Year Results of the NNWSI Unsaturated Test Procedure, SRL 165 Glass Application," Argonne National Laboratory, ANL-85-41, August 1986.

Bibler, N. E., Plodinec, M. J., Wicks, G. G., and Jantzen, C. M., "Glass Performance in a Geologic Setting," Summer National Meeting of the American Institute of Chemical Engineers, 1986.

Brehm, F., Lutton, J. M., Rivera, C. L., Maffei, H. P., Bohringer, A. P., Paine, D. D., and Pingel, P. A., "BWIP General Corrosion Studies, Summary of Report of Activities in FY-1984," Westinghouse Hanford Company, Corrosion Technology Section, B047154, 1984.

Chick, L. A., Bowen, W. M., Lokken, R. O., Wald, J. W., Brunnel, L. R., and Strachan, D.M., "West Valley High-Level Nuclear Waste Glass Development: A Statistically Designed Mixture Study," Pacific Northwest Laboratory, Richland, WA, PNL-4992, October 1984.

Clark, D. E., "ERG Review of the SRP Salt Irradiation Effects Program," Battelle Memorial Institute, Office of Nuclear Waste Isolation, BMI/ONWI-626, November 1986.

DOE see U. S. Department of Energy.

Einzinger, R. E., "Test Plan for Long Term, Low-Temperature Oxidation of Spent Fuel, Series 1," Hanford Engineering Development Laboratory, HEDL-7560, June 1986.

Gangloff, R. P., Graham, D. E., and Funkenbusch, A. W., "Influence of Environment Purity on Gaseous Iodine Embrittlement of Zircaloy-2 and High Purity Zirconium, Corrosion, 35(7), July 1979.

GAO see U. S. Government Accounting Office

Interrante, C. G. (editor), "Evaluation and Compilation of DOE Waste Package Test Data: Biannual Report December 1985-July 1986," National Bureau of Standards, NUREG/CR-4735, Volume 1, March 1987a.

Interrante, C. G. (editor), "Draft Evaluation and Compilation of DOE Waste Package Test Data: Biannual Report August 1986-January 1987," National Bureau of Standards, NUREG/CR-4735, Volume 2, May 1987b.

Jantzen, C. M., "Methods of Simulating Low Redox Potential (Eh) for a Basalt Repository," the Materials Research Society Symposium Proceedings, 26, 613-621, 1984.

Levy, P. W., "Radiation Damage Studies on Natural Rock Salt from Various Geologic Localities of Interest to the Radioactive Waste Disposal Program," Nuclear Technology, 60, 231-243, 1983.

Levy, P. W. and Kierstead, J. A., "Very Rough Preliminary Estimate of the Colloidal Sodium Induced in Rock Salt by Radioactive Waste Canister Radiation," in Materials Research Society, 1983 Symposium Proceedings, Vol. 26, Scientific Basis for Nuclear Waste Management, McVay, G. (editor), Elsevier Science Publishing Co., 1984, p. 727-734.

Mallet, R. H., "Buckling Design Criteria for Waste Package Disposal Containers in Mined Salt Repositories," Swanson Engineering Associates Corporation, BMI/ONWI-597, December 1986.

Mendel, J. E., "Final Report on the Defense High-Level Waste Leaching Mechanisms Program, Pacific Northwest Laboratory, PNL-5157, August 1984.

Oversby, V. M., "Spent Fuel as a Waste Form - Data Needs To Allow Long Term Performance Assessment Under Repository Disposal Conditions," Lawrence Livermore National Laboratory, UCRL-94659, December 1986.

Pitman, S. G., "Enviromechanical Testing of AISI 1020 Steel in Hanford Grande Ronde Groundwater," Pacific Northwest Laboratory, B023959, July 1983.

Smith, H. D., "C-Ring Stress Corrosion Cracking Scoping Experiment for Zircaloy Spent Fuel Cladding," Hanford Engineering Development Laboratory, HEDL-7546, March 1986a.

Smith, H. D., "Zircaloy Spent Fuel Cladding Electrochemical Experiment at 170°C and 120 psia H₂O," Hanford Engineering Development Laboratory, HEDL-7545, April 1986b.

U. S. Department of Energy, Office of Civilian Radioactive Waste Management, "OCRWM Mission Plan Amendment with Comments on the Draft Amendment and Responses to the Comments," DOE/RW-0128, June 1987.

U. S. Government Accounting Office, Resources, Community, and Economic Development Division, "Nuclear Waste: Status of DOE's Nuclear Waste Site Characterization Activities," GAO/RCED-87-10FS, March 1987.

Van Konynenburg, R. A., "Radiation Chemical Effects in Experiments to Study the Reaction of Glass in an Environment of Gamma-Irradiated Air, Groundwater, and Tuff," Lawrence Livermore National Laboratory, UCRL-53719, May 1986.

Westerman, R. E., Haberman, J. H., Pitman, S. G., and Perrin, J. S., "Corrosion of Iron-Base Waste Package Container Materials in Salt Environment," Pacific Northwest Laboratories, PNL-SA-14029, March 1986.

Wicks, G., Bibler, N. E., Jantzen, C. M., and Plodinec, M. J., "Repository Simulation Tests," American Ceramic Society Annual Meeting, 1984.

Appendix A. Draft NBS Reviews and Guidelines for Reviewers
of DOE Reports Concerning the Durability of
Proposed Packages for High-Level Radioactive
Waste

Appendix A. Draft NBS Reviews and Guidelines for Reviewers
of DOE Reports Concerning the Durability of
Proposed Packages for High-Level Radioactive
Waste

	Page
Waste Package Data Review Form Guidelines	A-5
NNWSI -- NEVADA NUCLEAR WASTE STORAGE INVESTIGATIONS	
Abrajano, T., Bates, J., Ebert, W., and Gerding, T., "The Effect of Gamma Radiation on Groundwater Chemistry and Glass Leaching as Related to the NNWSI Repository Site", UCRL-15825, Preprint SANL-510-001, May 1986	A-9
Acton, C. F. and McCright, R. D., "Feasibility Assessment of Copper-Base Waste Package Container Materials in a Tuff Repository," UCID-20847, September 30, 1986	A-13
Van Konynenburg, R. A., "Radiation Chemical Effects in Experiments to Study the Reaction of Glass in an Environment of Gamma-Irradiated Air, Groundwater, and Tuff", UCRL-53719, May 1986.....	A-15
Smith, H. D., "Zircaloy Spent Fuel Cladding Electrochemical Experiment at 170°C and 120 psia H ₂ O," HEDL-7545, April 1986	A-19
Smith, H. D., "C-Ring Stress Corrosion Cracking Scoping Experiment for Zircaloy Spent Fuel Cladding", HEDL-7546, March 1986	A-22
Bates, J. K. and Gerding, T. J., "One-Year Results of the NNWSI Unsaturated Test Procedure: SRL 165 Glass Application", ANL-85-41, August 1986	A-25
Einzigler, R. E., "Test Plan for Long Term, Low-Temperature Oxidation of Spent Fuel, Series 1", HEDL-7560, June 1986	A-29
Oversby, V.M., "Spent Fuel as a Waste Form--Data Needs to Allow Long Term Performance Assessment Under Repository Disposal Conditions", UCRL-94659, December 1986	A-33

Ballou, L. B. and McCright, R.D., "LLNL, Attachment 1 to letter dated 8 March 1985" to M. Steindler, Argonne National Laboratory, 1985	A-39
Ballou, L. B. and McCright, R.D., "LLNL, Attachment 2 to letter dated 8 March 1985" to M. Steindler, Argonne National Laboratory, 1985	A-41
BWIP -- BASALT WASTE ISOLATION PROJECT	
Anantatmula, R. P., "Effects of Grande Ronde Basalt Groundwater Composition and Temperature on the Corrosion of Low-Carbon Steel in the Presence of Basalt-Bentonite Packing," RHO-BW-SA-391P, August 1985	A-43
Pitman, S. G., "Slow-Strain-Rate Testing of 9%Cr, 1%Mo Wrought Steel and ASTM A27 Cast Steel in Hanford Grande Ronde Groundwater," SD-BWI-TS-008, August 1984	A-45
Yung, S. C., Toyooka, R.T. and McCall, T. B., "Thermal Analysis of Waste Package Preliminary Reliability Assessment," RHO-BW-SA-509P, March 1986	A-49
Brehm, F., Lutton, J. M., Rivera, C. L., Maffei, H. P., Bohringer, A. P., Paine, D. D. and Pingel, L. A., "BWIP General Corrosion Studies, Summary Report of Activities in FY-1984", B047154, 1984	A-53
Pitman, S. G., "Enviromechanical Testing of AISI 1020 steel in Hanford Grande Ronde Groundwater", B023959, July 1983	A-56
Barney, G. Scott, Lane, Douglas L., Allen, Carlton C., and Jones, Thomas C., "Sorptions and Desorption Reactions of Radionuclides with a Crushed Basalt-Bentonite Packing Material", RHO-BW-SA-416 P, April 1986	A-59
Jantzen, C. M., "Methods of Simulating Low Redox Potential (Eh) for a Basalt Repository," Materials Research Society Proceedings, 1978	A-65

SRP -- SALT REPOSITORY PROJECT

Mallett, R. H., "Buckling Design Criteria for Waste Package Disposal Containers in Mined Salt Repositories", BMI/ONWI-597, December 1986	A-70
Levy, P. W., "Radiation Damage Studies on Natural Rock Salt from Various Geological Localities of Interest to the Radioactive Waste Disposal Program," Nuclear Technology, <u>60</u> , 231-243, (1983)	A-76
Clark, D. E., "ERG Review of the SRP Salt Irradiation Effects Program", BMI/ONWI-626, November 1986	A-80
Westerman, R. E., Haberman, J. H., Pitman, S. G., and J. S. Perrin, "Corrosion of Iron-Base Waste Package Container Materials in Salt Environments," PNL-SA-14029, March 1986	A-88
Levy, P. W. and Kierstad, J. A., "Very Rough Preliminary Estimate of the Colloidal Sodium Induced in Rock Salt by Radioactive Waste Canister Radiation", Mat. Res. Soc. Symp. Proc., Vol 26 (1984) p. 727-734	A-92
VITRIFICATION OF HIGH-LEVEL WASTE	
Feng, X., Adiga, R., Barkatt, A., Barkatt, A., Freeborn, W., Macedo, P., Mohr, R., Montrose, C., Mowad, R., Saad, E., and Sousanpour, W., "Effects of Composition On the Leach Behavior of West Valley HLW Glasses," September 1986	A-95
Eisenstatt, L. R., "Description of the West Valley Demonstration Project Reference High-Level Waste Form and Canister," Revision 0, WVDP-056, July 28, 1986	A-98
Wicks, G. C., Bibler, N. E., Jantzen, C. M. and Plodinec, M. J., "Repository Simulation Tests," American Ceramic Society Annual Meeting, 1984	A-102
Bibler, N.E., Plodinec, M. J., Wicks, G. C. and Jantzen, C. M., "Glass Performance in a Geologic Setting," Summer National Meeting of the American Institute of Chemical Engineers, 1986	A-105

Waste Package Data Review Form Guidelines

DATA SOURCE

Full document reference. This section will be completed for the reviewer before he/she receives the document. If completing this section yourself, use the following format:

TECHNICAL REPORT:

Pitman, S. G., "Slow-Strain-Rate Testing of Steel,"
Rockwell Hanford Operations, SD-BWI-TS-008, August 1984.

CONFERENCE PAPER:

Abrajano, T. A., Jr. and Bates, J. L., "Transport and Reaction Kinetics at the Glass: Solution Interface Region: Results of Repository-Oriented Leaching Experiments," in Materials Research Society, 1983 Symposia Proceedings, Vol. 26, Scientific Basis for Nuclear Waste Management, McVay, G. L. (editor), North-Holland, 1984, p. 533-542.

DATE REVIEWED

Give the date the document review was completed. Add an additional date each time that the review is revised, e.g. 11/25/86; Revised 12/01/86.

TYPE OF DATA

- (1) Scope of the Report, e.g. Experimental, Theoretical, Literature Review, Data Analysis.
- (2) Failure Mode or Phenomenon Studied, e.g. Corrosion, Creep, Fatigue, Leaching, Pitting, Hydrogen Embrittlement, Debonding, Dealloying

MATERIALS/COMPONENTS

Description of the material studied, e.g., 304L stainless steel, brass, zircaloy cladding, welds in 316 stainless steel, packing material, basalt. Also describe, if specifically addressed, component parts e.g. the screw-type cap on a waste cylinder.

TEST CONDITIONS

- (1) State of the material being tested -- cold worked or annealed 304L stainless steel, thermo-mechanical history of the material (or component) studied.
- (2) Specimen Preparation -- prestressed, precracked, size, type of specimen.
- (3) Environment, pressures, and other test parameters of the material being tested, e.g. aqueous environment, radioactive surrounding, electrolytes or corrosive agents present, temperature and pressure (externally applied or not) during the test.

METHODS OF DATA COLLECTION/ANALYSIS

This section includes data measurement methods and types of data measured, as well as data analysis techniques, e.g. electron microscopy, weight loss vs. time, slow strain rate tensile test, x-ray diffraction, differential thermal analysis, A.C. electrical resistivity using a Wheatstone bridge, mass spectroscopic chemical analysis of the corrosive environment, Latin Hypercube method, Monte Carlo techniques.

AMOUNT OF DATA

This section includes the number of tables and graphs together with their titles and axes (including the range in values). If a listing of figure and table titles is provided, the reviewer should add the limits given on each axis, i.e. for temperature, or other explanatory information as appropriate.

Sometimes a synthesis is preferable to a listing of table and figure titles:

Five tables of temperature and time data for five molten-glass pouring operations, each table including the data from ten sensor locations. The temperatures ranged from 1100°C to 0°C over a time period of 24 hours.

UNCERTAINTIES IN DATA

Included here are error bars and uncertainties in the data as stated by the author. This also includes qualitative statements by the author on the reliability of the data:

The author states that, "Temperatures carry an accuracy of +5°C while the times are reported to within +15 sec. It was felt that under real glass pouring operations (without well controlled crucible cooling) the temperature-time curves will be shifted to somewhat higher temperatures than shown here.

DEFICIENCIES/LIMITATIONS IN DATABASE

Statements by the author on the applicability of the data are given here:

The author states "Extrapolation of the temperature-time (time < 24 hrs) data presented here to times in excess of 100 years should not be performed. The data presented here is useful only for indicating trends and qualitative parameter relationships, not for the purpose of presenting absolute values.

KEY WORDS

These are to be checked off on the keyword checklist. In general, these keywords should reflect the information given in the above categories. Additional keywords, which are truly different from terms on this list, should be added to the list under the category "other" which appears at the end of each keyword list.

COMMENTS

The reviewer's general comments on the document. This category is wide open as far as content. It contains information the reviewer did not enter into any of the above categories, but which is considered important for the reader to know. It is also in this section that the reviewer would put any of his/her comments on the deficiencies and uncertainties in the data and analysis:

This is a very comprehensive review of the literature on the temperature sensitization of stainless steels. Even though it neglects the definitive work of Bertocci, Shull, Kaufman, and Escalante [Phys. Rev. J13, (1979), pp. 15-358] in this area (presumably because of the difficulty in locating this document), this review still considers a sufficiently large number of other investigations to provide a good understanding of the present status of the field. The one discordant note here, however, is that it would have been a much more useful review if stainless steel types 301, 303, 304, 316, and 440°C had also been addressed.

Statements such as, "Further tests in this area are needed," or "More data is required," require an explanation. To state the need is valuable, however such statements do not provide enough information.

Abstracts taken from the document to be reviewed will be attached to the review. The abstract is also available in the database. Therefore, references to the abstract may be made.

RELATED HLW REPORTS

The report number(s) of any report(s) known to be directly related to the report being reviewed should be entered here so that these reports may be cross-referenced in the database.

The reviewer might also indicate any other reports, e.g. those taken from the reference list in the report being reviewed, that might be useful to acquire and include in the database.

APPLICABILITY OF DATA TO LICENSING -- READ, BUT DO NOT COMPLETE THIS SECTION, NOT TO BE FILLED IN BY THE REVIEWER

Indicated here is the licensing issue addressed by this paper. It is either (a) a specific Listed licensing Issue in an NRC Site Characterization Plan (ISTP) or (b) a new issue not yet identified in an ISTP.

The ranking of the paper is determined as follows: The "Key Data" box is marked if the paper contains data that is of sufficient quality that it must be considered by NRC in an evaluation of a license application. Such a paper must meet at least one of the following criteria: (1) it is an in-depth review of the pertinent literature, (2) it contains data that is found to be especially significant after being assessed for scientific merit and quality, or (3) it contains data with such a small uncertainty that it must be considered in a performance evaluation of a license application. If the paper does not meet any of the above three criteria, it is indicated as "Supporting Data".

Reviewer's comments on the listing of the document may be included with the appropriate Issue Listing in subcategory (a) or (b).

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Argonne National Laboratory, Chemical Technology,
Division, 9700 South Cass Avenue, Argonne, Illinois
60439.

(b) Author(s), Reference, Reference Availability

Abrajano, T., Bates, J., Ebert, W., and Gerding, T.,
"The Effect of Gamma Radiation on Groundwater Chemistry
and Glass Leaching as Related to the NWWSI Repository
Site," UCRL-15825, Preprint SANL-510-001, May 1986.
Available from NTIS.

DATE REVIEWED: 1/6/86; Revised 6/23/87; 7/13/87.

TYPE OF DATA

Leach and pH data.

MATERIALS/COMPONENTS

SRL 165 glass containing U, Cs, and Sr, (SRL U glass), SRL U
glass containing added ^{237}Np , ^{239}Pu , and ^{241}Am , (SRL A
glass), J-13 water pre-equilibrated at 90°C for two weeks
with Topopah Spring tuff, (EJ-13), tuff, 304L SS, air.

TEST CONDITIONS

Detailed test conditions that have been presented by Bates,
et al. (see RELATED HLW REPORTS) are repeated here except for
changes. Tests were run in type 304L stainless steel reaction
vessels which contained the sample submerged in EJ-13 water
with an air space at the top. Vessels were sealed from the
environment with silicone gaskets and exposed to a gamma
radiation field produced by a ^{60}Co source at 1×10^4 rd/h.
The temperature was maintained at 90°C. The test matrices
were as follows: (1) two SRL U disks in pre-equilibrated J-13
water (EJ-13), Surface area/Volume (SA/V) = 0.3 cm^{-1} , R= gas
volume/liquid volume = 0.3, (2) two SRL A disks in EJ-13
water with a polished tuff core wafer, SA/V= 0.3 cm^{-1} , R=
0.3, (3) EJ-13, R= 0.3, (4) EJ-13 with a polished tuff core
wafer, R= 0.3. Each matrix was run at 90°C for periods of
14, 28, 56, 91, and 182 days. Duplicate samples were run for
each time period. When possible, the protocol of the
Materials Characterization Center (MCC-1) was followed.

METHODS OF DATA COLLECTION/ANALYSIS

Solutions were cooled to room temperature and analyzed for pH, cations by inductively coupled plasma spectroscopy (ICP), anions by ion chromatography (IC), uranium by atomic fluorescence (AF), Cs by atomic absorption spectroscopy (AA), and radionuclides by gamma and alpha counting, and dissolved gases by Van Slyke gas chromatography. The solid test components were measured for weight change and were analyzed by scanning electron microscopy (SEM) and associated energy dispersive X-ray analysis (SEM/EDS), secondary ion mass spectroscopy (SIMS), nuclear resonance profiling and ion microprobe.

AMOUNT OF DATA

Tables

1. Concentration of Fixed Nitrogen Species for blank, SRL U, and SRL A glass. Concentrations of NO_2^- , NO_3^- and total in nanomoles/milliliter ($\mu\text{ mol/l}$) for EJ-13 and EJ-13 + tuff after 14, 28, 56, 91 and 182 days.
2. Concentration, Normalized Transuranic Release, and pH Values for Tests Containing SRL A Glass for EJ-13 and EJ-13 + tuff. Lists period in days, pH, concentrations for unfiltered, and acid strip reported in disintegrations/second per 100 lamda of solution and normalized release rate for Am, Pu and Np respectively.

Figures

1. Variation of pH with time for the non-tuff containing tests; pH (6.5 to 8.0) vs time in days (0 to 200) for SRL A, SRL U, and EJ-13 tests.
2. Normalized loss for (a) Li, (b) Na, (c) B, and (d) mass for SRL A, SRL U, SRL A + tuff and SRL U + tuff. Normalized release rate in g/m^2 (0 to 6) vs time in $\text{days}^{1/2}$ (0 to 16).
3. SIMS profile of SRL U glass + tuff leached for 91 days showing lithium (7), boron (11), sodium (23) and iron (56). Intensity ratio to m/e (mass/ionic charge) of 28 (0 to 4) vs sputter time in minutes (0 to 84). (Indicates concentration of element vs depth in glass).

UNCERTAINTIES IN DATA

None given.

DEFICIENCIES/LIMITATIONS IN DATABASE

All tests showed gradually increasing acidity for 91 days with an actual reversal of the trend at 182 days. This observation was believed to result from loss of acid volatiles from the system because of slight leakage from the test vessels. Loss of CO₂ and N₂ from the gas phase would reduce the amount of bicarbonate in the solution phase and decrease the production of nitric acid by radiolysis.

RELATED HLW REPORTS

Bates, J. K., Fischer, D. F., and Gerding, T. J., "The Reaction of Glass During Gamma Irradiation in a Saturated Tuff Environment, Part 1, SRL 165 Glass," ANL-85-62, 1985.

KEY WORDS

Experimental data, supporting data, weight change, ICP, IC, AF, AA, SEM, SEM/EDS, SIMS, laboratory, air, J-13 water, tuff, cobalt 60, high temperature, acidic solution, basic solution, doped glass, ²³⁷Am, ²³⁹Pu, ²⁴¹Am.

COMMENTS

This report presents data on the influence of gamma irradiation on the reaction of actinide doped borosilicate glass (SRL 165 A and SRL 165 U) in a test environment containing tuff. This is a continuation of experiments at various radiation doses (in this case, 1 x 10⁴ Rd). The objective is to determine the effects of gamma radiation on air and groundwater, and how these interact to change the pH of the leachate and the resulting interaction with and nuclear glass in tuff. In the gamma radiation field, nitric acid is generated by radiolysis of air; thus the solution becomes more acidic. This effect is counteracted by dissolution of the glass and buffered by the bicarbonate in the tuff. Major changes in groundwater in the blank tests show a rapid lowering of the pH to the buffered region (6.4). This pH would be maintained unless the buffering capacity of the groundwater was exceeded by acid production, or acid production was decreased because of depletion of N₂ from the gas phase. The radiation levels at the end of the containment period are expected to be less than 100 rd/hr or about a factor of 100 less than those in the experiments reported in this paper.

APPLICABILITY OF DATA TO LICENSING:

[Ranking: key data (), supporting data (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified:

Related to issue 2.3.2.1.2, which involves the rates of dissolution associated with the potential mechanisms of waste form dissolution in the ISTP for the Nevada Nuclear Waste Storage Investigations (NWSI) Project.

- (b) New Licensing Issues
- (c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Lawrence Livermore National Laboratory, University of California, Livermore, CA 94550.

(b) Author(s), Reference, Reference Availability

Acton, C. F. and McCright, R. D., "Feasibility Assessment of Copper-Base Waste Package Container Materials in a Tuff Repository," UCID-20847, September 30, 1986. Available from NTIS.

DATE REVIEWED: 3/13/87.

TYPE OF DATA

Feasibility assessment

MATERIALS/COMPONENTS

Copper (CDA 102), Al Group (CDA 613), Cu-Ni alloy (CDA 715)

TEST CONDITIONS

Tuff environment, J-13 groundwater, γ -radiation

METHODS OF DATA COLLECTION/ANALYSIS

None given.

AMOUNT OF DATA

No original data, as all tables and figures are taken from other publications. Sources are given.

UNCERTAINTIES IN DATA

None given.

DEFICIENCIES/LIMITATIONS IN DATABASE

None given.

KEY WORDS

Feasibility assessment, laboratory, Yucca Mountain, J-13 water, tuff, gamma radiation field, copper base, CDA 102, CDA 613, CDA 715, corrosion (crevice), corrosion (pitting).

COMMENTS

The paper discusses the feasibility of using copper-base containers for HLW at the Nevada site. The conclusions are quite favorable. The authors agree that the extant data on questions such as the effect of γ -radiation on corrosion rates and the occurrence of localized corrosion are insufficient for final conclusions. Nevertheless, on the basis of work so far completed (mainly HEDL-7612 for corrosion studies) the outlook is quite good.

No attempt is made to rank the three materials considered, nor is a number suggested for a recommended thickness for the container. The reliability of the data used, particularly of the geochemical data characterizing the environment, is not discussed. Since the conclusions concerning corrosion resistance depend heavily on this, the uncertainty might be greater than the authors claim it is. The issue of stress corrosion cracking also has not been seriously addressed.

RELATED HLW REPORTS

Many. In particular, Yunker, W. H., "Corrosion of Copper-Base Materials in Gamma Radiation," HEDL-7612, 1985.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to issue 2.2.4.1, rates of corrosion as a function of time for the various corrosion modes of the waste package container in the ISTP for the Nevada Nuclear Waste Storage Investigations (NNWSI) Project.

- (b) New Licensing Issues
(c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Lawrence Livermore National Laboratory, University of California, Livermore, CA 94550.

(b) Author(s), Reference, Reference Availability

Van Konynenburg, R. A., "Radiation Chemical Effects in Experiments to Study the Reaction of Glass in an Environment of Gamma-Irradiated Air, Groundwater, and Tuff," UCRL-53719, May 1986. Available from NTIS.

DATE REVIEWED: 4/10/87; Revised 6/15/87.

TYPE OF DATA

Discussion of kinetic modeling of chemical reactions induced by gamma radiation of air, groundwater and other waste package components.

MATERIALS/COMPONENTS

Considers experimental data reported by Bates et al. and Abrajano et al. (see RELATED HLW REPORTS below). This report considers experiments involving SRL U glass, SRL A glass, J-13 water pre-equilibrated at 90°C for two weeks with Topopah Spring tuff (EJ-13 water), tuff, 304L SS, and air.

TEST CONDITIONS

As reported by Bates and Abrajano, leach tests were run in stainless steel reaction vessels. The samples were submerged in about 16 ml of EJ-13 water with at least 4 ml of air at the top. These vessels were sealed from the environment and exposed to a gamma radiation field produced by a ⁶⁰Co source of 2×10^5 (Bates) or 1×10^5 rd/h (Abrajano) at a temperature of 90°C. Samples consisted of two glass disks or two glass disks with tuff. Tests for each of the glasses were run in duplicate for 7, 14, 28, and 56 days (Bates) or 14, 28, 56, 91, and 182 days (Abrajano). Similar tests were run on two blanks containing EJ-13 water and EJ-13 water plus tuff.

METHODS OF DATA COLLECTION/ANALYSIS

Details of data collection and analysis are reported in detail in the review of Bates et al. and Abrajano et. al. cited below.

AMOUNT OF DATA

Tables

1. Composition of AISI standard type 304L stainless steel.
2. Composition of SRL glasses.
3. Composition of Topopah Spring tuff expressed as oxides.
4. Composition of "Equilibrated J-13" water at 20°C (first set of experiments).
5. Parameters influencing composition of gas and liquid phases. Parameter, (e.g., vapor pressure of water), value at 20°C, value at 90°C, reference.
6. Changes in compositions of gas and liquid phases due to heating, in vessels originally containing 16 ml of water. Gas phase volume, pressure, liquid phase volume, concentration of species at 20 and 90°C.
7. Composition of standard dry air.
8. Primary products of gamma irradiation of liquid water for pH of 5 to 9.
9. Reactions and rate constants for pure water at 25°C (from four sources).

Figures

1. Nitrogen fixation in 2×10^5 rd/h experiment, Increase in concentration of fixed nitrogen in 10^{-4} M (-.40 to 1.60) vs Time in days (0 to 60).
2. Nitrite-nitrate ratios in 10^4 rd/h experiments, Ratio $[\text{NO}_2^-](\text{M})/[\text{NO}_3^-](\text{M})$ (0 to 7) vs Time in days (0 to 200).
3. Nitrite-Nitrate ratios in 2×10^5 rd/h experiments, Ratio $[\text{NO}_2^-](\text{M})/[\text{NO}_3^-](\text{M})$ (0 to 2) vs Time in days (0 to 60).

UNCERTAINTIES IN DATA

Uncertainties in anion analyses of ± 5 percent, dose ± 10 percent, yield (No. of particles of a particular species created or destroyed per 100 ev) ± 15 percent.

DEFICIENCIES/LIMITATIONS IN DATABASE

The author states, "Since a thoroughgoing computer model of the system of interest was not available, I elected to perform an approximate analysis of the radiation chemistry considering only the dominant reactions."

KEY WORDS

Air, cobalt 60, data analysis, effect of radiation on leaching, gamma radiation field, J-13, kinetic model, SRL U glass, SRL A glass, theory, tuff.

COMMENTS

This report discusses the formation of a number of species that could be formed by interaction of gamma radiation with components present in a repository setting. Initially, in this report an attempt to model the experimental results obtained in leach experiments by Bates et al and Abrajano et al. is reported. Van Konynenburg used an equation developed by Burns et al., which predicts that the formation of fixed nitrogen (i.e., nitrites or nitrates) will be proportional to the ratio of the volume of air to liquid and the total dose. This equation gives a reasonable fit to the experimental data. Depending on the conditions, many possible reaction products can result from radiolysis. For the experiments considered here, the principal reactions include the following: (1) a net radiolysis of water into H_2 and O_2 , (2) nitrogen fixation to NO_2^- and NO_3^- with the formation of an equivalent amount of H^+ which tends to lower the pH against the buffering action of dissolved carbonate, tuff, and glass, and (3) the formation of a colloidal Fe^{+3} substances suspended in the solution as a result of interactions with the vessel walls. It should be noted that when groundwater first breaches the waste canister some 300 to 1000 years after closure, the gamma radiation dose rate will be at least three orders of magnitude below those used here.

RELATED HLW REPORTS

Bates, J. K., Fischer, D. F., and Gerding, T. J., "The Reaction of Glass During Gamma Irradiation in a Saturated Tuff Environment, Part 1, SRL 165 Glass," ANL-85-62, 1985.

Abrajano, T., Bates, J., Ebert, W., and Gerding, T., "The Effect of Gamma Radiation on Groundwater Chemistry and Glass Leaching as Related to the NWWSI Repository Site," UCRL-15825, Preprint SANL-510-001, May 1986.

Burns, W. G., Hughes, A. E., Marples, J. A. C., Nelson, R. S., and Stoneham, A. M., "Effects of Radiation on the Leach Rates of Vitrified Radioactive Waste," J. Nucl. Mater. 107, 245, 1982.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting data (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to issue 2.4.3 concerning how the radionuclide species (i.e., particles, colloids and solubles) change with time in the waste package in the ISTP for the Nevada Nuclear Waste Storage Investigations (NNWSI) Project.

- (b) New Licensing Issues
- (c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Westinghouse Hanford Laboratory, P. O. Box 1970,
Richland, Washington.

(b) Author(s), Reference, Reference Availability

Smith, H. D., "Zircaloy Spent Fuel Cladding
Electrochemical Experiment at 170°C and 120 psia H₂O,"
HEDL-7545, April 1986. Available from NTIS.

DATE REVIEWED: 1/19/87.

TYPE OF DATA

There is no data. This is a research plan.

MATERIALS/COMPONENTS

Zircaloy spent-fuel cladding from the H. B. Robinson fuel assembly B-05 (removed from service, May 6, 1974 after 799 full-power days, average burnup of 28.0 MWd/kgM and peak burnup, 31.4 MWd/kgM), identified as MCC Approved Testing Material ATM-101; cladding with surface oxide and cladding with the oxide removed to expose the bare metal.

TEST CONDITIONS

Two environments, considered to be critical, are used. The first occurs after 90 to 100 years with an unbreached container but with breached fuel containing water. This test is designed to expose cladding in 120 psi, 170°C deionized water in an autoclave. The second environment occurs after 1000 years and the canister is breached. Cladding is exposed to 90°C tuff-equilibrated J-13 water. Six experiments are planned. The first two tests are scoping tests and results will be used to refine future tests. Bundles of spent fuel cladding mimicing the configuration in repository storage will be placed in Hastelloy-276 autoclave for periods of 2, 6 and 12 months. The fuel with Zircaloy-4 plugged ends will be bundled in a hexagonal array, wrapped in 304 stainless steel sheet, clamped with stainless steel, and will sit on alumina plates. Alumina spacers will be used to electrically isolate the cladding from the autoclave. Some C-clamp specimens will be loaded to test for stress corrosion cracking.

METHODS OF DATA COLLECTION/ANALYSIS

A thermocouple will be used to monitor the autoclave temperature, the pressure will be monitored, and the amount of water at the beginning and end of the test and any added water will be measured. The water level will be about one half of the distance to the top of the autoclave. Records will be kept in a dedicated HEDL notebook. At intervals in the test, 5 ml of water will be drawn to analyze for pH, Zr, ^{14}C , and ^{137}Cs . Evaluation after testing will use photography to document exposed specimens. Selected specimens will be prepared metallographically and observed with light microscopy and with the scanning electron microscopy. Auger analysis in conjunction with ion milling will be used to analyze thin film growth.

AMOUNT OF DATA

This report gives no data from experimental tests. There are five figures. Four of these figures are "Section Diagrams" and "Sample Identifiers Correlated to the Cs-137 Gamma Scan of H.B. Robinson Fuel Rod Segments (J12C, N4C, C5T, and C5B)"; these show activity counts per 300 s vs distance from the bottom in cm. The fifth figure is a "Schematic Cross Section of the Autoclave with the Spent Fuel Cladding Bundle in Place." There is one table which gives the "Distribution of Spent Fuel Specimens (from Figures 1, 2, 3, and 4) Between the Three Experimental Bundles."

UNCERTAINTIES IN DATA

Corrosion rates at 180°C on the order of tens of angstroms may be detectable by profiling thin films with Auger analysis/ion milling techniques. Photographic and microscopic evaluation rely on comparative observations to identify and measure corrosion.

DEFICIENCIES/LIMITATIONS IN DATABASE

None given.

KEY WORDS

Planned work, corrosion, surface film, pitting, visual examination radioactivity level simulated field, Yucca Mountain, J-13 water, deionized water, high temperature high pressure, cladding, spent fuel, Zircaloy, Zircaloy-4, ^{14}C , ^{137}Cs .

COMMENTS

This seems to be a good experiment for scoping corrosion behavior under the conditions given. The sampling, apparatus, testing procedures, and specimen analyses appear to be planned well. The data from these tests will show whether corrosion does or does not occur within the testing time. There are no electrical measurements, and electrochemical measurements are the type of data needed to describe corrosion reactions and to predict long-term behavior. Tests with electrochemical connections should be considered for future planned tests. In the meantime, the data, as obtained from the tests as planned, should be useful.

RELATED HLW REPORTS

Five reports are cited in the references: HEDL-7455, HEDL-TC-2562, PNL-5109, UCID-20172 (reviewed at NBS) and HEDL-7455 Rev. 1.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to issue 2.3.6, potential damage and failure mechanism for spent fuel cladding in the ISTP for the Nevada Nuclear Waste Storage Investigations (NNWSI) Project.

- (b) New Licensing Issues
- (c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Westinghouse Hanford Company, P. O. Box 1970, Richland, Washington.

(b) Author(s), Reference, Reference Availability

Smith, H. D., "C-Ring Stress Corrosion Cracking Scoping Experiment for Zircaloy Spent Fuel Cladding," HEDL-7546, March 1986. Available from NTIS.

DATE REVIEWED: 4/2/87; Revised 6/24/87.

TYPE OF DATA

There is no data. This is a research plan.

MATERIALS/COMPONENTS

Zircaloy cladding from Turkey Point spent fuel, some specimens will have a thick oxide coating (10 μm) and other specimens will have a thin oxide coating (3 μm).

TEST CONDITIONS

This "C-Ring" test method is patterned after ASTM G 38, "Standard Recommended Practice for Making and Using C-Ring Stress-Corrosion Test Specimens". The environment for this scoping test is 90°C tuff equilibrated J-13 well water. (Another experimental series, to be reported later, will use an environment of 170°C water at 120 psi in an autoclave). The stress is applied by C-ring loading. The yield stress of the C-rings will be determined in air to establish load levels for the stress corrosion cracking (SCC) tests.

METHODS OF DATA COLLECTION/ANALYSIS

Each experiment will be monitored using a linear variable displacement transducer (LVDT). A time vs deflection record will be kept, and from these data a failure load stress level can be defined. The experiment will be terminated at a predetermined deflection which is characteristic of failure. Specimens will be examined in the scanning electron microscope to study the fracture surface, the outside surface near the SCC crack, and the relationship between the surface oxide layer fracture and the fracture of the metal. Failure rate vs load under given environmental conditions will be

determined. The chemistry of the water will be monitored regularly and adjusted if needed. Quality assurance procedures will be followed.

AMOUNT OF DATA

There is no data. There are three figures describing the experiment: Figure 1, "C-Ring" Experiment Apparatus. Arms with weights in place lowered to "C-Ring" stressing position; Figure 2, Schematic Cross Section of the Water Tank of the "C-Ring" Stress Corrosion Cracking Scoping Experiment Apparatus with the Anvils in Position Stressing a "C-Ring" Specimen; and Figure 3, Cladding "C-Ring" Specimen. Figure 1A in the appendix shows plots of the variation of the "apparent mechanical advantage" (R) versus the distance from the design load line (x).

UNCERTAINTIES IN DATA

None given.

DEFICIENCIES/LIMITATIONS IN DATABASE

None given.

KEY WORDS

Planned work, laboratory, Yucca Mountain, stress corrosion cracking (SCC), corrosion, test, J-13 water, water, tuff, ambient temperature, high temperature, static (no flow), Zircaloy, mixed stress loading, spent fuel.

COMMENTS

This test is described for use in a scoping experiment, and it is a practical test for this purpose. The circumferential stress in the "C-Ring" specimen is not uniform. The stress will vary through the specimen thickness, around the circumference to the middle of the arc, and across the width of the ring. The transverse stress also varies and is a maximum at mid-width of the specimen and zero at the edges. The applied stress in the "C-Ring" test can be measured accurately with deflection methods. Surface oxide thickness can influence SCC susceptibility. Solution pH can influence SCC by causing the surface oxide to be unstable. An attempt should be made, during the microscopic analyses, to determine whether the failure is due to SCC or some other form of local corrosion, such as hydrogen embrittlement, corrosion fatigue, etc. The absence of SCC susceptibility after running this test would not be conclusive. Other tests such as slow-strain-rate tests, low frequency corrosion-fatigue tests, and electrochemically controlled SCC tests should be conducted to characterize the material in terms of resistance to SCC.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to issue 2.3.6, potential damage and failure mechanisms for spent fuel cladding in the ISTP for the Nevada Nuclear Waste Storage Investigations (NNWSI) Project.

- (b) New Licensing Issues
- (c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Argonne National Laboratory, Argonne, Illinois 60439.

(b) Author(s), Reference, Reference Availability

Bates, J. K., and Gerding, T. J., "One-Year Results of the NNWSI Unsaturated Test Procedure: SRL 165 Glass Application," ANL-85-41, August 1986. Available from NTIS.

DATE REVIEWED: 1/5/87; Revised 6/12/87.

TYPE OF DATA

Leach data (unsaturated conditions).

MATERIALS/COMPONENTS

J-13 well water equilibrated with tuff at 90°C (referred to as EJ-13 water); type 304 L stainless steel, tuff, glass made by mixing SRL-165 black frit with appropriate amount of UO_2 , SrO , and $CsNO_3$ to provide a glass with approximately 1 percent U, and 0.1 percent Sr and Cs.

TEST CONDITIONS

The unsaturated test procedure refers to the moisture content of the tuff and the fact that the glass test material is not totally immersed in groundwater. The reaction vessel allows J-13 water droplets of 0.1 ml per drop to drip at a predetermined leak rate onto the waste form, which in this case is a cylindrical doped SRL-165 glass. Water drips into a reservoir at the base of the test vessel to allow for simulation of unsaturated conditions at a temperature of 90°C and pressure of 1 atm. The glass specimen, representing the waste form, is held in position by a stainless steel holder consisting of perforated plates above and below the specimen. The plates were held together by stainless steel rods. The rods were welded to the bottom plate using Tungsten Inert Gas (TIG) welding. Groundwater may be circulated, by evaporation and condensation due to temperature gradients in the test apparatus, but this is not made clear in the report. See general comments below.

METHODS OF DATA COLLECTION/ANALYSIS

Specimens representing two of the anticipated waste-package components (waste form and canister) are contacted intermittently by dripping water. The glass was analyzed for phase separation using X-ray diffraction (XRD) and scanning electron microscopy (SEM). The glass composition was determined by colorimetry (Si, P), atomic absorption (Cs), isotopic dilution mass spectrometry (B), and inductively coupled plasma spectroscopy (ICP) (all other elements). Many of the deposits, glass surfaces and steel parts of the test apparatus were characterized visually, by Scanning Electron Microscopy/Energy Dispersive Spectroscopy (SEM/EDS) and Secondary Ion Mass Spectrometry (SIMS).

AMOUNT OF DATA

Figures

1. NNWSI Waste Form Test Apparatus. (a) Cutaway view, (b) Schematic, (c) Selected parts.
2. Photograph of a Reacted Sample of Glass from Test F-4. Figures 3a-18 contain twenty-one photomicrographs of selected reaction sites or reaction products at specified locations; analysis of top and bottom of canister by SIMS; and SIMS Spectrum of the Nonsensitized Surface of the Reference Type 304L Stainless Steel.

Tables

1. Test Matrix for Unsaturated Tests.
2. Composition of SRL Glass Used in Testing.
3. General Observations of Canister Sections
4. General Observations of the Glass after Disassembly.
5. Water Loss During Testing.
6. Analyses of Equilibrated J-13 Water Used in Unsaturated Testing.
7. Results of the Blanks for the Unsaturated Tests.
8. Solution Results for the Continuous Tests.
9. Solution Analyses for the NNWSI Unsaturated Tests.
10. Results from the Dissolution of Tuff Cups.
11. Analyses Performed on Components from the Unsaturated Tests.
12. Component Weight Changes in NNWSI Unsaturated Tests.
13. Composition of 304L Stainless Steel Used in the Unsaturated Tests.
14. SIMS Analysis of Tuff Samples.
15. Total B, Li, and U Release from the Waste Form.
16. Solution Results of Glass Parametric Test No. 1.
17. Test Conditions and Selected Results from the Analog Tests.

Appendix 1. Conditions and Selected Results of the Unsaturated Test Matrix.

Appendix 2. Detailed Solution Analyses for the Unsaturated Tests.

Appendix 3. Modified Test Vessel Design.

UNCERTAINTIES IN DATA

Uncertainties in some of the chemical analyses are discussed briefly.

DEFICIENCIES/LIMITATIONS IN DATABASE

The objective of the tests was to obtain leach data as a function of time with a "reasonable" trend in elemental release required for modeling repository behavior. The objective was not achieved because apparently different release trends were observed owing to sensitization of stainless steel.

RELATED HLW REPORTS

Bates, J. K. and Gerding, T. J., "NNWSI Phase II Materials Interaction Test Procedure and Preliminary Results," ANL-84-81, 1984.

Van Konynenburg, R. A., "Radiation Chemical Effects in Experiments to Study the Reaction of Glass in an Environment of Gamma-Irradiated Air, Groundwater, and Tuff," UCRL-53719, May 1986.

KEY WORDS

Data analysis, experimental data, supporting data, X-ray diffraction, visual examination, weight change, SIMS, SEM/EDS, SEM, laboratory, air, J-13 water, tuff, high temperature, stainless steel, 304L stainless steel, doped SRL-165 glass, ^{238}U .

COMMENTS

This report describes leach data obtained using an unsaturated test procedure. In this leach procedure, the waste form is not totally immersed in water, but the method devised does allow liquid water to be in contact with the waste form if water is present and the temperature gradients in the canister are appropriate. The section of the report describing the means of water injection into the test apparatus is totally inadequate. In ANL 84-81 (1984), which is a more detailed report of the test method, the authors describe an injection system in which water and air are injected into the apparatus in prescribed amounts and intervals. In this report, the method described in ANL 84-81 is not mentioned. The statement that the "temperature

differential between the waste package and the test vessel is based on the thermal equilibration of test component" could be interpreted as meaning that the water flow is driven by a temperature gradient. There is also some question concerning the pressure at which the measurements were made. Although it is stated that the pressure is 1 atm, Van Konynenburg's analysis of similar measurements indicated higher pressures due to expansion of the initial air and the partial pressure of water at 90°C.

Much of this report deals with interactions between the waste form, water, and stainless steel, resulting from sensitization of stainless steel due to tungsten-inert-gas weldments on the waste support holder. Since there may be weldments on the stainless steel canisters, the effect of sensitized stainless steel on the leaching kinetics of the waste form may be important. Most nuclear waste glasses may undergo leaching simultaneously by both hydration and matrix breakdown. Hydration initially occurs more rapidly than matrix breakdown, but since it follows parabolic ($t^{1/2}$) kinetics, the penetration of the hydration front slows with time. When sensitized stainless steel is present, the formation of Fe, Ni, and Cr silicates increases the rate of matrix breakdown so that it may become the dominant leach process. Matrix breakdown is a process in which the constituents that form the matrix of the glass are simultaneously released so that normalized release rates of all the elements are the same. The kinetics are linear with time. The extent of interaction of leachate with stainless steel in the data obtained in this report varied broadly from extensive to slight.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting data (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified:

Related to issue 2.3, concerning when, how, and at what rate radionuclides will be released from the waste form in the ISTP for the Nevada Nuclear Waste Storage Investigations (NNWSI) Project.

- (b) New Licensing Issues
(c) General Comments

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Hanford Engineering Development Laboratory, P. O. Box
1970, Richland, WA 99352.

(b) Author(s), Reference, Reference Availability

Einzigler, R. E., "Test Plan for Long Term, Low-
Temperature Oxidation of Spent Fuel, Series 1,"
HEDL-7560, June 1986. Available from NTIS.

DATE REVIEWED: 3/26/87.

TYPE OF DATA

Plan for low-temperature oxidation of spent fuel. Oxidation rate to be determined from weight gain as a function of time at specified temperatures.

MATERIALS/COMPONENTS

Selected spent fuel from Turkey Point, air, water vapor, Ni/Cr crucibles.

TEST CONDITIONS

Spent fuel samples consisting of fragments sized from -10/+24 mesh and -24/+60 mesh will be oxidized in dry air, (dew point below -55°C), and moist air, (dew point of 80°C), at temperatures of 175, 130 and 110°C. Samples of 10 grams will be contained in Ni/Cr crucibles and heated in an aluminum block dry bath. Test duration will be 2 years. Time intervals between periodic weighings of 100 to 400 hours will be adjusted as data become available in order to obtain optimal weight gains. Mesh sizes 10, 24, and 60 correspond to 1.7, 0.71, and 0.25 mm respectively. Dew points of -55 and 80°C correspond to water vapor partial pressures of less than 0.016 and 355 torr respectively.

METHODS OF DATA COLLECTION/ANALYSIS

Rate constants will be determined from weight gain data fit to models. Models assume grain boundary diffusion in early stages of oxidation followed by bulk diffusion. Post test samples will be examined by scanning electron microscopy (SEM) and X-ray diffraction (XRD) to obtain additional phase information.

AMOUNT OF DATA

Tables

1. Test Matrix.
2. Determination of D_g (grain boundary diffusion constant) from Thermogravimetric Analysis (TGA) data.
3. Time Ranges when Bulk Diffusion Becomes Controlling Oxidation Mechanism.
4. Turkey Point Fuel Available for Testing.
4. Thermal Conductivity of Uranium Oxides.

Figures

1. Rate Constant for Spent Fuel Oxidation Determined by TGA Testing. Rate constant (10^{-9} to 10^{-3} cm^2/h) vs $10^4/T$ (19 to 26°K^{-1}).
2. Weight Gain Projections for 10g Sample Based on Single Mechanism Oxidation. Weight gain (0 to 150 mg) vs time (0 to 20,000 h)
3. Weight Gain Projections after Slow Grain Boundary Penetration. Weight gain (0 to 200 mg) vs time (0 to 20,000 h).
4. Oxidation of Spent Turkey Point PWR Fuel in Air at 200°C . $[1 - (3 \Delta O/M)^{1/3}]$ (0 to 0.20) vs $t^{1/2}$ (0 to $15 \text{ h}^{1/2}$).
5. Grain Boundary Diffusion of O_2 into Spent Fuel as a Function of Temperature Based on TGA data. Diffusion constant (10^{-10} to 10^{-7} cm^2/s) vs $10^4/T \text{ K}^{-1}$ (20 to 26).
6. Time to Complete the Grain Boundary Diffusion Stage as a Function of Fragment Radius at 175, 130, and 110°C . Radius of fragment (0 to 2 mm) vs $t^{1/2}$ (0 to $140 \text{ h}^{1/2}$).
7. Cutting Diagram for Rods Used in Testing.
8. Relationship of Characterization and Test Rods in Assembly B17.
9. Gamma Scans of Companion Rods from Assembly B17. Relative activity (0 to 100) vs distance from bottom fuel pellet (0 to 150 inches).
10. SEM Examination of Fuel Fragments from Rod F6.
11. Dry Bath Oxidation System.
12. Dry bath with Blocks, Thermocouples and Gas Lines.
13. Positioning of Crucible and Fuel Sample in the Aluminum Thermal Blocks.
14. Placement of Thermocouples in Dry Bath Diagnostic Testing.
15. Sample Crucible.

UNCERTAINTIES IN DATA

None given.

DEFICIENCIES/LIMITATIONS IN DATABASE

If diffusion along the grain boundaries is slow with respect to the test duration, measurements of weight gain utilizing fuel fragments will not reflect the rate limiting bulk diffusion step, but will represent a combination of grain boundary and bulk diffusion.

KEY WORDS

Planned work, oxidation of spent fuel, supporting data, diffusion model, weight change, SEM, XRD, laboratory, air, water vapor, spent fuel (PWR reactor), high temperature, ambient pressure.

COMMENTS

Spent fuel is a potential waste form for isolation in a nuclear waste repository. Oxidation of spent fuel is expected to have an effect on both the rate of leaching and the concentration of specific radionuclides in the leachate. This report deals with oxidation of spent fuel in breached Zircaloy cladding. Defected cladding may allow the spent fuel to oxidize to a more leachable higher oxidation state before the fuel comes into contact with groundwater. A plan is described for obtaining oxidation data in dry or moist air at temperatures in the range of 110 to 175°C. From previous measurements, the authors believe that oxidation of spent fuel by air involves an initial oxidation mechanism of grain-boundary diffusion followed by a bulk diffusion process into the individual grains. This is a plausible concept, however, the data presented in support of it is not very convincing because only a single data point falls on the line purported to represent grain-boundary diffusion. It is possible that the deviant point thought to represent grain-boundary diffusion is due to random error in the measurements. Although the oxidation of spent fuel will not take place within leaktight Zircaloy cladding, the lifetime of cladding under repository conditions is uncertain. The conditions for the oxidation study in dry or moist air are very different. The moist-air (water) pressure would be 355 torr as compared to 0.016 torr for the dry-air measurements. This could lead to different rates of oxidation because, at a total pressure of one atmosphere, the partial pressure of O₂ would be lowered. Also, interaction of radiation from the spent fuel with water vapor might lead to formation of different gaseous species which could change the oxidation mechanism. Knowledge of rate constants for both grain-boundary and bulk diffusion could provide an estimate of the overall oxidation rate of the spent fuel if it was possible to determine the time period during which each diffusion process was important.

RELATED HLW REPORTS

Einzigler, R. E., and Woodley, R. E., "Low Temperature Spent Fuel Oxidation under Tuff Repository Conditions," HEDL-SA-3271FP, 1985, in Proceedings of the Symposium on Waste Management, Tucson, Arizona, March 24-28, 1985.

Einzigler, R. E., and Woodley, R. E., "Test Plan for Series 2 Thermogravimetric Analysis of Spent Fuel Oxidation," HEDL-7556, February 1986.

Einzigler, R. E., and Woodley, R. E., "Evaluation of the Potential for Spent Fuel Oxidation under Tuff Repository Conditions," HEDL-7452, March 1985.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting data (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to issue 2.3.6.3, concerning how the presence of defects alter the radionuclide retention capability of the waste form. Oxidation of the spent fuel through pinholes or other fissures is a potential failure mechanism in the ISTP for the Nevada Nuclear Waste Storage Investigations (NNWSI) Project.

- (b) New Licensing Issues
- (c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Lawrence Livermore National Laboratory, Livermore, CA
94550.

(b) Author(s), Reference, Reference Availability

Oversby, V. M., "Spent Fuel as a Waste Form--Data Needs to Allow Long Term Performance Assessment Under Repository Disposal Conditions," UCRL-94659, December 1986.

DATE REVIEWED: 5/4/87; Revised 7/27/87.

TYPE OF DATA

(1) Scope of the Report

The report is an analysis and technical review of factors affecting radionuclide release from spent fuel under repository conditions. (See reports listed under RELATED HLW REPORTS for the original information and greater detail of the methods and results than are given in this report.) The paper presents an analysis [details of calculations not given in this report] of NRC and EPA regulations and from that analysis a ranking of the radionuclides in spent fuel is derived. Areas are suggested where more work is needed to support performance assessment calculations.

(2) Failure Mode or Phenomenon Studied

Dissolution of spent fuel and assembly components in high-level waste repositories.

MATERIALS/COMPONENTS

Radionuclides for which release rates are discussed include the following: ^{241}Am , ^{242}Am , ^{243}Am , ^{14}C , ^{242}Cm , ^{245}Cm , ^{246}Cm , ^{135}Cs , ^{129}I , ^{94}Nb , ^{59}Ni , ^{63}Ni , ^{237}Np , ^{239}Np , ^{107}Pd , ^{238}Pu , ^{239}Pu , ^{240}Pu , ^{241}Pu , ^{242}Pu , ^{226}Ra , ^{79}Se , ^{151}Sm , ^{126}Sn , ^{99}Tc , ^{230}Th , ^{233}U , ^{234}U , ^{235}U , ^{236}U , ^{238}U , ^{93}Zr .

Besides the spent fuel itself, other radioactive elements found in components are mentioned, specifically the nickel in stainless steels, the zirconium in Zircaloy, and the carbon-14 activation product in the Zircaloy.

TEST CONDITIONS

(1) State of the Material being Tested

In the tests for which results are reviewed (see Reports HEDL-TME 85-22 and UCID-20926, Figures 1, 2, 3), the spent fuel used was pressurized-water reactor (PWR) fuel of average burnup from the H.B. Robinson reactor. Bare fuel as well as fuel with the cladding hulls were included in the tests. Some Turkey Point bare fuel was also tested.

(2) Specimen Preparation

None given.

(3) Environment of the Material being Tested

The Nevada Nuclear Waste Storage Investigations (NNWSI) Series 2 dissolution test conditions were used (details describing these tests are not given in the report). The solution used for all cycles of the testing was J-13 well water, a dilute sodium bicarbonate groundwater.

METHODS OF DATA COLLECTION/ANALYSIS

The author discusses and compares the NRC rule (10 CFR 60) and Environmental Protection Agency standards (40 CFR 191) for HLW disposal in geologic repositories. The EPA standards set limits on the cumulative release of radionuclides to the accessible environment for 10,000 years. Release limits are set for individual radionuclides and for total activity released. For individual radionuclides, there must be a probability of less than 0.1 for releases to exceed one part in 100,000 of the inventory at 1000 years after repository closure and a probability of less than 0.001 for the releases to exceed 10 times those values. The NRC has rules to implement the EPA standards. Siting Guidelines (10 CFR 960) also require long-range performance assessment of proposed repositories and a comparison of performance prior to specific site selection. The comparison is based on two calculations of system performance for 100,000 years. The first calculation uses a specified high value for release of radionuclides from the engineered barrier system, and the second uses a realistic site-specific value. These calculations [not given in the report] require performance predictions for 10 times longer than the NRC rule. The NRC rule requires that the release rate of any radionuclide from the engineered barrier system following the 300-1000 year containment period be less than one part in 100,000 of the inventory of that radionuclide present after 1000 years after closure. The most stringent control that must be demonstrated is one part in 10^5 of a radionuclide inventory at 1000 years after closure or one part in 10^6 of the total

inventory present 1000 years after emplacement, whichever is greater. For most radionuclides the total inventory value is applicable.

The control factors are calculated in the following way. (See UCRL-94222 in which the calculations are described fully.) Using half-life values for the various radionuclides in spent fuel from a pressurized-water reactor (PWR), the amount of activity was calculated for each radionuclide after 1000 years from discharge from the reactor. The total activity of the fuel in curies per metric ton of initial heavy metal (Ci/MTIHM) is calculated to be 1742 after 1000 years. The calculated release rate limit is, therefore, 0.01742 Ci/MTIHM based on the NRC rule requiring the release rate to be 1 part in 100,000 of the inventory after 1000 years. The annual release of any nuclide must be controlled to 1/100,000 of its own 1000-year inventory or to 0.01742 Ci/MTIHM, whichever is greater. This annual controlled release rate (either 0.01742 Ci/MTIHM or 1/100,000 of the inventory), when divided by the 1/100,000 inventory value yields a ratio which is the release rate control factor. The higher the factor, the less need for control of the release rate since the entire inventory could be dissipated over relatively short time periods (a few thousand years). Those nuclides for which the factor is one require the greatest release control.

The analysis of release rates indicate that americium and plutonium require the most reduction in release, that is, the greatest release rate control of the radionuclides. Suggested methods to accomplish this are lower waste form dissolution rates, demonstration of reduction in transportable species resulting from precipitation reactions, retardation of transport due to ion exchange or other sorption processes, or long groundwater travel times.

The results of NNWSI Series 2 dissolution tests of the effect of leaching solutions on the concentrations of radionuclides in stored fuel are quoted. Tests were run in cycles of approximately 6 months in the same solution. At the end of each cycle the solution and fuel samples were removed from the quartz tests vessel and transferred to a new vessel with fresh solution. Solution samples were taken periodically during a cycle. At the end of a cycle, the vessel was rinsed and acid stripped to recover any precipitated solution.

AMOUNT OF DATA

There are four tables, five figures, and seventeen references cited.

Table I - "Release rate control required by 10 CFR 60," lists 10 radionuclides whose release must be controlled to 1 part

in 100,000 of their own inventory at 1000 years after repository closure and, 23 radionuclides for which the calculated release rate applies and the factors [for which the calculations are not given in this report] by which their release rates may exceed 1 part in 100,000 of their own inventory at 1000 years after repository closure.

Table II - "Release rate control based on chemical element," lists the control of release rate for 18 chemical elements based on the most stringent control required for any isotope of that element, in parts in 100,000 of the 1000 year post-closure inventory of that element.

Table III - "Comparison of NRC and EPA allowed releases assuming that no nuclide contributes more than 0.035 EPA units to the sum of release ratios. Comparison is made at the edge of the engineered barrier system," lists the ratios of NRC/EPA allowed releases for 17 elements.

Table IV - "Summary of release data for NNWSI Series 2 H.B. Robinson bare fuel samples, Cycles 1 and 2, conducted at ambient hot cell temperature," lists Total Release in parts in 10^5 , and Percent in Solution for nine elements.

Figure 1 - "Concentration of uranium in solution for the four cycles of the NNWSI Series 2 dissolution tests. Test run at ambient hot cell temperature in quartz vessel using bare fuel with split cladding hulls present in the test." Data are plotted for 0 to 5 ppm uranium for tests of up to 240 days duration for four different cycles of tests.

Figure 2 - "Activity in solution for cesium-137, NNWSI Series 2 tests, cycles 2, 3, and 4. Release for cycle 1 was about 40 times higher than for cycle 2." Data for tests of up to 240 days duration ranging from 0 to 3 microcuries/ml are plotted.

Figure 3 - "Activity of technetium in solution, NNWSI Series 2 tests." Data for four different cycles for tests of up to 240 days duration are plotted for pCi/ml values ranging from 0 to 500.

Figure 4 - "Correlation of fission gas release and rapid release fraction of cesium from CANDU fuel." Measured and calculated values for stable xenon release ranging from 0.01 to 10.0 percent are plotted versus ^{137}Cs release values ranging from 0.01 to 10.0 percent.

Figure 5 - "Uranium concentrations in unfiltered solutions for NNWSI Series 3 tests and for the H.B. Robinson Series 2 bare fuel sample. See text for symbol explanation." Concentration in micrograms per milliliter for seven solutions is plotted against test durations up to 240 days.

UNCERTAINTIES IN DATA

The review discusses several factors for which available data are inadequate to characterize radionuclide release from waste-form components. These factors are described in three categories:

- (1) Effects of sample preparation
- (2) Sample storage conditions
- (3) Experiment design variables.

See the next section for details of the deficiencies in the database.

DEFICIENCIES/LIMITATIONS IN DATABASE

The author identifies six areas where new data are most needed to judge repository license application:

- (1) the effect of reactor type and burnup on dissolution properties of spent fuel. Fuel dissolution probably will not depend heavily on these parameters, but population variability must be addressed in licensing arguments.
- (2) dissolution studies on stainless steel clad fuel. Part of the existing inventory of spent fuel and fuel in use is clad in stainless steel and no dissolution data exist.
- (3) dissolution studies of oxidized spent fuel. The effect of oxidation state on dissolution rate and solubility is needed to assess the effects in the repository environment and the effects of air storage of test specimens.
- (4) dissolution studies using assembly components. There are no data for the rate of radionuclide release from such components in aqueous solutions.
- (5) inventory and release characteristics of carbon-14. Data are needed on both release in air and release into aqueous solutions of carbon-14.
- (6) thermodynamic properties of solids that might limit radionuclide solubility. Silicate minerals may limit the solubility of uranium and affect the dissolution properties of spent fuel. Data for uranium silicates are sparse to nonexistent as well as data for compounds thought to limit solubility of actinides. Modeling of long-term behavior of geochemical systems depends on good thermodynamic data for the relevant phases.

KEY WORDS

Data analysis, literature review, leaching solution analysis, simulated field, air, J-13 water, ambient temperature, stainless steel, zirconium base, spent fuel (PWR reactor), spent fuel (BWR reactor), ^{241}Am , ^{242}Am , ^{243}Am , ^{244}Am , ^{14}C ,

²⁴²Cm, ²⁴⁵Cm, ²⁴⁶Cm, ¹³⁵Cs, ¹²⁹I, ⁹⁴Nb, ⁵⁹Ni, ⁶³Ni, ²³⁷Np, ²³⁹Np, ¹⁰⁷Pd, ²³⁸Pu, ²³⁹Pu, ²⁴⁰Pu, ²⁴¹Pu, ²⁴²Pu, ²²⁶Ra, ⁷⁹Se, ¹⁵¹Sm, ¹²⁶Sn, ⁹⁹Tc, ²³⁰Th, ²³³U, ²³⁴U, ²³⁵U, ²³⁶U, ²³⁸U, ⁹³Zr.

COMMENTS

A comprehensive review of spent-fuel radionuclide release factors and data are presented with identification of needs for further study. No new data are included. See the section "Deficiencies/Limitations in Database" for the data needed to provide an adequate database for characterizing radionuclide release from waste-form components. [This report should be read in conjunction with report UCRL-94222, in which the calculation of release rate control factors is fully explained.] In an attempt to make this review more widely understood, the reviewer has extracted parts of this calculational procedure from UCRL-94222 and presented them under METHODS OF DATA COLLECTION/ANALYSIS.

RELATED HLW REPORTS

UCRL-94222

HEDL-TME 85-22

UCID-20926

UCRL-90855

UCRL-94708

PNL-5109

UCRL-94633

HEDL-TME 84-30

See also 40 CFR Part 191; Federal Register vol. 50; No. 182
1985;
10 CFR Part 60; U.S. Government Printing Office
1983;
10 CFR Part 960; Federal Register vol. 49; No. 236
1984.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (); supporting data (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to issue 2.3, when, how and at what rate will radionuclides be released from the waste form in the ISTP for the Nevada Nuclear Waste Storage Investigations (NNWSI) Project.

- (b) New Licensing Issues

- (c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Lawrence Livermore National Laboratory, Livermore, CA
94550.

(b) Author(s), Reference, Reference Availability

Ballou L. B. and McCright, R. D., "LLNL, Attachment 1 to Letter Dated 8 March 1985," to M. Steindler, Argonne National Laboratory, as background information for Materials Review Board ad hoc panel review of NNWSI (and other) repository project corrosion testing programs, MRB-0418, 1985. Available from the authors.

DATE REVIEWED: 10-1-85; Revised 12-3-85; 7-20-87.

TYPE OF DATA

(1) List of planned tests: Dry oxidation, corrosion, stress corrosion cracking, localized corrosion test data

MATERIALS/COMPONENTS

Various rocks and glasses. For corrosion tests: Zircaloy, 304L, 316L, 321, Incoloy 825 stainless steels, cast iron, various steels and alloys.

TEST CONDITIONS

Mostly tuff environment, J-13 water alone and with additions (e.g., chlorides).

METHODS OF DATA COLLECTION/ANALYSIS

None given.

AMOUNT OF DATA

None given.

UNCERTAINTIES IN DATA

None given.

DEFICIENCIES/LIMITATIONS IN DATABASE

None given.

KEY WORDS

Corrosion tests, SCC tests.

COMMENTS

This report is a list of experiments planned or in progress. Neither results nor detailed description of experimental conditions are given. It also covers experiments outside corrosion.

APPLICABILITY OF DATA TO LICENSING

[Ranking: Key data (), supporting data (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to issue 2.2.4, potential corrosion failure modes for the waste package container in the ISTP for the Nevada Nuclear Waste Storage Investigations (NNWSI) Project.

- (b) New Licensing Issues
- (c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Lawrence Livermore National Laboratory, Livermore, CA
94550.

(b) Author(s), Reference, Reference Availability

Ballou L. B. and McCright, R. D., " LLNL, Attachment 2 to Letter Dated 8 March 1985," to M. Steindler, Argonne National Laboratory, as background information for Materials Review Board ad hoc panel review of NNWSI (and other) repository project corrosion testing programs, MRB-0418, 1985. Available from the authors.

DATE REVIEWED: 10-1-85; Revised 12-3-85; 7-21-87.

TYPE OF DATA

Plans for future testing: Corrosion, pitting, stress corrosion cracking. This is a proposed plan for testing Cu and Cu alloys as a possible package material in tuff environment and possibly basalt. A small amount of initial testing should occur in FY 85.

MATERIALS/COMPONENTS

Copper and Cu alloys, CDA 102, CDA 172, CDA 181, CDA 613, CDA 715; also as entire canister

TEST CONDITIONS

Tuff geochemical environment, with and without γ -radiation

METHODS OF DATA COLLECTION/ANALYSIS

Principally electrochemical methods

AMOUNT OF DATA

None given.

UNCERTAINTIES IN DATA

None given.

DEFICIENCIES/LIMITATIONS IN DATA/ANALYSIS

None given.

KEY WORDS

Copper; copper alloys; corrosion, tuff.

COMMENTS

Cu and Cu alloys will be examined as possible container materials, not only from the corrosion standpoint, but also from the mechanical and economic.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting data (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to issue 2.2.4, potential corrosion failure modes for the waste package container in the ISTP for the Nevada Nuclear Waste Storage Investigations (NNWSI) Project.

- (b) New Licensing Issues

- (c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

- (a) Organization Producing Data

Rockwell International, Richland, Washington.

- (b) Author(s), Reference, Reference Availability

Anantatmula, R. P., "Effects of Grande Ronde Basalt Groundwater Composition and Temperature on the Corrosion of Low-Carbon Steel in the Presence of Basalt-Bentonite Packing," RHO-BW-SA-391P, August 1985. Available from NTIS.

DATE REVIEWED: 1/28/87; Revised 4/30/87.

TYPE OF DATA

Experimental data. Weight-loss corrosion tests. Statistical analysis.

MATERIALS/COMPONENTS

1020 AISI Steel packed in 75% basalt/25% bentonite, in the presence of solutions containing various amounts of NaCl, NaF, Na₂SO₄ and Na₂CO₃

MATERIALS/COMPONENTS

Steel as received (hot-rolled). T = 100°C and 250°C in pressure vessels. No oxygen.

METHODS OF DATA COLLECTION/ANALYSIS

Weight loss after 4 weeks. Analysis by the Plackett-Burman statistical method.

AMOUNT OF DATA

1 Table. Weight losses for various solution compositions and temperatures.

UNCERTAINTIES IN DATA

95 percent confidence level.

DEFICIENCIES/LIMITATIONS IN DATABASE

None given.

KEY WORDS

Experimental data, Plackett-Burman statistical design, weight change, laboratory, deionized, Cl⁻, F⁻, SO₄²⁻, CO₃²⁻, basalt, bentonite, high temperature, carbon steel, 1020 carbon steel, hot-rolled, chloride, basalt, bentonite.

COMMENTS

It is an extremely limited test, so that its relevance is minor. Can be taken as indicating that groundwater composition is not too important under reducing conditions.

The conclusion "if resaturation of the repository occurs at a higher temperature (200 to 250°C) the effect on corrosion of low-carbon steel in the presence of the anions within the concentration range tested will be negligible" is not justified by the data [see page 6, paragraph 2]. Lack of statistical significance does not imply absence of a real effect.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting (X)]

- (a) Relationship to Waste Package Performance Issues
Already Identified

Related to issues 2.2.4, what are the corrosion modes of the waste package container and 2.2.4.3, how does the packing material affect the corrosion rates in the ISTP for the Basalt Waste Isolation Project (BWIP).

- (b) New Licensing Issues
- (c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Pacific Northwest Laboratory, Richland, Washington
99352.

(b) Author(s), References, Reference Availability

Pitman, S. G., "Slow-Strain-Rate Testing of 9%Cr, 1%Mo Wrought Steel and ASTM A27 Cast Steel in Hanford Grande Ronde Groundwater", SD-BWI-TS-008, August 1984.

DATE REVIEWED: 2/26/87; Revised 7/31/87.

TYPE OF DATA

1. Scope: Experimental Results
2. Failure Mode: Environmental Induced Cracking; Stress Corrosion Cracking

MATERIALS/COMPONENTS

2 Candidate Container Alloys

9Cr-1Mo Steel (ASTM A387 Gr. 9)
(normalized at 900°C for 52 min, air cooled, tempered at 720°C)

ASTM A27 Cast Steel
(tested as cast)

The specific compositions of the alloys are given in tables 1 and 2.

The specimens were procured and fabricated according to MD-82-1, Rev. 0.

The third candidate alloy was the subject of another report (see RELATED HLW REPORTS).

TEST CONDITIONS

Slow-Strain-Rate Tests

- Standard Proc: MD-82-7, "Slow-Strain-Rate Studies, Unirradiated"
- Strain Rates: 1×10^{-4} , 1×10^{-5} and 2×10^{-7} /s
- Autoclave environment (150°C)
- Simulated Grande Ronde Groundwater

- Flowing (9 ml/h), through crushed basalt then autoclave
- Deaerated with either pure Ar or Ar-20%O₂
- Dissolved O₂ levels: Ar = <1ppm; Ar-20%O₂ = 8ppm

METHODS OF DATA COLLECTION/ANALYSIS

Load and Displacement measurements

- Yield Strength
- Ultimate Tensile Strength

Direct Measurement of Sample

- Reduction in area
- Strain to Failure

AMOUNT OF DATA

6 Tables

1. Composition of 9Cr-1Mo Steel
2. Composition of ASTM A27 Steel
3. Composition of Umtanum Flow Basalt
4. Composition of Hanford Grande Ronde (basalt) Groundwater
5. Results of SSR Tests on 9Cr-1Mo Steel at 150°C
6. Results of SSR Tests on ASTM A27 Steel at 150°C

5 Figures

1. Reduction in Area (0 to 70%) vs Displacement Rate (10^{-7} to 10^{-3}) for 9Cr-1Mo Steel at 150°C in air and groundwater.
2. Load (0 to 4500 lbs.) vs Displacement (0 to 0.5 in) for 9Cr-1Mo steel at 150°C in groundwater.
3. Fractography of 9Cr-1Mo steel tested at 1×10^{-6} in/s in groundwater.
4. Reduction in Area (0 to 70%) vs. Displacement Rate ($1e-7$ to $1e-3$) for A27 Steel 150°C in air and groundwater.
5. SEM Fractography of A27 Steel tested at 150°C in groundwater showing ductile "MVC" fracture.

UNCERTAINTIES IN DATA

"The basalt rock and groundwater used in these tests were the BWIP reference compositions at time of usage. Current (FY-1985) reference compositions are GR-4 groundwater and Cohasset flow basalt. Differences in composition between Cohasset and Umtanum basalt are slight and no difference in corrosion behavior are expected to result."

DEFICIENCIES/LIMITATIONS IN DATABASE

"It is recognized that the groundwater flow rate, oxygen concentration levels, specimen environment and imposed stresses may not be identical to those anticipated for the waste container in a repository. However, for the stated purpose of assessing relative susceptibility of different canister materials to environmental assisted cracking, the test conditions are thought to be sufficient."

KEY WORDS

Experimental data, supporting data, microscopy (SEM), tensile testing, visual examination, slow strain rate, laboratory testing, basalt groundwater, high temperature, steel (A27 and A387), cast steel, elongation, tensile strength, yield strength, corrosion (SCC), hydrogen embrittlement.

COMMENTS

1. The author assumes that hydrogen embrittlement and SCC are separate and distinctly different phenomena.
2. The author assumes that, since a 2 week pre-exposure had no effect on the SSR test ductility at 1×10^{-4} /s, the failure mechanism is SCC -- presumably, what the authors means is that the mechanism of SCC was some mechanism other than hydrogen embrittlement. However, no reduced ductility was found for tests conducted in the environment at this strain rate. If this strain rate was too fast to cause a reduction in the ductility in the environment, then why should it be slow enough to test the hydrogen embrittlement hypothesis? The experiments used to determine if hydrogen is responsible for the reduced ductility should have been conducted at strain rates at which the environmentally reduced ductility is most observable. To thoroughly evaluate the potential role of hydrogen, a whole program of hydrogen absorption measurements and mechanical testing should be undertaken, not a single high-strain-rate tensile test. There is insufficient evidence to conclude that hydrogen embrittlement is not responsible for the observed crack propagation.
3. The author concludes that SCC is not occurring. This is based on the presence of dimples on the fracture surface (even though numerous secondary cracks and a reduced ductility were observed). Mechanisms have been proposed for hydrogen embrittlement and SCC which would be consistent with a dimple morphology. As a result, it is premature to conclude that there is not environmental contribution to crack propagation especially when a reduction in the ductility and secondary cracks are observed.

RELATED HLW REPORTS

Pitman, S. G., "Environmental Testing of AISI 1020 Steel in Hanford Grande Ronde Groundwater," Pacific Northwest Lab., SD-BWI-TI-152, July 1983.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting data (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to issues 2.2.4.1, the corrosion rates for various corrosion modes of the waste package container, and 2.2.4.2, the effect of radiation on the corrosion behavior of the waste container in the ISTP for the Basalt Waste Isolation Project (BWIP).

- (b) New Licensing Issues
- (c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Rockwell Hanford Operation, Richland, WA.

(b) Author (s), Reference, Reference Availability

Yung, S. C., Toyooka, R. T., and McCall, T. B., "Thermal Analysis of Waste Package Preliminary Reliability Assessment," Symposium on Radioactive Waste Management '86, Tucson, Arizona, RHO-BW-SA-509P, March 2-6, 1986.

DATE REVIEWED 2/5/87; Revised 6/30/87.

TYPE OF DATA

A three-dimensional integrated model was used to simulate and predict thermal conditions for the BWIP waste package and its environment. Axial temperature gradients in the waste form and container are predicted. The predicted temperature histories of the waste package container are employed to assess the container lifetimes. Calculations, made from a theoretical model, describe the time dependence of the temperature at various places in the repository.

MATERIALS/COMPONENTS

Consolidated spent fuel (CSF), Intact spent fuel assembly (SFA), West Valley High-Level Waste (WVHLW) / Waste Form, Container, Packing.

TEST CONDITIONS

The assumption of the model are as follows:

- (1) The repository and its environment is in a homogeneous basalt flow and extend vertically to the boundaries of the problems investigated.
- (2) All waste packages are simultaneously emplaced in the basalt repository.
- (3) All components of the waste package are made of isotropic and homogeneous materials.
- (4) Material properties remain constant in each computer run.

- (5) The heat of vaporization and condensation of groundwater in the host rock and convective transport of heat are not considered.

METHODS OF DATA COLLECTION/ANALYSIS

Calculation of temperatures as a function of time and position via the three-dimensional integrated model, HEATING.

AMOUNT OF DATA

One table and 10 figures

Tables

1. Important temperatures from HEATING computation results -- Design-allowable temperatures and peak calculated temperatures for consolidated spent fuel, spent fuel assembly and West Valley High Level Waste.

Figures

1. Diagram Illustrating Waste Package Terminology.
2. Underground Repository Layout.
3. Integrated Three Dimensional Thermal Model Based on Assumption of Geometric Symmetry and Waste Package Simultaneous Emplacement.
4. Detailed XZ Plane Dimensions of the Integrated Three-Dimensional Model.
5. Temperature Histories in and Near Consolidate Spent Fuel Waste Package in the Nominal Case, Calculated by the Integrated Thermal Model, for 1-10000 years, in some points: waste (axial center), container (end), borehole (inner surface), basalt (1.6m from waste center), emplacement room center, temperature range: 50-300°C.
6. Axial Temperature Profiles in Consolidated Spent Fuel Waste Form Midplane, 1, 5, 10, 25, 50 years after emplacement. For distance along the waste form of 0-4m in temperature range of 100-300°C.
7. Axial Temperature Profiles in Container for Consolidated Spent Fuel Waste Form, 1, 5, 10, 25, 50 years after emplacement. For distance along the waste form of 0-4m and temperature range of 100-300°C.
8. Temperature Profiles in the Near Field of the Consolidated Spent Fuel Waste Package, 1, 5, 10, 25, 50 years after emplacement. For distance from waste package center of 0-2m and temperature range of 50-250°C.

9. Isotherms in the XZ Plane through Consolidated Spent Fuel Waste Package Center, 1, 5, 25, 50 years after Emplacement. For distance from waste package center of 0-3m and temperature range of 100-200°C.
10. Far Field Temperature Profiles in YZ Plane through Center of Consolidated Spent Fuel Waste Package, 50, 100, 500, and 1000 years after emplacement. For depth of 0-2000m below ground surface and temperature range of 0-250°C.

UNCERTAINTIES IN DATA

The decay power and the thermal conductivity of the waste form and packing have been varied in their estimated ranges. It was determined that the conductivities of the waste form and the packing are the most influential parameters affecting the temperature profiles. The ranges considered in the study showed that a temperature difference of more than 70°C may result from the uncertainty of the conductivities.

DEFICIENCIES/LIMITATIONS IN DATABASE

Neither the heat of vaporization and condensation of ground water in the host rock, nor the convective transport of heat were considered in the model utilized here.

KEY WORDS

Model/methodology, waste form, physical properties, data analysis, three dimensional integrated model, thermal analysis simulation, air, basalt, commercial high level waste (CHLW), spent fuel, thermal properties, thermal instability.

COMMENTS

This report is only a theoretical evaluation without any experimental results to validate the results. The modeling approach that was taken is significant in that it simultaneously provides both the thermal fields of the waste package and its near-field and far-field environment.

The fact that the heat of vaporization and condensation of the groundwater in the host rock was not considered could be very important in case of significant groundwater flow through the repository site.

Although a temperature difference of more than 70°C may result from the uncertainty of the conductivities, these calculations are still valuable because any change in the conductivities will shift the results along the temperature axis but the shape will stay the same.

RELATED HLW REPORTS

BMI/ONWI-517

BMI/ONWI-612

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting data (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to ISTP for the Basalt Waste Isolation Project (BWIP) issue 2.3.7, how does the waste form design accomodate all potential waste package conditions) by calculating the thermal history of the waste package and repository area due to the waste form. Three different waste forms were studied.

- (b) New Licensing Issues
- (c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Corrosion Technology Section, Westinghouse Hanford Co.,
P. O. Box 1978, Richland, Washington 99352.

(b) Author(s), Reference, Reference Availability

Brehm, F., Lutton, J. M., Rivera, C. L., Maffei, H. P.,
Bohringer, A. P., Paine, D. D., and Pingel, L. A., "BWIP
General Corrosion Studies, Summary Report of Activities
in FY-1984", B047154, 1984.

DATE REVIEWED: 2/5/87; Revised 6/18/87.

TYPE OF DATA

Experimental.

MATERIALS/COMPONENTS

Test coupons of cast and wrought AISI 1020 steel, Fe-9Cr-1Mo steel, Cupro-nickel 90-10, weldments of these materials, OFHC copper and phosphorus-deoxidized copper. AISI 1020 steel with artificial pits. Ferrallium 255, Hastelloy C-276, Inconel 600 and Inconel 625 were obtained as alternate materials with higher corrosion resistance, and these will be used for future testing.

TEST CONDITIONS

An air-steam chamber (ovens with exposure boxes to operate at 150, 200, 250 and 300°C) to simulate the environment of the preclosure period; post-closure anoxic high-temperature environment (200°C, 1250 psig) simulated by static pressure vessels (Parr type) and autoclaves containing basalt-bentonite packing using Grande Ronde #4 synthetic groundwater and corrosion specimens. Anion effects (specific amounts of Cl, F, SO₄, or CO₃ added to test solution at 100 and 200°C) on 48 specimens of 9Cr-1Mo-Fe. Packing material used in the tests was a 3:1 basalt:bentonite mixture.

METHODS OF DATA COLLECTION/ANALYSIS

Weight-loss determinations; electrode potential measurements, pit count, pit diameter and pit area measurements

AMOUNT OF DATA

The eight figures are listed as follows:

- Fig. 1. Operator installing a four vessel rack in oven. Two other racks can be seen, one on each level. Negative 8401740-13CN
- Fig. 2. Air/Steam test with atmosphere chamber installed. The cover flange of the box has been removed to show the coupon racks in place. Negative 8401740-19CN
- Fig. 3. Autoclave flow diagram
- Fig. 4. Riffle sample splitter
- Fig. 5. BWIP General corrosion test specimen summary
- Fig. 6. Average corrosion rates (and standard deviations)
- Fig. 7. BWIP Corrosion test-100°, anion effect on corrosion of 9Cr-1Mo-Fe
- Fig. 8. BWIP Corrosion test-200°C, anion effect on corrosion of 9Cr-1Mo-Fe.

There are three numbered tables

- Table 1. Composition of actual and synthetic Grande Ronde 4 solutions,
- Table 2. Reagents required for preparation of one liter basic stock solution
- Table 3. Reagents for preparation of one liter of stock solution. There is one table with no number which lists "Compiled Data for Wrought AISI Steel Coupons"

UNCERTAINTIES IN DATA

None given.

DEFICIENCIES/LIMITATIONS IN DATABASE

Data collected and reported in the anionic effects tests do not give accurate analyses of corrosion rates due to limitations of the analytical balance which was used for weighing the specimens.

KEY WORDS

Planned work, experimental data, measurements, simulated groundwater, basalt, bentonite, high temperature, steel, cast and wrought 1020 and 1025 carbon steels, weld, corrosion, pitting, chloride, fluoride, sulfate, carbonate, preclosure, postclosure.

COMMENTS

Equipment was set up and tested for the conduct of three types of tests on candidate waste package materials and, in some cases, their weldments. Candidate materials and alternative materials were obtained. These tests simulated repository environmental conditions (except that no radiation was present in these tests) before closure, after closure, and a third test determined the effects of anionic species. Some pitting studies were conducted, but results were not conclusive. This type of simulated testing is valuable in producing data on the durability of materials under the environments of the repository before and after closure. These tests provide an indication of reactivity of these materials on a short-term basis. Tests were conducted to check out the equipment and additional tests were reported to be in progress and results should be available by now. Additional electrochemical measurements should be carried out to supplement these data and to identify the corrosion processes.

RELATED HLW REPORTS

Westinghouse Hanford Company reports on corrosion studies in years preceding and following the period of this report.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to issues 2.2.4, regarding potential corrosion failure modes for the waste package container, 2.2.4.1, dealing with corrosion rates, 2.2.4.3, dealing with effects of packing materials on corrosion in the ISTP for the Basalt Waste Isolation Project (BWIP).

- (b) New Licensing Issues
- (c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Pacific Northwest Laboratory.

(b) Author(s), Reference, Reference Availability

Pitman, S. G., "Enviromechnical Testing of AISI 1020 Steel in Hanford Grande Ronde Groundwater", B023959, July 1983.

DATE REVIEWED: 5/19/87; Revised 7/7/87.

TYPE OF DATA

Experimental, environmentally assisted cracking

MATERIALS/COMPONENTS

1020-steel waste canister

TEST CONDITIONS

Hot-rolled wrought 1020 steel. Slow-strain-rate tests in air and Grande Ronde groundwater, 150°C, refreshed autoclave system

METHODS OF DATA COLLECTION/ANALYSIS

Slow-strain-rate tensile test with LT and TL orientations, SEM observations

AMOUNT OF DATA

Tables listing compositions of 1020-steel test material, Umtanum flow basalt and Hanford Grande Ronde basalt groundwater.

Table giving detailed results of 20 slow-strain-rate tests in 150°C groundwater, 150°C air and 20°C air. Strain rates of 10^{-4} and 2×10^{-7} /s, with 1020-steel samples tested on longitudinal and transverse orientations.

Three figures plotting data from Table (above):

Figure 3 - Yield and ultimate strength (35 to 70 ksi) versus strain rate (10^{-4} and 2×10^{-7} /s) for 1020-steel (LT orientation) in air and groundwater.

Figure 4 - Similar to Figure 3. Reduction in area (45 to 65%) and elongation (25 to 30%) plotted as function of strain rate.

Figure 5 - Similar to Figure 4. Data for 1020-steel tested in TL orientation. 20 to 60 percent reduction in area and 15 to 25 percent elongation.

Optical micrograph of 1020-steel structure, 100x and 250x

Macrograph of slow-strain-rate specimen immediately after testing. Specimen strained to failure in 150°C groundwater at 2×10^{-7} /s; 21 day test.

Fifteen SEM photographs of fracture surfaces of slow strain rate test specimens. Includes illustration of pitting attack.

UNCERTAINTIES IN DATA

Author states that groundwater used in this study differs somewhat from composition now being considered as the reference Grande Ronde groundwater, but it is unlikely that differences affect environmentally assisted cracking kinetics. Specific groundwater composition differences not described in report.

DEFICIENCIES/LIMITATIONS IN DATABASE

Author states that definitive conclusions concerning structural barrier material selection and design are beyond scope of document.

KEY WORDS

Experimental data, corrosion, simulated field, simulated groundwater, Cl, ambient temperature, high temperature, carbon steel, 1020 carbon steel, hot worked, slow strain rate, groundwater, elongation, tensile strength, yield strength, cracking (environmentally assisted).

COMMENTS

Author does not state thickness of hot-rolled steel plate used to prepare test specimens. Significant structural

differences exist hot-rolled plates: i.e. for the thicknesses required for canister construction as compared with those for the thinner gauge plate. These structural differences may affect EAC test results.

Data provide clear indication of environmentally assisted cracking for 1020 steel tested at a low strain rate (2×10^{-7} /s) in Grande Ronde groundwater. Further studies are needed to relate conclusion to structural barrier material selection.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to issue 2.2.4, what are the various corrosion modes for the waste package container in the ISTP for the Basalt Waste Isolation Project (BWIP).

- (b) New Licensing Issues
- (c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Rockwell International, Rockwell Hanford Operations,
P. O. Box 800, Richland, Washington 99352.

(b) Author(s), Reference, Reference Availability

Barney, G. S., Lane, D. L., Allen, C. C., and Jones, T. C.,
"Sorption and Desorption Reactions of Radionuclides with a
Crushed Basalt-Bentonite Packing Material", RHO-BW-SA-416P,
April 1986. Available from NTIS.

DATE REVIEWED: 1/10/87; Revised 4/12/87.

TYPE OF DATA

Laboratory sorption and desorption measurements of selected radionuclides, (^{239}Pu , ^{240}Pu , ^{237}Np , ^{238}U , ^{99}Tc , ^{79}Se , and ^{226}Ra) on fresh or hydrothermally altered packing materials. Twelve run Plackett-Burman statistical design to determine important variables in groundwater composition.

MATERIALS/COMPONENTS

Umtanum basalt characterized as sample RUE-2 (-120 to 230 mesh), commercial Wyoming bentonite clay (-400 mesh), synthetic groundwater and hydrothermally altered packing material prepared using a basalt/bentonite weight ratio of 3/1, synthetic groundwater/solids ratio of 2 in rocking, or rolling autoclaves at 300°C, and 30MPa for 1 month. The synthetic groundwater was selected to simulate Grande Ronde Basalt groundwater that had been altered by interaction with the basalt-bentonite mixture. The model for this groundwater was a solution generated by reacting a crushed basalt-bentonite mixture (1:1 by weight) with synthetic Grande Ronde basalt groundwater at 150°C for 3 months. A synthetic composition based on the analysis of the resulting water was used as the groundwater.

TEST CONDITIONS

Equilibrated samples (at 90°C) of packing material, radioactive tracers, and groundwater were used for measuring the radioactive distribution between the solid and liquid phases. The radionuclide oxidation state was controlled either by removing sufficient oxygen by evacuation to allow the solids and dissolved redox couples to control oxidation states, or by making the solutions .01 M in hydrazine.

METHODS OF DATA COLLECTION/ANALYSIS

Distribution of radioactivity between the liquid and solid phases of the samples was determined from the initial and the final solution activity as established by counting techniques. The basalt and bentonite were characterized before and after hydrothermal alteration using X-ray diffraction, scanning electron microscopy and scanning transmission electron microscopy. Analysis of groundwater was made using inductively coupled plasma, atomic emission spectrometry for elements such as silicon, potassium and sodium, ion chromatography for F^- , Cl^- , and SO_4^{2-} , total carbon analyzer for carbonate, and ion selective electrode for sulfide. Sorption data are plotted using the Freundlich isotherm equation.

AMOUNT OF DATA

Figures

1. Concentration of Technetium ($\log Tc$, -4 to -7 M) Remaining in Solution Versus Initial Hydrazine Concentration ($\log N_2H_4$, -4 to -1 M) for Sorption Experiments with Packing Material.

The data in the following figures were obtained at 90°C using altered packing material.

- 2 and 3. Cation (2) and Anion (3) Concentrations (1-1,000 mg/L) Versus Time (0 to 24 d) for Groundwater Reactions.
4. Sorption Rate Curve for Uranium on Altered Packing Material ($\log U$ concentration, -9 to -4 M versus time, 0 to 30 d)
5. First-order Plots for Uranium Sorption. ($\log C/C_0$, -3 to 0 versus time, 0 to 30 d).
- 6, 7, 8. Sorption Rate Curves for Neptunium, Selenium, and Radium respectively. ($\log Np$, -8 to -3 M; $\log Se$, -8 to -4 M; $\log Ra$, -11 to -7 M) versus Time, 0 to 30 d)
- 9, 10, 11. Sorption Isotherms for Uranium, Neptunium, and Selenium respectively using (a) Basalt, or (b) 0.05 M Hydrazine as Redox Control: $\log S$ (Sorption, mol/g) vs $\log C$ (Concentration, M). Typical order of magnitude sorption and concentration ranges are (-10 to -6) and (-9 to -5) respectively.

12. Sorption Isotherms for Technetium using 0.05 M Hydrazine as Redox control, log S mol/g (-9 to -5) vs log C, M (-9 to -5).
13. Uranium Concentration Desorbed into the Groundwater for Consecutive Desorption Equilibrations, log C, M (-5 to -7) vs equilibration number (1 to 8).
- 14, 15. Desorption Isotherms for Uranium in absence and presence of 0.05 M Hydrazine respectively: log S, mol/g (-7 to -6) vs log C, M (-7 to -4).
- 16, 17. Desorption Isotherms of Neptunium in absence and presence of 0.05 M Hydrazine respectively: log S, mol/g (-7 to -5) vs log C, M (-8 to -5).
- 18, 19, 20. Desorption Isotherms for Selenium and Technetium in presence of .05 M Hydrazine and Radium respectively, log S, mol/g, vs log C, M: Se, (-7 to -6) vs (-7 to -5); Tc, (-6.5 to -5.5) vs (-7 to -6); Ra, (-10.5 to -9.5) vs (-11 to -9).

The data in the following figures used unaltered packing material.

- 21, 22. Calculated Concentration in Solution and Effect of Hysteresis Along a 10 cm Column Filled with Packing Material for Uranium(IV) at (a) 600 d and (b) 100, 200, 400, and 600 d and for Selenium(II) respectively at, (a) 50 d and (b) 50 and 100 d: U, (a) log C/C₀ (-4 to 0) vs Distance (1 to 10 cm), (b) log C/C₀ (-6 to -0) vs Distance (1 to 10 cm); Se, log C/C₀ (-5 to 0) vs Distance (1 to 10 cm).
23. Log Normal Probability Plot for Plutonium Sorption on Packing Materials, log K_d (ml/g x 10⁻³) (1 to 1000) vs Probability of Value < K_d (%) (.01 to 99.99)

Tables

1. Comparison of Synthetic "Steady State" Groundwater Composition with Solution from Hydrothermal Experiments.
2. Stock Solutions Used in Preparation of the Steady State Synthetic Groundwater.
3. Packing Material Alteration Run Parameters.
4. Solution Analysis of Packing Material Alteration Tests.
5. Oxidation States of Radionuclides Reduced by 0.01 M Hydrazine in Groundwater Solutions.

6. Groundwater Composition (mg/l) versus Time for Reaction with Altered Packing Material at 90°C.
- 7, 8, 9, 10, 11. Uranium, Neptunium, Selenium, Technetium, and Radium Sorption Kinetics Data respectively.
12. First Order Rate Constants for Uranium and Neptunium Sorption on Altered Packing Material at 90°C.
13. Radionuclide Distribution Between Groundwater and Altered Packing Material at 90°C (average of duplicate measurements).
14. Freundlich Constants for Sorption of Radionuclides on Altered Packing Material at 90°C.
15. Radionuclide Desorption Data for U, Np, Se, Tc and Ra from Altered Packing Material into Groundwater at 90°C.
16. Freundlich Constants for Desorption of Radionuclides from Altered Packing Material into Groundwater at 90°C.
17. Ratios of Freundlich N values for Radionuclide Sorption and Desorption at 90°C.
18. Composition of Synthetic Groundwater Used in the Plackett-Burman Experimental Design.
- 19, 20, 21, 22, 23. Data from the Plackett-Burman Experiments for Uranium, Neptunium, Plutonium, Selenium, and Technetium Sorption respectively, on Altered and Fresh Packing Material at 90°C.
24. Significant Groundwater Variables for Radionuclide Sorption on Packing Material at 90°C concluded from the Plackett-Burman Experiments.
25. Effect of Carbonate Concentration on K_d Values (distribution coefficients) of Uranium, Neptunium and Technetium.
26. Representative Formation Constants for 1:1 Actinide Complexes with Groundwater Ligands.
27. Difference in Radionuclide Sorption between Altered and Fresh Packing Materials.

UNCERTAINTIES IN DATA

Statistical analysis was performed on fit of data to Freundlich isotherm equation. Standard errors from scatter in data are reported.

DEFICIENCIES/LIMITATIONS IN DATABASE

None given.

KEY WORDS

Adsorption of radionuclides, air, basalt, basic solution, bentonite, kinetics of adsorption, data analysis, desorption, experimental data, Freundlich isotherm, high temperature, laboratory, ^{237}Np , Plackett-Burman Test, ^{239}Pu , ^{226}Ra , ^{76}Se , simulated groundwater, ^{99}Tc , ^{238}U .

COMMENTS

The radionuclides with the exception of ^{99}Tc are strongly adsorbed on the basalt-bentonite packing material. The basalt provides a reducing environment in which most of the radionuclides will slowly be reduced to lower oxidation states in which form they are strongly adsorbed on the packing material. The adsorption of ^{99}Tc by basalt requires that oxygen potentials lower than those obtained in this work in the absence of hydrazine, be obtained. Only the adsorption of ^{76}Se was significantly different in the hydrothermally altered packing material. The sorption and desorption data presented in this report are empirical distribution coefficients and sorption and desorption isotherms. They are steady-state values obtained over weeks or months of equilibration time, but do not represent thermodynamic equilibrium. Sorption rates were generally much faster than desorption rates.

The addition of hydrazine as a means of obtaining reduced forms of the radionuclides could possibly interfere with some radionuclide reactions. Kelmers et al. have suggested a number of potential problems relative to the use of hydrazine in this type of experiment.

RELATED HLW REPORTS

Kelmers, A. D., Kessler, J. H., Arnold, W. D., Meyer, R. E., Cutshall, N. H., Jacobs, G. K., and Lee, S. Y., "Progress in Evaluation of Radionuclide Geochemical Information Developed by DOE High-Level Nuclear Waste Repository Site Projects, Report for Oct-Dec 1983," NUREG/CF-3581, Vol 1, ORNL/TM-9191/VI, Oak Ridge National Laboratory, Oak Ridge, TN.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting data (X)]

(a) Relationship to Waste Package Performance Issues Already Identified

Related to issue 2.14, how does the packing material control the composition of the groundwater passing through it. It deals with the sorption and desorption of the radionuclides leached from the waste form after a waste container breach. This will have an effect on the rate of escape of waste package radionuclides into the environment in the ISTP for the Basalt Waste Isolation Project (BWIP).

(b) New Licensing Issues

(c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

E. I. duPont de Nemours & Company, Savannah River Laboratory, Aiken, South Carolina 29808.

(b) Author(s), Reference, Reference Availability

Jantzen, C. M., "Methods of Simulating Low Redox Potential (Eh) for a Basalt Repository," 1983 Symposia Proceedings, Vol. 26, Scientific Basis for Nuclear Waste Management VII, McVay, G. L. (editor), North-Holland, 1984, p. 613-621. Available from NTIS.

DATE REVIEWED: 6/16/87.

TYPE OF DATA

Experimental study.
Glass leaching and Eh-pH relationships in simulated basalt repository conditions.

MATERIALS/COMPONENTS

SRL 165 glass, ductile iron.

TEST CONDITIONS

Deionized water and GR-3 basaltic groundwater were used as leachants. Ductile-iron bars and crushed Hanford Umtanum basalt were used as redox-active solids. Deoxygenated experiments were run in a glove box continually purged with argon.

METHODS OF DATA COLLECTION/ANALYSIS

Solution analyses were carried out using inductively coupled plasma (ICP), ion chromatography (IC), and atomic absorption (AA). Solution Eh and pH were monitored continuously in situ. The Eh measurements were made using a Pt electrode. Monolithic samples and filtered precipitates were dried at 90°C for 1 h. Surfaces and precipitates were examined by x-ray diffraction. Glass monolith surfaces were examined by electron microprobe.

AMOUNT OF DATA

Figures

1. Eh-pH changes measured (± 0.5 V) for deoxygenated deionized water and Umtanum basalt and the Eh-pH changes measured for deoxygenated GR-3 simulated basaltic groundwater (Plot of Eh, 1 V to -1 V, vs pH, 0 to 14).
2. Eh-pH relations measured when SRL 165 waste glass and ductile iron are present in deionized water under oxic and anoxic conditions. Boundaries which are dependent on the amount of iron in solution are calculated for the actual iron concentrations found in the solutions (Two plots of Eh, 1 V to -1 V, vs pH, 0 to 14).
3. Concentrations of Si, Fe, B, and Na leached from SRL 165 waste glass under oxic conditions with ductile iron present, under oxic conditions with no ductile iron present and under anoxic conditions with ductile iron present. All samples in deionized water at 70°C (Leach periods 4 to 28 days).

UNCERTAINTIES IN DATA

Solution analyses showed poor reproducibility when colloids were present, even when the solutions were acidified.

DEFICIENCIES/LIMITATIONS IN DATABASE

None given.

KEY WORDS

Experimental data, deionized water, GR-3 water, basalt, leaching, DHLW.

COMMENTS

In this paper, redox-active solids (crushed basalt and ductile iron) are used to control the oxidation potential of solution of waste-glass leachant. Crushed basalt was found to be the most reactive material to maintain a negative (i.e., reducing, anoxic) Eh. Reproducing the basaltic repository redox environment using materials that will actually be present is certainly a better approach than adjusting Eh values by adding hydrazine or other foreign materials to the solution, as has been done in other studies.

The experimental data are used to show that the redox characteristics of the leachant electrolyte have a significant influence on leaching behavior. These redox characteristics, i.e., the ability to act as an oxidizing or reducing agent, are assumed to be represented by a measured potential, Eh. Further, some interpretation of the data is

given to illustrate several specific phenomena that distinguish oxic (high Eh) from anoxic (low Eh) conditions. For example, the corrosion of iron and glass were shown to be synergistic, with each enhancing the corrosion of the other. However, the presence of oxygen to convert neutral iron to the ferrous ion was a key element in this behavior, so that mutually induced corrosion should be less severe in anoxic environments such as those expected in basalt repositories.

Certainly, the relative oxidizing power of the leachant and the specific chemical species present are important in determining leaching behavior. While the present work contributes to establishing Eh as a tool for predicting leaching behavior, the effects of the host rock and metallic components of the environment could probably be described just as well by considering the leaching solution chemistry, without applying the Eh concept. However, Eh measurements are fast and easy to make (subject to the limitations discussed below), and have the advantage of summing up several variables in one numerical value. This introduces a potential pitfall: the same Eh value can be measured for different solutions. For example, when the redox characteristics of a solution are dominated by a single redox couple, e.g. $\text{Fe}^{+2}/\text{Fe}^{+3}$, Eh is determined by the ratio, not the actual concentrations, of the two species. Any combination of concentrations giving the same ratio also gives the same Eh. However, the concentrations determine the extent of possible chemical reactions. As a result, Eh gives an indication of the tendency of various reactions to occur (the driving force), but no indication of how long they will continue (the capacity). These questions have not been addressed in the present paper or in other related papers reviewed to date. For this reason, strict quantitative interpretation of the results with respect to determining extents of reaction from Eh values, which the authors avoid, must be viewed with caution.

The Eh measurement method used is a matter of potential concern. In the present work, Eh was measured using a Pt electrode. There is evidence that this method is not always satisfactory. Grenthe, for example, in KBS Technical Report no. 90, points out that either a low redox buffer capacity or poisons in the electrolyte can make the measured Eh values unrepresentative of the redox potential of the system. In addition, there is often a high degree of scatter in measurements made with a Pt electrode. A gold electrode has been recommended as a better choice. The authors of the present study discuss some of the limitations of the method, and it must be assumed that their measurements were conducted carefully. They reported that stable and reproducible Eh values were measured at Pt electrodes when iron was present in sufficient quantities in the ferrous and ferric states.

The potential drop across the Pt-leachant interface depends on the nature of both the solid and solution phases. The Pt electrode is highly inert in leachant solutions, i.e., it does not dissolve or react with the components normally present except perhaps to form a stable oxide on the surface. The glass-leachant interface, however, is a site of chemical reactions which depend on the chemistries of the glass and the leachant, and their interactions (hydration and dissolution of the glass, alkalization of the solution, etc.) with each other. The Eh of the glass-leachant system, if it could be measured, would change as the system approached steady state. In the slow-flow conditions expected in repositories, a steady-state situation will be reached in which both phases are modified in the glass-leachant interfacial region where Eh is determined. The steady state redox characteristics at the interface will determine long-term leaching behavior. The Pt probe senses changes in the redox characteristics of the solution in contact with the waste glass as this approach to steady state occurs, as shown in Figure 2 of the paper by the convergence of the data to the equilibrium calculated time. Distinctly different behavior is seen under oxic and anoxic conditions in this work. This result is important in two respects. It indicates that the anoxic conditions expected in the basalt repository should be less aggressive toward the glass waste, and that laboratory measurements of leaching should be carried out under anoxic conditions to be representative of repository behavior.

RELATED HLW REPORTS

1. Jantzen, C. M., "Effects of Eh (Oxidation Potential) on Borosilicate Waste Glass Durability," Second International Symposium on Ceramics in Nuclear Waste Management, 1984.
2. Jantzen, C. M. and Wicks, G. G., "Control of Oxidation Potential for Basalt Repository Simulation Tests," Mat. Res. Soc. Proc. Vol. 44, page 29, 1985.
3. Mendel, J. E., Sci. Basis for Nuclear Waste Management VI, D. C. Brookins, ed., Elsevier Publ. Co., New York 1-7, 1983.
4. Jacobs, G. K. and Apted, M. J., EOS Trans. Amer. Geophys. Union 62, 1065, 1981.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting data (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to issues 2.3, how will the radionuclides be released from the waste form, 2.3.3, what colloids will be formed, 2.3.5, how does the waste container material (and packing material) alter the radionuclide release rate in the ISTP for the Basalt Waste Isolation Project (BWIP).

- (b) New Licensing Issues

- (c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Swanson Engineering Associates Corporation, McMurray, PA.

(b) Author(s), References, Reference Availability

Mallett, R. H., "Buckling Design Criteria for Waste Package Disposal Containers in Salt Repositories", BMI/ONWI-597, December 1986. Available from NTIS.

DATE REVIEWED: 6/16/87.

TYPE OF DATA

1. Scope: This document is a survey of the literature on buckling analysis and experiments; no new theoretical development or buckling experiments were conducted. The purpose of this work was to provide guidance in establishing a waste-container design criteria to ensure protection against buckling of the container
2. Failure Mode: Elastic, elastic-plastic and plastic buckling

MATERIALS/COMPONENTS

Waste disposal container of low-carbon steel

No experiments were performed; however, the survey focuses on low-carbon steels and their properties.

TEST CONDITIONS

This document is a survey of the literature on buckling analysis and experiments; no new tests or experiments were performed for this document.

METHODS OF DATA COLLECTION/ANALYSIS

This document is a survey of the literature on buckling analysis and experiments. The results of buckling experiments are compared to the predictions of different analytical models. No new experiments or analyses are presented.

AMOUNT OF DATA

12 Tables

- 3-1. Summary of Waste Package Design Features (Container and Canister length, diameter and thickness also borehole information)
- 3-2. Summary of Waste Package Performance Parameters (temperatures, heat loads, corrosion penetrations and corrosion allowances)
- 3-3. Comparison of Low Carbon Steel Specifications (Chemistry and physical properties of container material, AISI 1018 and ASTM 216 steels)
- 3-4. ASME Boiler and Pressure Vessel Code Design Stress Intensity Values (Nominal composition of steel, yield strength, ultimate tensile strength and critical stress intensity for metal at different temperatures)
- 4-1. Reference Disposal Container Length Parameters
- 4-2. Reference Disposal Container Thickness Parameters
- 4-3. Reference Disposal Container Thick-Wall Stress
- 4-4. Reference Disposal Container Ovality Effect
- 4-5. Reference Disposal Container Buckling
- 4-6. Minimum (R/t) for Elastic Buckling and Maximum (Et/E) for Elastic-Plastic Buckling
- 4-7. Recent Cylinder Buckling Results
- 4-8. Small Cylinder Buckling Results

22 Figures

- 3-1. Conceptual Waste Disposal Container Design (diagram)
- 3-2. ASME Code Buckling Chart for Factor A (Length to Outside Diameter ratio) (Factor A)
- 3-3. ASME Code Buckling Chart for Factor B (10-5 to 100 Factor A)
(2,500 to 25,000 Factor B)
- 3-4. Creep Behavior for Salt (Time, $0-1.6 \times 10^{-7}$ seconds)
(axial strain, 0-10%)

- 3-5. Defense High-Level Waste Package Performance (0-150°C temperature, 15-20 MPa pressure and 0-1.0 cm. corrosion penetration) (0.1-1000 years after emplacement)
- 3-6. Commercial High-Level Waste Package Performance (0-150°C temperature, 15-20 MPa pressure and 0-1.0 cm. corrosion penetration) (0.1-1000 years after emplacement)
- 3-7. Consolidated Spent Fuel (12 Pressurized-Water Reactor Assemblies) Waste Package Performance (0-150°C temperature, 15-20 MPa pressure and 0-1.0 cm. corrosion penetration) (0.1-1000 years after emplacement)
- 4-1. Typical Stress Versus Strain Curve (0-0.10 in/in strain) (0-50 ksi stress)
- 4-2. Typical Tangent Modulus Curve (15-50 ksi stress) (0.5 x 10⁻⁶ MPa Tangent Modulus)
- 4-3. Compilation of Cylinder Buckling Results (1-1000 in/in Radius to thickness ratio) (0-1.4 collapse pressure to theoretical collapse pressure ratio)
- 4-4. Steel Capsules After Pressure Testing
- 4-5. Correlation of Buckling Analysis and Test (0-15 radius to thickness ratio) (0-20 ksi collapse pressure)
- 4-6. Collapse Mechanism Diagrams (a) (0-0.1 logarithmic strain) - (0-600 MPa true stress), (b) (-0.06-0 circumferential strain)-(0-0.5 pressure/yield strength ratio), (c) (-1.0-1.0 load parameter) - (0-0.8 pressure to yield strength ratio) and (d) (-1.0-1.0 load parameter) - (0-0.6 pressure to yield strength ratio)
- 4-7. Bifurcation Pressure Versus Thickness to Mean Radius Ratio (0-0.5 wall thickness to radius ratio) (0-2.0 bifurcation pressure to yield strength ratio)
- 4-8. Curves of Pressure Versus Displacement on the External Surface (0-0.02 displacement/radius ratio) (0-1.0 pressure to critical pressure ratio)
- 4-9. Atomic Energy of Canada Limited Prototype Waste Package Container Collapse Shape (diagram)
- 4-10. Atomic Energy of Canada Limited Prototype Waste Package Container Collapse Shape (photograph)

- 4-11. Atomic Energy of Canada Limited Prototype Waste Package Container Behavior (+400 to -2000 5m/m strain) (0-18.96 MPa pressure)
- 4-12. Stress Versus Strain Curve for Atomic Energy of Canada Limited Test Specimen (0-20000 5m/m strain) (0-413.7 MPa stress)
- 4-13. Tangent Modulus Curve for Atomic Energy of Canada Limited Test Specimen (50-250 MPa) (0-0.150 x 10⁶ MPa tangent modulus)
- 5-1. BS5500 Buckling Design Curves (0-12 K) (0-0.7 k)
- 7-1. Selected ASME Code Provisions for Plastic Analysis (strain or displacement, no units) (load, no units)

UNCERTAINTIES IN DATA

The buckling analyses neglect the effects of transient pressure, seismic loading, shear loading and corrosion other than uniform. Also, interactions such as creep, radiation-induced creep, aging of the metal (thermal and radiation induced), radiation-induced corrosion and stress corrosion are neglected. The properties of the material are assumed uniform, and inhomogeneities such as welds, weld heat affected zones, casting defects (inclusion and voids) are neglected.

DEFICIENCIES/LIMITATIONS IN DATABASE

The waste disposal container can be treated in a buckling analysis as a long cylinder. Neglect of the support provided by the end closure is conservative and will not significantly alter the results of the analysis. The waste disposal container must be analyzed as a thick wall cylinder. The use of average stresses in the basic buckling equations is an approximation which must be verified by testing. The collapse pressure of a thick walled cylinder is strongly dependent on the work-hardening characteristics of the material. Imperfections in the container will increase the ovality of the container reducing the collapse pressure. However, for practical imperfections the reduction in the collapse pressure should not be significant. The cylinder collapse test results reviewed indicate that buckling of a thick wall cylinder does not result in loss of wall continuity. That is, buckling of a waste disposal container onto the waste form may not result in leaking. However, the tensile stresses resulting from buckling may lead to failure by other mechanisms. As a result, after the retrieval period, buckling of the container does not by itself constitute failure. The basic equations for buckling

overestimate the critical buckling pressure for thin wall cylinders and overestimate the critical pressure for thick wall cylinders. As a result, these equations are conservative estimates of the critical pressure. The experimental results reviewed in this report indicated that finite-element analyses frequently result in predictions for the critical collapse pressure, which are no better than the predictions of the simple relationships. However, a finite element analysis can predict the critical pressure within 3 percent. The simple buckling equations underestimate the critical collapse pressure and the use of a load factor (defined as the ratio of the critical collapse pressure to the maximum expected service pressure) of 1.5 or 3, as is used in external pressure buckling design standards, should be a conservative design criteria. However, it is assumed that the geometry, material and applied loading are specified with conservatism appropriate to their uncertainty.

KEY WORDS

Literature review, design, salt, steel, collapse load tests, waste form (CHLW, DHLW and spent fuel) modulus of elasticity, tangent modulus, yield strength, tensile strength, stress, strain, ovality, buckling, elastic buckling, plastic buckling, elastic-plastic buckling.

COMMENTS

This is not a critical review.

RELATED HLW REPORTS

Bathe, K. J., ASME Boiler and Pressure Vessel Code, Nuclear Power Plant Components, American Society of Mechanical Engineers, 1983 (ASME), New York, 1976.

Crosthwaite, J. L., Barrie, J. N. and Nuttall, K., "ADINA A Finite Element Program for Automatic Dynamic Incremental Nonlinear Analysis," Report 82448-1, Acoustics and Vibration Laboratory, Mechanical Engineering Department, Massachusetts Institute of Technology, Cambridge MA, 1982.

DeSalvo, G. J., and Becker, H., "Design, Fabrication and Testing of a Prototype Stressed-Shell Fuel Isolation Container," AECL-6823, Atomic Energy of Canada Limited, Pinawa, Manitoba, Canada, 1957.

Hibbitt, K., Handbook of Structural Stability, Part III, "Buckling of Curved Plates and Shells," NACA-TN-3783, National Advisory Committee for Aeronautics, Washington DC, 1981.

Huang, N. C. and Pattillo, P. D., "ABAQUS Computer Program Manuals," Volumes 1-4, Sorenson, Inc., Providence, RI, 1982.

"Collapse of Oil Well Casing", J. Pressure Vessel Technology, 104m, 36-41, 1974.

"BOSOR5, A Computer Program for Buckling of Elastic-Plastic Complex Shells of Revolution Including Large Deflection and Creep," LMSC-D407166, Lockheed Missiles and Space Company, Inc., Sunnyvale, CA, 1971.

Timoshenko, S. P. and Gere, J. M., "MARC-CDC Nonlinear Finite Element Analysis Program, MARC Analysis Corporation and Control Data Corporation," Minneapolis, MN, Theory of Elastic Stability, Second Edition, McGraw Hill, NY, 1961.

APPLICABILITY OF DATA TO LICENSING

[Ranking: Key Data (), Supporting Data (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to issue, 2.2.3, what are the possible mechanical failure modes for the waste package container in the ISTP for the Salt Repository Project (SRP).

- (b) New Licensing Issues

- (c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Brookhaven National Laboratory, Upton, New York 11973.

(b) Author(s), Reference, Reference Availability

Levy, P. W., "Radiation Damage Studies on Natural Rock Salt from Various Geological Localities of Interest to the Radioactive Waste Disposal Program," Nuclear Technology, 60, 231-243, 1983.

DATE REVIEWED: 4/27/87.

TYPE OF DATA

Radiation damage of rock salt by 1.5 MeV electron beam which is identical to damage produced by gamma radiation. Emphasis is on sodium colloid formation in the rock salt.

MATERIALS/COMPONENTS

Fourteen natural rock salt samples were irradiated by a 1.5 MeV electron beam.

TEST CONDITIONS

Samples are irradiated at constant temperature and extent of radiation damage is determined by optical measurements.

METHODS OF DATA COLLECTION/ANALYSIS

Extent of radiation damage is determined by optical absorption methods. Measurements are made as a function of temperature, dose, and strain in the crystals.

AMOUNT OF DATA

Figures

1. Appearance of rock salt as function of distance from spent fuel element in the Radioactive Waste Disposal Demonstration Project, Lyons, Kansas.
2. Schematic of test radiation equipment.
3. Typical optical absorption and luminescence data.

4. Colloid concentration versus irradiation time curves as a function of temperature. Absorption Coefficient (0 to 50 cm^{-1}) vs Irradiation Temperature (100 to 300°C) vs Irradiation Time (0 to 10000 s).
5. Colloid formation in 14 natural rock salt samples irradiated at 150°C at a dose rate of 1.2×10^8 rd/h. Colloid Band Area (.1 to 50 arbitrary) vs Time (1 to 10^4 s).
6. Colloid growth curves for natural rock salt from WIPP site recorded using strained crystals. Absorption at 2.14 eV, (0 to 50 cm^{-1} vs irradiation time (0 to 9×10^3 s) for 11%, 3.9% and undeformed crystals at 150°C, 120 Mrd/h)
7. Colloid formation in natural rock salt at an irradiation temperature of 150°C and dose rates of 30, 60 and 120 Mrd/h Absorption Coefficient (0 to 40 cm^{-1}) vs dose, (0 to 200 Mrd).
8. A black and white version of a colored photomicrograph of irradiated rock salt showing regions of F centers and colloidal sodium metal.

Tables

1. Constants for 14 specimens for the equation, mole fraction NaCl converted to colloidal sodium = Ct^n where C and n are constants and t is the time in seconds.
2. Impurities in colloid-rich and colloid-free areas in irradiated natural rock salt.
3. Percent sodium metal colloid expected in rock salt at canister interfaces for 10^{10} and 2×10^{10} rd, (about 50 to 400 y dose rate at 2×10^4 rd/h).

UNCERTAINTIES IN DATA

None given.

DEFICIENCIES/LIMITATIONS IN DATABASE

The author states that because of the differences in dose rates, irradiation times, and rapidly applied stresses in laboratory experiments in contrast to anticipated dose rates, irradiation times and stresses under repository conditions, an accurate estimate of the total amount of radiation induced colloid and its spatial distribution requires appreciably more data than is presently available. To extrapolate from laboratory to repository conditions requires a better understanding of the radiation-damage formation kinetics in rock salt.

KEY WORDS

Brine, chlorine, colloidal sodium in SRP, experimental data, gamma radiation field, high temperature, laboratory, radiation damage, radiation damage of rock salt.

COMMENTS

This report presents experimental work on radiation-induced sodium-metal colloid formation in rock salt. The technique involves bombardment of rock salt with a high energy (1.5 MeV) electron beam, which is equivalent to the effect produced by gamma-ray recoil electrons. This work is of importance to salt repositories because of the drastic change in pH that could take place in the repository environment if chlorine is lost from the rock salt and, at some later time, large amounts of sodium colloid react with brine. The experimental data show that the induction period for colloid formation is shortened with strained samples, increases on a unit dose basis as the dose rate decreases, and appears to be affected by the salt impurity level, being suppressed in regions of crystals containing about 1 percent calcium and sulfur. The colloid formation rate is low or negligible below irradiation temperatures of 100 to 115°C, increases to a broad maximum at 150 to 175°C then decreases to a negligible level at 275 to 300°C. Using the $C(\text{dose})^n$ relationship to estimate the colloid formed in actual repositories indicates that in 50 to 400 years, a dose of 10^{10} rd will convert 0.1 and 10 percent, and 2×10^{10} rd will convert between 1 and 50 percent of the salt to colloidal sodium. In the laboratory, cleaved or broken irradiated samples emit the odor of chlorine. Obviously, the fate of chlorine in the irradiated rock salt is very important. The authors plan to attempt to detect the escape of chlorine from irradiated samples using a mass spectrometer detector. Whether chlorine escapes from the rock salt or can limit the sodium colloid buildup by some type of recombination reaction is an important problem for the salt repository.

RELATED HLW REPORTS

Levy, P. W. and Kierstad, J. A., "Very Rough Preliminary Estimate of the Colloidal Sodium Induced in Rock Salt by Radioactive Waste Canister Radiation," in Mat. Res. Soc. Symp. Proc., Vol. 26, Elsevier Science Publ. Co., p. 727-734, 1984.

APPLICABILITY OF DATA TO LICENSING:

[Ranking: key data (), supporting data (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified
- (b) New Licensing Issues
- (c) General Comments on Licensing

None of the ISTP issues previously identified appear to specifically relate to the interaction of brine with colloidal sodium in rock salt. Such an interaction could lead to a large change in pH which would drastically change the local waste canister environment.

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Office of Nuclear Waste Isolation, Battelle Memorial Institute, 505 King Ave., Columbus, OH 43201-2693.

(b) Author(s), References, Reference Availability

Clark, D. E., "ERG Review of the SRP Salt Irradiation Effects Program", BMI/ONWI-626, November, 1986. Available from NTIS.

DATE REVIEWED: 6/19/87.

TYPE OF DATA

1. Scope: This document is a report of the August 1985 meeting of the engineering review group (ERG) where the salt repository project (SRP) salt irradiation effects program was reviewed; no new tests or experiments were performed for this document and no data are presented in this document. This review is the seventh in the series of regular ERG reviews conducted for ONWI. For this review, the ERG reviewed the work on irradiation effects at Pacific Northwest Laboratory and Brookhaven National Laboratory which was supported by the SRP and completed at the time of the review (see RELATED HLW REPORTS).
2. Failure Mode: For a salt repository, the concern is that radiation induced changes in the chemical and physical properties of the near-field environment will impact waste package performance with respect to any of the potential failure modes.

MATERIALS/COMPONENTS

The experiments reviewed by the ERG were conducted on single crystals of pure NaCl for the purpose of modeling the behavior of the bedded salt environment.

TEST CONDITIONS

This document is a report of the 1985 ERG meeting at which the SRP salt irradiation effects program was reviewed; no new tests or experiments were performed for this document. Specific test conditions vary for each experiment and are not covered in this document (see RELATED HLW REPORTS).

METHODS OF DATA COLLECTION/ANALYSIS

This document is a report of the 1985 ERG meeting at which the SRP salt irradiation effects program was reviewed; the methods of data collection and analysis are not covered in this document (see RELATED HLW REPORTS).

AMOUNT OF DATA

No new tests or experiments were performed for this document and no data is presented (see RELATED HLW REPORTS).

UNCERTAINTIES IN DATA

The ERG identified uncertainties in the salt irradiation effects database and made recommendations on actions which should remove these uncertainties. ONWI's response to each of these items is given in the DEFICIENCIES/LIMITATIONS IN DATABASE section of this review.

DEFICIENCIES/LIMITATIONS IN DATABASE

The uncertainties in the database identified by the ERG are as follows:

1. Experiments on pure single crystals are not relevant to the bedded salt environment and the extent of the damage to the salt structure itself is of little interest.
2. Repository conditions and designs need to be finalized so that testing in representative conditions can begin.
3. Long-term and low-dose-rate tests need to begin now so that the low-dose-rate hypothesis of Levy et al., 1984, can be tested.
4. Investigations need to be integrated.
5. The significance of hydrogen production by irradiation of the brine, oxidation of radiation induced colloidal sodium, and oxidation of the steel overpack should be evaluated.
6. Radiolysis will promote oxidizing conditions and corrosion of the steel overpack will promote reducing conditions. The relative significance of these two need to be evaluated.
7. The effects of various reactions on the pH of the environment need to be assessed using the results of ongoing projects.

8. Factors contributing to waste package degradation appear minor based on current design assumptions and knowledge. However, these factors need to be quantified to the extent possible and unanticipated factors identified.
9. To determine the chemical environment at the waste package as a function of time, the SRP needs to (1) place bounds on the colloidal sodium and chlorine production rates, (2) determine the mobility of Cl_2 and H_2 , (3) identify sources of volatile gases in natural salt, (4) compute H_2 fugacities, and (5) integrate radiation, corrosion and brine migration models.
10. Calculations of the chlorine release at low dose rates need to be performed to indicate whether or not the pH will change significantly and alter the corrosion behavior.
11. Chlorine release rate calculations need to be integrated with brine migration studies.
12. Calculations should be made based on available data to determine the potential impact of colloid formation on brine chemistry.
13. Modeling of coupled subsystems will assess the importance of individual processes.
14. Calculations need to be carried out to indicate whether or not the dose-rate dependence of Levy et al. is of major engineering significance.
15. The effect of higher pH around the waste package needs to be assessed.
16. The effect of chlorine release on corrosion needs to be assessed.
17. A detailed calculation of the effects of stored energy are needed.
18. The amount of colloidal sodium present does not appear significant.
19. To properly assess the effects of irradiation, brine chemistry and corrosion, a suite of realistic scenarios must be invoked and evaluated.
20. Experiments on the mechanical properties of irradiated salt are needed.

21. Compare Levy's F-center formation rate data to those measured by others and available in the literature.
22. Conduct experiments which compare colloid concentration data to TEM examinations.
23. The effect of corrosion and hydrogen embrittlement on the waste package cannot be ascertained at this time and an ERG meeting should be called with experts on steel corrosion and embrittlement present.

DEFICIENCIES/LIMITATIONS IN DATABASE

ONWI responded to each point raised by the ERG and identified the action being taken to eliminate the deficiencies in the salt irradiation effects database which are responsible for these uncertainties. ONWI's response to each point can be summarized as follows:

1. The testing has been limited to single crystals because of experimental constraints. However, experiments on aggregates have begun which measure the chlorine release. These experiments will be correlated with the measurements of colloidal sodium. In the future, small-angle neutron scattering may be employed to determine colloidal sodium.
2. ONWI agrees with the need to finalize site selection and repository design.
3. While there is potential value in carrying out long-term testing, there is not a pressing need to start them in the near future.
4. ONWI agrees and integration will be taken into account in future plans.
5. ONWI agrees and these factors will be considered in future package analyses.
6. Future testing should resolve this matter.
7. ONWI agrees. The work of Pederson addresses this subject in part (see RELATED HLW REPORTS section).
8. The SRP waste package testing program is directed towards providing a quantification of these and other factors.
9. Current testing and future modeling efforts will address these issues.
10. ONWI agrees. Currently, data are not available; however, results should be available in FY 86.

11. ONWI agrees that, to the extent possible, these calculations should be integrated.
12. ONWI does not anticipate any significant problems of this nature.
13. ONWI agrees and has structured its program accordingly.
14. These calculations have been performed and demonstrate that without a detailed knowledge of the temperature and transport, reliable estimate cannot be obtained.
15. While changing the pH may alter the reaction rate, the total extent of corrosion is limited by stoichiometry and the quantity of brine reaching the container.
16. This will be included in more detailed analyses of the expected waste package environment.
17. The effects of stored energy do not appear significant.
18. ONWI agrees that this is not a significant amount and ONWI feels that this is still a conservatively high estimate. More precise calculations will be carried out in the detailed performance assessment.
19. ONWI agrees.
20. Some experiments on the mechanical properties of salt are planned.
21. So far as known to ONWI, there are no other F-center formation rate measurements to compare to Levy's.
22. TEM provides only qualitative information and cannot be used to obtain concentrations.
23. ONWI agrees with this importance of this meeting and has scheduled a meeting for the fourth quarter of FY 86.

KEY WORDS

Review, gamma radiation, chlorine, hydrogen, radiolysis, colloid, salt, corrosion (uniform or general), hydrogen embrittlement, radiation effects.

COMMENTS

The report reviewed here (BMI/ONWI-626) is a report covering a meeting of the engineering review group (ERG) at which the SRP salt irradiation effects program was reviewed. This report does not present detailed descriptions of the experimental procedures nor is any data formally presented. As a result, these factors cannot be critically reviewed here. In their review of the SRP salt irradiation effects program, the ERG reach two very important conclusions about the overall program. First, they point out that radiation induced changes in the structure and properties of the crystalline salt are not likely to significantly influence container performance for the expected repository conditions. The ERG point out that experiments can be conducted to test this conclusion. Second, the ERG concluded that while the experiments were well designed, the program was structured to address fundamental scientific questions and ignored the applied questions of interest to the program. That is, the program is designed to address fundamental questions about radiation damage in ionic solids while issues concerning container integrity and potential failure modes are ignored.

RELATED HLW REPORTS

Bergsma, J., Helmholdt, R. B., and Heijboer, P. J., "Radiation Dose Deposition and Colloid Formation in a Rock Salt Waste Repository," Nuclear Technology, Vol. 71, 597-607, 1985.

Hobbs, L. W., "Transmission Electron Microscopy of Defects in Alkali Halide Crystals," Journal de Physique (Paris), Colloque C9-227, 1975.

Jockwer, N., "Transmission Electron Microscopy of Extended Defects in Alkali Halide Crystals," Surface and Defect Properties of Solids," The Chemical Society, London, UK., 4, 152, 1984.

Levy, P. W., "Laboratory Investigations on Radiolysis Effects on Rock Salt With Regard to the Disposal of High-Level Radioactive Wastes," Proceedings of a Materials Research Society Symposium, Vol. 26, Scientific Basis for Nuclear Waste Management VII, McVay, G. L. (editor) Elsevier Science Publishing Company, New York, NY, p. 17-23, 1983.

Levy, P. W. and Kierstead, J. A., "Radiation Damage Studies on Natural Rock Salt from Various Geological Localities of Interest to the Radioactive Waste Disposal Program," Nuclear Technology, 60, 231-243, 1984.

Levy, P. W. and Kierstead, J. A., "Very Rough Preliminary Estimate of the Colloidal Sodium Induced in Rock Salt by Radioactive Waste Canister Radiation," Proceedings of a Materials Research Society Symposium, Vol. 26, Scientific Basis for Nuclear Waste Management VII, McVay, G. L. (editor) Elsevier Science Publishing Company, New York, NY, p. 727-734, 1984.

Levy, P. W., Loman, J. M., and Kierstead, J. A., "Radiation Induced F-Center and Colloid Formation in Synthetic NaCl and Natural Rock Salt: Applications to Radioactive Waste Repositories," Nuclear Instruments and Methods in Physics Research B1, 549-556, 1984.

Levy, P. W., Loman, J. M., Swyler, K. J., and Klaffky, R. W., "Radiation Damage Studies on Synthetic NaCl Crystals and Natural Rock Salt for Radioactive Waste Disposal Applications," P. L. Hofman (editor), The Technology of High-Level Nuclear Waste Disposal, DOE/TIC-4621, Vol. 1, Technical Information Center, U.S. Department of Energy, Oak Ridge, TN.

Panno, S. V., and Soo, P., "Potential Effects of Gamma Irradiation on the Chemistry and Alkalinity of Brine in High-Level Nuclear Waste Repositories in Rock Salt," Nuclear Technology, 67, p. 268-281, 1984.

Pederson, L. R., "Chemical Implications of Heat and Radiation Damage to Rock Salt," Proceedings of a Materials Research Society Symposium, Vol. 44, Materials Research Society, Scientific Basis for Nuclear Waste Management VII, Jantzen, C. M., Stone, J. A., and Ewing, R. C. (editors), Pittsburgh, PA, p. 701-708, 1985.

U.S. Department of Energy, "Mission Plan for the Civilian Radioactive Waste Management Program," Vols. I and II, Office of Civilian Radioactive Waste Management, Washington, DC, DOE/RW-0005, 1985.

U.S. Department of Energy, "Salt Repository Project Technical Progress Report for the Quarter 1 January-31 March," Office of Civilian Radioactive Waste Management, Washington, DC, DOE/CH/10140-03(85-2), 1983.

Westinghouse Electric Corporation, "Engineered Waste Package Conceptual Design: Defense High-Level Waste (Form 1), Commercial High-Level Waste (Form 1), and Spent Fuel (Form 2) Disposal in Salt," prepared for Office of Nuclear Waste Isolation, Battelle Memorial Institute, Columbus, OH, ONWI-438, 1983.

Westinghouse Electric Corporation, "Waste Package Reference Conceptual Designs for a Repository in Salt," prepared for Office of Nuclear Waste Isolation, Battelle Memorial Institute, Columbus, OH, BMI/ONWI-517, 1986.

APPLICABILITY TO LICENSING

[Ranking: Key Data (), Supporting Data (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to issue 2.1.3.1, involving how the chemical characteristics of the brine reaching the waste package container will be affected by radiolysis in the ISTP for the Salt Repository Project (SRP).

- (b) New Licensing Issues
- (c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Pacific Northwest Laboratory, Richland, Washington
99352.

(b) Author(s), Reference, Reference Availability

Westerman, R. E., Haberman, J. H., Pitman, S. G., and
Perrin, J. S., "Corrosion of Iron-Base Waste Package
Container Materials in Salt Environments," PNL-SA-14029,
March 1986. Available from NTIS.

DATE REVIEWED: 6/22/87; Revised 7/31/87.

TYPE OF DATA

Experimental, general corrosion

MATERIALS/COMPONENTS

Cast ASTM A-216 mild steel grade WCA (candidate waste
package material)

TEST CONDITIONS

Steel tested as-cast, homogenized (long-term austenization
-- 930°C/24 h/AC)) and normalized (short-term austenization
-- 930°C/1 h/AC).

Casting size: 160 kg with minimum dimension of 120 mm
(Ref. 1).

Specimen size: 15mm x 15mm x 1.5mm (as machined).

Aqueous environments: Bulk of data from tests reported
conducted in brine/water (moist salt). Two synthetic Permian
Basin brines used the following solutions: (1) dissolution
of salt horizon cores & (2) high Mg⁺⁺ "inclusion brine".
Moist salt prepared from dried synthetic salt horizon brine
with 20 weight percent synthetic inclusion brine added to
provide solid salt/brine mixture. Single test reported for
unrefreshed autoclave exposure in synthetic salt horizon
brine. Specimens exposed in sealed cans at 150°C. Maximum
test period was 12 months.

DATA COLLECTION/ANALYSIS

Corrosion rates based on weight-loss measurement after descaling with formaldehyde-inhibited HCl. Analysis of corrosion products by X-ray diffraction and chemical analysis.

AMOUNT OF DATA

Data presented are summarized from the tables and figures, as follows:

Two tables

1. Composition of a single casting Steel Tested (element, weight percent)

C	0.25	Mn	0.71	Si	0.45	Cr	0.41
Ni	0.23	Cu	0.14	S	0.018	Fe	balance

2. Compositions of Synthetic Brines (ion, concentration mg/l))

<u>ion</u>	<u>synthetic salt horizon</u>	<u>synthetic inclusion brine</u>
Na ⁺	123,000	23,000
Ca ²⁺	1,600	15,000
Mg ²⁺	130	53,000
K ⁺	40	10,000
Cl ⁻	191,000	210,000
SO ₄	3,200	160
HCO ₃	30	-
Br ⁻	32	2,400

Four figures

- (1) total penetration of as-cast steel in moist salt tests:
0 to 12 months, 0 to 0.5 mm penetration.
- (2) corrosion rates of as-cast steel in moist salt tests:
0 to 12 months, 0 to 1.0 mm/y.
- (3) composition of corrosion products from 12 month moist-salt test: Cl, Fe, H₂O, Na, Mg; 0 to 40 weight percent on dry-weight basis.
- (4) microstructures of as-cast and normalized steel.

UNCERTAINTIES IN DATA

Author describes test conditions as "severe and conservative" with unlimited quantities of reactants.

DEFICIENCIES/LIMITATIONS IN DATABASE

None given.

KEY WORDS

Experimental data, supporting data, corrosion, X-ray diffraction, weight change, simulated field, brine, brine (high ionic content), brine (low ionic content), Cl, Mg, high temperature, static (no flow), cast mild steel, A216 Grade WCA, cast, austenitized, homogenized, normalized, corrosion (general), corrosion (pitting).

COMMENTS

Paper quantifies several important factors affecting corrosion of cast steel in brine environments including the following:

(1) significantly higher corrosion rates observed in brines containing 53,000 mg/l Mg as compared with low-Mg (130 mg/l) brines.

(2) austenizing heat treatment (normalization or homogenization) can reduce corrosion resistance of cast steel, a factor which must be considered when assessing microstructural changes due to weld closures or specified casting heat treatments to optimize mechanical properties.

(3) presence of solid brine phase is not necessary for high corrosion rates to occur

(4) corrosion rates decrease rapidly over the initial 12 months of exposure reflecting corrosion product buildup.

(5) pitting rates in moist salt are similar to average penetration rates based on weight losses.

The authors assume no effect of irradiation on corrosion rate, citing a previous report (see RELATED HLW REPORTS). The authors do not address the potential effects of H₂ pressure buildup in sealed containers in reducing cathodic reactions. Changing corrosion rate (with exposure time and environmental fluctuation) is a key factor needing further study to assure valid extrapolations to longer-term exposures and anticipated environmental variations. More detailed studies of corrosion products (formation, structure and retention) would be particularly useful. The experiments described in this report assume that the canisters will be subject to a constant environment. The potential effects of alternate wetting and drying or waterline exposure should be considered.

RELATED HLW REPORTS

- (1) Westerman, R.E., Haberman, J.H., Pitman, S.G., and Pulsipher, B.A., "Corrosion and Environmental-Mechanical Characterization of Iron-Base Nuclear Waste Package Structural Barrier Materials Annual Report FY 1984," PNL-5426, March 1986.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting data (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to issue 2.2.4.1, the rates of corrosion as a function of time for the various corrosion modes of the waste package container, and 2.4, at what rates will radionuclides migrate through failed waste package in the ISTP for the Salt Repository Project (SRP).

- (b) New Licensing Issues
(c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Brookhaven National Laboratory, Upton, New York 11973.

(b) Author(s), Reference, Reference Availability

Levy, P. W. and Kierstad, J. A., "Very Rough Preliminary Estimate of the Colloidal Sodium Induced in Rock Salt by Radioactive Waste Canister Radiation", Proceedings of a Materials Research Society Symposium, Vol. 26, Scientific Basis for Nuclear Waste Management VII, McVay, G. L. (editor) Elsevier Science Publishing Co., New York, 1984, p. 727-734.

DATE REVIEWED: 12/31/86; Revised 5/22/87.

TYPE OF DATA

Model calculation of interaction of gamma radiation with rock salt leading to formation of colloidal sodium.

MATERIALS/COMPONENTS

Rock salt, gamma radiation

TEST CONDITIONS

Not applicable

METHODS OF DATA COLLECTION/ANALYSIS

None given.

AMOUNT OF DATA

Figure 1. Typical Canister configuration, cocoon approximation and dimensions used for computations.

Figure 2. Radiation Induced Colloid Growth Curves used for computations, absorption coefficient (cm^{-1}) vs total dose, (Mrd).

Figure 3. Salt converted to Na colloid (percent) vs time (y) after emplacement for each layer of surrounding canister.

Figure 4. Total colloid mass (kg) in each layer vs time (y) after emplacement.

Figure 5. Percent salt converted to colloid vs distance (cm) into salt for 50, 100, 150 and 300 years after placement.

Figure 6. Total colloid mass (kg) in the first 25 cm surrounding the canister vs time after emplacement.

Table 1. Properties of the four waste canisters used to estimate the radiation induced Na (sodium) colloid expected in rock salt adjacent to emplaced canisters (includes dimensions of canisters, air gap, thickness of carbon steel and other overpacks, active length, overpack length, distance from waste centerline to salt, initial heat load, and initial radioactivity).

Table 2. Total mass in kg of radiation induced Na metal produced in natural rock salt from the WIPP site by gamma-ray radiation from the four canisters described in table 1 at various times after emplacement.

UNCERTAINTIES IN DATA

The authors state that, the estimates are based on minimal data and require a large number of assumptions and extrapolations.

DEFICIENCIES/LIMITATIONS IN DATABASE

The authors state that "These estimates are based on minimal data and require a large number of assumptions and extrapolations. For better radiation damage estimates, particularly of the Na metal colloid formed in repository rock salt, improved data are essential."

KEY WORDS

Brine, colloidal sodium in SRP, gamma radiation field, laboratory, model for radiation damage of rock salt, radiation damage of rock salt, salt, theory, steel.

COMMENTS

This report discusses model calculations involving the formation of a sodium colloid formed in the vicinity of waste canisters in a SRP Nuclear Waste Repository.

Although the authors consider the calculations as crude, the basic contention is that the formation of massive colloids of sodium in the vicinity of the canisters will eventually react with brine to form sodium hydroxide which will drastically change the pH of the local environment. The most important question involves the fate of chlorine formed as a result of radiation of the rock salt. The reviewer does not consider it likely that large amounts of a reactive gas like chlorine will

escape from the local environment. More likely, reaction with brine will occur with the formation of HOCl or similar chloric acids which should react with and neutralize the sodium. But more definitive data on the fate of chlorine needs to be obtained.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting data (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to issue 2.1.3.1, involving how the chemical characteristics of the brine reaching the waste package container will be affected by radiolysis in the ISTP for the Salt Repository Project (SRP).

- (b) New Licensing Issues
- (c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

Vitreous State Laboratory, The Catholic University of America, Washington, D. C.

(b) Author(s), Reference, Reference Availability

Feng, X., Adiga, R., Barkatt, A., Barkatt, A.O., Freeborn, W., Macedo, P., Mohr, R., Montrose, C., Mowad, R., Saad, E., and Sousanpour, W., "Effects of Composition On the Leach Behavior of West Valley HLW Glasses," September 1986.

DATE REVIEWED: 4/21/87.

TYPE OF DATA

Experimental data on glass leaching.
Measured viscosities at 1100°C.

MATERIALS/COMPONENTS

West Valley Demonstration Project reference glass WV-205 and 18 other compositional variants were studied. Six of the glasses contained radioactive uranium (0.5-1.0 weight percent UO₂) and thorium (3.2-3.6 weight percent ThO₂); the remainder contained Al and Zr surrogates.

TEST CONDITIONS

The 4-gram glass samples were ground into -100/+200 mesh powders. A static powder leach test (modified MCC-3 test) was used. The leaching environment was 40 mls of deionized water at T = 90°C.

METHODS OF DATA COLLECTION/ANALYSIS

Leaching Experiments:

Leachate concentrations were analyzed at 7 and 28 days. Dissolved boron was used to indicate the extent of glass dissolution. Boron concentration in leachant was plotted vs reduced composition variable (referenced to WV-205 glass). No procedures were specified for determining viscosity. This reduced composition variable describes how a test glass varies from West Valley WV-205 reference glass in terms of

concentration of the three most important elements (Si, Al, Zr) in the glass. It is computed as a weighted sum of the differences in concentrations of Si, Al, and Zr between the two glasses.

AMOUNT OF DATA

Data presented are summarized in two tables and one figure, as follows:

Two tables

1. Compositions of WV-205 and Derivative Glasses.
2. Powder Leach Test Results and Viscosities for WV-205 and Derivative Glasses.

One figure

1. Concentration of boron in leachant for modified MCC-3 leach tests plotted as a function of the reduced composition variable. (Ordinate: boron concentration, mg/l. Abscissa: reduced composition variable, wt%).

UNCERTAINTIES IN DATA

None given.

DEFICIENCIES/LIMITATIONS IN DATABASE

In the abstract, the authors state that the conclusion that glass durability can be expressed as a function of a single reduced composition variable is valid for the narrow glass composition range studied, as long as the pH of the leachate remains nearly constant.

KEY WORDS

Data analysis, experimental data, laboratory, deionized, high temperature, static (no flow), 90°C (leaching), borosilicate glass, U, Th, viscosity, leaching.

COMMENTS

Corrosion resistance and processability are two of the primary criteria for nuclear waste glasses. Modifying the composition of borosilicate waste glasses to improve one of these properties generally has an adverse effect on the other. The present work attempts to show that certain compositional changes increase durability more than they degrade processability, i.e., increase viscosity. Specifically, aluminum is cited as being somewhat more effective in increasing durability than in increasing viscosity.

The data do in fact indicate that several high aluminum glasses are among the most corrosion resistant, but viscosity data on several of these glasses are absent. As a result, it

is doubtful that the conclusion is justified from the data presented. In fact, inspection of Table 2 indicates that the Defense Waste Reference Glass has a better combination of corrosion resistance and viscosity than any of the West Valley glasses, which are the focus of this study. The work does, however, demonstrate that, for the compositional variants in this study, the durability can be related to a single reduced composition variable.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting (X)]

(a) Relationship to Waste Package Performance Issues Already Identified

Related to issues 2.3.2.1.1, which waste form dissolution mechanism or mechanisms are most likely, 2.3.2.1.2, what are the rates of dissolution associated with the potential waste form dissolution mechanism, and 2.3.2.2, what non-radioactive dissolution products are likely to be produced from the waste form in the ISTP.

(b) New Licensing Issues

(c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

West Valley Demonstration Project, West Valley, New York

(b) Author(s), Reference, Reference Availability

Eisenstatt, L. R., "Description of the West Valley Demonstration Project Reference High-Level Waste Form and Canister," WVDP-056, Revision 0, July 28, 1986.

DATE REVIEWED: 4/20/87.

TYPE OF DATA

Three main data groups are given: (1) Composition, radioactivity, leaching behavior and physical properties of the WVDP High Level Waste form, each primarily on experimental measurements, (2) WVDP HLW canister dimensions, material, fabrication, labeling, and handling, according to present plans, and (3) expected characteristics of canistered waste, based on calculations.

MATERIALS/COMPONENTS

West Valley 205 glass waste forms that were melted either in a full-scale Slurry-Fed Ceramic Melter (SFCM) or in a laboratory scale melter. Surface finish was either 200 grit as-cut or 600 grit as-polished.

TEST CONDITIONS

Leaching tests were carried out using MCC-1 tests (90°C deionized water for 28 days, 400 mm² glass monoliths with S/V = 10/m) and pulsed flow tests (90°C deionized water, 25 percent exchange per week for 12 weeks).

METHODS OF DATA COLLECTION/ANALYSIS

Methods for chemical and radioactivity analyses were not specified.

Viscosities were determined by beam-bending viscometer (annealing range) and rotating spindle viscometer (high temperature).

Heat capacities were determined on differential scanning calorimeter at 20°C per minute.

Mathematical methods were used to calculate expected range of canistered waste characteristics.

AMOUNT OF DATA

Twenty-three tables

1. A. PUREX Insoluble Solids Chemical Composition.
B. PUREX Solids Fission Products.
2. PUREX Supernatant Chemical Composition.
3. THOREX Waste Chemical Composition.
4. IE-96 Nominal Composition.
5. Glass Formers Added to West Valley HLW to Melt WV-205.
6. Reference 1987 Radionuclide Content (Curies) of West Valley Waste.
7. Composition of WV-205.
8. Reference Radionuclide Content of a Canister of WVDP HLW.
9. Composition of a Nonradioactive Analogue WV-205.
10. WV-205/SFCM MCC-1 Test Results, 200 Grit Cut Finish Specimens.
11. WV-205/SFCM MCC-1 Test Results, 600 Grit Polish Specimens.
12. WV-205/SM MCC-1 Test Results, 200 Grit Cut Finish Specimens.
13. WV-205/SM MCC-1 Test Results, 600 Grit Polish Specimens.
14. WV-205/SFCM Pulsed Flow Test Results.
15. WV-205/SM Pulsed Flow Test Results.
16. WV-205 Glass Physical Property Data: Summary.
17. Annealing Range Viscosity Data: WV-205.
18. High Temperature Viscosity Data.
19. Glass Transition Temperatures.
20. Heat Capacity (C_p) of WV-205.
21. Chemical Composition Requirements for Type 304 Stainless Steel.
22. Temperature Distribution in the Canister.
23. Fissionable Material Content of a Canister of WVDP HLW.

Eight figures

1. West Valley High Level Waste Processing Flow Sheet.
2. Flow Test Results. (Leach rate of DWRG plotted vs residence time in years.)
3. Viscosity vs Temperature for WV-205.
4. Linear Thermal Expansion vs Temperature for WV-205.
5. Heat Capacity vs Temperature for WV-205.
6. CTS WVNS Canister. (Design drawing.)
7. West Valley High Level Waste Canister Labeling.
8. WVNS Canister Grapple.

UNCERTAINTIES IN DATA

Activities of fission products may vary from Table VI values as follows: U and Pu about 5 percent, Th about 20 percent, and other actinides about 50 percent.

Table VII contains composition ranges for major WV-205 components, based on uncertainties in waste sample analysis and expected waste stream variations.

Ranges of canister radioactivities are given for each radionuclide corresponding to 80-90 percent canister filling. Uncertainty limits are presented with several glass physical properties:

Glass transition temperature: 451.3-494.8°C
Linear expansion coefficient: ±5 percent
Temperature for 100 poise glass viscosity: ±5 percent
Dilatometric softening point of WV-205: ±5°C
Upper and lower annealing points: ±5°C

DEFICIENCIES/LIMITATIONS IN DATABASE

Further glass durability testing is needed. Repository groundwater will be added to the test matrix.

KEY WORDS

Experimental data, planned work, radioactivity measurements, chemical analysis, differential scanning calorimetry, laboratory, deionized, high temperature, static (no flow), dynamic (flow rate given), stainless steel, 304 stainless steel, cold worked, commercial high-level waste (CHLW), borosilicate glass, density, heat capacity, thermal expansion, viscosity, leaching (spent fuel).

COMMENTS

The purpose of this report is to provide information on the West Valley High Level Waste product which is (a) useful in dealing with the waste and (b) required for Waste Acceptance Preliminary Specifications (WAPS). The report does contain a considerable amount of tabulated information on waste form characteristics based on experimental measurements. It is also a good source of summary information on waste canister plans and calculated expected properties of canistered waste. Glass properties discussed include density, viscosity, thermal expansion, and heat capacity. Leaching studies are given without much detail and include data reported elsewhere. As a result, this report is not a primary source of leaching information.

RELATED HLW REPORTS

1. "Waste Acceptance Preliminary Specifications for the West Valley Demonstration Project High-Level Waste Form, Draft for Concurrence," OGR/B-9 (draft), U. S. Department of Energy, Washington, D.C., April 1986.
2. Baxter, R. G., "Description of Defense Waste Processing Facility Reference Waste Form and Canister," DP-1066, Rev. 1, E. I. DuPont de Nemours and Co., Savannah River Plant, Aiken, SC, August 1983.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting data (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to issues 2.3.1., what are the physical, chemical, and mechanical properties of the waste form, and 2.3.2.2, what non-radioactive dissolution products are likely to be produced from the waste form in the ISTP.

- (b) New Licensing Issues
- (c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

E. I. duPont de Nemours and Co., Savannah River
Laboratory, Aiken, South Carolina 29808.

(b) Author(s), Reference, Reference Availability

Wicks, G. G., Bibler, N. E., Jantzen, C. M., and
Plodinec, M. J., "Repository Simulation Tests," American
Ceramic Society Annual Meeting, 1984. Available from the
American Ceramic Society.

DATE REVIEWED: 6/12/87.

TYPE OF DATA

Description of repository simulation leaching test methods.
Experimental data on glass leaching.

MATERIALS/COMPONENTS

SRP simulated waste glasses (exact type and composition not
specified), both non-radioactive and radioactive.

TEST CONDITIONS

The repository simulation test is a static MCC-1 based test,
modified so that the primary leaching vessel is made of the
host rock (tuff was used in this experimental study). The
leachant was G-4 groundwater at 90°C. Surface area to volume
(SA/V) ratio was 1.0 cm⁻¹. The cup also contained a 304L
stainless steel sample cage.

METHODS OF DATA COLLECTION/ANALYSIS

Tests were run for periods of 1, 3, and 6 months. Leachates
were analyzed after exposure to determine both pH and species
extracted from the waste glass and package components. Method
of leachate analysis was not specified.

AMOUNT OF DATA

Three tables

1. Repository Simulation Studies (list of three repository
sites).

2. Repository Simulation Test Conditions (see Test Conditions above).
3. Tuff Tests - Phase 1 (pH changes vs time).

Seven figures

1. Analyses and Responsibilities (division of responsibilities between SRL and repository designer).
2. Experimental Apparatus.
3. Rock Cups and Waste Glass Samples (photograph).
4. Experimental Unit (photograph).
5. NL (normalized elemental mass loss) of Lithium in J-13 Tuff GW and System (graphed vs time, 0-6 months).
6. NL (normalized elemental mass loss) of Boron in J-13 Tuff GW and System (graphed vs time, 0-6 months).
7. NL (Li) for Radioactive vs Non-Radioactive Tests (J-13 Tuff GW and System) (graphed vs time, 0-90 days).

UNCERTAINTIES IN DATA

Even with rock samples from adjacent positions within a single core, the leaching behavior may vary significantly. Thus, the results of a few experiments may not give a true indication of the effects of the host rock on glass leaching performance.

DEFICIENCIES/LIMITATIONS IN DATABASE

The number of tests performed thus far under simulated repository conditions is limited, and interpreting the many possible interactions in the system is complex. Determining the concentrations of various species in the leachate is not sufficient to describe the glass behavior if those species can also originate from the host rock or other system components. Accordingly, internal calibrations for the species leached from the host rock are obtained from a separate volume of groundwater outside the host rock cup (i.e., in contact with the cup but not with the glass specimen). Data thus far are limited and more tests are needed to determine applicability of the method. Ultimately, a complete mass balance may be necessary.

KEY WORDS

Experimental data, supporting data, simulated field, Yucca Mountain, tuff groundwater, tuff, static, DHLW, leaching.

COMMENTS

This paper describes repository simulation tests designed "to assess the performance of SRP waste glass under the most realistic repository conditions that can be obtained in the laboratory." The factors that went into development of the test method are described. Particularly useful is a

discussion of the limitations in repository simulation and the ways that they are addressed by the present method. Some limited data are presented from experiments in which the test is used to characterize leaching in tuff host rock.

In the experimental work, the effects of the host rock and canister material were incorporated into the leaching experiment. This procedure represents an advance in laboratory testing of glass leaching over the standard MCC-1 test. The use of actual groundwater as the leachant contributes to the realism of the simulation, although testing in pure water to approximate "worst case" conditions still has merit. Incorporation of groundwater flow into the test, which the authors suggest is possible, would make the test an even better simulation of repository conditions.

The limited experimental data illustrate the test method but have limited applicability. Because the composition of the waste glasses was not specified, the data are useful only for establishing internal consistency and demonstrating that the radioactive and non-radioactive glasses behaved similarly. The preliminary results presented suggest that the buffering action of tuff will stabilize groundwater pH at lower values and thereby retard glass leaching. This critical aspect of work on the tuff and other repositories is being investigated and reported in other papers scheduled for review. Such behavior should be substantiated and quantified with the final candidate waste form, once its composition has been decided.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting data (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to issue 2.3.2, what is the solubility of the waste form under the range of potential repository conditions (tuff primarily) in the ISTP.

- (b) New Licensing Issues
(c) General Comments on Licensing

WASTE PACKAGE DATA REVIEW

DATA SOURCE

(a) Organization Producing Data

E. I. duPont de Nemours and Company, Savannah River Laboratory, Aiken, South Carolina 29808.

(b) Author(s), Reference, Reference Availability

Bibler, N. E., Plodinec, M. J., Wicks, G. G., and Jantzen, C. M., "Glass Performance in a Geologic Setting," Summer National Meeting of the American Institute of Chemical Engineers, 1986. Available from the American Institute of Chemical Engineers.

DATE REVIEWED: 6/24/87.

TYPE OF DATA

The paper is a literature review of experimental leaching tests and leaching models. The tests reviewed are laboratory and in-situ simulated repository tests.

MATERIALS/COMPONENTS

Four glass compositions were generally studied in the reviewed work:

1. SRL-165
2. Defense Waste Reference Glass
3. SRL-131
4. Radioactive glass containing waste from SRP tank 8.

TEST CONDITIONS

Detailed descriptions of test conditions were not given. In general, tests were conducted under simulated repository conditions, both in the laboratory and in-situ.

METHODS OF DATA COLLECTION/ANALYSIS

Not applicable - review paper.

AMOUNT OF DATA

Data presented are summarized in four tables and seven figures:

Four tables

1. Principal Composition of Typical Glasses Used to Measure Performance of DWPF Glass.
2. Summary of Expected Repository Conditions.
3. Compositions of Groundwater in Potential Repositories.
4. Calculated Release from DWPF Glass in a Saturated Tuff Repository Using the Mass Transfer Model.

Seven figures

1. Time Dependent Release of B from DWPF Glass (SRL-131) at 90°C in Deionized Water and Three Synthetic Groundwaters. (0 to 750 d, normalized mass loss range 0 to 140 g/m²)
2. Effect of pH (1 to 11) on Silica Dissolution from Simulated DWPF Glass (SRL-131) at 90°C.
3. Dissolution of Cs-137 (0 to 4 g/m²) from Radioactive DWPF Glass at 90°C in Tuff Groundwater in the Presence and Absence of Tuff Rock. (Leach time 0 to 160 d)
4. Time Dependent Release of Li and B from DWPF Glass (SRL-165 Glass) at 90°C in Reduced and Oxidic Simulated Basalt and Granite Groundwaters. (0 to 30 d leach periods)
5. Comparison of the Durability of DWPF Glass (SRL-165 Glass and SRL-131 Glass) with Basalt Rock and also Other Glasses Based on the Thermodynamic Hydration Model. (Mass loss based on Si, ranging from 0.1 to 1000 g/m², plotted vs free energy of hydration, 10 to -20 kcal/mol)
6. Release of ²³⁹Pu from DWPF Glass (DWRG Glass) in Brine Solution at 90°C. (ppb ²³⁹Pu plotted vs time, 0 to 60 d)
7. Coupling of Glass Performance and Repository Performance Based on the Model of Cheung. Peak Individual Dose Rates Calculated using Release Rates for DWPF Glasses Measured under Laboratory or In-situ Conditions. (Limiting individual peak dose rate as fraction of background, 10⁻⁶ to 1, plotted vs glass release rate 10⁻⁶ to 10⁻³/y)

UNCERTAINTIES IN DATA

Not applicable - review paper.

DEFICIENCIES/LIMITATIONS IN DATABASE

1. Site-specific properties of the actual repositories need to be determined.
2. Testing is needed using site-specific groundwaters and rock.
3. The role of colloids in repositories containing iron as the waste package overpack is not understood.
4. The effect of radiation on leaching in reducing groundwaters needs to be studied further.
5. Leaching of additional radionuclides in groundwater needs to be studied.

KEY WORDS

Literature review, leaching, simulated field, DHLW.

COMMENTS

This paper reviews published studies on Defense Waste Processing Facility (DWPF) glass degradation in simulations of the proposed repository environments. Such studies overcome some of the limitations of similar experiments in which repository conditions are ignored. This is important because the performance of the glass, as the authors point out, can be directly affected by the test method. This question of test methodology and the ability to predict and simulate repository conditions remains a central issue in evaluating studies of glass waste form leaching. A considerable amount of the discussion in this paper concerns test methods.

The specific effects of simulated tuff, salt, basalt, and granite repository environments on waste glass durability comprise the major part of the review. The paper contains a short overview of the effects of solution composition, pH, and pressure. In addition to reviewing experimental data, the paper discusses two models that couple glass leaching with repository conditions. The first model calculates radionuclide migration rates using known equations for mass transfer by convection and diffusion, assuming that groundwater flow is so slow that radionuclide concentrations at the glass surface are controlled by solubility. The second model is similar to the first, except that it calculates individual peak dose rates that would be obtained at the edge of the repository by drinking the groundwater. Both models are shown to predict low radionuclide release rates in repository environments.

The studies reviewed represent a growing body of work which supports the authors' hypothesis that Defense Waste Processing Facility glass will be more durable in the repository than in predictive laboratory tests. It must be recognized, however, that this hypothesis includes the implicit assumption that the repository simulation tests do indeed simulate the (as-yet poorly characterized) repository sites.

While the review is not exhaustive or extremely detailed, it is a well written, clear, useful summary of available data. Furthermore, it presents current thinking on some of the relationships between the repository environment and glass durability, and identifies several areas which must be studied further.

It is interesting to note that the paper points out that the 131-TDS glass, discussed in the paper, is no longer used for

testing glass durability. There has been a shift to higher silica glasses to maximize overall glass properties. A considerable amount of the existing data on waste form leaching, and resulting hypotheses on leaching mechanisms, are based on this glass. As a result, it will be necessary to verify that what has been learned is applicable to the new compositions.

RELATED HLW REPORTS

1. Wicks, G. G., Bibler, N. E., Jantzen, C. M., and Plodinec, M. J., "Repository Simulation Tests", American Ceramic Society Annual Meeting, 1984.

APPLICABILITY OF DATA TO LICENSING

[Ranking: key data (), supporting data (X)]

- (a) Relationship to Waste Package Performance Issues Already Identified

Related to issues 2.3, when, how, and at what rate will radionuclides be released from the waste form, 2.3.2, what is the solubility of the waste form under the range of potential repository conditions, 2.3.2.1.1, which waste form dissolution mechanism or mechanisms are most likely, 2.3.2.2, what non-radioactive dissolution products are likely to be produced from the waste form, 2.3.2.3, what are the solubilities of the radionuclides released from the waste form, 2.3.2, what colloids or other suspended particles will be produced from the waste form in the ISTP.

- (b) New Licensing Issues
- (c) General Comments on Licensing

Appendix B. Database Activities for the NBS/NRC Database for
Reviews and Evaluations of High-Level Waste Data

Work on improving the searching capabilities and the speed of searching the Database (for Reviews and Evaluations on High-Level Waste) continued during the six months from February 1987 to July 1987. Enhancements to the software developed during this period are highlighted below.

Various system routines were developed: Items B, C, and D listed below are largely transparent to the user, but these changes enhance efficiency of data handling and retrieval.

Item A -- Help Menus Version 1.0 and 1.1 have been developed. Examples of help menu screens developed at NBS are located in the Monthly Letter Status Report for April 1987 (FIN-A-4171-6). Help menus lead a user through a series of choices. The end result of these choices is a completed search or query. By using the help menus, a novice user of the NRC/NBS database is able to search for information more quickly and easily. In the first test version (1.0) of Help Menus, each time new keywords were added to the database, it was necessary for a systems programmer to update a series of help menu screens. This process has been automated in Version 1.1, so that whenever keywords are added, the information specialist runs a program and the menu system will be updated to merge the new keywords with the older keywords. The new file is reflected immediately in the help screens.

Item B -- Previously, there was no command that would instruct the user on the organization or logic structure of the database. The logic structure of the database is referred to as the database tree. Now, using the command DATABASE.TREE, the current version of the database tree is derived from the structure that exists at the time the command is given. This is important when frequent minor changes are made in the file structure. A tree derived in this way can be printed to the screen or the printer.

Item C -- A command has been added to find empty fields in a file. This command, called FIND.EMPTY, will locate the empty fields in a record and print the field names to either the screen or printer. This is helpful in verification of data entry and in answering a query.

Item D -- The input screen routines for abstracts have been modified. During data entry, if a document does not contain an abstract, the input routine will automatically place the text string, "No abstract.", in the field. This speeds data entry and retrieval.

Other software enhancements have been made and are listed below:

The NBS program for tracking documents has been modified and expanded.

2. Command words used in REVELATION® were modified to cause records to be printed with encoded superscripts, subscripts, and overstrikes, so that they appear as normal typed text on the terminal screen and on a simple printer. A subset of commands uses the LaserJet codes to make a more elegant copy.
3. The internal format of the REVELATION® files was restructured to decrease retrieval time on the PC.
4. Developed data processing for the NRC REVELATION® files to allow for clean searches, i.e. searches that ignore any formatting codes inserted by text processors.
5. Developed a method for searching all fields in a record simultaneously rather than one field at a time.
6. Developed procedures and programs to allow the transfer of WordPerfect® files into REVELATION® files.
7. The review-form file, the abstract file, and the figures file are now entered into WordPerfect®, corrected in WordPerfect®, and at a later date entered into REVELATION®. This eliminates the clumsy screen method used up to now and has effectively added more input devices as any PC with WordPerfect® can be used.
8. Work was done on improving procedures and programs used to supply reviewers with start-up materials. The reviewer will be given a floppy disc which contains WordPerfect® files of the abstract, figure headings, and a review form. The data center staff will have already filled out some items in the review form. This floppy disc will be used as input to the REVELATION® files after the review is completed.

A list of programs and files created or modified is given below:

1. Created Data Dictionaries for the following new REVELATION® files:

WORK.ABS, WORK.FIG, WORK.REF, NRC.ABS, NRC.REF, NRC.REV,
NRC.KEY, NRC.FIG, ASSIGNED.READERS.

2. Created new data fields within existing REVELATION® files:

DATA.SOURCE, ALLFIELDS, RELEVANT, TYPE.REVIEW, NOTES,
DATE.FROM.LEAD.WORKER, DATE.FROM.REVIEWER,
DATE.FROM.PROJECT.MANAGER.

3. Created Macros inside WordPerfect® to assist in the conversion from WordPerfect® files to REVELATION® files:

WPABC1.MAC, WPABC2.MAC, WPABC3.MAC, WPREV.MAC.

4. Created REVELATION® RBASIC Programs for processing files into and out of REVELATION®:

WP.TO.FIG, WP.TO.ABS, WP.TO.REV, WORK.TO.REV, TO.WP.FORM, REWORK.WORK, FIND.SIZE.

5. Created special purpose command words in REVELATION®:

ONE.ITEM, ONE.ITEM.PLAIN, ONE.ITEM.LASER, FTF, SUPER, SUPER.LASER, SUPERLIST, SUPERLIST.LASER.

In addition to the enhancements listed above, two new items under development are listed below:

1. Integration of the existing database with the new Advanced Revelation®, which is being purchased for use in the HLW Program at NBS --

The new Advanced Revelation® will enable the user to conduct searches more rapidly and will be even more "user friendly." In Advanced Revelation® the help menus will be modified to use "point and click" technology. A user will move a cross hair to a particular location on the screen by using the cursor keys or, possibly, a "mouse." The screen location will have text describing a particular action to be performed. When the cross hair is over a particular location on the screen, the user can push a button and the action described by the text string will be performed. Through the use of "point and click" technology, the help menus will become easier to use and much more user friendly.

2. Integrate an optical liner scanner into the data entry system --

An optical scanner that digitizes typed or printed items on a line-by-line bases has been purchased and installed on a personal computer. This scanner is expected to speed data entry for the review and tracking systems used in the HLW Data Center.

BIBLIOGRAPHIC DATA SHEET

NUREG/CR-4735
 Volume

SEE INSTRUCTIONS ON THE REVERSE

2. TITLE AND SUBTITLE

Evaluation and Compilation of DOE Waste
 Package Test Data
 Biannual Report February 1987 - July 1987

3. LEAVE BLANK

4. DATE REPORT COMPLETED

MONTH: November YEAR: 1987

5. AUTHOR(S)

C. Interrante, E. Escalante, A. Fraker, D. Hall,
 S. Harrison, W. Liggert, M. Linzer, R. Ricker,
 J. Ruspi, R. Shull

6. DATE REPORT ISSUED

MONTH: May YEAR: 1987

7. PERFORMING ORGANIZATION NAME AND MAILING ADDRESS (Include Zip Code)

U.S. Department of Commerce
 National Bureau of Standards
 Center for Materials Science and Engineering
 Metallurgy Division - Corrosion Section
 Gaithersburg, MD 20899

8. PROJECT/TASK/WORK UNIT NUMBER

9. FIN OR GRANT NUMBER

A4171

10. SPONSORING ORGANIZATION NAME AND MAILING ADDRESS (Include Zip Code)

Division of High-Level Waste Management
 Office of Nuclear Material Safety and Safeguards
 U.S. Nuclear Regulatory Commission
 Washington, DC 20555

11a. TYPE OF REPORT

Technical

b. PERIOD COVERED (Inclusive dates)

12. SUPPLEMENTARY NOTES

13. ABSTRACT (200 words or less)

This report summarizes evaluations by the National Bureau of Standards (NBS) of Department of Energy activities on waste packages designed for containment of high-level nuclear waste (HLW). The waste package is a proposed engineered barrier that is part of a permanent repository for HLW. Metal alloys are the principal barriers within the engineered barrier system. The corrosion of candidate container materials, particularly carbon steels, stainless steels and copper, is discussed. The level of understanding of several proposed container materials is questioned for the candidate repository in tuff. Three issues are addressed: (1) The possibility of stress-induced failure of Zircaloy, (2) possible corrosion of copper and copper alloys and (3) the lack of site-specific characterization data. The Basalt Waste Isolation Project (BWIP) section discusses localized corrosion and environmentally-assisted cracking of AISI 1020 steel at elevated temperatures (150°C). For the proposed salt site, the importance of the duration of corrosion tests and conditions that may preclude prompt initiation of long-term testing are discussed. NBS work related to vitrification of HLW borosilicate glass at the West Valley Demonstration Project (WVDP) and at the Defense Waste Processing Facility (DWPF) is discussed. Activities of the Materials Characterization Center (MCC) are presented. To stress the necessity of independent data interpretations, an illustration is given of a conclusion drawn from published data that is different from the conclusion reached by the investigator.

14. DOCUMENT ANALYSIS - KEYWORDS/DESCRIPTORS

pitting corrosion salt
 general corrosion borosilicate glass
 austenitic stainless steels nuclear waste
 tuff
 basalt

15. AVAILABILITY STATEMENT

Unlimited

16. SECURITY CLASSIFICATION

(This page)

Unclassified

(This report)

Unclassified

17. NUMBER OF PAGES

18. PRICE

19. IDENTIFIERS/OPEN-ENDED TERMS

UNITED STATES
NUCLEAR REGULATORY COMMISSION
WASHINGTON, D.C. 20555

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE, \$300

SPECIAL FOURTH-CLASS RATE
POSTAGE & FEES PAID
USNRC
PERMIT No. G-87

120555078877 1 1AN1CH1WA1WD1
US NRC-OARM-ADM
DIV OF PUB SVCS
POLICY & PUB MGT BR-PDR NUREG
W-537
WASHINGTON DC 20555